

This is a repository copy of *Direct Imaging of Kinetic Pathways of Atomic Diffusion in Monolayer Molybdenum Disulfide*.

White Rose Research Online URL for this paper:

<https://eprints.whiterose.ac.uk/117124/>

Version: Accepted Version

Article:

Hong, Jinhua, Pan, Yuhao, Hu, Zhixin et al. (5 more authors) (2017) Direct Imaging of Kinetic Pathways of Atomic Diffusion in Monolayer Molybdenum Disulfide. *Nano Letters*. pp. 3383-3390. ISSN 1530-6984

<https://doi.org/10.1021/acs.nanolett.6b05342>

Reuse

Items deposited in White Rose Research Online are protected by copyright, with all rights reserved unless indicated otherwise. They may be downloaded and/or printed for private study, or other acts as permitted by national copyright laws. The publisher or other rights holders may allow further reproduction and re-use of the full text version. This is indicated by the licence information on the White Rose Research Online record for the item.

Takedown

If you consider content in White Rose Research Online to be in breach of UK law, please notify us by emailing eprints@whiterose.ac.uk including the URL of the record and the reason for the withdrawal request.

Direct imaging of kinetic pathways of atomic diffusion in monolayer molybdenum disulfide

Jinhua Hong, Yuhao Pan, Zhixin Hu, Danhui Lv, Chuanhong Jin, Wei Ji, Jun Yuan, and Ze Zhang

Nano Lett., **Just Accepted Manuscript** • Publication Date (Web): 26 May 2017

Downloaded from <http://pubs.acs.org> on May 31, 2017

Just Accepted

“Just Accepted” manuscripts have been peer-reviewed and accepted for publication. They are posted online prior to technical editing, formatting for publication and author proofing. The American Chemical Society provides “Just Accepted” as a free service to the research community to expedite the dissemination of scientific material as soon as possible after acceptance. “Just Accepted” manuscripts appear in full in PDF format accompanied by an HTML abstract. “Just Accepted” manuscripts have been fully peer reviewed, but should not be considered the official version of record. They are accessible to all readers and citable by the Digital Object Identifier (DOI®). “Just Accepted” is an optional service offered to authors. Therefore, the “Just Accepted” Web site may not include all articles that will be published in the journal. After a manuscript is technically edited and formatted, it will be removed from the “Just Accepted” Web site and published as an ASAP article. Note that technical editing may introduce minor changes to the manuscript text and/or graphics which could affect content, and all legal disclaimers and ethical guidelines that apply to the journal pertain. ACS cannot be held responsible for errors or consequences arising from the use of information contained in these “Just Accepted” manuscripts.



Direct imaging of kinetic pathways of atomic diffusion in monolayer molybdenum disulfide

Jinhua Hong^{†, §, ¶}, Yuhao Pan^{‡, §}, Zhixin Hu[‡], Danhui Lv[†], Chuanhong Jin^{†, *}, Wei Ji^{‡, *},

Jun Yuan^{†, ¶, *}, Ze Zhang[†]

[†]*State Key Laboratory of Silicon Materials, School of Materials Science and Engineering, Zhejiang University, Hangzhou, Zhejiang 310027, China*

[‡]*Beijing Key Laboratory of Optoelectronic Functional Materials & Micro-Nano Devices, Department of Physics, Renmin University of China, Beijing 100872, China*

[¶]*Department of Physics, University of York, Heslington, York, YO10 5DD, United Kingdom*

[§] *These authors contributed equally to this work.*

Direct observation of atomic migration both on and below surfaces is a long-standing but important challenge in materials science as diffusion is one of the most elementary processes essential to many vital material behaviors. Probing the kinetic pathways, including metastable or even transition states involved down to atomic scale, holds the key to the underlying physical mechanisms. Here, we applied aberration-corrected transmission electron microscopy (TEM) to demonstrate direct atomic-scale imaging and quasi-real-time tracking of diffusion of Mo adatoms and vacancies in monolayer MoS₂, an important 2D transition metal dichalcogenide (TMD) system. Preferred kinetic pathways and the migration potential-energy landscape are determined experimentally and confirmed theoretically. The resulting three-dimensional knowledge of the atomic configuration evolution reveals the different microscopic mechanisms responsible for the contrasting intrinsic diffusion rates for Mo adatoms and vacancies. The new insight will benefit our understanding of material processes such as phase transformation and heterogeneous catalysis.

Key words: transition metal dichalcogenides, adatom and vacancy, surface migration, energy landscape, single-atom tracking

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
Diffusion phenomena on surfaces and inside solids are important material processes closely associated with solid-state phase transformation¹, nanomaterials growth²⁻⁴, single-atom doping¹ and heterogeneous catalysis⁵. To tailor or design these diffusion-related properties⁶, it is essential to understand the underlying atomic process involved. However, the determination of microscopic mechanisms is non-trivial as diffusion can proceed along many different kinetic pathways. Even for simple self-diffusion inside solids, for example, it can take place via vacancy, interstitial or direct exchange mechanisms. Experimental determination of the stable and metastable configurations and their evolutions remains important to identify the dominant kinetic pathways involved, as well as providing vital realistic calibration to the complex *ab-initio* calculation.

24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
Among the available experimental techniques, scanning tunneling microscopy (STM)^{7, 8}, atomic force microscopy (AFM)⁹, and field ion microscopy (FIM)¹⁰ have the required atomic resolution to image the surface migration of adatoms¹¹⁻¹⁵, and the rotation¹⁶, transformation^{9, 17, 18} and self-assembly¹⁹ of adsorbate molecules. With the development of aberration correction optics, transmission electron microscopy (TEM) has been demonstrated as an alternative technique with a proper time window to observe adatom diffusion²⁰ or defect evolution²¹⁻³⁷. However, the experimental single-atom tracking and statistical analysis of the metastable/intermediate states in atomic migration via different mechanisms are still limited. Furthermore, in contrast with the well-known one-dimensional pathway-dependent barrier, the two-dimensional potential landscape of the surface diffusion has never been mapped experimentally.

47
48
49
50
51
52
53
54
55
56
57
58
59
60
In this paper, we report a direct observation of the dynamics of bulk-like in-plane diffusion of Mo vacancies and surface migration of Mo adatoms in monolayer MoS₂, by atomic-scale tracking using chemically sensitive scanning transmission electron microscopy (STEM). As monolayer MoS₂ has a sandwich structure consisting of a Mo layer bonded by surface S layers on both sides, it is an ideal model system to study and contrast atom migration both on and below the surface. Specifically, we show that such observation can help identify the preferred migration pathway and

1
2
3 outline the two-dimensional migration energy landscape. *Ab-initio* density function
4 theory (DFT) calculation further provides detailed quantum mechanical description of
5 the atomic processes along such kinetic pathways, accounting for the different diffu-
6 sion rates measured for adatoms and vacancies. As a member of transition metal
7 dichalcogenides³⁸, MoS₂ has shown considerable potential in applications such as ca-
8 talysis³⁹⁻⁴³ and electrode materials for batteries^{44, 45}. The insight gained can enhance
9 our understanding and optimization of applications of such materials and the relevant
10 systems involving mass transport under either electronic, chemical or ionic currents.
11
12
13
14
15
16
17
18
19

20 21 Results

22
23 **The migration of Mo vacancy and its metastable state.** Figure 1a-d shows the
24 time-lapsed annular dark-field (ADF) images of the migrating Mo vacancy within
25 monolayer MoS₂ at room temperature. According to the Z-contrast mechanism re-
26 sponsible for ADF-STEM imaging, it is easy to quantitatively assign the nature of lat-
27 tice atoms and vacancy defects in monolayer MoS₂. The total duration of observation
28 was sufficiently short that we did not detect additional loss of Mo or S atoms in this
29 area of interest. Note that the vacancy diffusion is actually the motion of the neigh-
30 boring Mo atom, highlighted with arrows in Fig. 1a-c. The vacancy migration in Fig.
31 1a-c went through an intermediate state (labeled as V'_{Mo}) and gives the clue to the ki-
32 netic pathway for the hopping of Mo vacancy from one site in the Mo sublattice to the
33 next (Fig. 1d). More vacancy hopping examples can be found in Supplementary
34 Fig.S1-2 and Animation1-3.
35
36
37
38
39
40
41
42
43
44

45 We have also analyzed the kinetic pathway of Mo vacancy migration by *ab-initio*
46 DFT calculation, starting with the atomic geometries deduced from TEM observation.
47 Figure.1e-h show DFT fully-relaxed atomic models associated with Fig.1a-d, in
48 which the migrating Mo atom is emphasized in blue and purple. The overall agree-
49 ment between the experimental images and those derived from the DFT calculations
50 confirms the correct identification of three-dimensional structure of the most stable
51 vacancy configuration V_{Mo} (Fig. 1a,e) and metastable state V'_{Mo} (Fig.1b,f).
52
53
54
55
56
57
58
59
60

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Figure 2a,b show the statistical counts and dwell-times of different configurations of Mo vacancy (V_{Mo} and V'_{Mo}) observed during their migration. The dominating counts and longer dwell time of vacancies in the V_{Mo} state support the proposition that it is the ground-state configuration whereas V'_{Mo} is a metastable configuration. Our experimentally determined kinetic pathway (Fig.1e-g) for Mo vacancy migration is consistent with the most-favored pathway derived from *ab-initio* DFT calculation, after considering various possibilities, as shown in Fig.2c where the transition state (TS) and the energetics involved are also presented. The red arrows in Fig.2c indicate the motion of neighboring Mo atom (in blue) with the details shown in Fig. 2d (see also Supplementary Animation 4). The TS state has an energy of 2.9 eV relative to that of the most stable Mo vacancy state (V_{Mo}). The origin of such a high energy barrier is the unsaturated Mo-S bonds and reorganization of the bond length (Fig. 2d). On the other hand, the energy of the metastable state V'_{Mo} (local energy minimum in Fig.2c) is only 0.6 eV below that of the TS state, which explains the limited dwell time and observation frequency for the V'_{Mo} state. This probably also explains the slight distortion of lattice Mo atoms seen in the experimental images in Fig. 1 as the atomic configuration is more mobile in such a shallow potential well to be captured precisely. Nevertheless, both activation energies are higher than the background thermal energy, suggesting the migration processes seen in Fig. 1 is electron-beam assisted. This is similar to that found for vacancy hopping in graphene^{31,46}. Despite that, an analysis of the migration trajectories (Supplementary Fig.S3) indicates that the vacancy migration within Mo sublattice is without directional preference. The travel distance and displacement of Mo vacancy both follow the trend expected for the random walk of particles (Supplementary Fig.S4). This suggests that the effect of the electron beam is probably limited to boosting the mobilities of the atoms with high migration barriers.

The tracking of Mo adatoms and their metastable states. For comparison, Figure. 3a-f show a time-lapse sequential of ADF-STEM images indicating the migration of a Mo adatom on the surface of a monolayer MoS₂. The Mo adatom⁴⁷ can be easily

1
2
3 identified and this assignment is supported by additional simulation and analysis
4 shown in Supplementary Fig.S5-6. More examples of adatom hopping are presented
5 in Supplementary Fig.S7 and Animation 5-7.
6
7

8
9 After analyzing numerous Mo adatoms (over 500 cases), we identified three
10 most-frequently observed configurations of Mo adatoms: on top of Mo sites (T_{Mo}),
11 above the center of the hexagon or the hollow site (H), and on top of S sites (T_S),
12 shown in Fig. 4a,c,e, respectively. The corresponding atomic models are shown in Fig.
13 4b,d,f, all based on experimentally suggested geometry and fully-relaxed by *ab-initio*
14 calculation. Side views of these structures are presented in Supplementary Fig. S8.
15 The image simulations (Supplementary Fig. S9) based on these structural models are
16 in agreement with the experiments.
17
18

19
20 The statistical analysis of the observed adsorption states in Fig. 4g demonstrates
21 that T_{Mo} is the most common adatom configuration, H and T_S are less common by
22 comparison. Correspondingly, the dwell time of adatoms shown in Fig. 4h also indi-
23 cates that T_{Mo} is more stable than H and T_S , although the differences in the counting
24 statistics and the dwell times among T_{Mo} , H and T_S are smaller than those found in the
25 case of Mo vacancy. Consistent with the experimental result, DFT calculations give
26 their relative energy as 0, 0.33 and 0.99 eV for T_{Mo} , H and T_S , respectively. Accord-
27 ingly, we regard T_{Mo} as the most stable state and H, T_S as metastable states. The pres-
28 ence of more than one metastable state for adatom migration is a reflection of the in-
29 creased degree of freedom of adatoms compared with that of the in-plane vacancy
30 diffusion. This illustrates the richness of the surface diffusional phenomena and ne-
31 cessity of determining the dominant kinetic pathway.
32
33

34
35 *Ab-initio* calculation confirms that the experimental most-favored kinetic path-
36 ways for Mo adatom migration follows a $T_{Mo1} \rightarrow H \rightarrow T_{Mo2}$ transition (red arrows
37 shown in Fig.4i and observed in Supplementary Animation 5), with an initial energy
38 barrier of 0.62eV. The energy barrier for the less-favored $T_{Mo} \rightarrow T_S$ transition is calcu-
39 lated to be 1.11eV by comparison (Supplementary Fig.S10 and Animation 8). The de-
40 tailed structure evolution across the $T_{Mo1} \rightarrow H \rightarrow T_{Mo2}$ transition can be followed in
41 Fig.4j where the migrating adatom is emphasized in blue (see also Supplementary
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 Animation 9). Compared with Mo vacancy diffusion, the reduced energy barriers for
4 surface adatom migration are related to the smaller structural relaxation (Supplemen-
5 tary Fig.S11) with breaking of at most only one Mo-S bond.
6
7

8
9 Although both MoS₂ and graphene surfaces are considered to be inert, the kinetic
10 pathways for the adatoms are very different and depend on both the surface and the
11 adatoms, indicating strong chemical adatom-surface interaction in both cases. For
12 example, adatoms on graphite still migrate in a similar hexagonal lattice but they fol-
13 low either T₁→B→T₂ (Au adatom), H₁→B→H₂ (Al or Cr) or B₁→B₂ (C adatom)
14 pathways^{24, 48}. Here B stands for bridge sites above the center of C-C bonds. By
15 contrast, the bridge-site adsorption on MoS₂ is not, even locally, a stable configuration
16 for Mo adatoms. The preference for the T_{Mo1}→H→T_{Mo2} pathway on MoS₂ surface is,
17 we believe, due to the tendency of the d-electrons of the Mo adatom to form covalent
18 bonds with the surface S in a triangular-prismatic or octahedral coordination⁴⁹. This
19 chemically-sensitive adatom diffusion may dominate the diffusion rate of intercalating
20 ions in layered materials as battery electrodes⁴¹.
21
22

23
24 Similar to the Mo vacancy case, the migration trajectory of Mo adatoms suggests
25 that the migration jumps have no obvious directional preference (Supplementary
26 Fig.S12). The travel distance and displacement of the hopping Mo adatom (Supple-
27 mentary Fig.S4) is typical of random walk or Brownian motion of particles, suggest-
28 ing the electron beam may help overcome the migration energy barriers.
29
30

31
32 **Hopping statistics of defect migration and potential energy landscape.** The Mo
33 adatom hopping statistics can be visualized spatially in terms of the polar scatter dia-
34 gram shown in Fig.5a. The red-star dots indicate the final sites of one-step adatom
35 hopping from the initial site on Mo (coordinate origin), all superimposed on the hex-
36 agonal MoS₂ lattice. The radii of inscribed circles represent the range of the hopping
37 steps that can be reached from the circle center. Most hoppings are between T_{Mo} and
38 H, without directional preference. The density distribution of dots in this polar dia-
39 gram reflects the two-dimensional potential landscape of a Mo adatom on monolayer
40 MoS₂, as higher density means more stable atomic configuration. The density distri-
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

bution indeed coincides qualitatively with the theoretical adsorption potential diagram shown in Fig.5b. The T_{Mo} , H and T_S sites are all valleys in this potential-energy landscape, corresponding to the ground and metastable states, shown in Fig.4, respectively. The contrasting energy barriers between $T_{Mo} \rightarrow H$ (0.62 eV) and $T_{Mo} \rightarrow T_S$ (1.11 eV) indicate that the $T_{Mo} \rightarrow H$ transition should be the elementary hopping process in thermally activated atomic migration.

Similarly, polar scatter diagram in Fig.5c summarizes the hopping step distribution of Mo vacancies, where green triangles stand for the final sites of one-step hopping of Mo vacancy whose initial site is the origin. Compared with the surface adatom migration, the energy landscape is much simpler as V_{Mo} jumps only between Mo sublattice sites. Moreover, this stable migration within the Mo layer also has no directional preference, indicating a 2D random walk behavior.

One should note that as individual one-step migration of defects occurs in picosecond, the transfer process itself is too fast to capture ‘in flight’. The possible much longer dwelling on the ground- or metastable-state sites allows us to capture different ground/metastable configurations. Hence, we consider the observed transition between two different states as one hopping step, much slower than the “ps” hopping dynamics. Based on the above analysis of the potential landscape for Mo adatoms, we interpret the observed long-range one-step jumps in Fig.5a as consisting of several $T_{Mo} \rightarrow H$ elementary hopping events. This is supported by the relative population of the jumping steps as shown in Fig.5d, based on an independent hopping model. Here the ‘zero peak’ represents those observations that adatoms remain at the same site or return to the same starting site. The first peak around 0.18 nm represents the transition from T_{Mo} to H (the elementary hopping), and the second peak is attributed to transition from T_{Mo1} to T_{Mo2} (two successive basic hopping), and the third peak is the result of second-nearest-neighboring hopping, as illustrated by the insets in Fig. 5d. They are compared with the theoretically-predicted relative probability distribution, where the relative probability ratio of the elementary hopping $T_{Mo} \rightarrow H$, nearest-neighboring-site hopping $T_{Mo1} \rightarrow H \rightarrow T_{Mo2}$, and second-nearest-neighboring-site hopping is 1: 2/3: 1/6 (red curve, see Supplementary Fig. S13 and Note 1 for details).

1
2
3 The calculated results agree well with the experiment except the discrepancy for peak
4
5 3 at 0.64 nm due to the limited counts for long-range jumps and the possible involve-
6
7 ment of the less-favored $T_{Mo} \rightarrow T_S$ pathway.
8

9 Figure 5e shows the hopping step of Mo vacancy. The vacancy has a much lower
10
11 possibility to migrate in comparison with the case of adatom hopping, due to its much
12
13 higher energy barrier. Nearest-neighboring vacancy hopping is responsible for the
14
15 first peak and the second-nearest neighboring hopping contributes to the second peak
16
17 (see inset pictures).
18

20 Discussion

21
22 For adatom surface migration, the structural evolution give rise to novel elec-
23
24 tronic properties, worth exploring by DFT calculation. We discover that certain ada-
25
26 tom configurations (ground state T_{Mo} and metastable state H, T_S) all have magnetic
27
28 moments $>2 \mu_B$ (Supplementary Fig.S14). They are all highly spin-polarized and lo-
29
30 calized mainly on Mo adatom, with a minor contribution from the neighboring S at-
31
32 oms. The significant density of states (mostly from the adatom's d orbitals) at Fermi
33
34 levels may play an essential role in the physical properties of MoS_2 , such as defect
35
36 magnetism and reactivity as a catalyst.
37

38 The very different magnitudes of the energy barriers for Mo adatoms and vacan-
39
40 cies can be ascribed to their contrasting microscopic diffusion mechanisms. In surface
41
42 diffusion, adatoms not only relax more easily into the vacuum, but also retain the
43
44 largest number of unbroken Mo-S bonds. A Mo adatom starts with three Mo-S bonds
45
46 in the triangular-prismatic coordination as the most stable state⁴⁹ at T_{Mo} site, to two
47
48 Mo-S bonds when going through a S-S bridge site, then to three Mo-S bonds in octa-
49
50 hedral coordination⁴⁹ (H site) which is less energetically favorable. In the vacancy
51
52 diffusion, Mo's migration within the confined Mo atom layer involves the breaking
53
54 and reconnection of more covalent Mo-S bonds (Fig.2d): from initial Mo site
55
56 (most-stable with six Mo-S bonds), through a S-S bridge site (two short Mo-S bonds
57
58 with the 'Klein'-like S atoms, two long and weak Mo-S bonds with the 'zig-zag'-like
59
60

1
2
3 S atoms, Supplementary Fig. S11b), to a hollow-like site (metastable with six Mo-S
4 bonds).
5
6

7 Finally, the observation of vacancy hopping and metastable adatom T_S , with en-
8 ergy barriers much higher than the thermal energy available, is a sign that the migra-
9 tion is influenced or even driven by the electron beam. Hence it is necessary to quan-
10 tify the beam induced effect. Considering elastic knock-on scattering mechanism
11 (Supplementary Fig. S15, 16), we conclude that the vacancy migration is induced
12 solely by the electron beam and adatom migration is influenced by both thermal acti-
13 vation and beam-atom interaction. Fortunately, the beam-atom interaction allows us to
14 explore more comprehensively different kinetic pathways, especially for vacancy dy-
15 namics inaccessible by thermal activation at a “safe” temperature. One may also note
16 the slight atomic distortion of the lattice Mo below the migrating Mo in the vacancy
17 hopping in Fig.1, which can be interpreted as a temporary displacement resulted from
18 the electron beam radiation on the shallow potential landscape shown above. In the
19 future studies, it would be very interesting to carry out *in-situ* TEM observation at
20 variable temperatures and with higher temporal resolution, which would allow us to
21 capture more precisely the atomic dynamics and determine quantitatively the migra-
22 tion kinetics experimentally, as a complement to DFT calculations.
23
24
25
26
27
28
29
30
31
32
33
34
35
36

37 In summary, we have demonstrated an efficient survey of the migration energy
38 landscape using single-atom tracking and *ab-initio* calculation, providing a successful
39 paradigm for exploration of the microscopic mechanisms of atom diffusion in solids.
40 Its application in monolayer MoS₂ reveals the two-dimensional Mo diffusions on and
41 below surface with very different covalent bonds reorganization along their preferred
42 kinetic pathway. The results from our joint experiment-theory approach should be
43 useful in the rational design of practical applications of TMDs, such as catalysts and
44 ion intercalation in electrodes for batteries, as well as bringing us a new perspective
45 on solid state mass transport in general.
46
47
48
49
50
51
52
53
54

55
56 During the review of this work, we noticed another work focused on the migra-
57 tion of single Pt atoms in MoS₂ monolayer⁵⁶.
58
59
60

Methods

Sample preparation Monolayer molybdenum disulfide was prepared onto silicon substrate with a 300-nm-thick oxide capping layer through standard mechanical exfoliation from bulky MoS₂ single crystals (SPI Supplies Inc.) using scotch tapes. Selected atomically thin samples were then transferred onto TEM grids and annealed at 200°C in vacuum (10⁻⁴ Pa) to remove surface residues and contaminations before loading into the TEM chamber.

ADF-STEM characterization ADF-STEM imaging was carried out in a FEI Titan ChemiSTEM microscope equipped with a probe corrector and operated at 200 kV. The probe current was set to be about 60 pA and the convergence angle to 22 mrad. The collection angle of the ADF-STEM detector was adjusted to 50~200 mrad. Time lapsed ADF-STEM images were recorded in three seconds interval with a frame size of 512×512 pixels (corresponding to 10×10 nm²) and a pixel dwell time of 10 μs. The total electron dose to the specimen for each frame was estimated to be 9.7×10⁶ e⁻/nm². ADF-STEM images were analyzed after a drift correction and Wiener filtering for a better signal-to-noise (S/N) ratio (Supplementary Fig. S17). All the observations were carried out at room temperature.

ADF-STEM image simulations, as shown in the Supplementary Fig. S9, were achieved by QSTEM⁵⁰ with the simulation parameters (the convergence and acceptance angles, the probe size) kept almost the same as those used experimentally.

Further analysis including the population, the duration time (or lifetime), and hopping step statistics were performed based on the raw ADF-STEM images recorded from clean regions of MoS₂ monolayers.

DFT calculations.

Density functional theory calculations were performed using the generalized gradient approximation for the exchange-correlation potential, the projector augmented wave

1
2
3 method⁵¹ and a plane-wave basis set as implemented in the Vienna *ab-initio* simula-
4 tion package (VASP)⁵². The energy cutoff for plane wave was set to 300 eV for
5 structural relaxation and increased to 600 eV for total energy calculations. Dispersion
6 correction was made at the van der Waals density functional (vdW-DF) level, with the
7 optB86b functional for the exchange potential⁵³. An 8×8 slab of monolayer MoS₂
8 with a 15Å vacuum layer perpendicular to the atomic plane was employed in all cal-
9 culations to minimize the interactions between a defect and its images. All atoms in
10 the supercell were allowed to relax until the residual force per atom was less than 0.01
11 eV•Å⁻¹. Barriers of different diffusion pathways were revealed by the nudged elastic
12 band (NEB) method⁵⁴. The climbing-image technique⁵⁵ was used to precisely identify
13 the transition state and the barrier height.
14
15
16
17
18
19
20
21
22
23
24
25

26 **Potential landscape.** The two-dimensional potential landscape of the adatom was
27 calculated as follows. We first mapped 25 adsorption sites onto one third of the lattice
28 hexagon, with equal spacing in the atomic plane (xy plane). A Mo adatom was put at
29 these sites with its x, y coordinates fixed and z coordinates free to relax. Given the
30 minimum energies at those sites, we extrapolate the energies into the whole hexagon
31 to yield a continuous two-dimensional projected potential.
32
33
34
35
36
37
38

39 ASSOCIATED CONTENT

40
41 **Supporting information:** Including Supplementary Figures 1-19 and Notes 1, 2. This material is
42 available free of charge via the internet at <http://pubs.acs.org>.
43
44

45 AUTHOR INFORMATION

46 Corresponding Authors

47
48 *Correspondence and request for materials should be addressed to C.J. (chjin@zju.edu.cn), W.J.
49 (wji@ruc.edu.cn) or J.Y. (jun.yuan@york.ac.uk).
50
51
52
53

54 Author contributions

55 J.H. and Y.P. contributed equally to this work. C.J., W.J. and J.Y. conceived the research. J.H. and
56 D.L. contributed to the sample preparations. J.H., C.J., and J.Y. did the STEM characterizations,
57
58
59
60

1
2
3 data analysis and image simulations. Y.P., Z.H. and W.J. did the DFT calculations. All authors
4 discussed the results and contributed to the preparation of the manuscript.
5

6 Notes

7 The authors declare no competing financial interests.
8
9

10 ACKNOWLEDGEMENTS

11 This work was financially supported by the National Science Foundation of China under grant
12 Nos. 51472215, 51222202, 91433103, 11274380, 11622437 and 61674171, the National Basic
13 Research Program of China under grant Nos. 2014CB932500 and 2015CB921004, and the Fun-
14 damental Research Funds for the Central Universities and the Research Funds of Renmin Univer-
15 sity of China under grant No. 16XNLQ01. The work on electron microscopy was done at the
16 Center of Electron Microscopy of Zhejiang University. Calculations were performed at the Phys-
17 ics Lab of High-Performance Computing of Renmin University of China and Shanghai Super-
18 computer Center. We acknowledge Dr. Fang Lin for her assistance on Wiener filtering. J.Y.
19 acknowledged the Pao Yukung International Foundation for the Chairprofessorship in Zhejiang
20 University, and the financial support from the EPSRC (UK) funding EP/G070326 and EP/J022098.
21 We also acknowledge Prof. Ray F. Egerton for careful reading of this paper and useful
22 suggestions.
23
24
25
26
27
28
29
30
31
32

33 REFERENCES

- 34
35 1. Lin, Y. C.; Dumcenccon, D. O.; Huang, Y. S.; Suenaga, K. *Nat. Nanotechnol.* **2014**, *9*, 391-396.
36 2. Hannon, J. B.; Kodambaka, S.; Ross, F. M.; Tromp, R. M. *Nature* **2006**, *440*, 69-71.
37 3. Hofmann, S.; Csanyi, G.; Ferrari, A. C.; Payne, M. C.; Robertson, J. *Phys. Rev. Lett.* **2005**,
38 *95*, 036101.
39 4. Jensen, L. E.; Bjork, M. T.; Jeppesen, S.; Persson, A. I.; Ohlsson, B. J.; Samuelson, L. *Nano Lett.*
40 **2004**, *4*, 1961-1964.
41 5. Satterfield, C. N., *Mass transfer in heterogeneous catalysis*. (The MIT Press, 1970).
42 6. Mantina, M.; Wang, Y.; Arroyave, R.; Chen, L. Q.; Liu, Z. K.; Wolverton, C. *Phys. Rev. Lett.* **2008**,
43 *100*, 215901.
44 7. Bollinger, M. V.; Lauritsen, J. V.; Jacobsen, K. W.; Norskov, J. K.; Helveg, S.; Besenbacher, F.
45 *Phys. Rev. Lett.* **2001**, *87*, 196803.
46 8. Kibsgaard, J.; Lauritsen, J. V.; Laegsgaard, E.; Clausen, B. S.; Topsøe, H.; Besenbacher, F. *J. Am.*
47 *Chem. Soc.* **2006**, *128*, 13950-13958.
48 9. de Oteyza, D. G.; Gorman, P.; Chen, Y. C.; Wickenburg, S.; Riss, A.; Mowbray, D. J.; Etkin, G.;
49 Pedramrazi, Z.; Tsai, H. Z.; Rubio, A.; Crommie, M. F.; Fischer, F. R. *Science* **2013**, *340*,
50 1434-1437.
51 10. Tsong, T. T. *Phys. Today* **1993**, *46*, 24-31.
52 11. Pedersen, M. O.; Osterlund, L.; Mortensen, J. J.; Mavrikakis, M.; Hansen, L. B.; Stensgaard, I.;
53 Laegsgaard, E.; Norskov, J. K.; Besenbacher, F. *Phys. Rev. Lett.* **2000**, *84*, 4898-4901.
54
55
56
57
58
59
60

- 1
- 2
- 3 12. Schaub, R.; Wahlstrom, E.; Ronnau, A.; Laegsgaard, E.; Stensgaard, I.; Besenbacher, F. *Science*
- 4 **2003**, 299, 377-379.
- 5
- 6 13. Lo, R. L.; Hwang, I. S.; Ho, M. S.; Tsong, T. T. *Phys. Rev. Lett.* **1998**, 80, 5584-5587.
- 7
- 8 14. Brune, H.; Wintterlin, J.; Behm, R. J.; Ertl, G. *Phys. Rev. Lett.* **1992**, 68, 624-626.
- 9
- 10 15. Wang, K. D.; Zhang, C.; Loy, M. M. T.; Xiao, X. D. *Phys. Rev. Lett.* **2005**, 94, 036103.
- 11
- 12 16. Gao, L.; Liu, Q.; Zhang, Y. Y.; Jiang, N.; Zhang, H. G.; Cheng, Z. H.; Qiu, W. F.; Du, S. X.; Liu, Y.
- 13 Q.; Hofer, W. A.; Gao, H. J. *Phys. Rev. Lett.* **2008**, 101, 197209.
- 14
- 15 17. Shi, D. X.; Ji, W.; Yang, B.; Cun, H. Y.; Du, S. X.; Chi, L. F.; Fuchs, H.; Hofer, W. A.; Gao, H. J. *J.*
- 16 *Phys. Chem. C* **2009**, 113, 17643-17647.
- 17
- 18 18. Cheng, F.; Ji, W.; Leung, L.; Ning, Z. Y.; Polanyi, J. C.; Wang, C. G. *ACS Nano* **2014**, 8,
- 19 8669-8675.
- 20
- 21 19. Maksymovych, P.; Sorescu, D. C.; Yates, J. T. *Phys. Rev. Lett.* **2006**, 97, 146103.
- 22
- 23 20. Lin, Y. C.; Dumcenco, D. O.; Komsa, H. P.; Niimi, Y.; Krasheninnikov, A. V.; Huang, Y. S.;
- 24 Suenaga, K. *Adv. Mater.* **2014**, 26, 2857-2861.
- 25
- 26 21. Komsa, H.-P.; Kurasch, S.; Lehtinen, O.; Kaiser, U.; Krasheninnikov, A. V. *Phys. Rev. B* **2013**, 88,
- 27 035301; Oh, S. H.; Benthem, K. v.; Molina, S. I.; Borisevich, A. Y.; Luo, W.; Werner, P.; Zakharov,
- 28 N. D.; Kumar, D.; Pantelides, S. T.; Pennycook, S. J. *Nano Lett.* **2008**, 8, 1016-1019.
- 29
- 30 22. Lehtinen, O.; Kurasch, S.; Krasheninnikov, A. V.; Kaiser, U. *Nat. Commun.* **2013**, 4, 2098.
- 31
- 32 23. Lee, J.; Zhou, W.; Pennycook, S. J.; Idrobo, J. C.; Pantelides, S. T. *Nat. Commun.* **2013**, 4, 1650.
- 33
- 34 24. Lehtinen, P. O.; Foster, A. S.; Ayuela, A.; Krasheninnikov, A.; Nordlund, K.; Nieminen, R. M.
- 35 *Phys. Rev. Lett.* **2003**, 91, 017202.
- 36
- 37 25. Kurasch, S.; Kotakoski, J.; Lehtinen, O.; Skakalova, V.; Smet, J.; Krill, C. E.; Krasheninnikov, A.
- 38 V.; Kaiser, U. *Nano Lett.* **2012**, 12, 3168-3173.
- 39
- 40 26. Gan, Y. J.; Sun, L. T.; Banhart, F. *Small* **2008**, 4, 587-591; Girit, Ç. Ö.; Meyer, J. C.; Erni, R.;
- 41 Rossell, M. D.; Kisielowski, C.; Yang, L.; Park, C.-H.; Crommie, M.; Cohen, M. L.; Louie, S. G.
- 42 *Science* **2009**, 323, 1705-1708.
- 43
- 44 27. Zhang, W.; Sun, L. T.; Xu, Z. J.; Krasheninnikov, A. V.; Huai, P.; Zhu, Z. Y.; Banhart, F. *Phys. Rev.*
- 45 *B* **2010**, 81, 125425.
- 46
- 47 28. Cretu, O.; Krasheninnikov, A. V.; Rodriguez-Manzo, J. A.; Sun, L. T.; Nieminen, R. M.; Banhart,
- 48 F. *Phys. Rev. Lett.* **2010**, 105, 196102.
- 49
- 50 29. Nakada, K.; Ishii, A. *Solid State Commun.* **2011**, 151, 13-16.
- 51
- 52 30. Krasheninnikov, A. V.; Nordlund, K.; Lehtinen, P. O.; Foster, A. S.; Ayuela, A.; Nieminen, R. M.
- 53 *Phys. Rev. B* **2004**, 69, 073402.
- 54
- 55 31. Kotakoski, J.; Mangler, C.; Meyer, J. C. *Nat. Commun.* **2014**, 5, 3991.
- 56
- 57 32. Robertson, A. W.; Allen, C. S.; Wu, Y. A.; He, K.; Olivier, J.; Neethling, J.; Kirkland, A. I.; Warner,
- 58 J. H. *Nat. Commun* **2012**, 3, 1144.
- 59
- 60 33. Wang, W. L.; Santos, E. J. G.; Jiang, B.; Cubuk, E. D.; Ophus, C.; Centeno, A.; Pesquera, A.;
- Zurutuza, A.; Ciston, J.; Westervelt, R.; Kaxiras, E. *Nano Lett.* **2014**, 14, 450-455.
34. Warner, J. H.; Margine, E. R.; Mukai, M.; Robertson, A. W.; Giustino, F.; Kirkland, A. I. *Science*
- 2012**, 337, 209-212.
35. Ishikawa, R.; Mishra, R.; Lupini, A. R.; Findlay, S. D.; Taniguchi, T.; Pantelides, S. T.; Pennycook,
- S. J. *Phys. Rev. Lett.* **2014**, 113, 155501.
36. Lin, J.; Pantelides, S. T.; Zhou, W. *ACS Nano* **2015**, 9, 5189-5197.
37. Wang, S.; Lee, G.-D.; Lee, S.; Yoon, E.; Warner, J. H. *ACS Nano* **2016**, 10, 5419-5430.

- 1
 - 2
 - 3
 - 4
 - 5
 - 6
 - 7
 - 8
 - 9
 - 10
 - 11
 - 12
 - 13
 - 14
 - 15
 - 16
 - 17
 - 18
 - 19
 - 20
 - 21
 - 22
 - 23
 - 24
 - 25
 - 26
 - 27
 - 28
 - 29
 - 30
 - 31
 - 32
 - 33
 - 34
 - 35
 - 36
 - 37
 - 38
 - 39
 - 40
 - 41
 - 42
 - 43
 - 44
 - 45
 - 46
 - 47
 - 48
 - 49
 - 50
 - 51
 - 52
 - 53
 - 54
 - 55
 - 56
 - 57
 - 58
 - 59
 - 60
38. Wang, Q. H.; Kalantar-Zadeh, K.; Kis, A.; Coleman, J. N.; Strano, M. S. *Nat. Nanotechnol.* **2012**, 7, 699-712.
39. Norskov, J. K.; Bligaard, T.; Rossmeisl, J.; Christensen, C. H. *Nat. Chem.* **2009**, 1, 37-46.
40. Hinnemann, B.; Moses, P. G.; Bonde, J.; Jorgensen, K. P.; Nielsen, J. H.; Horch, S.; Chorkendorff, I.; Norskov, J. K. *J. Am. Chem. Soc.* **2005**, 127, 5308-5309.
41. Gao, M. R.; Liang, J. X.; Zheng, Y. R.; Xu, Y. F.; Jiang, J.; Gao, Q.; Li, J.; Yu, S. H. *Nat. Commun.* **2015**, 6, 5982.
42. Sun, X.; Dai, J.; Guo, Y. Q.; Wu, C. Z.; Hu, F. T.; Zhao, J. Y.; Zeng, X. C.; Xie, Y. *Nanoscale* **2014**, 6, 8359-8367.
43. Xie, J. F.; Zhang, H.; Li, S.; Wang, R. X.; Sun, X.; Zhou, M.; Zhou, J. F.; Lou, X. W.; Xie, Y. *Adv. Mater.* **2013**, 25, 5807.
44. Liu, H.; Su, D. W.; Zhou, R. F.; Sun, B.; Wang, G. X.; Qiao, S. Z. *Adv. Energy Mater.* **2012**, 2, 970-975.
45. Li, W. F.; Yang, Y. M.; Zhang, G.; Zhang, Y. W. *Nano Lett.* **2015**, 15, 1691-1697.
46. Lee, G. D.; Wang, C. Z.; Yoon, E.; Hwang, N. M.; Kim, D. Y.; Ho, K. M. *Phys. Rev. Lett.* **2005**, 95, 205501.
47. Zhou, W.; Zou, X. L.; Najmaei, S.; Liu, Z.; Shi, Y. M.; Kong, J.; Lou, J.; Ajayan, P. M.; Yakobson, B. I.; Idrobo, J. C. *Nano Lett.* **2013**, 13, 2615-2622.
48. Hardcastle, T. P.; Seabourne, C. R.; Zan, R.; Brydson, R. M. D.; Bangert, U.; Ramasse, Q. M.; Novoselov, K. S.; Scott, A. J. *Phys. Rev. B* **2013**, 87, 195430.
49. Chhowalla, M.; Shin, H. S.; Eda, G.; Li, L. J.; Loh, K. P.; Zhang, H. *Nat. Chem.* **2013**, 5, 263-275.
50. Koch, C. T. QSTEM (2010); Koch, C.T. Determination of core structure periodicity and point defect density along dislocations. (Ph.D thesis, Arizona State University 2002).
51. Blochl, P. E. *Phys. Rev. B* **1994**, 50, 17953-17979.
52. Kresse, G.; Furthmuller, J. *Phys. Rev. B* **1996**, 54, 11169-11186.
53. Klimes, J.; Bowler, D. R.; Michaelides, A. *Phys. Rev. B* **2011**, 83, 195131.
54. Henkelman, G.; Jonsson, H. *J. Chem. Phys.* **2000**, 113, 9978-9985.
55. Henkelman, G.; Uberuaga, B. P.; Jonsson, H. *J. Chem. Phys.* **2000**, 113, 9901-9904.
56. Li, H.; Wang, S.; Sawada, H.; Han, G. G.; Samuels, T.; Allen, C. S.; Kirkland, A. I.; Grossman, J. C.; Warner, J. H. *ACS Nano* **2017**, 11, 3392-3403.

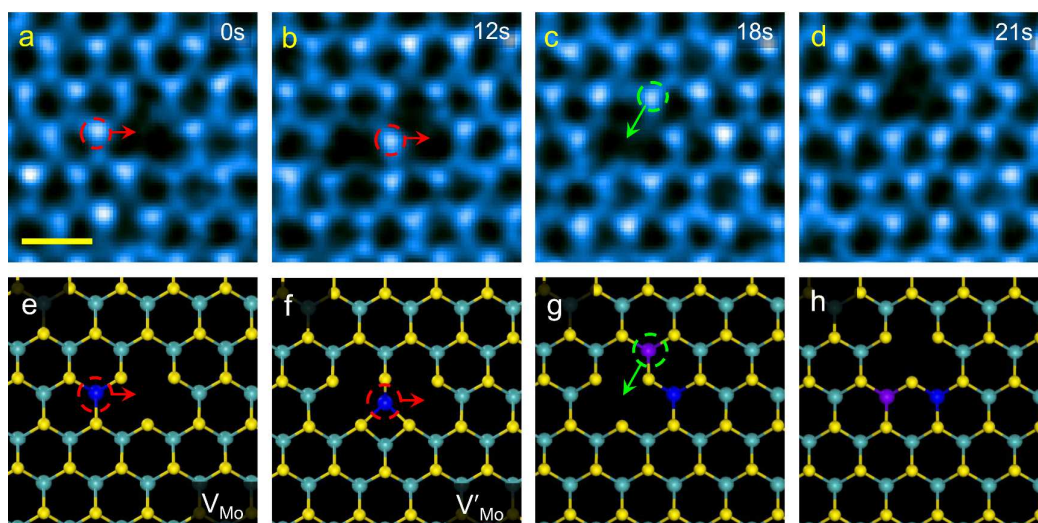


Figure 1. Atomic-scale migration of vacancy defects. (a-d) Time-lapse series of experimental ADF images of a Mo vacancy. Scale bar: 0.5nm. (e-h) DFT-relaxed atomic structures corresponding to the evolution in a-d from the Mo vacancy (V_{Mo} in a) to its metastable state (V'_{Mo} in b) and then to another Mo vacancy V_{Mo} in c. Scale bar: 0.5nm. Note the vacancy migration is actually the motion of a neighboring Mo atom, shown in blue or purple.


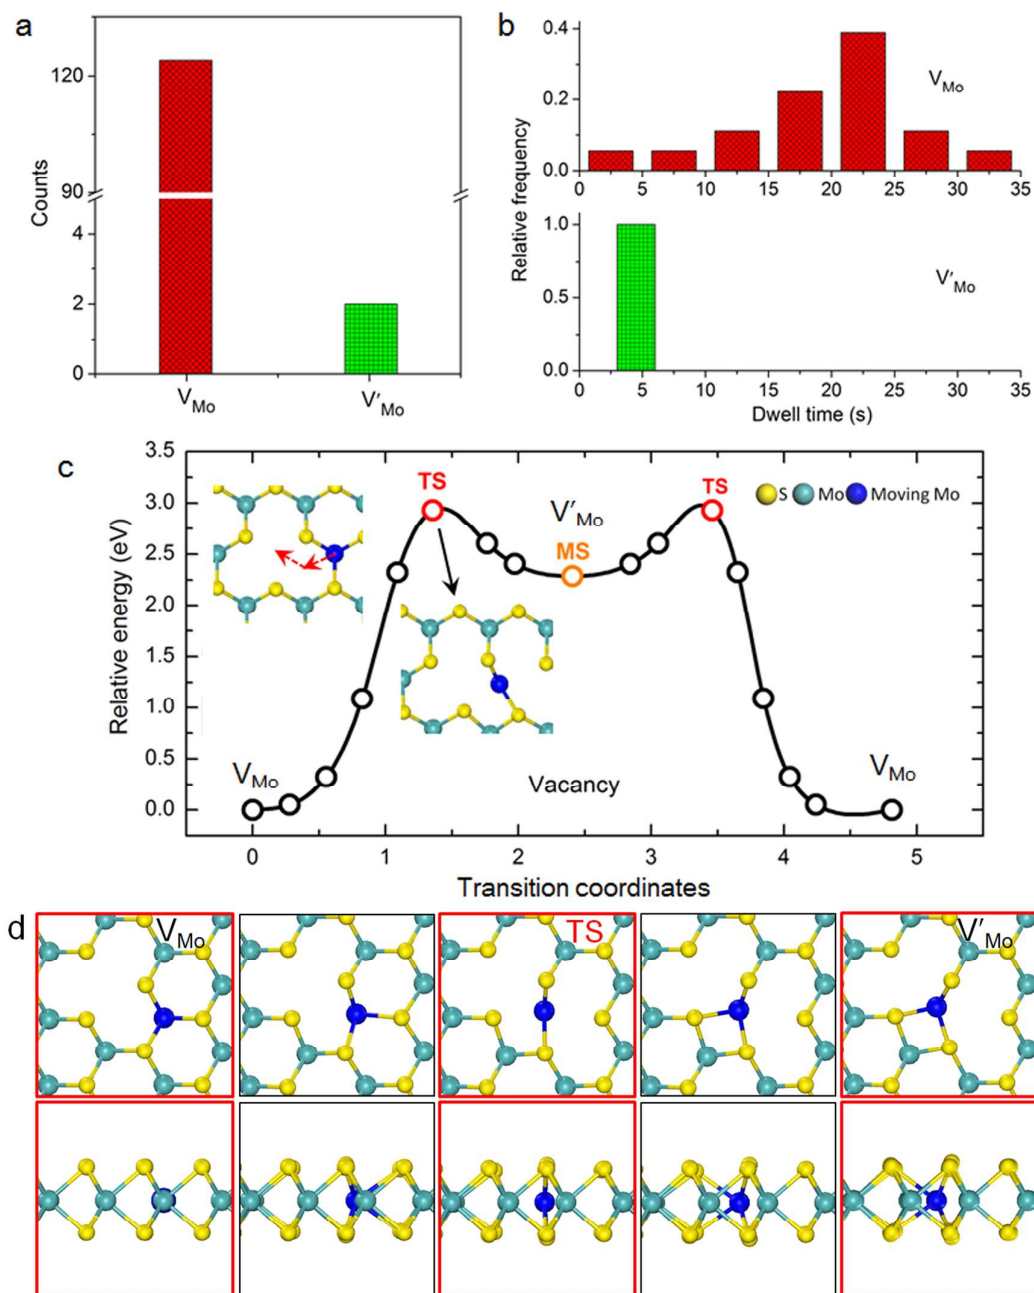


Figure 2. States of vacancy and their evolution. (a-b) Statistical counts and dwell time of vacancies and their metastable states during the migration of a Mo vacancy. (c) DFT calculated migration pathway of Mo vacancy. The dynamic process is shown by the inset atomic models with arrows illustrating the migration pathway of the neighboring Mo atom. (d) Detailed atomic dynamics of Mo vacancy migration with top-view and side-view, respectively. Note the $V_{Mo} \rightarrow V'_{Mo} \rightarrow V_{Mo}$ transition in c is symmetric, hence only the first half process of vacancy migration (right red arrow in c) is drawn detailed in d. Also note the top-view of the top-row structures

1
2
3
4 in **d** is rotated with respect to the structures in **c** and that in **Fig. 1**.
5
6
7
8

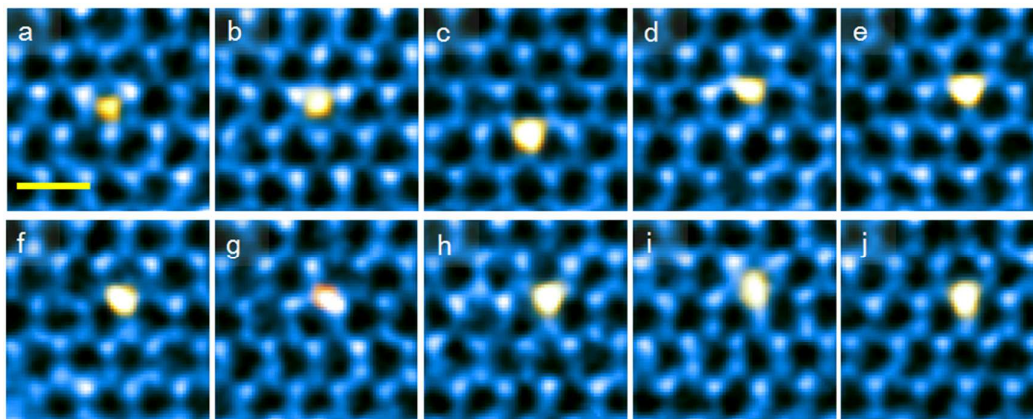

23 **Figure 3. Atomic migration of Mo adatom defects.** (a-j) Experimental time sequential of ADF
24 images of Mo adatom hopping as an example. Time interval: 3s. Scale bar: 0.5nm. Different false
25 colors are used for better visualization.
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

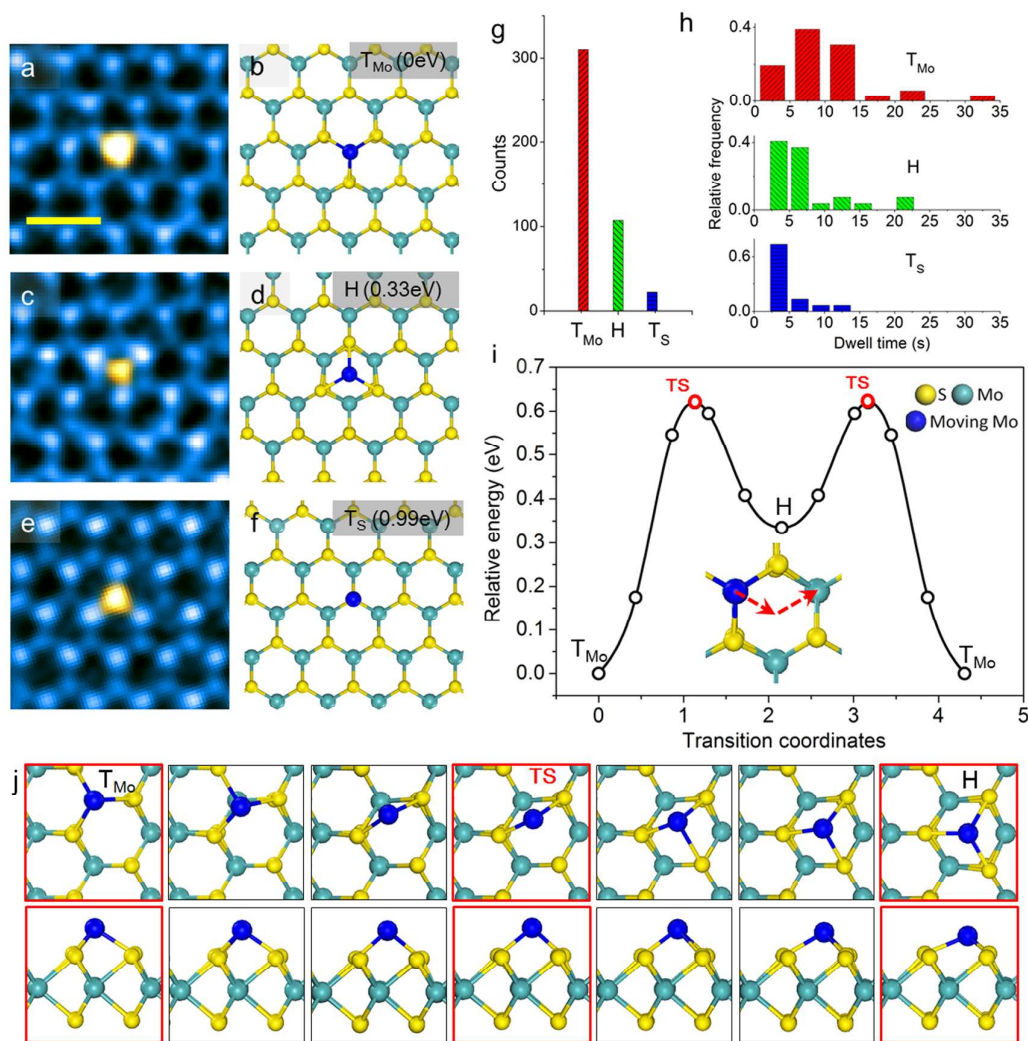


Figure 4. Adsorption states and their evolution along the kinetic pathway. (a-f) Atomically resolved ADF images and structure models of different adsorption states on top of Mo site (T_{Mo}), at hexagon-center or hollow site (H), and on top of S site (T_S), respectively. Scale bar: 0.5nm. False color is used to better illustrate the adatom configuration. Relative energies of different adatom states are given. (g) Statistical counts of different adsorption states in a,c,e. (h) Statistical dwell time of different adatom structures. (i) DFT revealed energetics and pathway for evolution between ground state T_{Mo} , transition state TS, and metastable state H. (j) Detailed atomic dynamics of transition from T_{Mo} to H with top view and side view of the three dimensional atomic structure respectively. Note the $T_{Mo1} \rightarrow H \rightarrow T_{Mo2}$ transition in i is symmetric, hence only the first half process (left red arrows in i) is drawn.



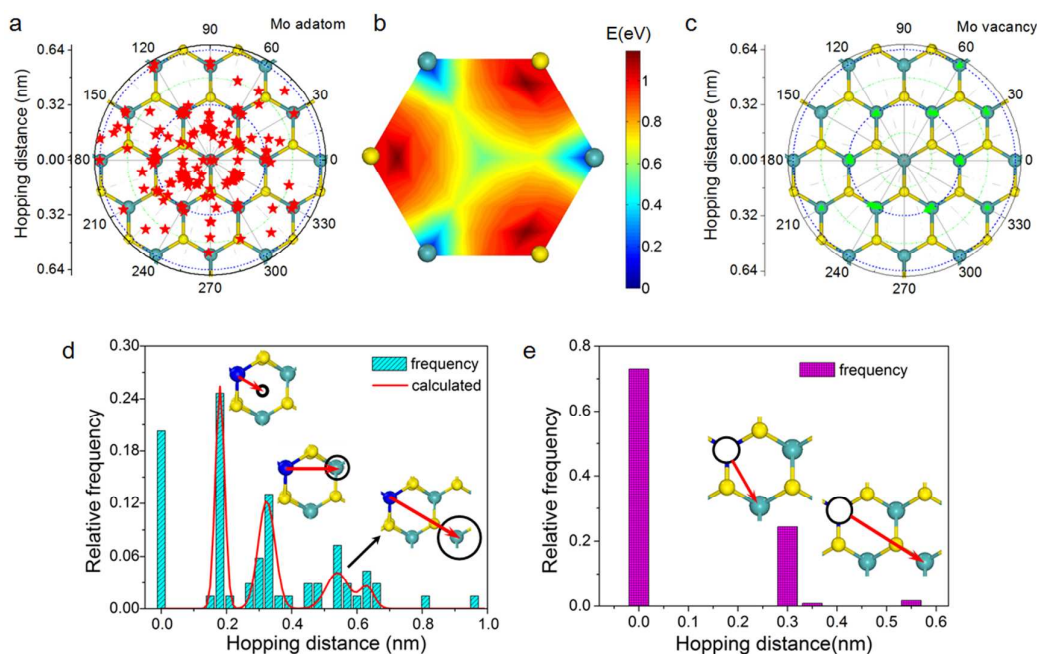



Figure 5. Statistical hopping steps of adatom and vacancy defects. (a) Polar scatter diagram of hopping steps from the coordinate origin where Mo lattice locates. Red star dots indicate the final position of adatom hopping from the initial state at the origin. The data is obtained from analyzing over 50 time-series of ADF images of adatom defects on MoS₂ monolayers, (b) DFT calculated two-dimensional potential diagram for a Mo adatom on the hexagonal MoS₂ lattice. T_{Mo} sites and hexagon center H site are potential valleys. (c) Polar scatter diagram showing hopping steps of Mo vacancy from the origin. (d) Hopping step statistics of Mo adatom migration. Insets show the corresponding atomic hopping models which are supported by the calculated probability distribution. (e) Hopping step distribution of Mo vacancy with inset models presenting the migration process.

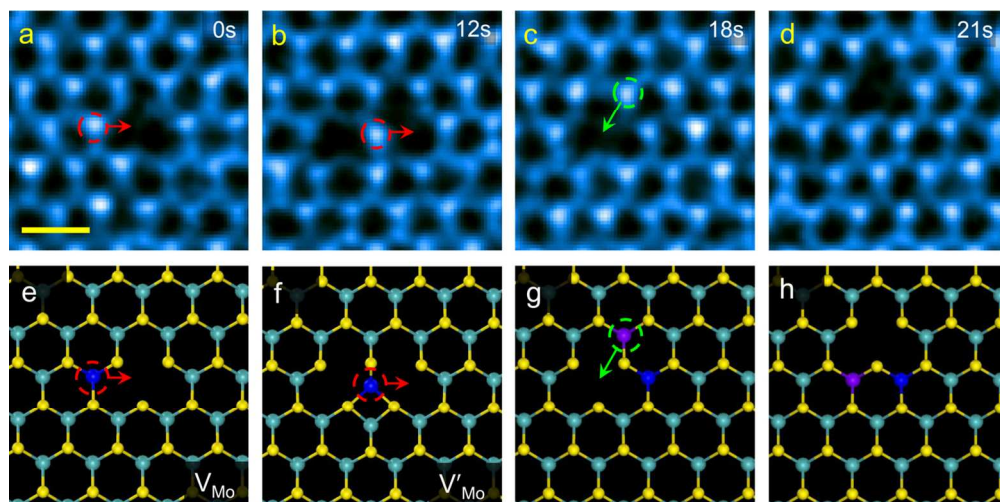


124x61mm (300 x 300 DPI)

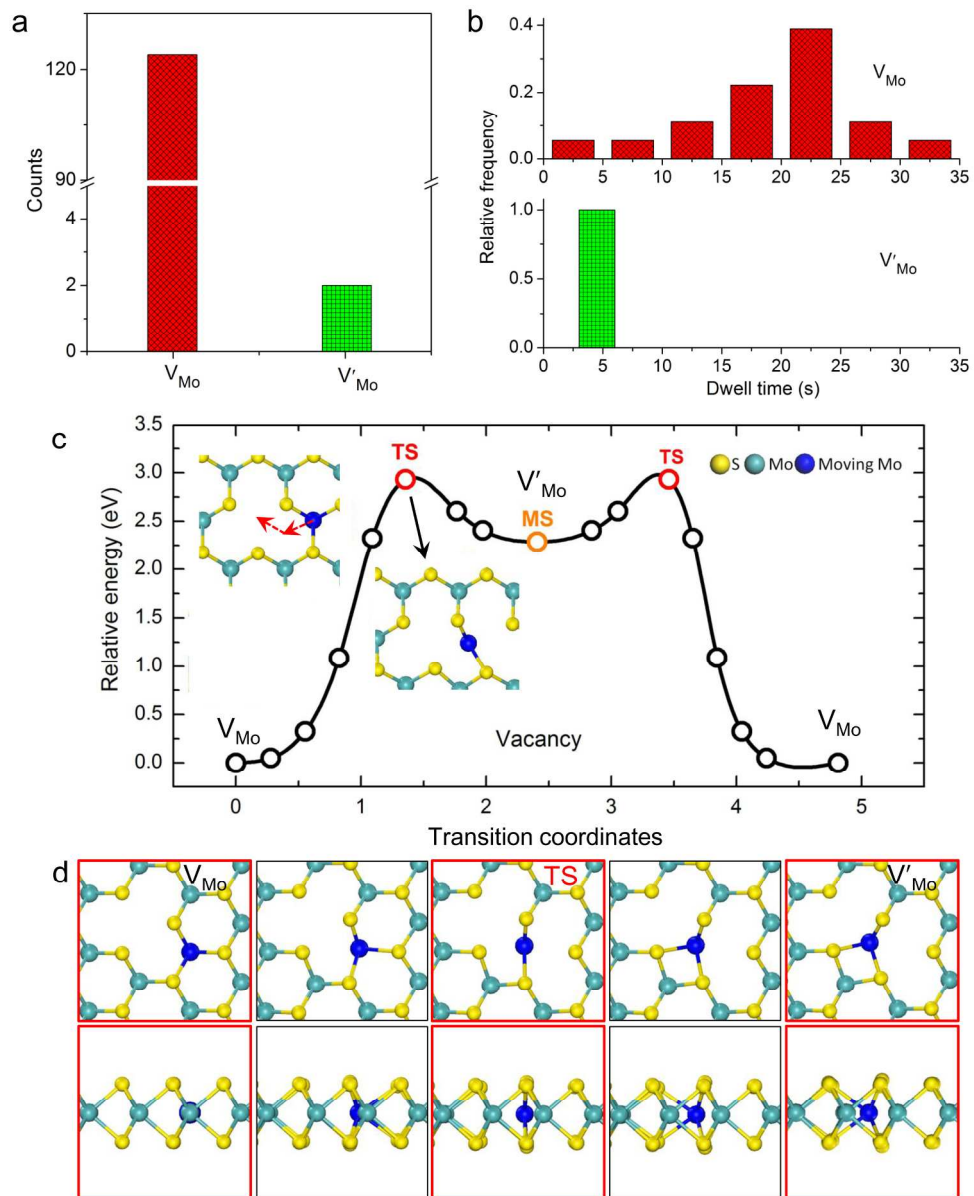


200x247mm (300 x 300 DPI)

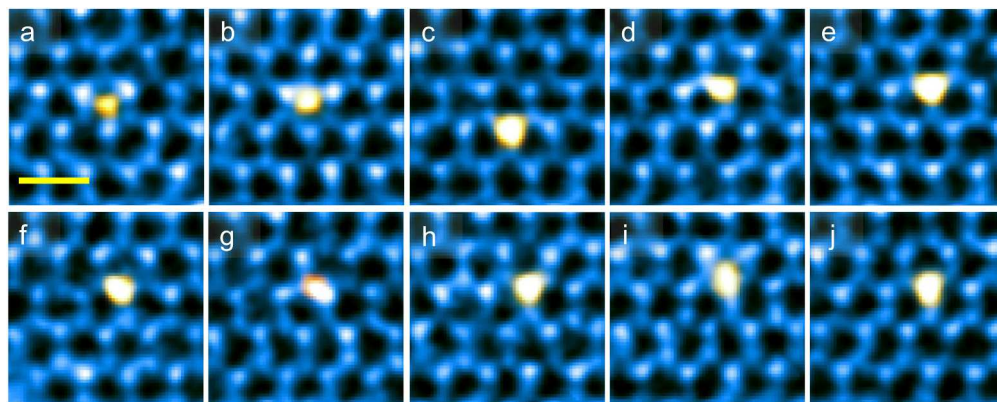

230x92mm (300 x 300 DPI)

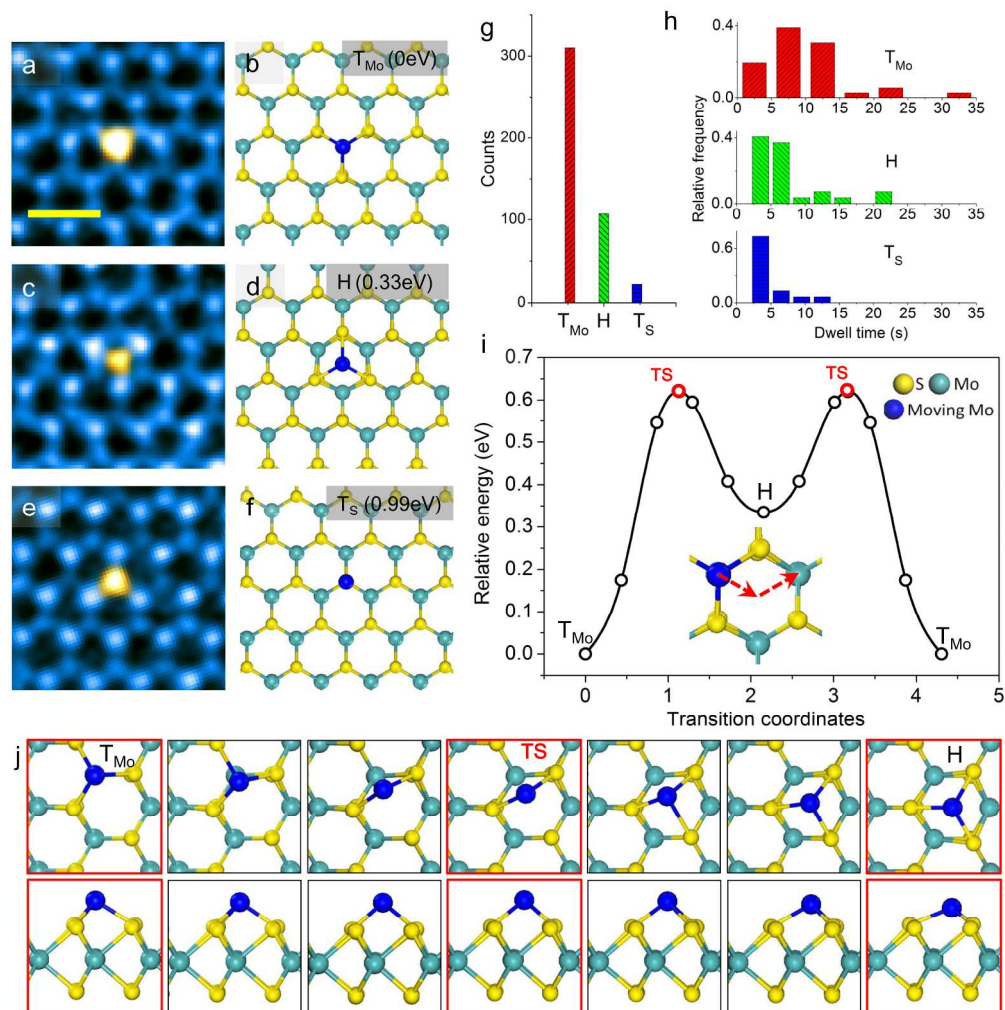

230x233mm (300 x 300 DPI)

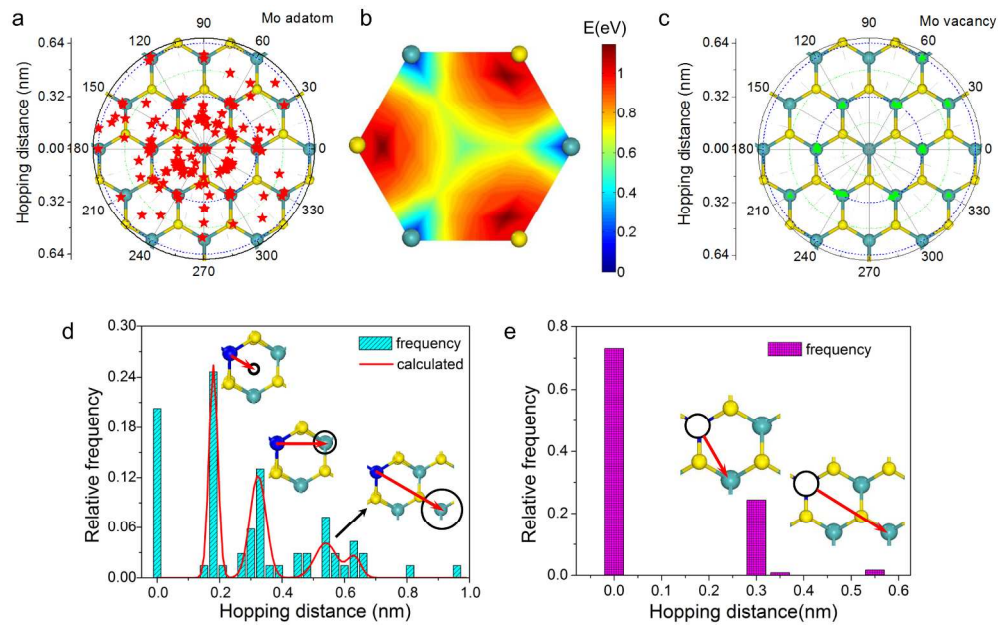

235x146mm (300 x 300 DPI)