

This is a repository copy of *Magnetic domain wall engineering in a nanoscale permalloy junction*.

White Rose Research Online URL for this paper:

<https://eprints.whiterose.ac.uk/123911/>

Version: Published Version

---

**Article:**

Wang, Junlin [orcid.org/0000-0002-0383-7864](https://orcid.org/0000-0002-0383-7864), Zhang, Xichao, Lu, Xianyang et al. (6 more authors) (2017) Magnetic domain wall engineering in a nanoscale permalloy junction. Applied Physics Letters. 072401. 072401-1 072401-5. ISSN 0003-6951

<https://doi.org/10.1063/1.4985662>

---

**Reuse**

This article is distributed under the terms of the Creative Commons Attribution (CC BY) licence. This licence allows you to distribute, remix, tweak, and build upon the work, even commercially, as long as you credit the authors for the original work. More information and the full terms of the licence here:

<https://creativecommons.org/licenses/>

**Takedown**

If you consider content in White Rose Research Online to be in breach of UK law, please notify us by emailing [eprints@whiterose.ac.uk](mailto:eprints@whiterose.ac.uk) including the URL of the record and the reason for the withdrawal request.

## Magnetic domain wall engineering in a nanoscale permalloy junction

Junlin Wang, Xichao Zhang, Xianyang Lu, Jason Zhang, Yu Yan, Hua Ling, Jing Wu, Yan Zhou, and Yongbing Xu

Citation: [Appl. Phys. Lett.](#) **111**, 072401 (2017);

View online: <https://doi.org/10.1063/1.4985662>

View Table of Contents: <http://aip.scitation.org/toc/apl/111/7>

Published by the [American Institute of Physics](#)

---

### Articles you may be interested in

[Fast switching and signature of efficient domain wall motion driven by spin-orbit torques in a perpendicular anisotropy magnetic insulator/Pt bilayer](#)

Applied Physics Letters **111**, 072406 (2017); 10.1063/1.4994050

[Negative tunneling magnetoresistance of Fe/MgO/NiO/Fe magnetic tunnel junction: Role of spin mixing and interface state](#)

Applied Physics Letters **111**, 072405 (2017); 10.1063/1.4999764

[Electric-field effect on spin-wave resonance in a nanoscale CoFeB/MgO magnetic tunnel junction](#)

Applied Physics Letters **111**, 072403 (2017); 10.1063/1.4999312

[On the limits of coercivity in permanent magnets](#)

Applied Physics Letters **111**, 072404 (2017); 10.1063/1.4999315

[Electric-field tuning of ferromagnetic resonance in CoFeB/MgO magnetic tunnel junction on a piezoelectric PMN-PT substrate](#)

Applied Physics Letters **111**, 062401 (2017); 10.1063/1.4997915


[Excitation of coherent propagating spin waves in ultrathin CoFeB film by voltage-controlled magnetic anisotropy](#)

Applied Physics Letters **111**, 052404 (2017); 10.1063/1.4990724

---



Lake Shore  
CRYOTRONICS

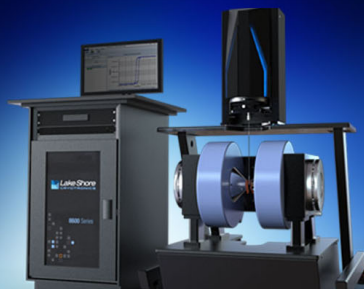

**8600 Series VSM**

For fast, highly sensitive  
measurement performance

LEARN MORE 

## Magnetic domain wall engineering in a nanoscale permalloy junction

Junlin Wang,<sup>1,2</sup> Xichao Zhang,<sup>3</sup> Xianyang Lu,<sup>4</sup> Jason Zhang,<sup>4</sup> Yu Yan,<sup>2</sup> Hua Ling,<sup>2</sup> Jing Wu,<sup>4</sup> Yan Zhou,<sup>3</sup> and Yongbing Xu<sup>1,2,a)</sup>

<sup>1</sup>York-Nanjing International Center of Spintronics (YNICS), Collaborative Innovation Center of Advanced Microstructures, School of Electronic Science and Engineering, Nanjing University, Nanjing 210093, China  
<sup>2</sup>Spintronics and Nanodevice laboratory, Department of Electronics, The University of York, York YO10 5DD, United Kingdom

<sup>3</sup>School of Science and Engineering, The Chinese University of Hong Kong, Shenzhen 518067, China

<sup>4</sup>Department of Physics, The University of York, York YO10 5DD, United Kingdom

(Received 31 May 2017; accepted 4 August 2017; published online 14 August 2017)

Nanoscale magnetic junctions provide a useful approach to act as building blocks for magnetoresistive random access memories (MRAM), where one of the key issues is to control the magnetic domain configuration. Here, we study the domain structure and the magnetic switching in the Permalloy (Fe<sub>20</sub>Ni<sub>80</sub>) nanoscale magnetic junctions with different thicknesses by using micromagnetic simulations. It is found that both the 90° and 45° domain walls can be formed between the junctions and the wire arms depending on the thickness of the device. The magnetic switching fields show distinct thickness dependencies with a broad peak varying from 7 nm to 22 nm depending on the junction sizes, and the large magnetic switching fields favor the stability of the MRAM operation. © 2017 Author(s). All article content, except where otherwise noted, is licensed under a Creative Commons Attribution (CC BY) license (<http://creativecommons.org/licenses/by/4.0/>). [<http://dx.doi.org/10.1063/1.4985662>]

The magnetoresistive random access memory (MRAM)<sup>1–6</sup> based on the tunneling magnetic resistance (TMR) effect has the potential to replace all existing memory devices in a computer or other hard disk drives as it could provide a high read/write operation speed and is also nonvolatile.<sup>7–9</sup> On the other hand, the magnetic domain wall gives a flexible approach in the data storage and the logic circuit.<sup>10–13</sup> Compared with the TMR-based MRAM devices, a domain wall motion-based magnetic junction could have a single layer structure, which might have great advantages in terms of fabrication and application.<sup>14,15</sup> The magnetic junction shows several types of the magnetoresistance effect by applying the magnetic field.<sup>16,17</sup>

The magnetic switching in the junction structure can be controlled by either the external magnetic field or the applied electrical current.<sup>18,19</sup> Recently, it has been reported that the magnetic switching induced by the spin-transfer torque (STT) can enable the junction to work as a STT-MRAM device.<sup>20,21</sup> There are also reports about the spin-polarized current that can induce the junction to generate spin waves.<sup>22–24</sup> It is found that the Permalloy junction has several metastable magnetization states, which can be used to store the information.<sup>18</sup> Thus, the reliable control of the magnetic domain configuration in the magnetic junction is an important task. In this letter, we present a micromagnetic study of the domain structures and the magnetic switching in the nanoscale Permalloy junctions within magnetic cross structures with different thicknesses. The numerical simulations are carried out by using the Object Oriented MicroMagnetic Framework (OOMMF) software.<sup>25</sup> It is found that the junction thickness has distinct effects on the domain wall configuration, the initial magnetic switching, and the coercivity. In

the initial states, both 45° and 90° domain walls are found to be formed in the studied model. Both the initial magnetic switching and the coercivity show the nonlinear dependences on the thickness, indicating the importance of controlling the thickness for the writing process when the nanoscale Permalloy junction works as a building block for information storage devices.

The micromagnetic simulations are performed using the standard micromagnetic simulator OOMMF software,<sup>25</sup> which stands on the Landau-Lifshitz-Gilbert equation<sup>26,27</sup>

$$\frac{d\mathbf{M}}{dt} = -|\gamma|\mathbf{M} \times \mathbf{H}_{\text{eff}} + \frac{\alpha}{M_S} \left( \mathbf{M} \times \frac{d\mathbf{M}}{dt} \right), \quad (1)$$

where  $\mathbf{M}$  is the magnetization of the magnetic layer,  $M_S$  is the saturation magnetization,  $\gamma$  is the Gilbert gyromagnetic ratio, and  $\alpha$  is the damping constant.  $\mathbf{H}_{\text{eff}}$  is the effective field, which is derived from the magnetic energy density

$$\mathbf{H}_{\text{eff}} = -\mu_0^{-1} \frac{\delta \varepsilon}{\delta \mathbf{M}}, \quad (2)$$

where  $\varepsilon$  contains the Heisenberg exchange, anisotropy, applied magnetic field, and demagnetization energy terms.

The magnetic material used for the micromagnetic simulation is Permalloy, i.e., Fe<sub>20</sub>Ni<sub>80</sub> alloy, which has a low coercivity and a high permeability. The size of the cross structure of the nanoscale junction is defined as 10 nm × 10 nm with a varying thickness from 2.5 nm to 25 nm, and the length of all the wire arms is fixed at 200 nm. The saturation magnetization is equal to 8.6 × 10<sup>5</sup> A/m. The exchange stiffness and the crystalline anisotropy constant are set at 13 × 10<sup>-12</sup> J/m and 0 J/m<sup>3</sup>, respectively. The simulation cell size is set as 2.5 nm × 2.5 nm × 2.5 nm, which is compared with the exchange length (5.3 nm) of Permalloy.

<sup>a)</sup>Electronic mail: yongbing.xu@york.ac.uk

The initially relaxed magnetization distributions around the junctions of the cross structures with different thicknesses are shown in Fig. 1(a), which are obtained by relaxing the cross structures with random magnetization distributions. The spins in the wire arms are all aligned in parallel along the wire directions due to the strong shape anisotropy. There are three types of domain configurations around the junctions. For the junctions with the thicknesses of 2.5 nm, 7.5 nm, and 12.5 nm, the spins in the junction are aligned in parallel with the spins in one of the wires, and the  $90^\circ$  domain walls form between another wires. For the cases with the thicknesses of 5 nm and 15 nm, the spins in the junctions are aligned largely in parallel, which can be described as a single magnetic domain or a coherent spin block (CSB), and the spin direction of these CSBs is in  $45^\circ$  with those in both wires. For the cases with thickness of 10 nm, the spins in the junction are form a  $90^\circ$  domain wall within the junction. Indeed, the initial magnetization distribution in the cross structure can also be controlled by the applying an external magnetic field. As shown in Fig. 1(b), the initial magnetization distribution in the cross structure can be modified to be  $45^\circ$  domain by applying a magnetic field pointing at an angle of  $45^\circ$  to the  $+x$ -direction. The required amplitude of the magnetic field corresponding to different thickness is given in Fig. 1(c). The applied magnetic field changes the domain structure to the coherence switching mode from the initially relaxed states, where the required magnetic field is different for samples with different initially relaxed magnetization distribution and thickness. Note that the magnetization distribution configuration in the thickness direction is uniform (see [supplementary material](#), Fig. S1).

In the following, we study the magnetization switching process driven by an external magnetic field for the junctions with different thicknesses. The simulated hysteresis loops are the same in different layers of the device. Figure 2 shows the result for the 2.5-nm-thick junction. The magnetic field is first applied along the  $+x$ -direction, of which the amplitude first increases from 0 Oe to 2000 Oe and reduces to 0 Oe. Then, the magnetic field changes in the same manner but along the  $-x$ -direction. The simulated hysteresis loop is given in Fig. 2, and the magnetization configurations illustrated in Fig. 3 are corresponding to the marked states in the hysteresis loop given in Fig. 2, which represent the magnetic switching process in the nanoscale junction. The initial magnetization configuration in the nanoscale junction is given in Fig. 3. The magnetic field of the first magnetic switching from the initially relaxed state to the state with a  $45^\circ$  domain wall is defined as the initial magnetization switching field ( $H_i$ ), which is indicated in Fig. 2(a). As the applied magnetic field increases from 0 Oe to 2000 Oe, the direction of the magnetization in the junction is switched where the amplitude of the critical switching field, i.e., the coercivity ( $H_c$ ) of the junction as indicated in Fig. 2(b), is equal to 1050 Oe.

The snapshots of the switching process given in Fig. 3 further show that the switching of the magnetization in the junction is coherent. The angle between the  $x$ -axis and the spins at the junction is defined as  $\theta$ . Before applying the magnetic field, the spins in the junction are in parallel with the  $y$ -axis, and the  $\theta$  is equal to  $-90^\circ$ . By increasing the applied magnetic field above 2000 Oe,  $\theta$  increases and then reaches  $0^\circ$ . When the applied magnetic field is reduced to 0 Oe,  $\theta$  decreases to  $-45^\circ$ . That means in the remanence

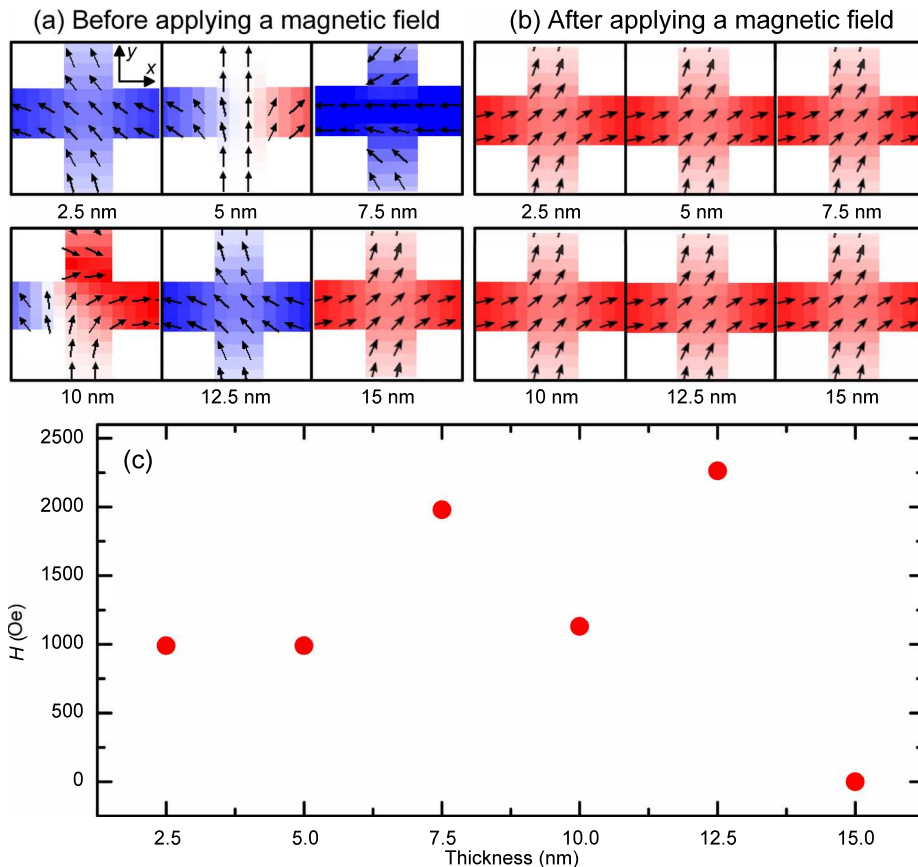


FIG. 1. (a) The magnetic domain configurations in the cross structure relaxed from random magnetization distributions for different thicknesses. (b) The magnetic domain configurations obtained by applying a magnetic field. (c) The amplitude of the magnetic field which changes the domain configurations shown in (a) to those shown in (b).

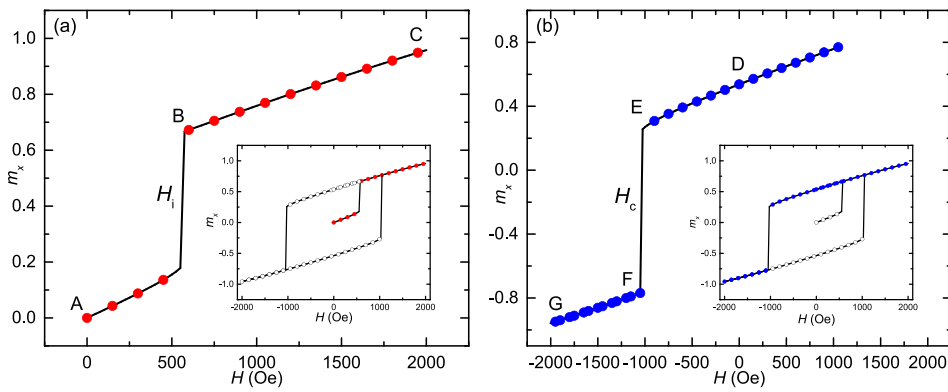


FIG. 2. The hysteresis loop for the cross structure with the thickness of 2.5 nm. The initial switching magnetic field ( $H_i$ ) and the coherence switching magnetic field ( $H_c$ ) are indicated in (a) and (b), respectively.

state, the spins in the junction are aligned  $45^\circ$  away from the wire direction, and  $45^\circ$  domain walls are formed between the junction and the wires. When the applied magnetic field decreases from 0 Oe to  $-2000$  Oe in the  $x$ -direction, the spins change to be paralleled with the  $x$ -direction, and the  $\theta$  increases from  $-45^\circ$  to  $0^\circ$ . It is found that the whole magnetization switching process in the junction is coherent and reversible.

The typical spin configurations during the magnetic switching process of the junctions with different thicknesses are shown in Fig. 4. From Fig. 4(a), we found that the junction with a different thickness usually has a different relaxed state. Before using the magnetic field to achieve reversible magnetic switching in the cross structure, the spins in the cross structure have to be tuned to the coherent switching mode. The coherent switching mode is defined as the states in Fig. 3(b) which shows  $45^\circ$  domain walls. The processes to enable the coherence switching modes are shown in Fig. 4. Unlike the magnetic switching processes shown in Fig. 3, the relaxed magnetization configuration at 0 Oe is different from the junctions with the thicknesses of 5 nm, 7.5 nm, 10 nm, 12.5 nm, and 15 nm. The spin configurations of the junctions with the thicknesses of 5 nm and 15 nm are similar to the spin configurations in Fig. 3(d) which are in the coherent switching mode. The junction with a thickness of 7.5 nm has the parallel spins in the cross structure with a  $\theta$  as  $-90^\circ$  between the  $x$ -direction. As the magnetic field increases to 3000 Oe,  $\theta$  decreases to  $0^\circ$  in the junction. When the

magnetic field reduces back to 0 Oe,  $\theta$  increases to  $45^\circ$ , and the CSB is formed. From the junction with a thickness of 10 nm, the initial  $90^\circ$  DW within the junction can be eliminated, and the CSB can be formed by controlling the magnetization process. When the thickness of the junction is 12.5 nm, the spins in the cross structure requires a large magnetic field up to 3825 Oe to reverse the magnetization direction. For the whole cross structures with the thicknesses of 5 nm, 7.5 nm, and 10 nm, the spin configurations in the  $y$ -arms have not been changed, and the spin configuration in the  $x$ -arms can be switched. However, for the cross structures with thicknesses of 12.5 nm and 15 nm, the spin directions rotate along the  $y$ -axis as well.

The magnetic switching field of the junction can be affected by the thickness of the junction. Figure 5 shows  $H_c$  as a function of the thickness for the junctions with different

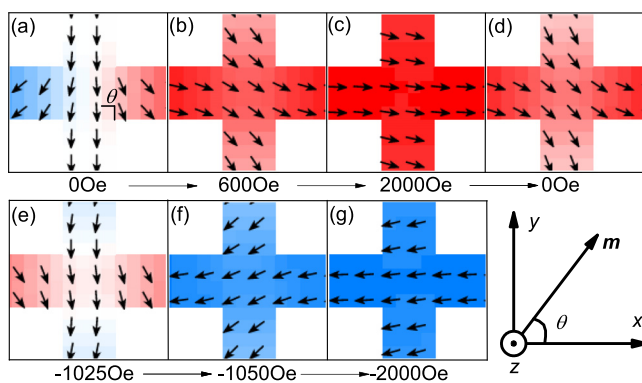


FIG. 3. The magnetic domain configurations of the 2.5-nm-thick junction at different applied magnetic fields. The magnetic field is applied along the  $x$ -direction. The labels correspond to the states indicated in Fig. 2, i.e., (a)  $H=0$  Oe, (b)  $H=600$  Oe (before switching), (c)  $H=2000$  Oe (after switching), (d)  $H=0$  Oe, (e)  $H=-1025$  Oe (before switching), (f)  $H=-1050$  Oe (after switching), and (g)  $H=-2000$  Oe.

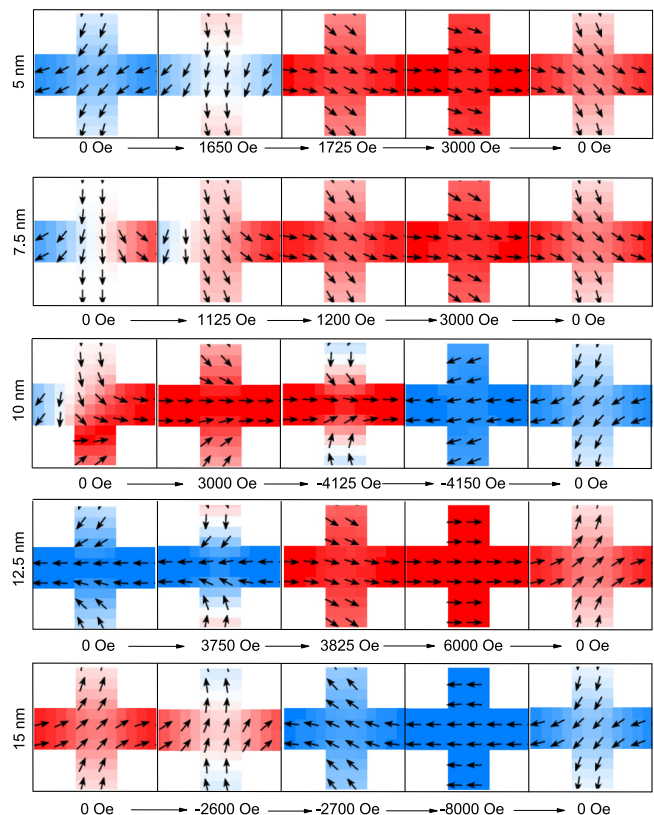


FIG. 4. The magnetic domain configurations of the junctions at different applied magnetic fields for different thicknesses. The magnetic field is applied along the  $x$ -direction.

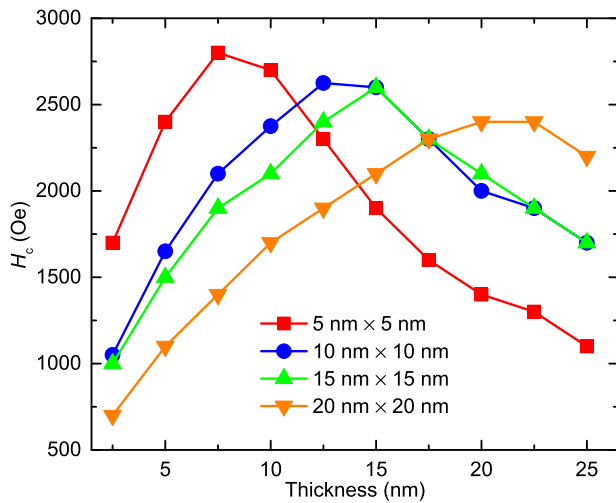


FIG. 5. The coercivity  $H_c$ , i.e., the switching field, as a function of the thickness for the junctions with different cross section sizes.

lateral sizes. The size of the device is varying from  $100 \text{ nm} \times 100 \text{ nm}$  to  $400 \text{ nm} \times 400 \text{ nm}$ , i.e., the length of the cross structure is varying from 5 nm to 20 nm.  $H_c$  increases first with increasing thickness and then decreases, showing a broad peak from 7 nm to 22 nm depending on the junction sizes. The reason is that for the junction with a certain cross section size, the magnetization switching is coherent. Thus,  $H_c$  is proportional to the total magnetization, which also means  $H_c$  increases with the thickness as the total magnetization is proportional to the thickness. However, when the thickness is larger than a certain critical value, multiple domains can be formed during the magnetization switching, leading to incoherent magnetization switching. In such a case,  $H_c$  decreases with the thickness, as thicker junction is more likely to form multiple domains, due to the demagnetization effect. Besides, the critical value of the thickness increases with increasing lateral dimensions of the junction. The reason is that the amplitude of the demagnetization effect resulting in the incoherent switching is proportional to thickness and is inversely proportional to the lateral dimensions of the junction (see [supplementary material](#), Figs. S2–S4). We note that there are large magnetic switching fields of around 2500 Oe, which favor the stability of the MRAM operation. The large magnetic switching fields, however, may lead to large current needed for the switching of the junction. One may need to explore the spin torque transfer or thermal assistant switching for future applications.

In conclusion, we have carried out a full micromagnetic study on the magnetization configuration and the magnetic switching process in a nanoscale Permalloy junction. The relationship between the magnetic switching fields and the thickness of the nanoscale junction has been investigated. While different types of domain walls can be formed in the initially relaxed states depending on the specific thicknesses, the junction acts as a single CSB where the spins are aligned in parallel during the magnetization process. The magnetization direction can be controlled and switched coherently by applying an external magnetic field. Both the initial magnetization field and the coercivity are found to depend on the thickness, and the large coercivity could enhance the

stability of the device operation. Our work shows that the nanoscale magnetic junction has the potential to be used as a building block for future spin-based data storage or logic computing technologies.

See [supplementary material](#) for magnetization distribution in device at different layers and side views of the magnetization distribution in device.

This work was supported by State Key Program for Basic Research of China (Grant Nos. 2014CB921101 and 2016YFA0300803), NSFC (Grants Nos. 61427812 and 11574137), Jiangsu NSF (No. BK20140054), Jiangsu Shuangchuang Team Program, Shenzhen Fundamental Research Fund under Grant Nos. JCYJ20160331164412545 and the UK EPSRC (EP/G010064/1).

- <sup>1</sup>J. Åkerman, *Science* **308**, 508 (2005).
- <sup>2</sup>E. Chen, D. Apalkov, Z. Diao, A. Driskill-Smith, D. Druist, D. Lottis, V. Nikitin, X. Tang, S. Watts, S. Wang, S. A. Wolf, A. W. Ghosh, S. Lu, J. W. Poon, W. H. G. S. Stan, M. Butler, C. K. A. Mewes, T. Mewes, and P. B. Visscher, *IEEE Trans. Magn.* **46**, 1873 (2010).
- <sup>3</sup>J.-G. Zhu, *Proc. IEEE* **96**, 1786 (2008).
- <sup>4</sup>T. Pramanik, U. Roy, L. F. Register, and S. K. Banerjee, *IEEE Trans. Nanotechnol.* **14**, 883 (2015).
- <sup>5</sup>Y. Yan, C. Lu, H. Tu, X. Lu, W. Liu, J. Wang, L. Ye, I. Will, B. Kuerbanjiang, V. K. Lazarov, J. Wu, W. Johnny, B. You, J. Du, R. Zhang, and Y. Xu, *AIP Adv.* **6**, 095011 (2016).
- <sup>6</sup>B. Liu, X. Ruan, Z. Wu, H. Tu, J. Du, J. Wu, X. Lu, L. He, R. Zhang, and Y. Xu, *Appl. Phys. Lett.* **109**, 042401 (2016).
- <sup>7</sup>J. J. Nahas, T. W. Andre, B. Garni, C. Subramanian, H. Lin, S. M. Alam, K. Papworth, and W. L. Martino, *IEEE J. Solid-State Circuits* **43**, 1826 (2008).
- <sup>8</sup>S. Tehrani, J. Slaughter, E. Chen, M. Durlam, J. Shi, and M. DeHerrera, *IEEE Trans. Magn.* **35**, 2814 (1999).
- <sup>9</sup>M. Krounbi, V. Nikitin, D. Apalkov, J. Lee, X. Tang, R. Beach, D. Erickson, and E. Chen, *ECS Trans.* **69**, 119 (2015).
- <sup>10</sup>D. A. Allwood, G. Xiong, C. Faulkner, D. Atkinson, D. Petit, and R. Cowburn, *Science* **309**, 1688 (2005).
- <sup>11</sup>S. S. Parkin, M. Hayashi, and L. Thomas, *Science* **320**, 190 (2008).
- <sup>12</sup>S. Lepadatu and Y. Xu, *Spintronic Mater. Technol.* **2006**, 179.
- <sup>13</sup>S. Li, A. Samad, W. Lew, Y. Xu, and J. Bland, *Phys. Rev. B* **61**, 6871 (2000).
- <sup>14</sup>J. A. Currivan, Y. Jang, M. D. Mascaro, M. A. Baldo, and C. A. Ross, *IEEE Magn. Lett.* **3**, 3000104 (2012).
- <sup>15</sup>S. Tehrani, B. Engel, J. Slaughter, E. Chen, M. DeHerrera, M. Durlam, P. Naji, R. Whig, J. Janesky, and J. Calder, *IEEE Trans. Magn.* **36**, 2752 (2000).
- <sup>16</sup>W. J. Gallagher and S. S. Parkin, *IBM J. Res. Dev.* **50**, 5 (2006).
- <sup>17</sup>Y. Xu, C. Vaz, A. Hirohata, C. Yao, W. Lee, J. Bland, F. Rousseaux, E. Cambil, and H. Launois, *J. Appl. Phys.* **85**, 6178 (1999).
- <sup>18</sup>Y. Xu, C. Vaz, A. Hirohata, H. Leung, C. Yao, J. Bland, E. Cambil, F. Rousseaux, and H. Launois, *Phys. Rev. B* **61**, R14901 (2000).
- <sup>19</sup>G. D. Chaves-O'Flynn, G. Wolf, D. Pinna, and A. D. Kent, *J. Appl. Phys.* **117**, 17D705 (2015).
- <sup>20</sup>U. Roy, T. Pramanik, M. Tsoi, L. F. Register, and S. K. Banerjee, *J. Appl. Phys.* **113**, 223904 (2013).
- <sup>21</sup>U. Roy, H. Seinige, F. Ferdousi, J. Mantey, M. Tsoi, and S. Banerjee, *J. Appl. Phys.* **111**, 07C913 (2012).
- <sup>22</sup>T. Pramanik, U. Roy, M. Tsoi, L. F. Register, and S. K. Banerjee, *J. Appl. Phys.* **115**, 17D123 (2014).
- <sup>23</sup>J. Z. Sun, *Phys. Rev. B* **62**, 570 (2000).
- <sup>24</sup>Y. Zhou, J. Åkerman, and J. Z. Sun, *Appl. Phys. Lett.* **98**, 102501 (2011).
- <sup>25</sup>M. J. Donahue and D. G. Porter, *OOMMF User's Guide* (US Department of Commerce, Technology Administration, National Institute of Standards and Technology, 1999).
- <sup>26</sup>K. I. Bolotin, F. Kuemmeth, and D. Ralph, *Phys. Rev. Lett.* **97**, 127202 (2006).
- <sup>27</sup>M. Lakshmanan and K. Nakamura, *Phys. Rev. Lett.* **53**, 2497 (1984).