



This is a repository copy of *Encapsulation of Crabtree's catalyst in sulfonated MIL-101(Cr): enhancement of stability and selectivity between competing reaction pathways by the MOF chemical microenvironment.*

White Rose Research Online URL for this paper:  
<http://eprints.whiterose.ac.uk/127107/>

Version: Accepted Version

---

**Article:**

Rosseinsky, M.J., Grigoropoulos, A., McKay, A.I. et al. (6 more authors) (2018)  
Encapsulation of Crabtree's catalyst in sulfonated MIL-101(Cr): enhancement of stability and selectivity between competing reaction pathways by the MOF chemical microenvironment. *Angewandte Chemie International Edition*. ISSN 1433-7851

<https://doi.org/10.1002/anie.201710091>

---

**Reuse**

Items deposited in White Rose Research Online are protected by copyright, with all rights reserved unless indicated otherwise. They may be downloaded and/or printed for private study, or other acts as permitted by national copyright laws. The publisher or other rights holders may allow further reproduction and re-use of the full text version. This is indicated by the licence information on the White Rose Research Online record for the item.

**Takedown**

If you consider content in White Rose Research Online to be in breach of UK law, please notify us by emailing [eprints@whiterose.ac.uk](mailto:eprints@whiterose.ac.uk) including the URL of the record and the reason for the withdrawal request.



[eprints@whiterose.ac.uk](mailto:eprints@whiterose.ac.uk)  
<https://eprints.whiterose.ac.uk/>

## Accepted Article

**Title:** Encapsulation of Crabtree's catalyst in sulfonated MIL-101(Cr): enhancement of stability and selectivity between competing reaction pathways by the MOF chemical microenvironment

**Authors:** Matthew J. Rosseinsky, Alexios Grigoropoulos, Alasdair I. McKay, Alexandros P. Katsoulidis, Robert P. Davies, Anthony Haynes, Lee Brammer, Jianliang Xiao, and Andrew S. Weller

This manuscript has been accepted after peer review and appears as an Accepted Article online prior to editing, proofing, and formal publication of the final Version of Record (VoR). This work is currently citable by using the Digital Object Identifier (DOI) given below. The VoR will be published online in Early View as soon as possible and may be different to this Accepted Article as a result of editing. Readers should obtain the VoR from the journal website shown below when it is published to ensure accuracy of information. The authors are responsible for the content of this Accepted Article.

**To be cited as:** *Angew. Chem. Int. Ed.* 10.1002/anie.201710091  
*Angew. Chem.* 10.1002/ange.201710091

**Link to VoR:** <http://dx.doi.org/10.1002/anie.201710091>  
<http://dx.doi.org/10.1002/ange.201710091>

## COMMUNICATION

# Encapsulation of Crabtree's catalyst in sulfonated MIL-101(Cr): enhancement of stability and selectivity between competing reaction pathways by the MOF chemical microenvironment

Alexios Grigoropoulos,<sup>[a]</sup> Alasdair I. McKay,<sup>[b]</sup> Alexandros P. Katsoulidis,<sup>[a]</sup> Robert P. Davies,<sup>[c]</sup> Anthony Haynes,<sup>[d]</sup> Lee Brammer,<sup>[d]</sup> Jianliang Xiao,<sup>[a]</sup> Andrew S. Weller<sup>[b]\*</sup> and Matthew J. Rosseinsky<sup>[a]\*</sup>


In memory of Professor Gérard Férey

**Abstract:** Crabtree's catalyst was encapsulated inside the pores of the sulfonated MIL-101(Cr) metal-organic framework (MOF) by cation exchange. This hybrid catalyst is active for the heterogeneous hydrogenation of non-functionalized alkenes either in solution or in the gas phase. Moreover, encapsulation inside a well-defined hydrophilic microenvironment enhances catalyst stability and selectivity to hydrogenation over isomerization for substrates bearing ligating functionalities. Accordingly, the encapsulated catalyst significantly outperforms its homogeneous counterpart in the hydrogenation of olefinic alcohols in terms of overall conversion and selectivity with the chemical microenvironment of the MOF host favouring one out of two competing reaction pathways.

Metal-organic frameworks (MOFs)<sup>[1]</sup> are crystalline and permanently porous materials which have emerged as promising hosts for the immobilization of organometallic catalysts,<sup>[2]</sup> since they allow for control of the steric and chemical microenvironment around the encapsulated catalytically active species. This in turn could promote catalytic activity and selectivity through extended coordination sphere interactions. These concepts lie behind the exceptional reactivity and selectivity of metalloenzymes,<sup>[3]</sup> however their transfer to the design and synthesis of artificial catalysts is challenging.<sup>[4]</sup> Several examples of MOF-supported catalysts showing exceptional overall catalytic activity have been reported.<sup>[5]-[6]</sup> Enhancement of selectivity between products of a single reaction pathway by control of the steric<sup>[7]</sup> or the chemical<sup>[8]</sup> microenvironment has also been demonstrated.

Crabtree's catalyst is one of the best commercially available homogeneous catalysts for hydrogenation of alkenes.<sup>[9]</sup> However, it is deactivated in solution under hydrogenation conditions, forming catalytically inactive polymeric clusters.<sup>[10]</sup> This

self-association reaction can be attenuated via modification of the coordination sphere of Ir<sup>[11]</sup> or employment of larger weakly coordinating anions.<sup>[12]</sup> Substrates bearing ligating functionalities such as olefinic alcohols show a more complicated behavior with Crabtree's catalyst since isomerization<sup>[13]</sup> can also take place in parallel with hydrogenation.<sup>[14]</sup>

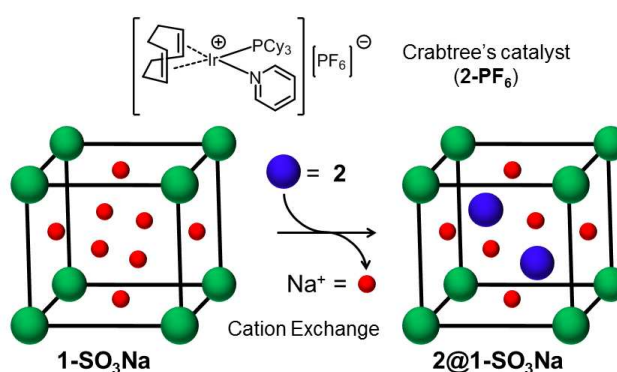

**Scheme 1.** Encapsulation of the cationic component of Crabtree's catalyst (**2**, blue sphere) in sulfonated MIL-101(Cr) (**1-SO<sub>3</sub>Na**, cube) by exchange of the charge-balancing Na<sup>+</sup> cations (red sphere).

Here we use the Na<sup>+</sup> salt of sulfonated MIL-101(Cr) MOF (**1-SO<sub>3</sub>Na**) as the anionic framework host for encapsulation of the cationic component of Crabtree's catalyst [Ir(cod)(PCy<sub>3</sub>)(py)][PF<sub>6</sub>] (**2-PF<sub>6</sub>**) by cation exchange,<sup>[15]</sup> forming **2@1-SO<sub>3</sub>Na** (Scheme 1). Encapsulation of cation **2** inside a well-defined, anionic and hydrophilic microenvironment forms an efficient heterogeneous catalyst for the hydrogenation of non-functionalized alkenes in solution, enables hydrogenation in the gas phase and most importantly enhances the catalyst's activity and selectivity for the hydrogenation of olefinic alcohols by suppressing the competing isomerization reaction. The MOF chemical microenvironment directs substrates along one of two distinct reaction pathways.

The sulfonated analogue of MIL-101(Cr) (**1-SO<sub>3</sub>H**)<sup>[16]</sup> is a robust, readily synthesized anionic MOF. It is isostructural with pristine MIL-101(Cr)<sup>[17]</sup> with two charge-balancing cations per formula unit, [H<sub>x</sub>Na<sub>2-x</sub>][Cr<sub>3</sub>(μ<sub>3</sub>-O)(BDC-SO<sub>3</sub>)<sub>3</sub>] (x = 1.8 ± 0.1, Figure S1, H<sub>2</sub>BDC-SO<sub>3</sub>Na = 2-sulfoterephthalic acid sodium salt). Each cubic unit cell (a = 87.63(3) Å) contains 8 bigger and 16 smaller mesopores, large enough to accommodate **2** (Figures S2, S3). It has been reported that the cations within **1-SO<sub>3</sub>H** can be partially exchanged with Ag<sup>+</sup><sup>[18]</sup> or [Rh(cod)(dppe)]<sup>+</sup> [dppe = 1,2-bis(diphenylphosphino)ethane].<sup>[19]</sup>

[a] Dr A. Grigoropoulos, Dr A. P. Katsoulidis, Prof. J. Xiao, Prof. M. J. Rosseinsky  
Department of Chemistry, University of Liverpool  
Liverpool L69 7ZD, UK  
E-mail: [M.J.Rosseinsky@liverpool.ac.uk](mailto:M.J.Rosseinsky@liverpool.ac.uk)


[b] Dr A. I. McKay, Prof. A. S. Weller  
Department of Chemistry, University of Oxford  
Chemistry Research Laboratories, Oxford OX1 3TA, U.K.  
E-mail: [andrew.weller@chem.ox.ac.uk](mailto:andrew.weller@chem.ox.ac.uk)

[c] Dr R. P. Davies  
Department of Chemistry, Imperial College London  
South Kensington, London SW7 2AZ, U.K.

[d] Dr A. Haynes, Prof. L. Brammer  
Department of Chemistry, University of Sheffield  
Brook Hill, Sheffield S3 7HF, U.K.

Supporting information and the ORCID identification number(s) for the author(s) of this article can be found in <https://>

## COMMUNICATION

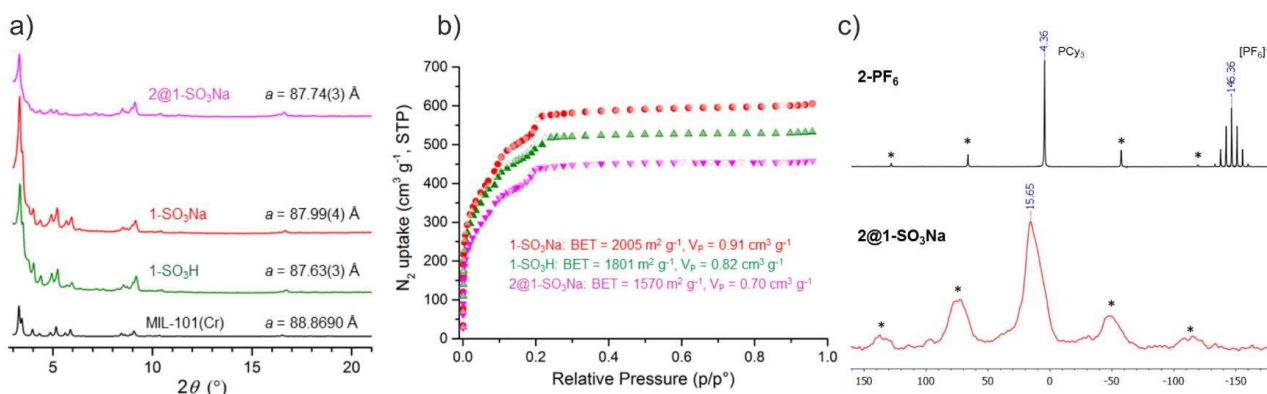


**Figure 1.** a) Comparison of PXRD patterns and unit cell parameter ( $Fd\bar{3}m$  space group) for **2@1-SO<sub>3</sub>Na** (magenta), **1-SO<sub>3</sub>Na** (red), **1-SO<sub>3</sub>H** (green) and **MIL-101(Cr)** (calculated, black).<sup>[17]</sup> Le Bail fits are included in the supporting information. b) N<sub>2</sub> uptake of the desolvated materials at 77 K (BET = surface area,  $V_p$  = pore volume). c) <sup>31</sup>P{<sup>1</sup>H} MAS NMR spectrum of **2-PF<sub>6</sub>** (black) and **2@1-SO<sub>3</sub>Na** (red). Spinning side bands are marked with an asterisk.

In order to increase the number of exchangeable Na<sup>+</sup> cations, **1-SO<sub>3</sub>H** was treated with AcONa/AcOH buffer solution (pH = 4.7), forming [H<sub>γ</sub>Na<sub>2-γ</sub>][Cr<sub>3</sub>(μ<sub>3</sub>-O)(BDC-SO<sub>3</sub>)<sub>3</sub>] (**1-SO<sub>3</sub>Na**,  $\gamma = 0.2 \pm 0.1$ , Table S1). **1-SO<sub>3</sub>Na** remains crystalline and mesoporous (Figures 1a, 1b) with only a small change in the cubic unit cell parameter ( $a = 87.99(4)$  Å) and a slight increase in the measured porosity (BET surface area = 2005 m<sup>2</sup> g<sup>-1</sup>,  $V_p = 0.91$  cm<sup>3</sup> g<sup>-1</sup>) and the pore size distribution, compared to **1-SO<sub>3</sub>H** (Figure S9).

After establishing an appropriate cation exchange protocol using [Cp\*<sub>2</sub>Co]<sup>+</sup> as a cationic probe (Table S2 and Figures S6, S9-S12), as we have shown previously,<sup>[15b]</sup> **2-PF<sub>6</sub>** was used as a cationic guest precursor. Since water can poison the catalytically active species,<sup>[12]</sup> cation exchange was carried out using desolvated **1-SO<sub>3</sub>Na** as the anionic host in dry and degassed acetone, producing **2@1-SO<sub>3</sub>Na**. Crystallinity was retained after cation exchange with only a minor change in the cubic unit cell parameter ( $a = 87.74(3)$  Å, Figure 1a, see Le Bail fit in Figure S7), whereas BET surface area (1570 m<sup>2</sup> g<sup>-1</sup>) and pore volume (0.70 cm<sup>3</sup> g<sup>-1</sup>) were reduced, compared to **1-SO<sub>3</sub>Na** (Figure 1b).

ICP-OES after digestion of **2@1-SO<sub>3</sub>Na** gave an Ir content of 2.28 wt %, indicating that 7% of the Na<sup>+</sup> cations have been exchanged with **2** (Table S3). ICP-OES also showed an equimolar Ir/P ratio, and only one broad peak was observed ( $\delta_p = 15.65$ , fwhm ~ 15 ppm) in the <sup>31</sup>P{<sup>1</sup>H} MAS NMR spectrum of **2@1-SO<sub>3</sub>Na**, assigned to the PCy<sub>3</sub> ligand (Figure 1c). Signals arising from the [PF<sub>6</sub>]<sup>-</sup> anion were not observed either in the <sup>31</sup>P{<sup>1</sup>H} MAS or the <sup>19</sup>F{<sup>1</sup>H} solution NMR spectra of **2@1-SO<sub>3</sub>Na** after digestion, in contrast with the respective spectra of **2-PF<sub>6</sub>** (Figure S13). The <sup>1</sup>H solution NMR spectrum of **2@1-SO<sub>3</sub>Na** after digestion showed three low intensity peaks at 8.22, 7.58 and 7.16 ppm, assigned to pyridine (Figure S14). Treatment of **2@1-SO<sub>3</sub>Na** with D<sub>2</sub> gas resulted in deuteration of the cod ligand and formation of d<sub>4</sub>-cyclooctane, as detected by <sup>2</sup>H MAS NMR spectroscopy (Figure S15). These analytical and spectroscopic data are consistent with cation **2** being encapsulated intact inside the mesopores of **1-SO<sub>3</sub>Na** by a simple cation exchange process. The down-field chemical shift and peak broadening observed for the signal due to the PCy<sub>3</sub> ligand in the <sup>31</sup>P{<sup>1</sup>H} MAS NMR spectrum of **2@1-SO<sub>3</sub>Na**, compared to **2-PF<sub>6</sub>**, likely originate from the different anionic environment surrounding **2**.<sup>[20]</sup>

To explore the possible interaction of the sulfonate groups decorating the pore walls of **1-SO<sub>3</sub>Na** with the Ir center of **2** after encapsulation, the tosylate anion [OTs]<sup>-</sup> was selected to model the BDC-SO<sub>3</sub> linkers. Two new complexes were synthesized, [Ir(cod)(PCy<sub>3</sub>)(py)][OTs] (**2-OTs**) and [Ir(cod)(PCy<sub>3</sub>)(OTs)] (**3**), in which OTs acts as a counter anion or as a ligand to Ir, respectively (Figures 2a, 2b, Figures S16, S17, Table S4). <sup>31</sup>P{<sup>1</sup>H} and <sup>1</sup>H EXSY NMR spectroscopy in CD<sub>2</sub>Cl<sub>2</sub> (Figures S18-S20) revealed that a dynamic reversible ligand exchange takes place between complexes **2-OTs** and **3**, with OTs replacing pyridine in the coordination sphere of Ir (Figure 2c). This suggests that the sulfonate groups in **2@1-SO<sub>3</sub>Na** may also play a non-spectator role, with potential implications in catalysis, as discussed next.

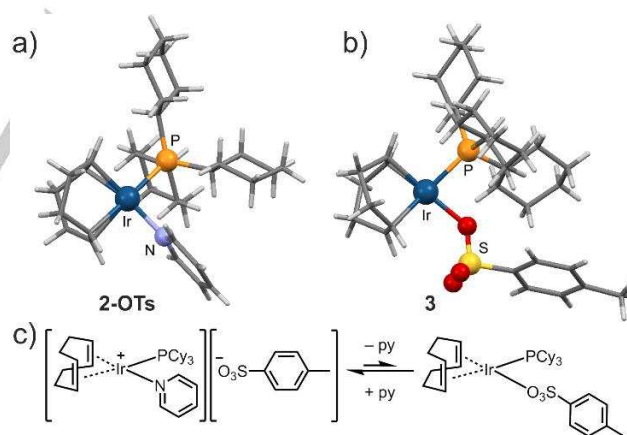

**Figure 2.** a) Single crystal structure of **2-OTs** ([OTs]<sup>-</sup> counter anion is not shown for clarity). b) Single crystal structure of **3** (OTs coordinated cis to PCy<sub>3</sub>). c) Reversible ligand exchange between **2-OTs** and **3** in CD<sub>2</sub>Cl<sub>2</sub>.

The catalytic performance of **2@1-SO<sub>3</sub>Na** was benchmarked against **2-PF<sub>6</sub>** in the hydrogenation of non-functionalized alkenes in CH<sub>2</sub>Cl<sub>2</sub> under mild conditions (Table 1). Control experiments verified that **1-SO<sub>3</sub>Na** does not catalyze the hydrogenation of oct-1-ene (**4**). Introduction of **2@1-SO<sub>3</sub>Na** as the catalyst afforded complete hydrogenation of **4** to n-octane, at loadings as low as 50 ppm (entries 1-3). When the loading was reduced to 10 ppm (entry 4), selective conversion of **4** to n-octane reached 83%



## COMMUNICATION

(TON =  $8.3 \times 10^4$ ). Homogeneous catalyst **2-PF<sub>6</sub>** under identical conditions produced comparable results, demonstrating that encapsulation is not detrimental to catalytic activity.








Table 1. Hydrogenation of non-functionalized alkenes with heterogeneous <b>2@1-SO<sub>3</sub>Na</b> and homogeneous <b>2-PF<sub>6</sub></b> catalysts. <sup>[a]</sup>							
Entry	Substrate	Loading (ppm)	Time (h)	<b>2@1-SO<sub>3</sub>Na</b>		<b>2-PF<sub>6</sub></b>	
				Conv <sup>[b]</sup>	TON	Conv <sup>[b]</sup>	TON
1		1000 <sup>[c]</sup>	3	>99%	>990	100%	1000
2		100 <sup>[d]</sup>	20	100%	10000	100%	10000
3	<b>4</b>	50 <sup>[e]</sup>	24	100%	20000	—	—
4		10 <sup>[f]</sup>	24	83%	83000	94%	94000
5		1000 <sup>[c]</sup>	3	>99%	>990	100%	1000
6	<b>5</b>		20	100%	1000	—	—
7		1000 <sup>[c]</sup>	3	10%	100	12%	120
8	<b>6</b>		20	26%	260	37%	370
9		1000 <sup>[c]</sup>	3	69%	690	100%	1000
10	<b>7</b>		20	81%	810	—	—

[a] CH<sub>2</sub>Cl<sub>2</sub> solvent, T = 20 °C; [b] conversion (%) based on GC; [c] [alkene] = 0.5 M, V = 1 mL, 8 mmol of H<sub>2</sub>; [d] [alkene] = 1.0 M, V = 4 mL, 16 mmol of H<sub>2</sub>; [e] [alkene] = 1.0 M, V = 10 mL, 48 mmol of H<sub>2</sub>; [f] [alkene] = 1.5 M, V = 12 mL, 48 mmol of H<sub>2</sub>.

The branched, but unhindered, aliphatic alkene, 3-methylhex-1-ene (**5**) was also completely hydrogenated using **2@1-SO<sub>3</sub>Na** at 1000 ppm loading (entries 5-6). The hindered aliphatic alkene, 2-methylhex-1-ene (**6**) was only partially hydrogenated with either catalyst after 20 h (entries 7-8). Conversion did not increase any further after 72 h in either system, reflecting catalyst deactivation. When cyclohexene (**7**) was employed as a substrate, conversion reached 69% in 3 h with **2@1-SO<sub>3</sub>Na** as the catalyst but increased only to 81% after 20 h. On the contrary, 100% conversion was observed with **2-PF<sub>6</sub>** in 3 h (entries 9-10).

The different response observed for this bulkier substrate is consistent with hydrogenation taking place within the pores and not on the surface of **2@1-SO<sub>3</sub>Na**. The heterogeneity of the reaction was further established by carrying out a leaching test (Figure S21). Recycling of **2@1-SO<sub>3</sub>Na** was also possible with a small decrease in activity (82% conversion) during the third cycle (Figure S22).

**2@1-SO<sub>3</sub>Na** is a versatile catalyst which can also be employed in a gas/solid reaction,<sup>[21]</sup> as demonstrated by the complete hydrogenation of but-1-ene over **2@1-SO<sub>3</sub>Na** in 2.5 h (4000 μmol of but-1-ene hydrogenated per 1 mg of Ir). Although finely ground solid **2-PF<sub>6</sub>** was also active, dispersion of **2** in the porous anionic solid-state support increases the number of accessible catalytic sites in **2@1-SO<sub>3</sub>Na**, resulting in a 6-fold

increase compared to the non-porous solid **2-PF<sub>6</sub>** (Figure 3). Recycling of **2@1-SO<sub>3</sub>Na** was also successful upon exposure to fresh but-1-ene (Figure S23).

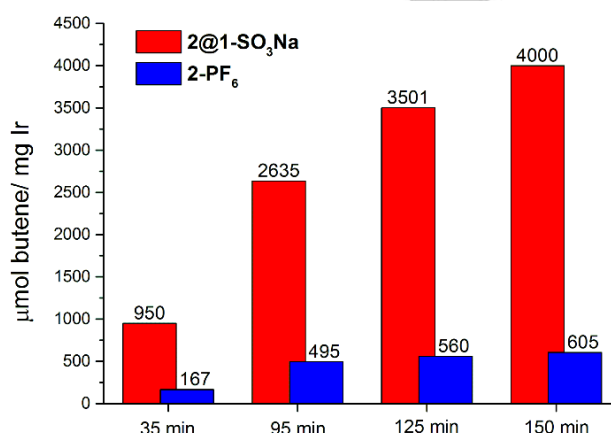



Figure 3. Gas/solid hydrogenation of but-1-ene over **2@1-SO<sub>3</sub>Na** (red) and **2-PF<sub>6</sub>** (blue). Conditions: T = 20 °C, P<sub>H<sub>2</sub></sub> < 4 bar, 0.5 mg of solid catalyst used.

The mesopores of **2@1-SO<sub>3</sub>Na** are hydrophilic due to the presence of H-bond accepting sulfonate groups as well as Lewis acidic Cr(III) sites and Na<sup>+</sup> cations. Therefore, the reactivity of Crabtree's catalyst with substrates bearing functional groups which can interact with such an environment could significantly change due to encapsulation. We chose to explore this by using olefinic alcohols as substrates, whose fundamental characteristic is the competition between hydrogenation and isomerization upon turnover.<sup>[22]</sup> Hydrogenation of a series of olefinic alcohols was carried out under a ~20-fold excess of H<sub>2</sub> (Table 2).

Complete hydrogenation of pent-4-en-1-ol (**8a**), pent-4-en-2-ol (**9a**) and 2-methylbut-3-en-1-ol (**10a**) to the respective alcohols **8b-10b** was observed with **2-PF<sub>6</sub>** in 3 h. Isomerization products were not detected (Figure S24), as reported for **2-PF<sub>6</sub>** using similar substrates.<sup>[23]</sup> Complete hydrogenation of **8a-10a** to **8b-10b** was also achieved with **2@1-SO<sub>3</sub>Na**, albeit in 24 h (entries 1-6). Isomerization products were again not detected. Conversion in 3 h correlates well with the steric hindrance around the double bond of the substrate: 10% for **10a** (more hindered), increasing to 22% for **9a** (less hindered) and reaching 34% for **8a** (linear). Olefinic alcohols **8a-10a** were hydrogenated considerably slower with **2@1-SO<sub>3</sub>Na**, compared to the sterically comparable non-functionalized alkenes **4** and **5** (Table 1). This is consistent with a strong interaction between the hydroxyl group of the olefinic alcohols and the chemical microenvironment of **2@1-SO<sub>3</sub>Na**.

Substrates which are intrinsically more susceptible to isomerization, such as the homoallylic **11a** and allylic **12a-13a** alcohols,<sup>[23-24]</sup> revealed a significant enhancement of reactivity and selectivity to hydrogenation with **2@1-SO<sub>3</sub>Na**, compared to its homogeneous counterpart. **2-PF<sub>6</sub>** afforded 56% conversion of **11a** in 3 h and 57% in 24 h, indicative of catalyst deactivation (entries 7-8, Figure S25). Moreover, isomerization of **11a** was also observed, producing a non-negligible amount of the internal olefinic alcohol **11c** and traces of the aldehyde **11d**. As a result, selectivity to hydrogenation and formation of n-butanol (**11b**) was only 85% for the homogeneous system.

## COMMUNICATION



**Table 2.** Substrate conversion<sup>[a]</sup> and product selectivity<sup>[a, b]</sup> for hydrogenation of olefinic alcohols with heterogeneous **2@1-SO<sub>3</sub>Na** and homogeneous **2-PF<sub>6</sub>** catalysts.<sup>[c]</sup>

Entry	Substrate	Time (h)	<b>2@1-SO<sub>3</sub>Na</b>				<b>2-PF<sub>6</sub></b>			
			Conv	<b>b</b>	<b>c</b>	<b>d</b>	Conv	<b>b</b>	<b>c</b>	<b>d</b>
1		3	34	100	n.d. <sup>[d]</sup>	n.d.	100	100	n.d.	n.d.
2		24	100	100	n.d.	n.d.	—	—	—	—
3		3	22	100	n.d.	n.d.	100	100	n.d.	n.d.
4		24	100	100	n.d.	n.d.	—	—	—	—
5		3	10	100	n.d.	n.d.	100	100	n.d.	n.d.
6		24	100	100	n.d.	n.d.	—	—	—	—
7		3	33	95	5	n.d.	56	85	13	2
8		24	100	100	n.d.	n.d.	57	83	13	4
9		3	41	93	n.d.	7	69 <sup>[e]</sup>	61	n.d.	35
10		24	96	92	n.d.	8	62 <sup>[e]</sup>	55	n.d.	19
11		3	26	92	n.d.	8	54 <sup>[e]</sup>	31	n.d.	54
12		24	82	90	n.d.	10	53 <sup>[e]</sup>	28	n.d.	26

[a] based on <sup>1</sup>H NMR using mesitylene as standard for verifying mass-balance; [b] yield of each product over total conversion; [c] 0.1 mol % loading, [substrate] = 0.5 M in CH<sub>2</sub>Cl<sub>2</sub>, V = 0.7 mL, ~8 mmol of H<sub>2</sub>; [d] not detected; [e] formation of ill-defined condensation products was also observed, especially after 24 h.

By contrast, the heterogeneous catalyst **2@1-SO<sub>3</sub>Na** afforded complete conversion and 100% selectivity to hydrogenation and formation of **11b** (entries 7-8, Figure S26). Monitoring conversion for both systems over time (Figure S27) verified that **2-PF<sub>6</sub>** is deactivated after 3 h, whereas **2@1-SO<sub>3</sub>Na** remained productive, affording full conversion in 6 h. Although traces of the internal olefin **11c** were detected in short reaction times, **11c** was subsequently also hydrogenated to **11b**. The encapsulated catalyst is thus more stable, more active with respect to overall conversion and more selective.


The superior performance of **2@1-SO<sub>3</sub>Na** was even more pronounced in the hydrogenation of allylic alcohols which can isomerize directly to the respective aldehydes. Conversion under hydrogenation conditions for trans-pent-2-en-1-ol (**12a**, entries 9-10) and trans-crotyl alcohol (**13a**, entries 11-12) in 3 h with **2-PF<sub>6</sub>** was 69% and 54%, respectively (Figure S28). Conversion did not increase after 24 h, indicating catalyst deactivation. Selectivity to hydrogenation was poor: 61% for alcohol **12b** in 3 h with a substantial amount of the aldehyde **12d** formed (35% selectivity) and 31% for alcohol **13b** in 3 h with the aldehyde **13d** now being the main product (54% selectivity). By contrast, overall conversion with **2@1-SO<sub>3</sub>Na** as the catalyst reached 96% for **12a** and 82% for **13a** in 24 h (Figure S29). Isomerization to the aldehydes **12d**

and **13d** was significantly suppressed, resulting in ≥90% selectivity for the alcohols **12b** and **13b**.

To probe the effect of the sulfonate group on stability and selectivity, we also investigated the homogeneous hydrogenation of crotyl alcohol using **2-OTs** and **3** as catalysts (Figure S30). Higher conversions were observed compared to **2-PF<sub>6</sub>** (77% for **2-OTs** and 83% for **3** in 24 h) in accordance with OTs being a more strongly coordinating anion, hence prolonging the catalyst's lifetime.<sup>[25]</sup> By contrast, selectivity to hydrogenation did not significantly improve (39% for **2-OTs** and 53% for **3**), remaining considerably lower than that of **2@1-SO<sub>3</sub>Na** (82%).

The reaction pathways for the hydrogenation or isomerization of olefinic alcohols with the homogeneous catalyst **2-PF<sub>6</sub>** likely share the same starting point, the formation of a cationic Ir(III)-dihydride complex in which the hydroxyl group is also coordinated to Ir (Scheme 2, intermediate **I**), followed by migratory insertion (intermediate **II**).<sup>[13-14]</sup> Bifurcation into separate, competitive pathways then occurs: (i) hydrogenation to the respective alcohol via reductive elimination (pathway **A**) or (ii) isomerization to the internal olefin via β-elimination, which requires an appropriately orientated vacant coordination site, followed by off-cycle tautomerization to the aldehyde (pathway **B**).

The significantly improved selectivity to hydrogenation observed with **2@1-SO<sub>3</sub>Na** suggests that isomerization is suppressed. We propose that this could take place due to extended coordination sphere interactions between the hydroxyl group of the olefinic alcohols and the chemical microenvironment around **2**, such as H-bonding to the sulfonate groups.

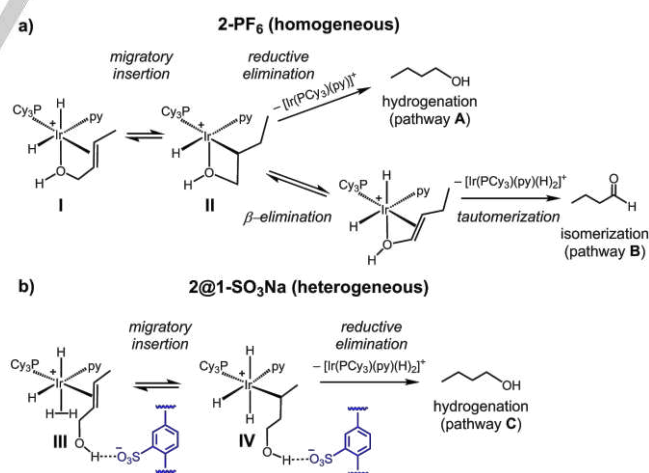

**Scheme 2.** a) Competing pathways for hydrogenation (**A**) and isomerization (**B**) of olefinic alcohols with **2-PF<sub>6</sub>**. b) Proposed pathway (**C**) for hydrogenation and suppression of isomerization with **2@1-SO<sub>3</sub>Na**.

This disfavors coordination of the hydroxyl group to Ir and enables formation of the dihydrogen complex **IV**, in preference to **I** (pathway **C**). Productive hydrogenation occurs via an octahedral

## COMMUNICATION

Ir(V)-trihydride species (**IV**), as proposed for non-functionalized alkenes with Crabtree-type catalysts<sup>[26]</sup> and  $\beta$ -elimination is suppressed since Ir is coordinatively saturated throughout.

**2@1-SO<sub>3</sub>Na** also resulted in higher overall conversions for the hydrogenation of olefinic alcohols, compared to **2-PF<sub>6</sub>**. A series of selective poisoning experiments revealed that the isomerization products are not responsible for catalyst deactivation (Table S7). We thus suggest that **2@1-SO<sub>3</sub>Na** has a longer lifetime due to: (i) spatial isolation of the positively charged catalytically active species inside the pores of the anionic MOF which hinders the formation of catalytically inactive clusters and/or (ii) reversible coordination of the sulfonate anion, as shown with **2-OTs** and **3**.

In summary, we demonstrate that the hybrid catalyst **2@1-SO<sub>3</sub>Na** is capable of hydrogenating non-functionalized alkenes at low loadings in solution and in the gas phase under mild conditions. It outperforms its homogeneous counterpart in the hydrogenation of olefinic alcohols, showing significantly higher conversions under otherwise identical conditions. In addition, encapsulation results in a pronounced selectivity enhancement in favor of hydrogenation by suppressing the competing isomerization reaction due to extended coordination sphere interactions of the catalytic center with the chemically functionalized internal surface of the MOF. Capitalizing on such stability and selectivity enhancements is likely to be important in deploying such hybrid systems in catalytic applications under continuous flow.<sup>[27]</sup> In metalloenzymes, it is well-established that well-positioned amino acid residues around the active site control its reactivity and selectivity.<sup>[3]</sup> Here, the well-defined, readily engineered MOF chemical microenvironment controls reactivity and selectivity of the encapsulated catalyst, allowing for discrimination between distinct reaction pathways.

## Acknowledgements

UK Catalysis Hub Consortium is kindly thanked for support and resources (EPSRC grants EP/K014706/1, EP/K014668/1, EP/K014854/1, EP/K014714/1 and EP/M013219/1).

**Keywords:** Crabtree's catalyst • encapsulation • hydrogenation • metal organic framework • allylic alcohol

- [1] a) H. Furukawa, K. E. Cordova, M. O'Keeffe, O. M. Yaghi, *Science* **2013**, 341, 1230444; b) B. Li, H.-M. Wen, Y. Cui, W. Zhou, G. Qian, B. Chen, *Adv. Mater.* **2016**, 28, 8819-8860; c) H.-C. Zhou, S. Kitagawa, *Chem. Soc. Rev.* **2014**, 43, 5415-5418 and references therein.
- [2] a) J. Gascon, A. Corma, F. Kapteijn, F. X. Llabrés i Xamena, *ACS Catal.* **2014**, 4, 361-378; b) A. H. Chughtai, N. Ahmad, H. A. Younus, A. Laypkov, F. Verpoort, *Chem. Soc. Rev.* **2015**, 44, 6804-6849; c) A. Grigoropoulos, in *Modern Developments in Catalysis*, World Scientific (Europe), **2016**, pp. 123-158; d) S. M. J. Rogge, A. Bavykina, J. Hajek, H. Garcia, A. I. Olivos-Suarez, A. Sepulveda-Escribano, A. Vimont, G. Clet, P. Bazin, F. Kapteijn, M. Daturi, E. V. Ramos-Fernandez, F. X. Llabrés i Xamena, V. Van Speybroeck, J. Gascon, *Chem. Soc. Rev.* **2017**, 46, 3134-3184.
- [3] a) S. W. Ragsdale, *Chem. Rev.* **2006**, 106, 3317-3337; b) M. Zhao, H.-B. Wang, L.-N. Ji, Z.-W. Mao, *Chem. Soc. Rev.* **2013**, 42, 8360-8375; c) R. H. Holm, E. I. Solomon, *Chem. Rev.* **2014**, 114, 3367-3368.
- [4] a) C. W. Jones, *Top. Catal.* **2010**, 53, 942-952; b) M. Raynal, P. Ballester, A. Vidal-Ferran, P. W. N. M. van Leeuwen, *Chem. Soc. Rev.* **2014**, 43, 1660-1733 and 1734-1787; d) C. J. Brown, F. D. Toste, R. G. Bergman, K. N. Raymond, *Chem. Rev.* **2015**, 115, 3012-3035; e) S. Hübner, J. G. de Vries, V. Farina, *Adv. Synth. Catal.* **2016**, 358, 3-25.
- [5] a) A. Fateeva, P. A. Chater, C. P. Ireland, A. A. Tahir, Y. Z. Khimyak, P. V. Wiper, J. R. Darwent, M. J. Rosseinsky, *Angew. Chem. Int. Ed.* **2012**, 51, 7440-7444; b) L. Mitchell, P. Williamson, B. Ehrlichová, A. E. Anderson, V. R. Seymour, S. E. Ashbrook, N. Acerbi, L. M. Daniels, R. I. Walton, M. L. Clarke, P. A. Wright, *Chem. Eur. J.* **2014**, 20, 17185-17197; c) K. Manna, T. Zhang, M. Carboni, C. W. Abney, W. Lin, *J. Am. Chem. Soc.* **2014**, 136, 13182-13185; d) H. Fei, S. M. Cohen, *J. Am. Chem. Soc.* **2015**, 137, 2191-2194; e) Z. Li, J.-D. Xiao, H.-L. Jiang, *ACS Catal.* **2016**, 6, 5359-5365; f) A. M. Fracaroli, P. Siman, D. A. Nagib, M. Suzuki, H. Furukawa, F. D. Toste, O. M. Yaghi, *J. Am. Chem. Soc.* **2016**, 138, 8352-8355; g) N. C. Thacker, Z. Lin, T. Zhang, J. C. Gilhula, C. W. Abney, W. Lin, *J. Am. Chem. Soc.* **2016**, 138, 3501-3509.
- [6] a) J. Canivet, S. Aguado, Y. Schuurman, D. Farrusseng, *J. Am. Chem. Soc.* **2013**, 135, 4195-4198; b) A. M. Rasero-Almansa, A. Corma, M. Iglesias, F. Sanchez, *Green Chem.* **2014**, 16, 3522-3527; c) S. A. Burgess, A. Kassie, S. A. Baranowski, K. J. Fritzsche, K. Schmidt-Rohr, C. M. Brown, C. R. Wade, *J. Am. Chem. Soc.* **2016**, 138, 1780-1783; d) M. Rimoldi, A. Nakamura, N. A. Vermeulen, J. J. Henkels, A. K. Blackburn, J. T. Hupp, J. F. Stoddart, O. K. Farha, *Chem. Sci.* **2016**, 7, 4980-4984; e) A. Burgun, C. J. Coghlan, D. M. Huang, W. Chen, S. Horike, S. Kitagawa, J. F. Alvino, G. F. Metha, C. J. Sumby, C. J. Doonan, *Angew. Chem. Int. Ed.* **2017**, 56, 8412-8416.
- [7] a) Z. Guo, C. Xiao, R. V. Maligal-Ganesh, L. Zhou, T. W. Goh, X. Li, D. Tesfagaber, A. Thiel, W. Huang, *ACS Catal.* **2014**, 4, 1340-1348; b) S. Yuan, Y. P. Chen, J. S. Qin, W. Lu, L. Zou, Q. Zhang, X. Wang, X. Sun, H.-C. Zhou, *J. Am. Chem. Soc.* **2016**, 138, 8912-8919.
- [8] a) D. J. Xiao, J. Oktawiec, P. J. Milner, J. R. Long, *J. Am. Chem. Soc.* **2016**, 138, 14371-14379; b) W. Shi, L. Cao, H. Zhang, X. Zhou, B. An, Z. Lin, R. Dai, J. Li, C. Wang, W. Lin, *Angew. Chem. Int. Ed.* **2017**, 56, 9704-9709; c) L. Li, Q. Yang, S. Chen, X. Hou, B. Liu, J. Lu, H.-L. Jiang, *Chem. Comm.* **2017**, 53, 10026-10029.
- [9] R. Crabtree, *Acc. Chem. Res.* **1979**, 12, 331-337.
- [10] a) D. F. Chodosh, R. H. Crabtree, H. Felkin, S. Morehouse, G. E. Morris, *Inorg. Chem.* **1982**, 21, 1307-1311; b) Y. Xu, M. A. Celik, A. L. Thompson, H. Cai, M. Yurtsever, B. Odell, J. C. Green, D. M. P. Mingos, J. M. Brown, *Angew. Chem. Int. Ed.* **2009**, 48, 582-585.
- [11] a) H. M. Lee, T. Jiang, E. D. Stevens, S. P. Nolan, *Organometallics* **2001**, 20, 1255-1258; b) L. D. Vazquez-Serrano, B. T. Owens, J. M. Buriak, *Inorg. Chim. Acta* **2006**, 359, 2786-2797; c) E. L. Kolychev, S. Kronig, K. Brandhorst, M. Freytag, P. G. Jones, M. Tamm, *J. Am. Chem. Soc.* **2013**, 135, 12448-12459.
- [12] a) S. P. Smidt, N. Zimmermann, M. Studer, A. Pfaltz, *Chem. Eur. J.* **2004**, 10, 4685-4693; b) G. L. Moxham, T. M. Douglas, S. K. Brayshaw, G. Kociok-Kohn, J. P. Lowe, A. S. Weller, *Dalton Trans.* **2006**, 5492-5505.
- [13] H. Li, C. Mazet, *Acc. Chem. Res.* **2016**, 49, 1232-1241.
- [14] a) G. Stork, D. E. Kahne, *J. Am. Chem. Soc.* **1983**, 105, 1072-1073; b) R. H. Crabtree, M. W. Davis, *J. Org. Chem.* **1986**, 51, 2655-2661.
- [15] a) D. T. Genna, A. G. Wong-Foy, A. J. Matzger, M. S. Sanford, *J. Am. Chem. Soc.* **2013**, 135, 10586-10589; b) A. Grigoropoulos, G. F. S. Whitehead, N. Perret, A. P. Katsoulidis, F. M. Chadwick, R. P. Davies, A. Haynes, L. Brammer, A. S. Weller, J. Xiao, M. J. Rosseinsky, *Chem. Sci.* **2016**, 7, 2037-2050.
- [16] a) G. Akiyama, R. Matsuda, H. Sato, M. Takata, S. Kitagawa, *Adv. Mater.* **2011**, 23, 3294-3297; b) Y.-X. Zhou, Y.-Z. Chen, Y. Hu, G. Huang, S.-H. Yu, H.-L. Jiang, *Chem. Eur. J.* **2014**, 20, 14976-14980; c) J. Juan-Alcaniz, R. Gielisse, A. B. Lago, E. V. Ramos-Fernandez, P. Serra-Crespo, T. Devic, N. Guillou, C. Serre, F. Kapteijn, J. Gascon, *Catal. Sci. Technol.* **2013**, 3, 2311-2318.
- [17] G. Férey, C. Mellot-Draznieks, C. Serre, F. Millange, J. Dutour, S. Surblé, I. Margiolaki, *Science* **2005**, 309, 2040-2042.
- [18] Y. Zhang, B. Li, R. Krishna, Z. Wu, D. Ma, Z. Shi, T. Pham, K. Forrest, B. Space, S. Ma, *Chem. Comm.* **2015**, 51, 2714-2717.
- [19] D. T. Genna, L. Y. Pfund, D. C. Samblanet, A. G. Wong-Foy, A. J. Matzger, M. S. Sanford, *ACS Catal.* **2016**, 6, 3569-3574.
- [20] Note: Although we cannot discount chemical shift changes in the <sup>31</sup>P SS NMR spectrum due to the presence of paramagnetic Cr(III) centers, no significant changes were reported when molecular species were incorporated into pristine MIL-101(Cr). See reference 17.
- [21] a) D. Yang, S. O. Odoh, J. Borycz, T. C. Wang, O. K. Farha, J. T. Hupp, C. J. Cramer, L. Gagliardi, B. C. Gates, *ACS Catal.* **2016**, 6, 235-247; b) F. M. Chadwick, A. I. McKay, A. J. Martinez-Martinez, N. H. Rees, T. Kramer, S. A. Macgregor, A. S. Weller, *Chem. Sci.* **2017**, 8, 6014-6029.
- [22] a) M. Moreno, L. N. Kissell, J. B. Jasinski, F. P. Zamborini, *ACS Catal.* **2012**, 2, 2602-2613; b) E. Sadeghmoghaddam, H. Gu, Y.-S. Shon, *ACS Catal.* **2012**, 2, 1838-1845.
- [23] a) L. Mantilli, C. Mazet, *Tetrahedron Lett.* **2009**, 50, 4141-4144; b) L. Mantilli, D. Gérard, S. Torche, C. Besnard, C. Mazet, *Angew. Chem. Int. Ed.* **2009**, 48, 5143-5147.
- [24] R. Uma, C. Crevisy, R. Gree, *Chem. Rev.* **2003**, 103, 27-51.
- [25] a) A. Rifat, G. Kociok-Köhn, J. W. Steed, A. S. Weller, *Organometallics* **2004**, 23, 428-432; b) E. Piras, F. Läng, H. Rügger, D. Stein, M. Wörle, H. Grützmacher, *Chem. Eur. J.* **2006**, 12, 5849-5858.
- [26] J. J. Veredel, O. Pàmies, M. Diéguez, P. G. Andersson, *Chem. Rev.* **2014**, 114, 2130-2169.

COMMUNICATION

---

[27] U. Hintermair, G. Francio, W. Leitner, Chem. Comm. **2011**, 47, 3691-3701.

WILEY-VCH

Accepted Manuscript




## COMMUNICATION

## Entry for the Table of Contents (Please choose one layout)

Layout 1:

## COMMUNICATION

Encapsulation of Crabtree's catalyst inside the sulfonated analogue of MIL-101(Cr) by cation exchange significantly increases activity and selectivity to hydrogenation of olefinic alcohols with the MOF chemical microenvironment directing the substrate along one out of two competing reaction pathways.

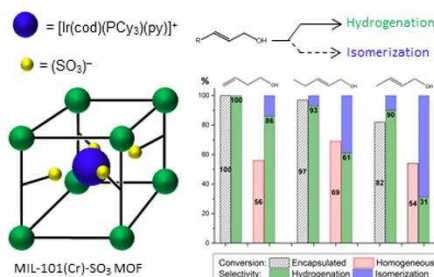

Dr A. Grigoropoulos, Dr A. I. McKay, Dr A. P. Katsoulidis, Dr R. P. Davies, Dr A. Haynes, Prof. L. Brammer, Prof. J. Xiao, Prof. A. S. Weller\* and Prof. M. J. Rosseinsky\*

**Encapsulation of Crabtree's catalyst in sulfonated MIL-101(Cr): enhancement of stability and selectivity between competing reaction pathways by the MOF chemical microenvironment**

Layout 2:

## COMMUNICATION

((Insert TOC Graphic here))

Author(s), Corresponding Author(s)\*

Page No. – Page No.

Title

Text for Table of Contents