



Deposited via The University of Sheffield.

White Rose Research Online URL for this paper:

<https://eprints.whiterose.ac.uk/id/eprint/100035/>

Version: Accepted Version

Article:

Shang, Y., Yu, X. and Romero-González, M.E. (2015) Screening of algae material as a filter for heavy metals in drinking water. *Algal Research*, 12. pp. 258-261. ISSN: 2211-9264

<https://doi.org/10.1016/j.algal.2015.09.003>

Reuse

Items deposited in White Rose Research Online are protected by copyright, with all rights reserved unless indicated otherwise. They may be downloaded and/or printed for private study, or other acts as permitted by national copyright laws. The publisher or other rights holders may allow further reproduction and re-use of the full text version. This is indicated by the licence information on the White Rose Research Online record for the item.

Takedown

If you consider content in White Rose Research Online to be in breach of UK law, please notify us by emailing eprints@whiterose.ac.uk including the URL of the record and the reason for the withdrawal request.

1 **Screening of Algae Material as a Filter for Heavy Metals in Drinking Water**

2 **ABSTRACT** Calcium alginate beads generated from alginic acid sodium salt from brown algae were
3 used to explore the adsorption processes of lead and copper ions in water. The main parameters in the
4 experiment were initial pH, equilibrium time, and concentration of metal ions. The adsorption processes
5 of lead and copper were carried out under specific pH values. Moreover, the multiple adsorption of lead
6 and copper was carried out to study the competition of two metal ions. It was found that the highest
7 adsorption percentage of lead and copper was achieved under the optimum pH respectively. Meanwhile,
8 the highest adsorption percentage of multiple adsorptions was lower than that of single metal adsorption
9 under pH of 4. The optimum pH was utilized in the kinetic experiment and equilibrium experiment. The
10 pseudo-second-order kinetic equations would fit the experimental data well. The maximum amounts of
11 adsorption for lead and copper based on Langmuir models were 250 mg/g and 62.5 mg/g respectively.

12 **Keywords:** Heavy metals adsorption; Biosorption; Dry Ca-alginate beads; Kinetic; Isotherm

13 **1. INTRODUCTION**

14 The security of water is the basic requirement and important to health for human. More and more
15 sources of fresh water such as rivers and ground water have been polluted by human activities. Among
16 all of the contaminants in water, lead is one of the most serious polluted components which must be
17 controlled below the maximum limits (Saleh & Gupta, 2012). It tends to generate bioaccumulation
18 effect in living systems and cause nervous disease to offspring (Tiwari & Tripathi, 2012). Copper is a
19 common kind of heavy metal that has been widely used for productions in many industries. The large
20 amount of copper-based wastes from different processes would release into water which would cause
21 serious pollution. Therefore, the treatment of lead and copper ions from water is significant to ensure
22 the quality of drinking water.

23 The Algae are available in fresh water and seawater; they could be found almost everywhere in water
24 environment systems. The algae have larger surface area with high binding affinity than other materials
25 (Sari & Tuzen, 2008). Thus, algae become cost-effective materials for removal of toxic compounds.
26 Among different kinds of algae biomass, the dry brown marine algal biomass has been considered one
27 of the potential biomass materials for removing toxic metals. The nature of the adsorption of heavy
28 metals is that the special structures of cell wall in algal biomass which contains many functional groups
29 such as carboxyl, amino, hydroxyl and sulphate that can bind heavy metal at a certain pH value (Gupta
30 & Rastogi, 2008).

31 In this project, the aim is to investigate the capacity of algal adsorption for the two target metal ions for
32 drinking water. The adsorption effect of lead and copper would be examined with different parameters
33 such as pH, equilibrium time and the initial concentration of metal ions. The equilibrium adsorption data
34 would be evaluated with kinetic model and Langmuir isotherm model.

35 **2. MATERIALS AND METHODS**

36 **2.1 Biomass Preparation**

37 A 2 % solution of Alginic acid sodium salt from brown algae (Sigma) was dripped into 0.05 mol/L
38 CaCl₂ solution with the gentle magnetic stirring to form calcium alginate beads. In order to stabilize the
39 beads, the Ca-alginate beads in CaCl₂ solution would be stored in a fridge at 4 °C for 24 h. Then the
40 beads were filtered and washed several times with deionized water to remove the excess CaCl₂ solution.
41 Finally, the beads were dried in an oven at 50 °C for 24 h to form the dry Ca-alginate beads which
42 would be used as biomass materials in the experiments. The dry beads would be stored in a clean and
43 dry bottle for further experiments.

44 **2.2 Reagents and Equipments**

45 All of the chemical reagents were analytical grade and without further purification. The solid
46 $\text{CuSO}_4 \cdot 5\text{H}_2\text{O}$ and $\text{Pb}(\text{NO}_3)_2$ (Fisher Scientific Company) would be used to generate 1000 mg/L
47 standard stock of lead solution and copper solution that would be diluted to different concentration for
48 experiments. 0.1 mol/L HNO_3 and 0.1 mol/L NaOH was prepared to adjust pH value in the batch
49 experiment. Meanwhile, a Perkin Elmer AAnalyst 200 flame atomic adsorption spectrometer (FAAS)
50 was used to measure the concentration of lead and copper in the batch experiments.

51 **2.3 Effect of Initial pH**

52 50 mg/L lead solution and copper solution were respectively used to study the effect of pH to the
53 adsorption of heavy metals on Ca-alginate beads. The adsorption effect of 25 mL of solution sample and
54 0.05 g alginate beads were tested under different pH of 4, 6 and 8 in the batch experiments. The samples
55 were triplicate in order to obtain the average concentration of the sample solution. All of the solution
56 samples were under rotary shaker at 140 rpm at room temperature for 24 h. The metal concentration for
57 solution samples was determined by FAAS. The adsorption percentage under different pH values would
58 be compared to test the optimum pH values for adsorption of lead and copper separately.

59 The percentage of metal adsorption on Ca-alginate beads was calculated as the equation below:

$$60 \quad \text{Adsorption (\%)} = \frac{(C_i - C_f)}{C_i} \times 100\% \quad \text{Eq. 2.1}$$

61 Where, C_i is the initial concentration of metal; C_f is the final concentration of the metal.

62 **2.4 Effect of Multiple Adsorption**

63 In order to study the metal adsorption on Ca-alginate beads, the multiple adsorptions for lead and copper
64 were carried out under pH of 4 and 6. The initial concentration of the lead and copper solution used in
65 this experiment was respectively 25 mg/L, 50 mg/L and 100 mg/L. 50 mL of the mixing solution with

66 the same initial concentration of lead and copper solution and 0.1 g Ca-alginate beads were tested under
67 the rotary shaker at 140 rpm for 2 h. Then the solution and beads would be filtered and the filtrate was
68 prepared to measure the concentration with FAAS. The percentage of multiple adsorptions would be
69 calculated as well.

70 **2.5 Equilibrium Experiments**

71 In equilibrium experiments, all of the solution samples were adjusted to optimum pH of 4. The solution
72 samples for lead and copper were respectively diluted to different concentration from 10 mg/L to 400
73 mg/L. 50 mL of solution sample and 0.1 g Ca-alginate dry beads were tested under the rotary shaker at
74 140 rpm for different contact time from 30 minutes to 48 h. The equilibrium time would be determined
75 from FAAS according to the results of solution concentration before and after experiment. The kinetic
76 models and Langmuir isotherm models for lead and copper adsorptions would be discussed in details in
77 following sections.


78 **3. DISCUSSION**

79 **3.1 Characterization of Ca-alginate Beads**

80 The weight measurement showed that the wet beads contained about 95% w/w water. The density for
81 wet beads was 0.9512 g/cm^3 . The particle sizes were determined by a sieving mesh system. The
82 diameter for most wet beads was in the range of 4mm, while the dry beads showed the maximum
83 diameter of 2 mm. It was shown that the volume of the beads after drying decrease rapidly. Even though
84 the porosity of the two types of beads were not examined, the previous study showed that wet beads
85 were with little pores while the dry beads were with a large ratio of porosity and the roughness of the
86 dry beads increased the surface area which were valuable for binding heavy metal ions.(Lagoa &
87 Rodrigues, 2009).

88 **3.2 Effect of Initial pH**

89 According to the adsorption percentage results in Figure 3.1, both lead and copper solution samples
90 achieved the highest adsorption performance under pH of 4. With increasing of pH, the adsorption
91 percentage of metal ions decreased. This result demonstrated that the dry Ca-alginate beads indeed had
92 the capacity of adsorbing heavy metals under proper pH conditions.

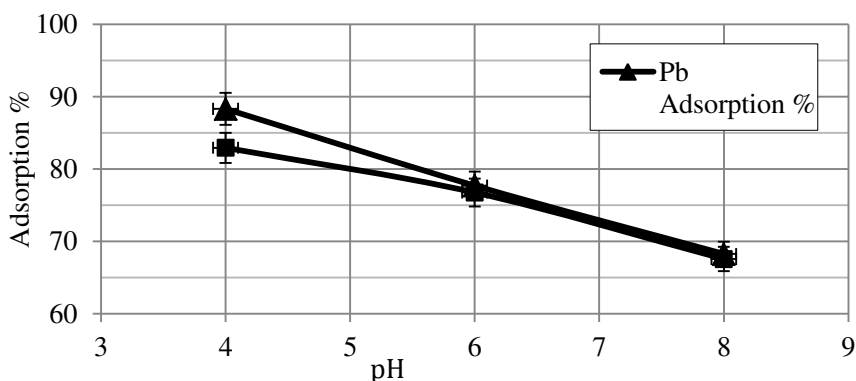


93

94 Figure 3.1 Effect of pH for Adsorption of 50 mg/L Lead and Copper Solution onto dry Ca-alginate
95 Beads for 24 h.

96 The carboxyl groups, the main functional groups on Ca-alginate beads were dependent on pH values.
97 Moreover, the initial pH would affect the mechanism of metal chemistry and the functional groups on
98 alginate materials. The surface of Ca-alginate beads were positively charged under low pH so that the
99 metal ions were not able to bind to functional groups on alginate biomass due to the competition
100 between hydrogen ions and the metal ions. With the increasing of pH, more ligands with binding sites
101 on the surfaces of beads particles released, as the surface of the particles were negatively charged and
102 the metal ions would be able to bind the functional groups on the bead particles. Therefore, the optimum
103 pH for adsorption of lead and copper was pH of 4. The reason was that under pH of 4 the solution was
104 not extremely protonated and suitable for the weak acidic nature of binding sites so that the metal ions
105 could bind to the functional groups carboxyl acid groups. The highest percentage of adsorption for lead

106 was about 88% while the best adsorption for copper under pH of 4 was about 83%. The similar results
 107 were obtained from literatures. The highest percentages of lead and copper adsorption with Ca-alginate
 108 were respectively around 90% and 80% (Sheng *et al.*, 2004). Therefore, pH of 4 would be used as
 109 optimum pH for further experiments.

110 3.3 Effect of Multiple Adsorption

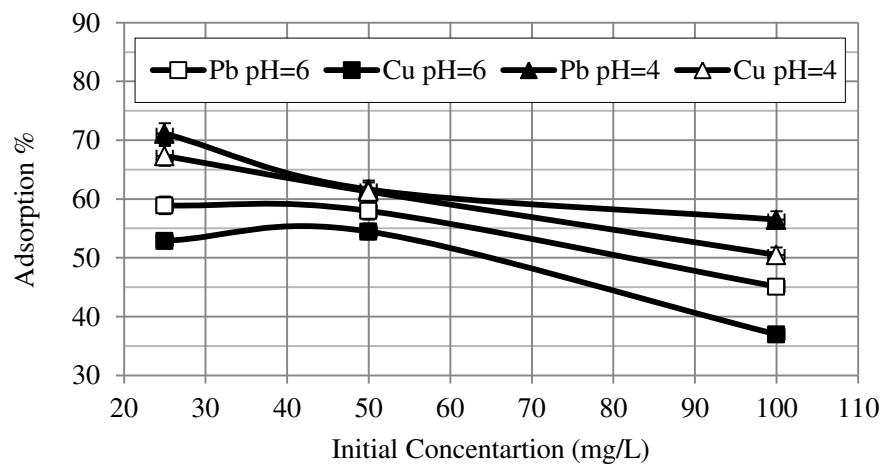

111

112 Figure 3.2 Effect of pH for Adsorption of Multiple Metal Solution of Different Initial Concentration

113

under pH of 4 and 6.

114 Figure 3.2 showed that the highest adsorption percentage for lead and copper were achieved under pH

115 of 4. The highest adsorption percentage for lead and copper were 72% and 68% under pH of 4. The

116 adsorption percentage decreased compared to the single adsorption systems. It was found that the

117 functional groups preferred to lead ions. The lead ions could be able to bind with carboxyl groups that

118 offered negatively charged sites and coordinative interaction better, these ions tended to have more

119 affinity to the functional groups on alginate beads. Meanwhile, the lead ions had larger radii than that of


120 copper ions (Chong & Volesky, 1995). The ions with large radii in the “egg box” would be stable. The

121 other properties such as the softness of the ions and electron negativity, electrode potentials for various

122 ions also could contribute to the competition for multiple metal adsorptions (Yun, 2004).


123 **3.4 Kinetic Adsorption Experiments**

124 Figure 3.3 and 3.4 showed that the concentration of lead and copper decreased rapidly within 2 h and
 125 finally reached the equilibrium concentration for 24 h respectively. The previous studies showed that
 126 equilibrium time were various as the reaction conditions were different. However, the equilibrium time
 127 for this experiment was a little long compared with other results in the literatures which demonstrated
 128 that the equilibrium time was only several hours for metal adsorption (Jalali *et al.*, 2002). The long
 129 equilibrium time would restrain the application for treating toxic metal ions significantly.

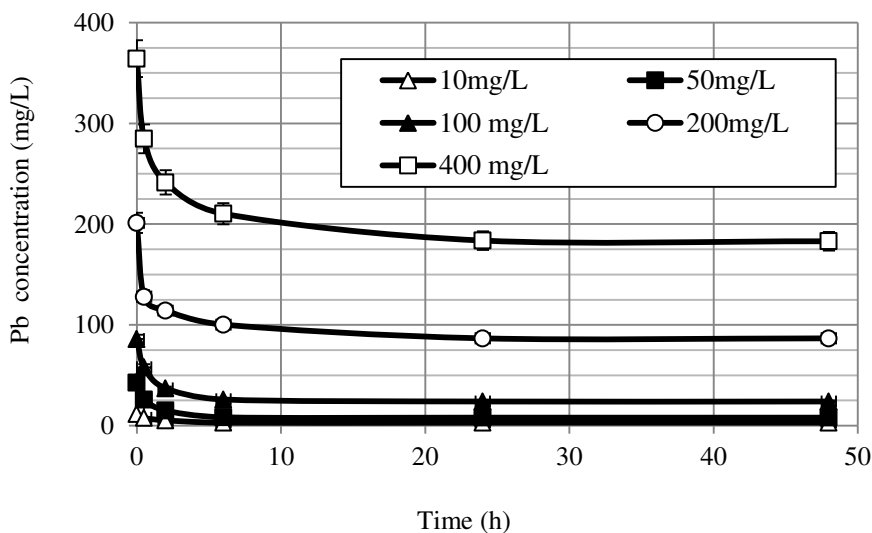

130

131 Figure 3.3 Kinetic Adsorption for Lead with Different Initial Concentration under pH of 4.

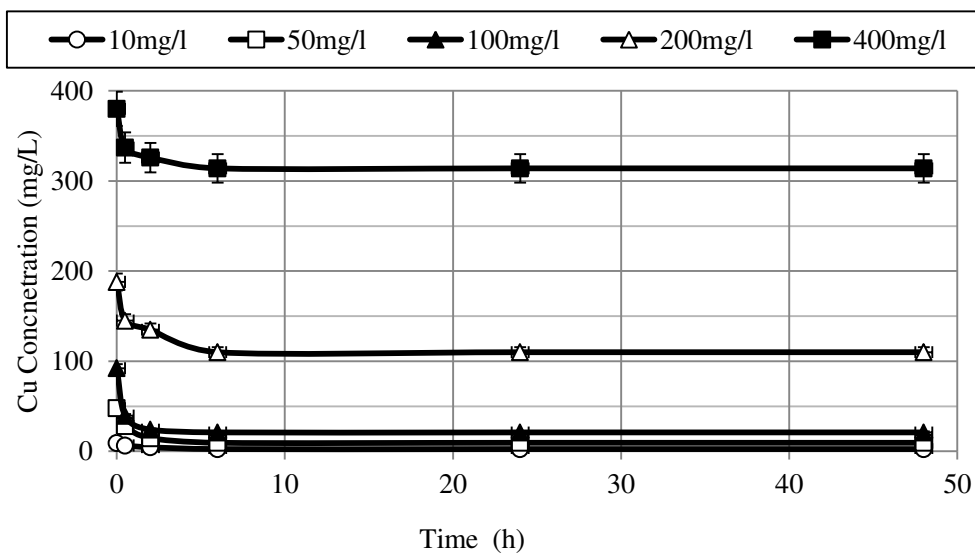

132

133 Figure 3.4 Kinetic Adsorption for Copper with Different Initial Concentration under pH of 4.

134 The kinetic models were useful to examine the quantitative description of the adsorption process
135 dynamics. The pseudo-second-order model was used in this experiment. The linear equation for
136 pseudo-second-order kinetic model was given as:

137
$$\frac{t}{q_t} = \frac{1}{k_2 q_e^2} + \left(\frac{1}{q_e}\right)t \quad \text{Eq. 3.1}$$

138 Where, q_t (mg/g) is the amount of adsorption at a given time t (h); q_e (mg/g) is the amount of adsorption
139 at equilibrium time; k_2 (g/mg h) is the rate constant of pseudo-second-order kinetic equation.

140 According to the results in Table 3.1, the correlation coefficients for both lead and copper solutions
141 indicated that the pseudo-second-order model could fit the concentration of lead and copper solutions
142 well. With the increasing of the initial concentration, the rate constants for lead adsorption were from
143 0.206 to 0.005 g/mg h while the constants for copper adsorption were from 0.119 to 0.022 g/mg h. It
144 was found that with the increasing of concentration, the rate constants decreased evidently. The rate
145 constants for lead adsorption were generally higher than that of copper adsorption. This result indicated
146 that the Ca-alginate beads would bind with lead ions faster. However, when the capacity of adsorption
147 was reached, the rate of adsorption would decrease seriously. According to previous studies, the results
148 of rate constant in this experiment were not comparable with some results from previous studies (Deng
149 *et al.*, 2006). The main reason was the various experiment conditions, including different temperature,
150 beads dosage, equilibrium time, and initial concentrations for different metal ions.

151 Table 3.1 the Kinetic Constants of Pseudo-Second-Order Equation for Adsorption.

Cu mg/L	K ₂ g/mg h	R ²	Pb mg/L	K ₂ g/mg h	R ²
10	0.119	0.997	10	0.206	0.999

Cu mg/L	K ₂ g/mg h	R ²	Pb mg/L	K ₂ g/mg h	R ²
50	0.057	0.999	50	0.065	0.998
100	0.098	0.999	100	0.028	0.999
200	0.012	0.998	200	0.021	0.999
400	0.022	0.999	400	0.005	0.999

152 3.5 Equilibrium Isotherm Models

153 The Langmuir isotherm was a widely used model to test the capacity of the biosorbents to heavy metals.

154 The assumption of Langmuir model was that the rate of occurring metal adsorption at each binding sites

155 of the beads was equal to each other. The linear equation for Langmuir isotherm model was represented

156 as:

$$157 \quad \frac{C_e}{q_e} = \frac{C_e}{q_m} + \frac{1}{K_L q_m} \quad \text{Eq. 3.2}$$

158 Where, q_e is the equilibrium concentration for metal ion on the Ca-alginate beads (mg/g); C_e is the

159 equilibrium concentration for metal ion in the solution (mg/L); q_m is the maximum adsorption capacity

160 for the calcium alginate beads (mg/g); K_L is the Langmuir adsorption constant (L/mg).

161 The correlation coefficients for lead and copper adsorptions were 0.960 and 0.989 respectively which

162 indicated the Langmuir models would fit the data well. The maximum capacities for adsorptions were


163 250 mg/g and 62.5 mg/g for lead and copper respectively. According to the intercepts of the equations,

164 the equilibrium constants would be determined and the values were 1.3×10^{-1} L/mg for lead adsorption

165 and $K_L 1.7 \times 10^{-2}$ L/mg for copper adsorption. The constants were related to the affinity of binding sites

166 (Deng *et al.*, 2006). The capacity of adsorption for lead was evidently higher than that of copper

167 adsorption. The adsorption capacity order was: Pb > Cu.

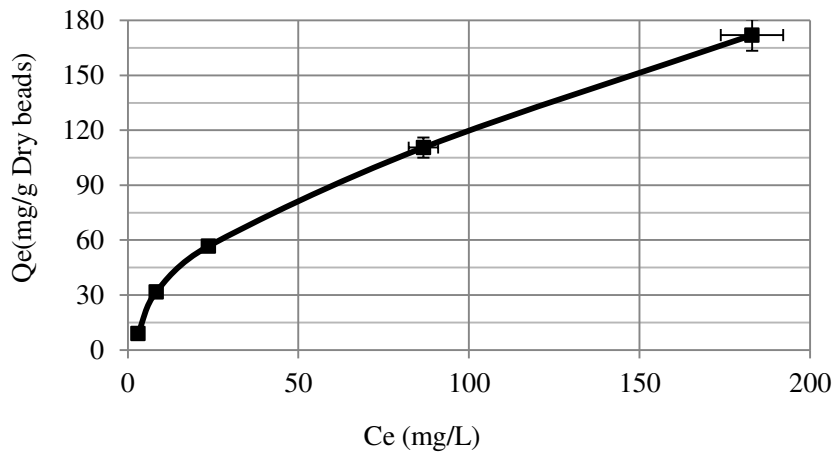


168

169 Figure 3.5 Langmuir Isotherms for Adsorption of Lead with Dry Ca-alginate Beads (Initial

170

Concentration from 10 mg/L to 400 mg/L, pH=4, 48h)

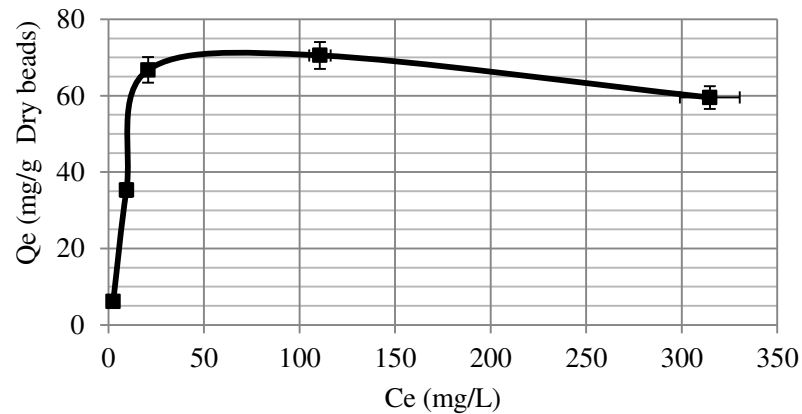

171

172 Figure 3.6 Langmuir Isotherms for Absorption of Copper with Dry Calcium-alginate Beads (Initial

173

Concentration from 10 mg/L to 400 mg/L, pH=4, 48 h)

174 According to Figure 3.5 and Figure 3.6, it was found that the amount of lead adsorption on beads would

175 not reach the maximum capacity while the capacity of copper adsorption on beads had reached its

176 maximum capacity for saturated state; therefore, the beads could not adsorb copper ions any more. It

177 was observed through the copper adsorption that after equilibrium, the amount of copper adsorption on

178 beads decreased with the increasing of initial concentration in solution. Due to the chemical property of

179 copper ions, the affinity of binding copper ions to Ca-alginate beads may be not strong enough and the

180 reaction would proceed towards the opposite direction which cause the occurrence of desorption for
181 copper ions. The order was similar to the result from previous literatures that demonstrated the affinity
182 order was $Pb > Cd > Cu > Ba > Sr > Ca > Co > Ni$ (Papageorgiou *et al.*, 2006). The result also indicated
183 that the active binding sites were preferred to metal ions with larger radii that would form a more
184 stable structure with the coordination of oxygen atoms.

185 **4. CONCLUSIONS**

186 As a whole, the optimum initial pH for adsorption of lead and copper ions in solution were both 4. In
187 the multiple adsorption systems, the adsorption percentage of both lead and copper decreased compared
188 with the results of single adsorption experiments. It was found that the pseudo-second-order model was
189 appropriate to fit the experimental data. According to Langmuir model, the maximum capacity of
190 adsorption for lead and copper were 250 mg/g and 62.5 mg/g respectively which indicated the potential
191 ability for removing heavy metals in water.

192 **ACKNOWLEDGEMENT**

193 The author would like to express her sincere appreciation to her supervisor Dr Maria who offered the
194 academic guidance. In addition, thanks to Thomas Turton for the technical guidance.

195

196 **5. REFERENCES**

197 Chong, K. H., & Volesky, B., (1995). Description of two-metal biosorption equilibria by Langmuir-type
198 models. *Biochem Eng J*, 47(4), 451–460.

199 Deng, L., Su, Y., Su, H., Wang, X., & Zhu, X., (2006). Biosorption of copper (II) and lead (II) from
200 aqueous solutions by nonliving green algae *Cladophora fascicularis*: equilibrium, kinetics and
201 environmental effects. *Adsorption*, 12(4), 267-277.

202 Gupta, V., & Rastogi, A., (2008). Biosorption of lead from aqueous solutions by green algae *Spirogyra*
203 species: Kinetics and equilibrium studies. *J. Hazard Mater*, 152(1), 407-414.

204 Jalali, R., Ghafourian, H., Asef, Y., Davarpanah, S. J., & Sepehr, S., (2002). Removal and recovery of
205 lead using nonliving biomass of marine algae. *J. Hazard Mater*, 92(3), 253-262.

206 Lagoa, R., & Rodrigues, J. R., (2009). Kinetic analysis of metal uptake by dry and gel alginate particles.
207 *Biochem Eng J*, 46(3), 320-326.

208 Papageorgiou, S., Katsaros, F., Kouvelos, E., Nolan, J., Le Deit, H., & Kanellopoulos, N., (2006).
209 Heavy metal sorption by calcium alginate beads from *Laminaria digitata*. *J. Hazard Mater*, 137(3),
210 1765-1772.

211 Saleh, T., & Gupta, V., (2012). Column with CNT/magnesium oxide composite for lead (II) removal
212 from water. *Environ Sci Pollut R*, 19(4), 1224-1228.

213 Sari, A., & Tuzen, M., (2008). Biosorption of total chromium from aqueous solution by red algae
214 (*Ceramium virgatum*): Equilibrium, kinetic and thermodynamic studies. *J. Hazard Mater*, 160(2),
215 349-355.

216 Sheng, P. X., Ting, Y. P., Chen, J. P., & Hong, L., (2004). Sorption of lead, copper, cadmium, zinc, and

- 217 nickel by marine algal biomass: characterization of biosorptive capacity and investigation of
218 mechanisms. *J. Colloid Interf Sci*, 275(1), 131-141.
- 219 Tiwari, S. & Tripathi, I., (2012). Lead Pollution-An Overview. *J. Environ Sci*, 1(4), 84-86.
- 220 Yun, Y. S., (2004). Characterization of functional groups of protonated *Sargassum polycystum* biomass
221 capable of binding protons and metal ions. *J. Microbiol Biotechnol*, 14(1), 29–34.