

This is a repository copy of *Towards financially viable phytoextraction and production of plant-based palladium catalysts*.

White Rose Research Online URL for this paper:

<https://eprints.whiterose.ac.uk/id/eprint/112752/>

Version: Accepted Version

---

**Article:**

Harumain, Zakuan A.S., Parker, Helen L. orcid.org/0000-0001-7576-2470, Muñoz García, Andrea et al. (10 more authors) (2017) Towards financially viable phytoextraction and production of plant-based palladium catalysts. *Environmental science & technology*. pp. 2992-3000. ISSN: 1520-5851

<https://doi.org/10.1021/acs.est.6b04821>

---

**Reuse**

Items deposited in White Rose Research Online are protected by copyright, with all rights reserved unless indicated otherwise. They may be downloaded and/or printed for private study, or other acts as permitted by national copyright laws. The publisher or other rights holders may allow further reproduction and re-use of the full text version. This is indicated by the licence information on the White Rose Research Online record for the item.

**Takedown**

If you consider content in White Rose Research Online to be in breach of UK law, please notify us by emailing [eprints@whiterose.ac.uk](mailto:eprints@whiterose.ac.uk) including the URL of the record and the reason for the withdrawal request.

This document is confidential and is proprietary to the American Chemical Society and its authors. Do not copy or disclose without written permission. If you have received this item in error, notify the sender and delete all copies.

## Towards financially viable phytoextraction and production of plant-based palladium catalysts

Journal:	<i>Environmental Science &amp; Technology</i>
Manuscript ID	es-2016-04821g.R1
Manuscript Type:	Article
Date Submitted by the Author:	n/a
Complete List of Authors:	SHAMSUL HARUMAIN, ZAKUAN AZIZI; INTERNATIONAL ISLAMIC UNIVERSITY MALAYSIA, BIOTECHNOLOGY Parker, Helen; Green Chemistry Centre of Excellence, Department of Chemistry Muñoz García, Andrea; Green Chemistry Centre of Excellence, Department of Chemistry Austin, Michael; Green Chemistry Centre of Excellence, Department of Chemistry McElroy, Con Robert; Green Chemistry Centre of Excellence, Department of Chemistry Hunt, Andrew; University of York, Green Chemistry Centre of Excellence Clark, James; Green Chemistry Centre of Excellence, Department of Chemistry Meech, John; University of British Columbia, NBK Institute of Mining Engineering Anderson, Christopher; Massey University, Soil and Earth Sciences Group Ciacci, Luca; Yale University, Center for Industrial Ecology Graedel, Thomas; Yale University, School of Forestry and Environmental Studies Bruce, Neil; University of York, Department of Biology Rylott, Elizabeth; University of York, Department of Biology

SCHOLARONE™  
Manuscripts

*Title:* Towards financially viable phytoextraction and production of plant-based palladium catalysts

Authors:

Zakuan A. S. Harumain<sup>1,6</sup>, Helen L. Parker<sup>2</sup>, Andrea Muñoz García<sup>2</sup>, Michael J. Austin<sup>2</sup>, Robert C. McElroy,<sup>2</sup> Andrew J. Hunt<sup>2</sup>, James H. Clark<sup>2</sup>, John A. Meech<sup>3</sup>, Christopher W. N. Anderson<sup>4</sup>, Luca Ciacci<sup>5</sup>, T. E. Graedel<sup>5</sup>, Neil C. Bruce<sup>1\*</sup>, Elizabeth L. Rylott<sup>1\*</sup>

<sup>1</sup>Centre for Novel Agricultural Products, Department of Biology, University of York, Wentworth Way, York, YO10 5DD, UK

<sup>2</sup>Green Chemistry Centre of Excellence, Department of Chemistry, University of York, York, UK, YO10 5DD.

<sup>3</sup>NBK Institute of Mining Engineering, University of British Columbia, Vancouver V6T 1Z4, Canada

<sup>4</sup>Institute of Agriculture and Environment, Massey University, Palmerston North, New Zealand.

<sup>5</sup>Center for Industrial Ecology, Yale University, New Haven, CT 06511

<sup>6</sup>Department of Biotechnology, Kuliyah of Science, International Islamic University of Malaysia, Kuantan Campus, Malaysia

19 \*Correspondence to: Elizabeth L. Rylott and Neil C. Bruce, Centre for Novel Agricultural  
20 Products, Department of Biology, University of York, Wentworth Way, York, YO10 5DD,  
21 UK

22 Phone: +44 (0)1904 328754

23 Fax: +44 (0)1904 328801

24 E-mail: [liz.rylott@york.ac.uk](mailto:liz.rylott@york.ac.uk) and [neil.bruce@york.ac.uk](mailto:neil.bruce@york.ac.uk)

25 Word count (Abstract, Introduction, Materials and Methods, Results, Discussion and  
26 Acknowledgement) = 4,963

27 Figures: 6 x 300 words per Figure, no Tables, total = 1,800

28 Total (Abstract, Introduction, Materials and Methods, Results, Discussion and  
29 Acknowledgements) plus figures) word count = 6,763

30 **ABSTRACT**


31 Although a promising technique, phytoextraction has yet to see significant  
32 commercialization. Major limitations include metal uptake rates and subsequent processing  
33 costs. However, it has been shown that liquid-culture-grown *Arabidopsis* can take up and  
34 store palladium as nanoparticles. The processed plant biomass has catalytic activity  
35 comparable to that of commercially available catalysts, creating a product of higher value  
36 than extracted bulk metal. We demonstrate that the minimum level of palladium in  
37 *Arabidopsis* dried tissues for catalytic activity comparable to commercially available 3%  
38 palladium-on-carbon catalysts was achieved from dried plant biomass containing between 12  
39 and 18 g·kg<sup>-1</sup> Pd. To advance this technology, species suitable for in-the-field application:  
40 mustard, miscanthus and sixteen willow species and cultivars, were tested. These species  
41 were able to grow, and take up, palladium from both synthetic and mine-sourced tailings.  
42 Although levels of palladium accumulation in field-suitable species are below that required  
43 for commercially available 3% palladium-on-carbon catalysts, this study both sets the target,  
44 and is a step towards, the development of field-suitable species that concentrate catalytically-  
45 active levels of palladium. Life cycle assessment on the phytomining approaches described  
46 here indicates that the use of plants to accumulate palladium for industrial applications has  
47 the potential to decrease the overall environmental impacts associated with extracting  
48 palladium using present-day mining processes.

49

50

51

## TOC/Abstract Art

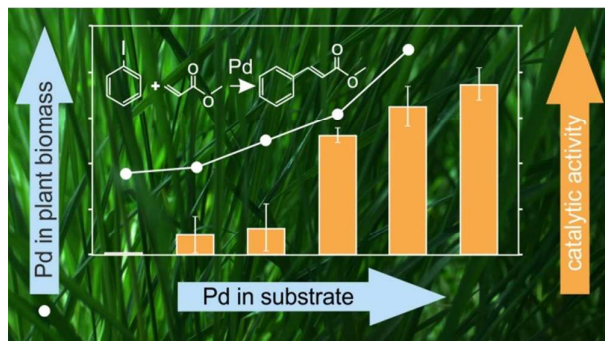

## INTRODUCTION

A number of plant species have been found to take up gold and deposit it as gold nanoparticles (NPs) in their tissues<sup>1</sup>, a phenomenon that has also been demonstrated for platinum group metals (PGMs) in *Arabidopsis* (*Arabidopsis thaliana*)<sup>2</sup>. Following a low-energy, pyrolysis treatment, the metal NP-containing plant biomass derived material can have catalytic activity comparable to that of commercially available catalysts and, critically, creates a product of higher value than the extracted bulk metal alone. These features present a potentially financially viable opportunity for the phytoextraction of these metals from PGM-rich sources and mine wastes<sup>3</sup>.

Phytoextraction was initially described in 1995 as ‘the use of metal-accumulating plants to remove toxic metals from soil’<sup>4</sup>, and expanded in 2001 as ‘the utilization of plants to transport and concentrate metals from the soil into the harvestable parts of roots and above-ground shoots’<sup>5</sup>. However, phytoextraction has now been around for several decades and, although a promising technique, it has yet to see significant commercialization<sup>6</sup>. A key factor for successful phytoextraction is that the value of the metal extracted needs to exceed the cost

70 of the recovery method. In the case of PGMs, the bulk value is relatively high. However, the  
71 costs of phytoextraction and subsequent harvesting, processing and smelting can still be  
72 inhibitory. By exploiting the natural ability of plants to accumulate PGMs as NPs,  
73 phytoextraction may be financially viable<sup>7</sup>.

74

75 The material potentially available for phytomining is the waste material (the ‘tailings’) that is  
76 separated from the valuable metals in mineral ores. Depending on the efficiencies of  
77 separation, tailings can contain variable amounts of a variety of metals, some valuable, and  
78 some toxic. Tailings, which typically consist of highly liquid slurries of silicates and other  
79 rock debris, are deposited in ponds during active ore processing and subsequently stabilized  
80 for long-term storage upon mine closure.

81 So far, the production of biomass which has catalytic activity has only been demonstrated in  
82 non-field conditions, using the non-crop species *Arabidopsis*<sup>2</sup>. There is a need to develop this  
83 technology in species suitable for field testing. While plants can grow in a diverse array of  
84 challenging environments, land for phytoextraction often contains deleterious traits, such as  
85 toxic levels of metals, sub-optimal pH, low organic matter content and low nutrient content.  
86 These properties result in suboptimal plant growth and low plant biomass. Even so, some  
87 species can be well-suited to the harsher conditions found in metal-rich land. Willows (*Salix*  
88 sp.), for example, are able to withstand concentrations of metals (copper, cadmium, nickel  
89 and zinc) considered toxic to many other plant species and can achieve high biomass in  
90 relatively poor soils<sup>8-12</sup>. Additionally, there is considerable genetic diversity within the  
91 willow genus that could be exploited to develop cultivars optimized for the environmental  
92 conditions present at a field site<sup>13</sup>. Other species with phytoextraction potential include

93 miscanthus (*Miscanthus x giganteus*)<sup>14</sup> and switchgrass (*Panicum virgatum*)<sup>15,16</sup>. These  
94 species are currently grown as bioenergy crops, and the necessary agricultural infrastructure  
95 for growing and harvesting is already in place<sup>17</sup>.

96 At the biological level, a major factor limiting the realization of phytoextraction is the low  
97 levels of PGMs taken up naturally by the plant. Significant progress towards the  
98 commercialization of nickel phytoextraction is being made with the use of hyperaccumulator  
99 species such as *Alyssum* sp.<sup>18,19</sup>; but, only a limited number of elements are known to be  
100 concentrated by hyperaccumulator species, and no suitable species have yet been found for  
101 PGMs.

102 At the physico-chemical level, poor metal uptake is linked to the chemical form of the metal.  
103 In the case of PGMs, these elements exist in field locations predominantly as chemically  
104 inert, zero-valent forms, or are bound to minerals. A highly effective recovery method for  
105 gold and PGMs is the use of cyanide for solubilization<sup>1</sup>.

106

107 However, irresponsible use of cyanide as a lixiviant in the mining industry has resulted in  
108 examples of serious, large-scale environmental pollution where toxic cyanide-containing  
109 complexes such as ferri- and ferro-cyanide, have accumulated in soils<sup>20, 21</sup>. Cyanide use is  
110 now tightly regulated in many countries, but is still the principal method used by the mining  
111 industry to recover gold, and silver, with this use representing approximately 15% of cyanide  
112 consumption globally<sup>22</sup>.



To achieve palladium NP formation in plants, and catalytic activity in the subsequently processed biomass, an as-yet-unknown threshold concentration of palladium in the tissues needs to be exceeded. In the present study, we have aimed to establish the minimum concentration of palladium needed in dry plant biomass to achieve catalytic activity comparable to that of commercially available 3% palladium-on-carbon catalysts. As an extension to previous studies in *Arabidopsis*<sup>2,23</sup>, we have extrapolated the experiments to plant species suitable for in-field application, including miscanthus and willow. The levels of palladium uptake by these species have been compared with target levels determined using our model *Arabidopsis* system.

Life cycle assessment (LCA) is a methodology that accounts for the environmental impacts associated with products and processes along the lifecycle of a material. In the mining industry, LCA has been utilized extensively<sup>24-28</sup>, and its application to understand the environmental implications of phytoaccumulation; and to highlight the related potential for opportunities of metal recovery from mine tailings, have been previously proposed<sup>3</sup>. Recently, LCA has been applied for nickel phytomining<sup>19</sup>. Here, we have used LCA to test if our phytomining approaches have the potential to decrease the overall environmental impacts associated with the current mining processes.

## **MATERIALS AND METHODS**

### *Synthetic and mine-collected tailings for plant growth*

Synthetic, palladium-rich tailings were created for the initial stages of this research, based on protocols for synthetic gold tailings, which have been extensively used for gold uptake experiments<sup>29</sup>. The elemental composition of the synthetic tailings, prior to dosing with

palladium, is shown in Table S1. Use of synthetic tailings enabled the concentration of palladium to be controlled in a background material that did not contain phytotoxic levels of metals, such as nickel, that are often present in mine samples and wastes. The use of synthetic tailings also meant that variables underpinning the process of palladium-uptake by plants (*i.e.*, lixiviant and metal concentration in soil) could be explored at a relatively low cost prior to using genuine mine wastes, which are more difficult to acquire in significant quantities. Mine-collected tailings were obtained from North American Palladium. Table S2 shows the elemental profiles, and Table S3 the gold and PGM profiles, of this material. Mustard plants were also grown on equivalent (v/v) amounts of vermiculite in palladium-free control experiments.

#### *Growing Arabidopsis, mustard, miscanthus, and willow*

*Arabidopsis* plants, ecotype Col0, were grown in liquid culture as described elsewhere<sup>2</sup>. For mustard, plastic P2 trays containing 1 kg of synthetic, or mine-collected, tailings were sown with 4.2g of mustard (*Brassica alba* L., cultivar Rivona) seed. The trays were placed in a glasshouse and watered as required. To measure the effect of a palladium solubilizing treatment on the uptake of palladium by the mustard plants, a potassium cyanide treatment was applied as follows: After seven days in the glasshouse, 100 ml of potassium cyanide (1 mg ml<sup>-1</sup> cyanide) was applied to selected P2 trays, the plants were then harvested 24 h later and dried overnight at 60 °C.

*Miscanthus* (*Miscanthus x giganteus*) rhizomes and willow rods (*Salix* sp.; Yorkshire Willow Ltd, UK) were rooted in sand for four weeks. Rooted, in-leaf plants were transferred to 1.5l pots containing either 1 kg (for *miscanthus*), or 1.5 kg (for willow), of synthetic tailings or mine-collected tailings. A general purpose fertilizer was added weekly according to the

manufacturer's instructions and the plants grown for four weeks. To measure the effect of a palladium solubilizing treatment on the uptake of palladium by the plants, half of the plants were dosed with 100 ml (for miscanthus), or 150 ml (for willow) of potassium cyanide (1 mg ml<sup>-1</sup> cyanide). One week later, all the plant roots and shoots were harvested and dried overnight at 60 °C.

#### *ICP-MS analysis*

Plant tissues were ground to a fine powder using ball bearings in an end-over-end mixer. To 0.5 g of tissue, 5 ml of aqua regia (3:1 hydrochloric acid (37%): nitric acid (70%)) was added. The samples were heated for 2 h at 70 °C then diluted to 50 ml with ultrapure water and filtered using a 0.45 µm filter. Metal content was determined using inductively coupled plasma mass spectrometry (ICP-MS) on an Agilent 7700x and calibrated against multi-element and precious calibration standards (Agilent Ltd).

#### *Testing catalytic activity*

To produce the catalyst, dried plant material was pyrolysed using the Barnstead Thermolyte 6000 Furnace under N<sub>2</sub> (1 K m<sup>-1</sup>) at 573 K (300 °C) as described<sup>2</sup>. For the reaction of iodobenzene with methyl acrylate, 5.00 mmol iodobenzene, 6.25 mmol methyl acrylate, and 6.25 mmol triethylamine in 1.75 mL of N-methyl-2-pyrrolidone, were added to a 25 ml round bottom flask. Once the flask had been heated to 393 K, 10 mg of palladium catalyst were added. For control experiments, no catalyst was added. Control reactions with 10 mg of pyrolysed, palladium-free plant material were also run. The reaction was allowed to proceed

for 2 hours at 393 K and the levels of substrate and product measured using a Gas Chromatography-Flame Ionization Detector (GC-FID) using diethyl succinate as a standard.

### *Life cycle assessment comparisons*

Details of the two LCA models developed are shown in Supplementary Material.

Two scenarios were developed to conduct a comparative LCA. The first scenario compared the environmental impacts associated with the production of Arabidopsis catalyst material relative to the commercial route for activated carbon-palladium catalysts. A second scenario modeled the phytoaccumulation of palladium from mine tailings and the processing of the biomass for the production of valuable products such as bio-gas, bio-oil, and bio-char containing palladium.

The models were carried out in accordance with the ISO 14040 guidelines, and developed using the SimaPro 8.0 software. To enable a comparative LCA study with real systems, the investigated processes were scaled up to a hypothetical facility based on extrapolation from laboratory scale studies and literature data. Modules of inventory data for raw material and chemical production, heat generation and grid electricity production mix, and transportation were derived from the ecoinvent 3.0 database. Direct and indirect mass and energy flows were accounted for according to the system boundaries set for the two systems investigated. A selection of standardized indicators was used for the assessment of environmental impacts to midpoint and endpoint categories, and is shown in Table S4. A detailed description of the two LCA scenarios is reported in the Supplementary Material.

## **RESULTS**

In previous studies, catalytic activity was recorded for pyrolysed *Arabidopsis* biomass containing 5 g·kg<sup>-1</sup> palladium. The biomass was derived from plants grown in liquid culture and dosed with 10 mM potassium tetrachloropalladate<sup>2</sup>. This experimental system was replicated in the current work as a model in which metal doses could be accurately controlled in a small-scale system. Using this model, the relationship between the *in planta* palladium concentration and catalytic activity of liquid-culture grown *Arabidopsis* plants dosed with a range of palladium concentrations (from 0.5 mM to 1 mM of potassium tetrachloropalladate) was investigated.

#### *Testing catalytic activity in Arabidopsis*

The concentration of palladium in the dried *Arabidopsis* material was found to increase from 0.18 to 18 g kg<sup>-1</sup> palladium with increasing concentrations (0.5 mM to 1 mM respectively) of potassium tetrachloropalladate (Figure 1). For pyrolysis of the plant biomass, the temperature chosen was 300 °C. This was based on an earlier study which demonstrated that at this temperature the mean nanoparticle diameter and frequency distributions were unaltered, with the remaining biomass comprising predominantly carbon and oxygen<sup>2</sup>. Previous studies using thermal gravimetric-infrared (TGIR) analysis of the post-pyrolysis material showed a 45% mass loss between 100 - 300°C, attributed to the loss of water and carbon dioxide<sup>2</sup>. Catalytic activity was tested using the Heck reaction between iodobenzene and methyl acrylate to form *trans*-methyl cinnamate. Figure 1 shows that there was no catalytic activity from plants dosed with 0.5 mM potassium tetrachloropalladate. However, product was observed from plants dosed with concentrations of 0.6 mM and above, with product yields increasing with higher concentrations of potassium tetrachloropalladate. Palladium on carbon 3% (Pd/C), a commercially available palladium catalyst, was used to compare with the performance of the

pyrolysed biomass. The yields obtained from plants dosed with 1 mM palladium were comparable to those obtained by Pd/C (64.9 % and 74.9 % respectively).

The results presented in Figure 1 indicate a palladium concentration of between 12 and 18 g·kg<sup>-1</sup> in dried *Arabidopsis* biomass is the target level above which catalytic activity would be comparable to that of commercially available catalysts. In order to assess if this target could be reached in species more suited to in-field application, mustard, willow, and miscanthus were tested in studies using synthetic tailings. To increase uptake by solubilizing the palladium, potassium cyanide was used. While there is currently no data available for palladium, a review comparing gold uptake by a number of plant species treated with a range of cyanide-based compounds indicated that potassium and ammonium thiocyanate yield the highest levels of gold uptake<sup>1</sup>. For *Brassica juncea*, the highest levels of uptake were observed using potassium cyanide<sup>1</sup>. As mustard and *Arabidopsis* are also in the Brassicaceae, and willow has been shown to effectively remediate potassium cyanide<sup>40</sup>, this compound was chosen as the lixiviant.

#### *Growth and palladium uptake by mustard*

The biomass of mustard plants grown on synthetic tailings containing up to 50 mg·kg<sup>-1</sup> palladium was not significantly different to the biomass of plants grown on the no-Pd control material, but the biomass of plants grown on synthetic tailings containing 100 mg·kg<sup>-1</sup> palladium was a third lower than in the absence of palladium ( $p < 0.05$ ; Figure 2A). The addition of cyanide significantly ( $p < 0.001$ ) increased the uptake of palladium by 26, 20, 30, and 23-fold in plants grown in synthetic tailings containing 5, 10, 50, and 100 mg·kg<sup>-1</sup> palladium, respectively (Figure 2B and Table S5). The pie charts shown in Figure S1 and data in Table S5, illustrate both the effect of increasing levels of palladium on the uptake of

other metals present in the synthetic tailings and the effect of the exogenous application of cyanide. The mustard plants grown on the synthetic tailings in the absence of cyanide or palladium contained predominantly zinc and copper. With increasing palladium concentration, and in the absence of cyanide, levels of palladium in the plant increased predominantly at the expense of copper, whereas in the presence of cyanide, levels of copper, which is also solubilized by cyanide, were less affected.

However, mine sourced materials often contain other elements at concentrations inhibitory to plant growth. To test growth and palladium uptake in this inhibitory background, PGM-rich mine-collected tailings from North American Palladium were used. The mine-collected tailings contained approximately 20 mg·kg<sup>-1</sup> palladium; a concentration that the synthetic tailings study (Figure 2) indicated was below the phytotoxicity level. In agreement with this result, no toxicity symptoms were seen in the mustard plants grown on the mine material (Figure S2). The biomass of seven-day-old seedlings grown on the mine-collected tailings was higher than those grown on vermiculite alone. We speculate that this could be due to additional nutrients present in the mine-collected tailings that were lacking in the vermiculite. As seen with the palladium-dosed synthetic tailings experiment (Figure 2), the addition of cyanide significantly ( $p < 0.001$ ) increased the uptake of palladium by 89, 333, and 8.4-fold in plants grown in mine-collected tailings containing 5, 10, and 20 mg·kg<sup>-1</sup> palladium, respectively (Figure S2).

#### *Growth and palladium uptake by miscanthus and willow*

Given the dramatic increase in the ability of mustard to take up palladium conferred by the application of cyanide, the potential of the more field-suitable species miscanthus and willow was next investigated. For miscanthus, the application of cyanide had no effect on the

biomass of root or shoot tissues (results not shown), whereas aerial tissues of the cyanide treated plants had almost 500-fold more palladium than those from untreated plants grown on synthetic tailings (undosed plants contained  $0.0013 \pm 0.0001 \text{ g} \cdot \text{kg}^{-1}$ ; cyanide-treated plants contained  $0.505 \pm 0.039 \text{ g} \cdot \text{kg}^{-1}$  palladium).

For the willow experiments, a fast-growing, bioenergy hybrid of *Salix viminalis*, 'Super Willow' was chosen. As seen with miscanthus, *S. viminalis* 'Super Willow' leaf biomass was unaltered by the cyanide treatment. At the lower concentrations of palladium-dosed synthetic tailings (5 and 10  $\text{mg} \cdot \text{kg}^{-1}$ ), leaf biomass was not significantly affected, however, at the higher concentrations of palladium (50 and 100  $\text{mg} \cdot \text{kg}^{-1}$ ) total leaf biomass significantly decreased ( $p < 0.05$ ; Figure 3A). The application of cyanide dramatically, and significantly ( $p < 0.001$ ), increased the uptake of palladium by 126, 127, 19 and 23-fold in plants grown at 5, 10, 50 and 100  $\text{mg} \cdot \text{kg}^{-1}$  palladium respectively (Figure 3B). In agreement with the data for mustard, (Figure 2B and Table S5), the cyanide treatment was observed to be less effective at promoting palladium uptake at palladium concentrations above 20  $\text{mg} \cdot \text{kg}^{-1}$ .

*Salix viminalis* 'Super Willow' was grown on mine-collected tailings and growth and palladium uptake measured. Figure S3A demonstrates that the application of cyanide did not affect leaf or stem biomass, yet it dramatically, and significantly ( $p < 0.001$ ), increased the levels of palladium in the leaf and stem by 65 and 49-fold, respectively (Figure S3B and C). The effect of the cyanide treatment moderately increased uptake of other metals present in the mine-collected tailings (cobalt, nickel, copper, cadmium and lead), with the greatest effect observed for copper: the treatment of *S. viminalis* 'Super Willow' with cyanide increased copper levels by 9.5 and 12.5-fold, respectively, in the leaves and stems (Figure S3 and Table S6).



There is a wealth of genetic variability for metal uptake within the willow genus<sup>13</sup>. To investigate the variation in palladium uptake, 16 different species and cultivars of willow were selected. Figure 4A shows the variation in leaf and stem dry weights. Across the 16 species and cultivars of willow, there was an 11.5 and 4.7-fold variation in leaf and stem biomass, respectively. *Salix alba*, *S. candida*, and *S. purpurea* (cv. Green Dicks) had consistently high leaf and stem biomass. In this experiment, the concentration of palladium in the leaves of *S. viminalis* was higher (Figure 4B, 0.313 g·kg<sup>-1</sup>) than in the previous experiment (Figure 3B, 0.094 g·kg<sup>-1</sup>), the discrepancy may have resulted from different environmental conditions in the glasshouse during the experiment for Figure 4: warmer, sunnier conditions would have increased transpiration rates and could lead to enhanced palladium uptake. Overall, across the 16 species and cultivars, there were 6.7 and 4.5-fold variations, respectively, in leaf and stem palladium content, with 6-fold more palladium present in the leaves than in the stems. Of the two species with consistently high palladium levels, *S. nigricans* and *S. purpurea* (cv. Green Dicks), the latter species also produced high leaf and stem biomass.

The palladium concentration in the non-Arabidopsis species tested in this work was below the 12 g·kg<sup>-1</sup> threshold established for catalytic activity. However, preliminary testing of the mustard, miscanthus, and willow (cv. Green Dicks) containing respectively 0.5, 1.5, and 0.8 g·kg<sup>-1</sup> palladium post-pyrolysis resulted in catalytic yields of 5, 7, and 1.2 % respectively.

### *Life Cycle Assessments*

To conduct the LCA, midpoint impact categories for the processes were defined (Table S4). This translated the total impact of a process into individual environmental themes. Figure 5A compares the commercial production route for Pd/C with that using liquid-culture grown

Arabidopsis for each selected midpoint impact category. The commercial production route for the Pd/C catalyst has higher impacts for climate change, metal depletion, fossil depletion, cumulative energy demand, and water scarcity single midpoints. The catalyst material obtained through the Arabidopsis process was found to have greater impacts for those categories associated with outputs to water and terrestrial compartments. Figure 5B shows aggregated scores for the two processes after weighting each (midpoint) impact category to damage impact categories (endpoint) for human health, ecosystems, and resources. Overall, the commercial Pd/C catalyst has a total environmental impact about three times higher than that produced through the Arabidopsis process.

The difference in environmental impacts between the two processes clearly favors the Arabidopsis process. However, phytoaccumulation efficiency is the most relevant parameter in influencing the LCA results. The Arabidopsis process was modeled by assuming that plants are dosed with the same amount of palladium required for the commercial production process. If the Arabidopsis process should require a greater input of palladium, or if part of the non-phytoaccumulated palladium is unrecovered, environmental impacts would increase significantly. Given that the environmental impacts favor the Arabidopsis process over the common production route for the Pd/C catalyst, the use of willow to make a Pd/C-equivalent catalyst is likely to be even more favorable. However, this would rely on the willow accumulating palladium to a level to be commercially viable as a catalyst.

Pyrolysis to 300 °C under N<sub>2</sub> is used for stabilization of the Arabidopsis Pd/C-equivalent catalyst. Whilst being very simple, this approach is not optimal to maximize value and process large volumes of biomass. Microwave assisted pyrolysis (MAP) is an alternative

approach that is being developed as a green technology for use as part of a holistic biorefinery<sup>30, 31</sup>.

Using this technique the biomass is stabilized via microwave heating at lower temperatures and shorter times than needed for conventional pyrolysis. In addition to the solid bio-char catalyst, bio-oil and bio-gas are collected during MAP and this not only prevents the release of greenhouse gasses but also brings extra value to the process.

In the second scenario the impacts of bio-gas, bio-oil, and palladium-containing bio-char production from willow biomass (Pd-willow) were compared to the impacts that would derive from the production of the same amount of gas, oil, and palladium from common extraction routes. Figure 6A shows that production of these three products from Pd-willow decreases the overall impact for all midpoint categories, with the exception of particulate matter formation and agricultural land occupation. In most cases, the environmental impacts were reduced by up to 100 %. The environmental benefits associated with the avoided production of natural gas, oil, and palladium concentrate lead to a distinct improvement in total environmental performance, with the avoided damage to resources being the endpoint category for which the best score was derived (Figure 6B). The results of the sensitivity analysis support the confidence of the model.

## DISCUSSION

Arabidopsis plants were grown hydroponically and dosed with solutions of potassium tetrachloropalladate, factors chosen to favour palladium uptake, and establish whether palladium concentrations in the biomass would be sufficient to obtain catalytically active material comparable to commercially available 3% carbon on palladium. The studies presented indicate that to obtain catalytically active material comparable to commercially

361 available 3% carbon on palladium, the dried plant biomass, prior to pyrolysis, needs to  
362 contain a minimum concentration of between 12 and 18 g·kg<sup>-1</sup> palladium. At this  
363 concentration, we have shown previously that the Arabidopsis tissues contain palladium NPs  
364 which confer catalytic activity<sup>2</sup>. We infer that tissues from other species containing above 12  
365 to 18 g·kg<sup>-1</sup> palladium would also contain palladium nanoparticles, but this should be tested  
366 in future studies. In combination with the application of cyanide, the highest concentrations  
367 of palladium achieved from plants grown on synthetic tailings in this study were 0.53 g·kg<sup>-1</sup>  
368 for mustard (with a KCN treatment 24 h pre-harvest), and 0.51 and 0.82 g·kg<sup>-1</sup> palladium  
369 (with a KCN treatment 1 week pre-harvest) for miscanthus and willow (cv. Green Dicks),  
370 respectively. At these levels, catalytic activity, albeit low (5, 7, and 1.2 % yields,  
371 respectively), from subsequently pyrolysed material was observed. However, the levels of  
372 palladium accumulated in biomass from KCN-treated plants grown on mine-collected tailings  
373 were significantly lower: 0.0085 g·kg<sup>-1</sup> for mustard and 0.0142 g·kg<sup>-1</sup> for willow leaf.  
374 Although not tested, it was considered unlikely that pyrolysed material from the plants grown  
375 on mine-collected tailings would yield detectable catalytic activity. The technology  
376 developed in these studies is aimed at phytoextracting PGMs from wastes such as mine  
377 tailings which have levels of palladium typically between 0.7- 1 mg·kg<sup>-1</sup>; significantly lower  
378 than for the mine-collected tailings used here. Thus, achieving plant biomass with between 12  
379 and 18 g·kg<sup>-1</sup> palladium is still a significant biotechnological challenge. However, our results  
380 demonstrate that in just one week, and following a single, non-optimized, cyanide treatment,  
381 the best performing willow cultivar had the biological capacity to take up approximately 10  
382 % of the palladium required to reach the target concentration. Given the extensive genetic  
383 resources available in this genus, screening or selective breeding programs would likely  
384 identify willow lines with further enhanced palladium uptake ability. Furthermore, this study

shows that willows and miscanthus are able to withstand the toxicities present in mine-sourced material; relative to ores and concentrates, tailings and other wastes will likely have correspondingly lower levels of phytotoxic metals. In field scenarios, species such as willow and miscanthus would be grown on significantly larger scale. Harvesting coppiced willow on a three to five year rotation in combination with repeated lixiviant treatments would be predicted to lead to further increases in palladium uptake.

On a global scale, implementing phytoaccumulation in field scenarios would maximize the extraction of valuable forms of palladium and other PGMs from natural deposits. Overall recovery rates of palladium from the processing of virgin ores are estimated at 80-90%<sup>32-35</sup>, resulting in considerable losses during comminution and concentration steps: the amount of cumulative palladium lost in mine tailings is estimated to represent about 5% of global reserve and reserve base values<sup>3</sup>. Thus, should palladium phytoaccumulation efficiency increase at levels to be financially viable, the exploitation of mine tailings would have a strong potential for supplementing primary palladium supply. From a perspective of resource conservation and environmental protection, the resulting potential benefits associated with recoverable palladium tailings would be greater still if phytoaccumulation led to lower environmental impacts of mining activity.

Results from the preliminary LCA reported in this paper are limited by the estimates used to enable the scaling of lab-based results up to a hypothetical full-scale facility. However, our analysis suggests that the use of plants to accumulate palladium, either for catalysts, or bio-gas, bio-oil, and palladium-containing bio-char production, as outlined here for willow, has the potential to decrease the overall environmental impacts (*i.e.*, computed as environmental impacts associated with the process, less the environmental burdens resulting from the

avoided production of equivalent products such as natural gas or oil) associated with palladium extraction by current mining processes.

Such a net-environmental performance improvement is of particular importance when considering the use of cyanide for palladium phytoaccumulation. In support of the use of cyanide in controlled phytoextraction conditions, it has been shown that plants can degrade cyanide, taking up both free cyanide and iron cyanides and metabolizing them to the amino acid asparagine<sup>36-40</sup>. These findings present the perhaps paradoxical situation whereby the application of cyanide might be the only mechanisms to enable the phytoextraction of PGMs to be financially viable.

However, in addition to environmental concerns, the use of cyanide treatments causes co-solubilization of significant levels of other metals such as gold, copper, and nickel. The presence of these metals in the pyrolysed biomass could affect subsequent catalytic activity<sup>41</sup>. Furthermore, the application of cyanide directly to the land results in the indiscriminate solubilization of the target metal throughout the material. This approach is inefficient for phytoextraction, because much of the solubilized metal is beyond the reach of the roots and is thus lost as leachate. Targeting solubilization to the rhizosphere, a microecological zone closely surrounding the roots, would enable more efficient metal uptake. This is an approach that could perhaps be combined with biomining, using precious metal accumulating bacteria such as *Cupriavidus metallidurans*<sup>42</sup> in the rhizosphere.

Whatever approaches to increase PGM accumulation are tested, there are large areas of land containing increasingly valuable PGM metals reserves that are currently un-vegetated and contain toxic levels of metals and wastes as by-products from the mining industry. The

combination of the phytoextraction process, in tandem with phytoremediation to re-vegetate, stabilize and restore ecological diversity, could be a win-win situation for the environment and for catalysis technologies. The approach described here increases the viability of green technologies and aids in promoting the use of biomass to replace fossil fuels.

#### ACKNOWLEDGEMENTS

This work was funded by the G8 Research Councils Initiative on Multilateral Research Funding grant code: EP/K022482/1 and by the US National Science Foundation under Grant 1256286. ZASH thanks the Ministry of Higher Education of Malaysia, the International Islamic University of Malaysia; and the Radhika Sreedhar fund. AMG thanks the Wild Fund Scholarship from the Department of Chemistry, University of York. We thank North American Palladium for providing the mine tailings samples. We thank also Philip Nuss for helpful discussion on LCA modeling. This paper is dedicated to the memory of John A. Meech.

**FIGURE LEGENDS**

**Figure 1.** Palladium uptake by *Arabidopsis* plants dosed with a range of concentrations of potassium tetrachloropalladate. Left axis (line), level of palladium in the dried plant biomass; right axis (column), catalytic activity of the pyrolysed plant biomass in the Heck reaction of iodobenzene and methyl acrylate to yield *trans*-methyl cinnamate (for Pd in dried plant material,  $n = 3$  biological replicates  $\pm$  s.e.m.; for % yield,  $n = 3$  technical replicates  $\pm$  r.s.d).

**Figure 2.** Growth and palladium uptake by mustard (*Brassica alba* L.) germinated and grown on synthetic tailings dosed with a range of palladium concentrations. After seven days, seedlings were dosed with  $100 \text{ mg}\cdot\text{kg}^{-1}$  cyanide (in the form of KCN), then harvested 24 h later. A) Biomass of aerial tissues, and B) concentration of palladium in the aerial tissues ( $n = 6$  biological replicates  $\pm$  s.e.m.).

**Figure 3.** Growth and palladium uptake by *Salix viminalis*, 'Super Willow' grown on synthetic tailings dosed with a range of palladium concentrations. After four weeks, plants were dosed with  $100 \text{ mg}\cdot\text{kg}^{-1}$  cyanide (in the form of KCN), then harvested after seven days. A) Leaf dry weight, and B) concentration of palladium in the leaf tissues ( $n = 5$  biological replicates  $\pm$  s.e.m.).

**Figure 4.** Growth and palladium uptake by a range of willow species (*Salix* sp.). Rooted cuttings were grown for four weeks on synthetic tailings containing  $50 \text{ mg}\cdot\text{kg}^{-1}$  palladium, dosed with  $100 \text{ mg}\cdot\text{kg}^{-1}$  cyanide (in the form of KCN), then harvested after one week. A) Leaf and stem dry weight, and B) concentration of palladium, in the leaf and stem tissues ( $n = 5$  biological replicates  $\pm$  s.e.m. except *Salix. alba*, *S. chermesina* and *S. alba vitellina* where  $n = 2$ ).



466 **Figure 5.** (A) Characterization results for midpoint categories. (B) Characterization results  
467 for endpoint categories; the y-axis reports absolute single points for total damage on  
468 resources, ecosystems, and human health according to the Europe ReCiPe H/A method.

469 **Figure 6.** (A) Characterization results for midpoint categories. (B) Characterization results  
470 for endpoint categories; the y-axis reports absolute single points ( $1 \text{ mPoint} = 10^{-3} \text{ Point}$ ) for  
471 total damage on resources, ecosystems, and human health according to the Europe ReCiPe  
472 H/A method. Negative values refer to avoided impacts.

## REFERENCES

1. Wilson-Corral, V.; Anderson, C. W. N.; Rodriguez-Lopez, M., Gold phytomining. A review of the relevance of this technology to mineral extraction in the 21st century. *J. Environ. Manage.* **2012**, *111*, 249-257; DOI 10.1016/j.jenvman.2012.07.037.
2. Parker, H. L.; Rylott, E. L.; Hunt, A. J.; Dodson, J. R.; Taylor, A. F.; Bruce, N. C.; Clark, J. H., Supported palladium nanoparticles synthesized by living plants as a catalyst for suzuki-miyaura reactions. *PLoS One* **2014**, *9*, e87192; DOI 10.1371/journal.pone.0087192.
3. Hunt A. J.; Anderson C. W. N.; Bruce, N.; García A. M.; Graedel T. E.; Hodson, M.; Meech J. A.; Nassar N. T.; Parker H. L.; Rylott E. L.; Sotiriou, K.; Zhang, Q.; Clark J. H., Phytoextraction as a tool for green chemistry. In *Green Process. Synth.* 2014; Vol. 3, pp 3-22; DOI 10.1515/gps-2013-0103.
4. Salt, D. E.; Blaylock, M.; Kumar, N. P.; Dushenkov, V.; Ensley, B. D.; Chet, I.; Raskin, I., Phytoremediation: a novel strategy for the removal of toxic metals from the environment using plants. *Biotechnology (N Y)* **1995**, *13*, 468-74; DOI 10.1038/nbt0595-468.
5. Garbisu, C.; Alkorta, I., Phytoextraction: a cost-effective plant-based technology for the removal of metals from the environment. *Bioresour. Technol.* **2001**, *77*, 229-36; DOI 10.1016/S0960-8524(00)00108-5.
6. Robinson, B. H.; Anderson, C. W. N.; Dickinson, N. M., Phytoextraction: Where's the action? *J. Geochem. Explor.* **2015**, *151*, 34-40; DOI 10.1016/j.gexplo.2015.01.001.
7. Shuttleworth, P. S.; De bruyn, M.; Parker, H. L.; Hunt, A. J.; Budarin, V. L.; Matharu, A. S.; Clark, J. H., Applications of nanoparticles in biomass conversion to chemicals and fuels. *Green Chem.* **2014**, *16*, 573-584; DOI 10.1039/C3GC41555D.
8. Kuzovkina, Y. A.; Knee, M.; Quigley, M. F., Cadmium and copper uptake and translocation in five willow (*Salix* L.) species. *Int. J. Phytorem.* **2004**, *6*, 269-87; DOI 10.1080/16226510490496726.
9. Zhivotovsky, O. P.; Kuzovkina, Y. A.; Schulthess, C. P.; Morris, T.; Pettinelli, D., Lead uptake and translocation by willows in pot and field experiments. *Int. J. Phytorem.* **2011**, *13*, 731-49; DOI 10.1080/15226514.2010.525555.
10. Evangelou, M. W.; Robinson, B. H.; Gunthardt-Goerg, M. S.; Schulin, R., Metal uptake and allocation in trees grown on contaminated land: implications for biomass production. *Int. J. Phytorem.* **2013**, *15*, 77-90; DOI 10.1080/15226514.2012.670317.
11. Pulford, I. D.; Watson, C., Phytoremediation of heavy metal-contaminated land by trees-a review. *Environ. Int.* **2003**, *29*, 529-40; DOI 10.1016/S0160-4120(02)00152-6.

- 506 12. Punshon, T.; Dickinson, N., Heavy Metal Resistance and Accumulation  
507 Characteristics in Willows. *Int. J. Phytorem.* **1999**, *1*, 361-385; DOI  
508 10.1080/15226519908500025.
- 509 13. Dos Santos Utmazian, M. N.; Wieshammer, G.; Vega, R.; Wenzel, W. W.,  
510 Hydroponic screening for metal resistance and accumulation of cadmium and zinc in twenty  
511 clones of willows and poplars. *Environ. Pollut.* **2007**, *148*, 155-65; DOI  
512 10.1016/j.envpol.2006.10.045.
- 513 14. Nsanganwimana, F.; Pourrut, B.; Mench, M.; Douay, F., Suitability of Miscanthus  
514 species for managing inorganic and organic contaminated land and restoring ecosystem  
515 services. A review. *J. Environ. Manage.* **2014**, *143*, 123-34; DOI  
516 10.1016/j.jenvman.2014.04.027.
- 517 15. Chen, B. C.; Lai, H. Y.; Juang, K. W., Model evaluation of plant metal content and  
518 biomass yield for the phytoextraction of heavy metals by switchgrass. *Ecotoxicol. Environ.*  
519 *Saf.* **2012**, *80*, 393-400; DOI 10.1016/j.ecoenv.2012.04.011.
- 520 16. Balsamo, R. A.; Kelly, W. J.; Satrio, J. A.; Ruiz-Felix, M. N.; Fetterman, M.; Wynn,  
521 R.; Hagel, K., Utilization of grasses for potential biofuel production and phytoremediation of  
522 heavy metal contaminated soils. *Int. J. Phytorem.* **2015**, *17*, 448-55; DOI  
523 10.1080/15226514.2014.922918.
- 524 17. Margaritopoulou, T.; Roka, L.; Alexopoulou, E.; Christou, M.; Rigas, S.;  
525 Haralampidis, K.; Milioni, D., Biotechnology Towards Energy Crops. *Mol. Biotechnol.* **2016**  
526 *58*, 149-58; DOI 10.1007/s12033-016-9913-6.
- 527 18. van der Ent, A.; Baker, A. J. M.; Reeves, R. D.; Chaney, R. L.; Anderson, C. W. N.;  
528 Meech, J. A.; Erskine, P. D.; Simonnot, M.-O.; Vaughan, J.; Morel, J. L.; Echevarria, G.;  
529 Fogliani, B.; Rongliang, Q.; Mulligan, D. R., Agromining: Farming for Metals in the Future?  
530 *Environ. Sci. Technol.* **2015**, *49*, 4773-4780; DOI 10.1021/es506031u.
- 531 19. Rodrigues, J.; Houzelot, V.; Ferrari, F.; Echevarria, G.; Laubie, B.; Morel, J.-L.,  
532 Simonnot, M.-O. & Pons, M.-N. Life cycle assessment of agromining chain highlights role of  
533 erosion control and bioenergy. *J. Cleaner Prod.* **2016**, *139*, 770-778; DOI  
534 10.1016/j.jclepro.2016.08.110.
- 535 20. Kostarelos, K.; Gavriel, I.; Stylianou, M.; Zissimos, A. M.; Morisseau, E.; Dermatas,  
536 D., Legacy soil contamination at abandoned mine sites: making a case for guidance on soil  
537 protection. *Bull. Environ. Contam. Toxicol.* **2015**, *94*, 269-74; DOI.
- 538 21. Donato, D. B.; Nichols, O.; Possingham, H.; Moore, M.; Ricci, P. F.; Noller, B. N., A  
539 critical review of the effects of gold cyanide-bearing tailings solutions on wildlife. *Environ.*  
540 *Int.* **2007**, *33*, 974-84; DOI .
- 541 22. Minerals Council of Australia. Fact Sheet - Cyanide and its Use by the Minerals  
542 Industry. **2005**.

- 543 <http://www.infomine.com/library/publications/docs/MineralsCouncilAustralia2005.pdf> (last  
544 accessed 6 Jan 2017).
- 545 23. Taylor, A. F.; Rylott, E. L.; Anderson, C. W.; Bruce, N. C., Investigating the toxicity,  
546 uptake, nanoparticle formation and genetic response of plants to gold. *PLoS One* **2014**, *9*,  
547 e93793; DOI 10.1371/journal.pone.0093793.
- 548 24. Stewart, M., The application of life cycle assessment to mining, minerals and metals.  
549 Report of the MMSD workshop on life cycle assessment. *New York*, **2001**.
- 550 25. Nuss, P.; Eckelman, M. J., Life cycle assessment of metals: a scientific synthesis.  
551 *PLoS One* **2014**, *9*, e101298; DOI 10.1371/journal.pone.0101298.
- 552 26. Norgate, T.; Jahanshahi, S., Reducing the greenhouse gas footprint of primary metal  
553 production: Where should the focus be? *Miner. Eng.* **2011**, *24*, 1563-1570; DOI  
554 10.1016/j.mineng.2011.08.007.
- 555 27. Giurco, D. P., Stewart, M., Petrie, J.G. , The role of LCA in performance assessment  
556 in minerals processing - a copper case study. In: Environmental issues and management of  
557 waste in energy and mineral production; Singhal, R., Mehrotra, A., Eds.; Rotterdam. **2000**; pp  
558 267-273.
- 559 Travis, E. R.; Hannink, N. K.; van der Gast, C. J.; Thompson, I. P.; Rosser, S. J.; Bruce, N. C.  
560 Impact of transgenic tobacco on trinitrotoluene (TNT) contaminated soil community.  
561 *Environ. Sci. Technol.* 2007, *41*, 5854-5861; DOI 10.1021/es070507a.
- 562 28. Stewart, M. H.; Y. Petrie, J. Critical issues for life cycle impact assessment in minerals  
563 processing and metals refining In: Green processing **2004**: 2nd international conference on  
564 the sustainable processing of minerals. Fremantle, Australia.
- 565 29. Anderson, C. W. N.; Bhatti, S. M.; Gardea-Torresdey, J.; Parsons, J., In Vivo Effect  
566 of Copper and Silver on Synthesis of Gold Nanoparticles inside Living Plants. *ACS*  
567 *Sustainable Chem. Eng.* **2013**, *1*, 640-648; DOI 10.1021/sc400011s .
- 568 30. Budarin, V. L.; Shuttleworth, P. S.; Dodson, J. R.; Hunt, A. J.; Lanigan, B.; Marriott,  
569 R.; Milkowski, K. J.; Wilson, A. J.; Breeden, S. W.; Fan, J.; Sin, E. H. K.; Clark, J. H., Use  
570 of green chemical technologies in an integrated biorefinery. *Energy Environ. Sci.* **2011**, *4*,  
571 471-479; DOI 10.1039/C0EE00184H .
- 572 31. Clark, J. H.; Budarin, V.; Deswarte, F. E. I.; Hardy, J. J. E.; Kerton, F. M.; Hunt, A.  
573 J.; Luque, R.; Macquarrie, D. J.; Milkowski, K.; Rodriguez, A.; Samuel, O.; Tavener, S. J.;  
574 White, R. J.; Wilson, A. J., Green chemistry and the biorefinery: A partnership for a  
575 sustainable future. *Green Chem.* **2006**, *8*, 853-860; DOI 10.1039/b604483m.
- 576 32. Nassar, N. T., Anthropospheric losses of platinum group elements In; Element  
577 Recovery and Sustainability; Hunt, A. Ed.; The Royal Society of Chemistry: Cambridge, UK  
578 **2013** pp185-206.

- 579 33. Vermaak, C. F., *Platinum-Group Metals: A Global Perspective* Mintek, Randburg,  
580 South Africa, **1995**.
- 581 34. S. M. Kozyrev, M. Z. K., L. N. Emelina, O. I. Oleshkevich, O. A. Yakovleva, D. V.  
582 Lyalinov and V. I. Maximov, , *The Geology, Geochemistry, Mineralogy and Mineral*  
583 *Beneficiation of Platinum-Group Elements*. Canadian Institute of Mining, Metallurgy and  
584 Petroleum: Montreal, Canada, **2002**.
- 585 35. R. K. W. Merkle and A. D. McKenzie, *The Geology, Geochemistry, Mineralogy and*  
586 *Mineral Beneficiation of Platinum-Group Elements*. Canadian Institute of Mining,  
587 Metallurgy and Petroleum: Montreal, Canada, **2002**.
- 588 36. Castric, P. A.; Farnden, K. J.; Conn, E. E., Cyanide metabolism in higher plants. V.  
589 The formation of asparagine from -cyanoalanine. *Arch. Biochem. Biophys.* **1972**, *152*, 62-9;  
590 DOI 10.1016/0003-9861(72)90193-2.
- 591 37. Yu, X. Z.; Gu, J. D., Uptake, accumulation and metabolic response of ferricyanide in  
592 weeping willows J. Environ. Monit.: *JEM* **2009**, *11*, 145-52; DOI 10.1039/B809304K.
- 593 38. Larsen, M.; Trapp, S., Uptake of iron cyanide complexes into willow trees. *Environ.*  
594 *Sci. Technol.* **2006**, *40*, 1956-61; DOI 10.1021/es051224q.
- 595 39. Larsen, M.; Trapp, S.; Pirandello, A., Removal of cyanide by woody plants.  
596 *Chemosphere* **2004**, *54*, 325-33; DOI 10.1016/S0045-6535(03)00662-3.
- 597 40. Ebbs, S.; Bushey, J.; Poston, S.; Kosma, D.; Samiotakis, M.; Dzombak, D., Transport  
598 and metabolism of free cyanide and iron cyanide complexes by willow. *Plant, Cell Environ.*  
599 **2003**, *26*, 1467-1478; DOI 10.1046/j.0016-8025.2003.01069.x.
- 600 41. Xu, Q.; Zhang, L.; Shi, W.; Cui, Y., Catalytic performances of cross-linking humic  
601 acids supported Pd/Ni bimetallic catalyst for heck reaction. In *Pol. J. Chem. Technol.*, 2009;  
602 Vol. 11, p 22; DOI 10.2478/v10026-009-0031-0.
- 603 42. Gwynne, P., Microbiology: There's gold in them there bugs. *Nature*, **2013**. *495*, S12-  
604 S13; DOI 10.1038/495S12a.
- 605 43. Wang, N.-Y.; Shih, C.-H.; Chiueh, P.-T.; Huang, Y.-F., Environmental Effects of  
606 Sewage Sludge Carbonization and Other Treatment Alternatives. *Energies* **2013**, *6*, 871; DOI  
607 10.3390/en6020871.
- 608 44. Nassar, N. T., Chapter 7 Anthropospheric Losses of Platinum Group Elements. In  
609 *Element Recovery and Sustainability*, The Royal Society of Chemistry: 2013; pp 185-206.
- 610 45. Witters, N.; Van Slycken, S.; Ruttens, A.; Adriaensen, K.; Meers, E.; Meiresonne, L.;  
611 Tack, F. G.; Thewys, T.; Laes, E.; Vangronsveld, J., Short-Rotation Coppice of Willow for  
612 Phytoremediation of a Metal-Contaminated Agricultural Area: A Sustainability Assessment.  
613 *Bioenerg. Res.* **2009**, *2*, 144-152; DOI 10.1007/s12155-009-9042-1.

- 614 46. Doka, G., Life cycle inventory data of mining waste: Emissions from sulfidic tailings  
615 disposal. In *Doka Life Cycle Assessments*, Zurich (CH): **2008**.
- 616 47. Singh, A.; Pant, D.; Korres, N. E.; Nizami, A.-S.; Prasad, S.; Murphy, J. D., Key  
617 issues in life cycle assessment of ethanol production from lignocellulosic biomass:  
618 Challenges and perspectives. *Bioresour. Technol.* **2010**, *101*, 5003-5012; DOI  
619 10.1016/j.biortech.2009.11.062.

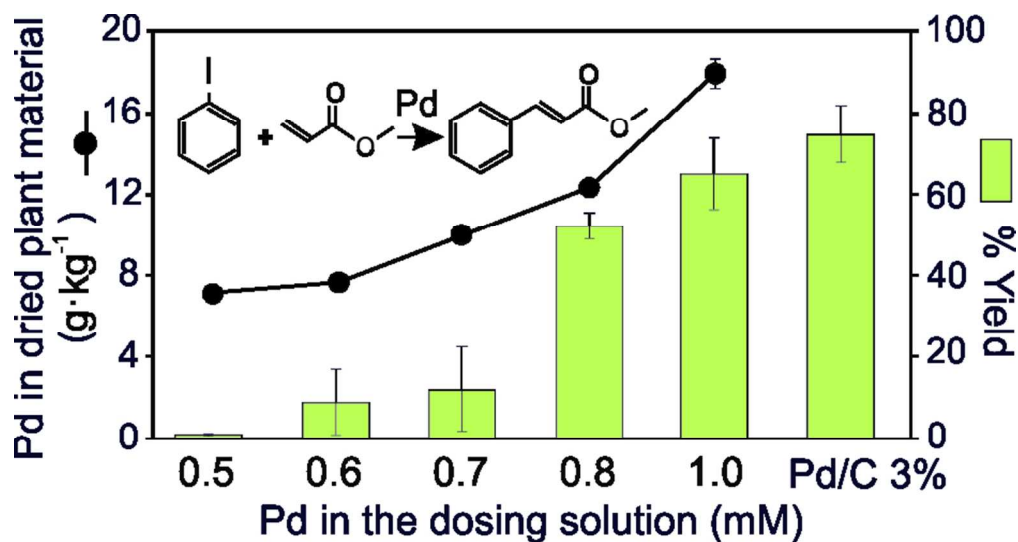


Figure 1. Palladium uptake by *Arabidopsis* plants dosed with a range of concentrations of potassium tetrachloropalladate. Left axis (line), level of palladium in the dried plant biomass; right axis (column), catalytic activity of the pyrolysed plant biomass in the Heck reaction of iodobenzene and methyl acrylate to yield trans-methyl cinnamate (for Pd in dried plant material,  $n = 3$  biological replicates  $\pm$  s.e.m.; for % yield,  $n = 3$  technical replicates  $\pm$  r.s.d.).

Figure 1

79x41mm (300 x 300 DPI)

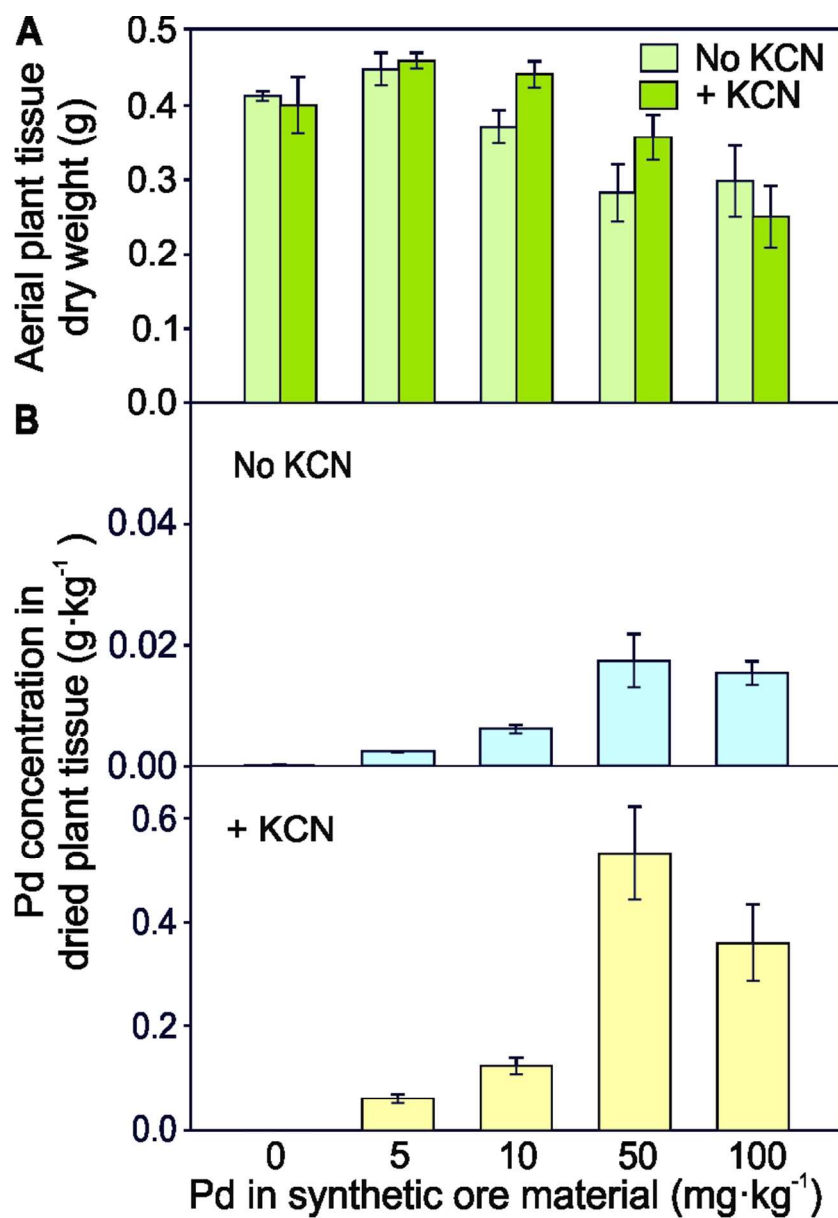


Figure 2. Growth and palladium uptake by mustard (*Brassica alba* L.) germinated and grown on synthetic tailings dosed with a range of palladium concentrations. After seven days, seedlings were dosed with 100 mg·kg<sup>-1</sup> cyanide (in the form of KCN), then harvested 24 h later. A) Biomass of aerial tissues, and B) concentration of palladium in the aerial tissues (n = 6 biological replicates ± s.e.m.).

Figure 2  
74x108mm (300 x 300 DPI)



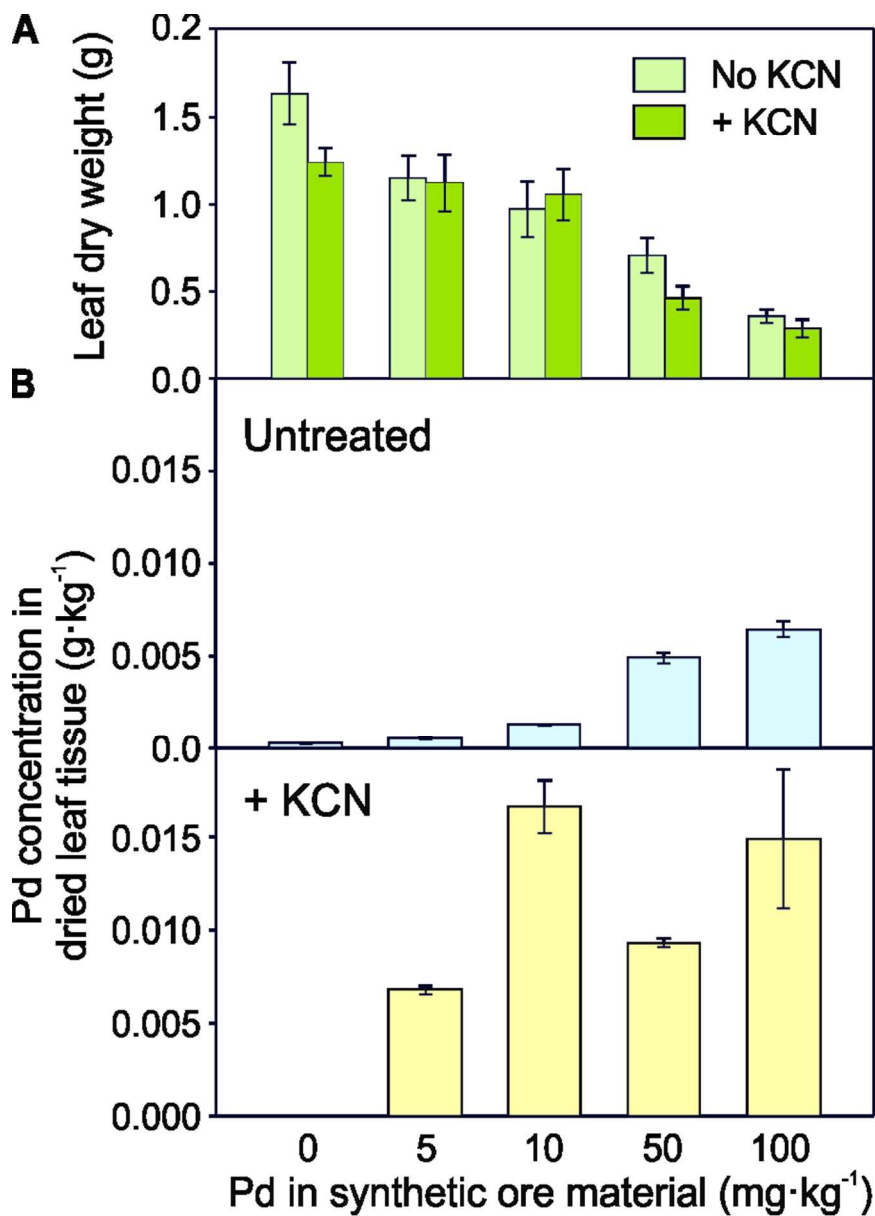


Figure 3. Growth and palladium uptake by *Salix viminalis*, 'Super Willow' grown on synthetic tailings dosed with a range of palladium concentrations. After four weeks, plants were dosed with 100 mg kg<sup>-1</sup> cyanide (in the form of KCN), then harvested after seven days. A) Leaf dry weight, and B) concentration of palladium in the leaf tissues (n = 5 biological replicates ± s.e.m.).

Figure 3  
76x106mm (300 x 300 DPI)

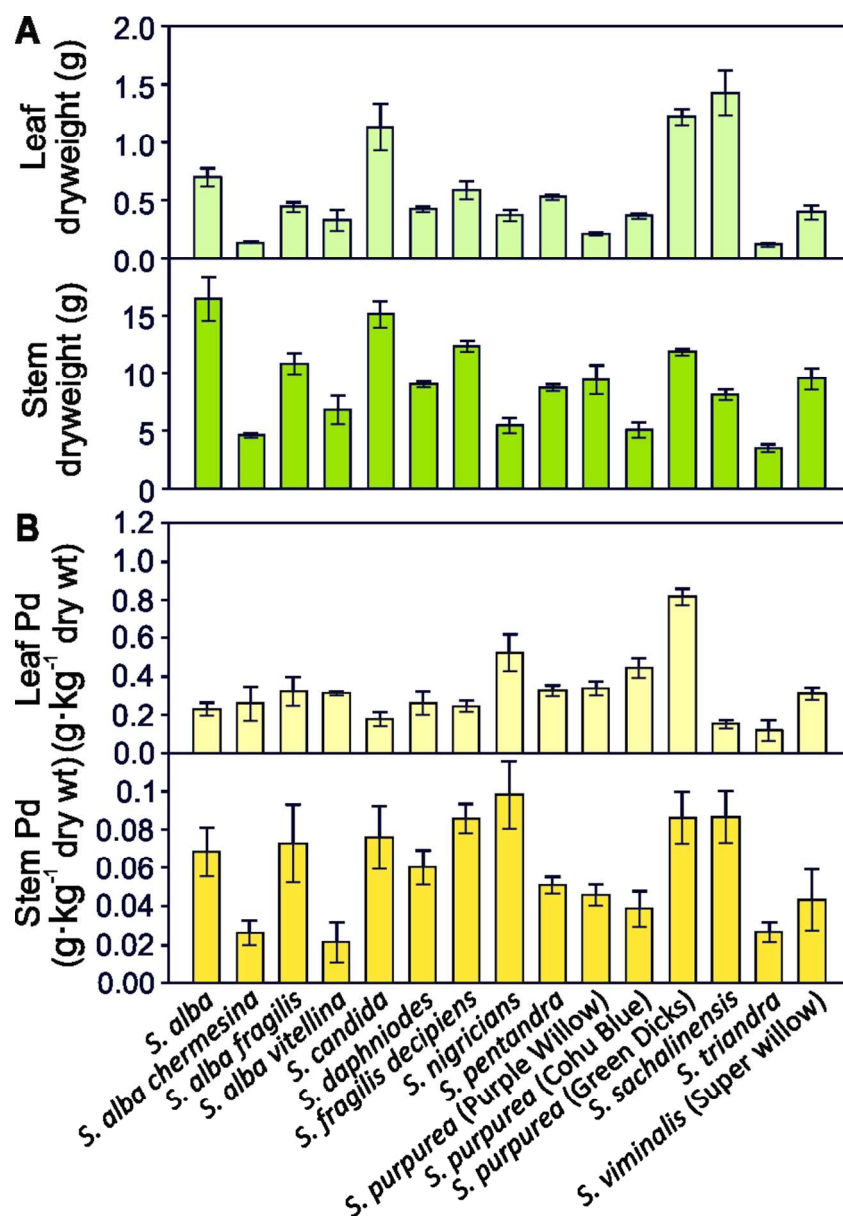


Figure 4. Growth and palladium uptake by a range of willow species (*Salix* sp.). Rooted cuttings were grown for four weeks on synthetic tailings containing 50 mg kg<sup>-1</sup> palladium, dosed with 100 mg kg<sup>-1</sup> cyanide (in the form of KCN), then harvested after one week. A) Leaf and stem dry weight, and B) concentration of palladium, in the leaf and stem tissues ( $n = 5$  biological replicates  $\pm$  s.e.m. except *Salix. alba*, *S. chermesina* and *S. alba vitellina* where  $n = 2$ ).

Figure 4

81x113mm (300 x 300 DPI)

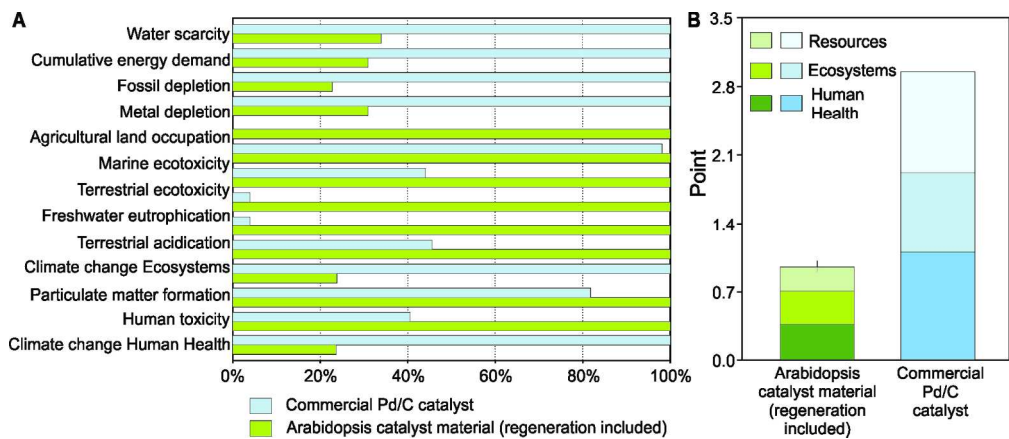


Figure 5. (A) Characterization results for midpoint categories. (B) Characterization results for endpoint categories; the y-axis reports absolute single points for total damage on resources, ecosystems, and human health according to the Europe ReCiPe H/A method.

Figure 5

173x73mm (300 x 300 DPI)

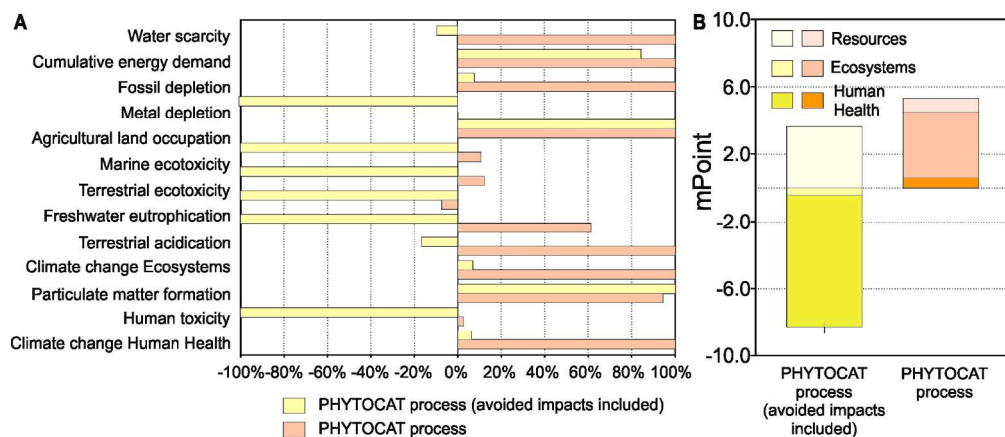


Figure 6. (A) Characterization results for midpoint categories. (B) Characterization results for endpoint categories; the y-axis reports absolute single points (1 mPoint =  $10^{-3}$  Point) for total damage on resources, ecosystems, and human health according to the Europe ReCiPe H/A method. Negative values refer to avoided impacts.

Figure 6  
174x74mm (300 x 300 DPI)