



This is a repository copy of *Scalable continuous production of high quality HKUST-1 via conventional and microwave heating*.

White Rose Research Online URL for this paper:  
<http://eprints.whiterose.ac.uk/118257/>

Version: Accepted Version

---

**Article:**

McKinstry, C., Cussen, E.J., Fletcher, A.J. et al. (2 more authors) (2017) Scalable continuous production of high quality HKUST-1 via conventional and microwave heating. *Chemical Engineering Journal*, 326. pp. 570-577. ISSN 1385-8947

<https://doi.org/10.1016/j.cej.2017.05.169>

---

**Reuse**

Items deposited in White Rose Research Online are protected by copyright, with all rights reserved unless indicated otherwise. They may be downloaded and/or printed for private study, or other acts as permitted by national copyright laws. The publisher or other rights holders may allow further reproduction and re-use of the full text version. This is indicated by the licence information on the White Rose Research Online record for the item.

**Takedown**

If you consider content in White Rose Research Online to be in breach of UK law, please notify us by emailing [eprints@whiterose.ac.uk](mailto:eprints@whiterose.ac.uk) including the URL of the record and the reason for the withdrawal request.



[eprints@whiterose.ac.uk](mailto:eprints@whiterose.ac.uk)  
<https://eprints.whiterose.ac.uk/>

# **Scalable continuous production of high quality HKUST-1 via conventional and microwave heating**

**Colin McKinstry<sup>a,b</sup>, Edmund J. Cussen<sup>b</sup>, Ashleigh J. Fletcher<sup>a</sup>, Siddharth V.**

**Patwardhan<sup>c</sup>, Jan Sefcik<sup>a</sup>**

<sup>a</sup> Department of Chemical and Process Engineering, University of Strathclyde, 75 Montrose  
Street, Glasgow, G1 1XJ, U.K.

<sup>b</sup> WESTCHEM, Department of Pure and Applied Chemistry, University of Strathclyde, 295  
Cathedral Street, Glasgow, G1 1XL, U.K.

<sup>c</sup> Department of Chemical and Biological Engineering, University of Sheffield, Mappin  
Street, Sheffield S1 3JD, U.K.

## ABSTRACT

Metal Organic Frameworks (MOFs) are materials with large surface areas and internal volumes, which result in a number of useful properties for applications such as catalysis, separations and gas storage. However, MOFs are challenging to produce at a large scale creating a barrier to becoming truly viable alternatives to current technologies. As a first step towards industrial scale manufacture, we demonstrate here the first scalable, continuous synthesis of high-quality HKUST-1 using ethanol as the solvent, resulting in a greener and potentially much more economical process (as solvent does not decompose and thus can be recycled). We also show that microwave heating can be used to produce HKUST-1 continuously, in timescales several orders of magnitude faster than by conventional heating. We demonstrated a novel approach to microwave assisted synthesis of HKUST-1, based on a recycle loop with microwave irradiation, which is scalable under both batch and continuous conditions and allows an independent control of microwave irradiation regime and the overall reaction time. The use of microwave heating for continuous production of HKUST-1 enabled STY of  $400,000 \text{ kg m}^{-3} \text{ day}^{-1}$ , which is higher than any production rates reported to date, even when using the preferred high yield solvent, DMF, and is 17 times more than the highest production rates reported to date for HKUST-1 in 'ethanol-only' systems.

## INTRODUCTION

Metal Organic Frameworks (MOFs) are one of the emergent materials of the last decade, due to the unique properties granted by their nature, such as large internal volumes and reduced dead spaces, resulting in MOFs having larger surface areas ( $>1000 \text{ m}^2/\text{g}$ ) than is thought to be possible for other porous materials, such as activated carbons or zeolites [1, 2]. This large internal volume and surface area allows MOFs to show significantly superior properties for uses in gas storage/separation [3] and catalysis [4].

MOFs are currently not used on an industrial scale due to the inability to economically produce desired high quality MOFs in sufficiently large quantities. MOFs are also potentially expensive compared to many materials with similar properties, such as zeolites due to the expensive solvents and ligands often required for MOF synthesis. A potential route to reduce the cost is to develop a scalable continuous synthesis process to replace current batch methods as continuous processing offers a number of benefits in terms of production rates, product quality and reliability. However, there are challenges pertaining to the design complexity of a continuous system, which need to be overcome [5]. The continuous synthesis of MOFs has been recently reviewed by Dunne, Lester and Walton [6], and it is clear that microfluidic reactors are commonly used at laboratory scale. Suspension of nanolitre scale droplets of reaction solution within oil allows for highly efficient heat and mass transfer due to the high surface area to volume ratio [7]; HKUST-1, MOF-5, MIL-53, IRMOF-3 and UiO-66 have all been successfully synthesized using this method [7].

Here we focus on HKUST-1 (also known as MOF-199) [8], which has the potential to be used in gas applications such as short chain hydrocarbon separation [9], hydrogen storage [10, 11] or purification [12], and  $\text{H}_2\text{S}$  sequestration [13]. HKUST-1 possesses accessible uncoordinated metal sites with high bonding energy towards target species [14], allowing

adsorbates to interact more strongly with the MOF. Combined with the fact that the copper dimers form dipoles, this can further increase the myriad potential applications of HKUST-1, and coupled with its stability [15-18], this makes HKUST-1 an ideal MOF to consider for scaled-up manufacture with increased efficiency. HKUST-1 has been synthesised continuously, where it was reported to form in short times by flowing reactants counter-currently at 300 °C and 250 bar, allowing the MOF to form in a 1 s residence time [19] with high surface area. Increasing the temperature and pressure of synthesis has been shown, previously, to provide thermodynamic conditions favourable for MOF formation [20], resulting in the formation of MOF at shorter times than for operation at ambient conditions. However, operating at elevated temperatures and pressures is likely to add significant cost to the overall process. It was subsequently shown that considerably less severe operating conditions can be used to form HKUST-1 in times of 5 min, however this still requires operation at 100 bar [21]. Rubio-Martinez et al. [22] showed the ability to operate relatively close to atmospheric pressure and produce high surface area HKUST-1. However, all syntheses described above use tubular micro-channels of low volumes (typically <20 mL).

Microwave assisted syntheses of MOFs – both in batch and continuous modes – have been reported, which are summarised in a recent review [6]. Of particular relevance, Ranocchiari and co-workers demonstrated continuous flow synthesis of MOFs using microwave heating [23]. They used a single pass microwave process using only DMF as a solvent to produce HKUST-1 with high STY values. Pressures of up to 6 bar were used to increase the solvent boiling point, although they reported that solvent boiling was nevertheless observed. Overheating of DMF and boiling even at pressures of up to 6 bars as reported by Ranocchiari seems to be especially problematic as decomposition pathways of DMF are not fully understood and it was previously suggested [24] that one of by-products is hydrogen gas.

Hence a robust and sustainable method is required for safe implementation at industrial production scales.

We have recently shown, with an example of MOF-5, that continuous stirred tank reactors (CSTR) provide several benefits when scaling-up MOF crystallisation [25, 26]. In this context we aimed to investigate scale-up at significantly higher outputs and across different solvent choices using widely available CSTRs. In order to make the process industrially applicable, we aimed to identify sustainable solvent systems. For many MOFs, including HKUST-1, microwave heating has shown considerable benefits at small scale batch level, mainly reducing the reaction time for MOF synthesis, often moving from hours to minutes timescales [27], while maintaining the required properties of the MOF product, such as surface area. However, these systems adopt a single pass approach which implies that all microwave assisted heating has to happen within the residence time available and so the design space is limited due to overheating and pressure control limitations. Therefore we aimed to investigate using microwaves to provide increased efficiency for continuous solvothermal synthesis of HKUST-1. Further, in order to achieve a robust control of microwave heating, we proposed a novel approach based on a recycle loop with microwave radiation, which allows an independent control of microwave irradiation and the overall reaction time.

## **2. EXPERIMENTAL**

### **2.1 Batch Synthesis of HKUST-1**

#### **2.1.1 Synthesis Using Conventional Heating**

We reviewed the available literature to establish the most consistent and reliable synthetic procedures for the production of HKUST-1. Due to scalability issues and continuous

processing difficulties with electrochemical and mechanochemical methods, we focused on solvothermal synthesis. We used a modified version of the synthesis route from Chowdhury et al. [28] as the basis for our experiments, modifying the procedure to produce material under conditions similar to Millange et al. [29] for comparison.

All batch tests were performed using 6 mL of total solvent volume and a metal:ligand (M:L) concentration ratio of 1.88:1, resulting in the metal being in excess (1.5:1 is the stoichiometric ratio). In all experiments, samples were stirred magnetically and heated using an oil bath and hot plate to reach the desired temperature, monitored by a thermocouple inserted into the reaction solution.

The solution was composed of equal parts in volume of N,N-dimethyl formamide (DMF) (Sigma Aldrich, 99.8%, anhydrous), deionised water and ethanol (Sigmas Aldrich, 99%). 0.231 g copper nitrate hemipentahydrate (Sigma Aldrich, 98%) and 0.111 g trimesic acid (Sigma Aldrich, 95%) were added to the solution (solids content of about 3% by mass). The sample vials were then capped and placed into an oil bath, which was preheated under constant stirring to the reaction temperature of 60 °C. Multiple samples were removed after various, preselected, time periods and analysed to determine how yield, purity, and porosity vary as a function of synthesis time. The experiment was then repeated using ethanol as the only solvent, keeping all other reaction parameters constant. The ethanol experiment was then repeated at a reaction temperature of 79 °C. This experiment was performed in a reflux condenser, and aliquots of identical volume were taken for analysis at preselected time intervals. To investigate the effect of process intensification on the ethanol only system, the experiment was repeated with reactant concentrations increased by up to a factor of 5, giving approximately 6%, 9% and 15% solids, based on theoretical yield.

### **2.1.2 Microwave Assisted Batch Synthesis of HKUST-1**


Using a domestic microwave oven, Logik L20MS10 (800 W), we investigated the main parameters affecting the production of HKUST-1 using microwave heating rather than conventional convective heating. It is important to note that, for safety reasons, we made no modifications to the casing of the microwave.

The solutions used were composed of 0.462 g copper nitrate hemipentahydrate and 0.222 g trimesic acid in 10 mL of ethanol (maintaining a M:L ratio of 1.88:1). As samples could not be agitated during the heating period, samples were stirred for 30 min by magnetic stirrer bar at room temperature before the stirrer bar was removed and the reaction vessel immediately placed in the centre of the microwave for reaction. A control sample was stirred at room temperature for 3 h without heating. As domestic microwaves do not produce a completely uniform field, hotspots within the chamber may vary [30]; we, therefore, placed the vials at the same location within the microwave to attempt to mitigate any variability due to this factor. In situ monitoring of temperature was not available, so final reaction temperature was determined using a thermocouple immediately upon reaction completion.

The samples were heated at 10% of the maximum power level of the microwave (~80 W) for 180 s. To investigate the effect of increasing the reaction time, 300 s and 600 s reaction times were also investigated. In order to determine the effect of heating rate on system output, the initial experiment was repeated using 20% of the maximum power of the microwave. This experiment was again repeated using percentage solids of 9 and 15% (based on theoretical yield), in order to investigate the effect of higher power inputs on the formation of HKUST-1 under microwave heating. All experiments were carried out in triplicate.

## 2.2 Continuous Synthesis of HKUST-1

### 2.2.1 Continuous Synthesis with Conventional Heating

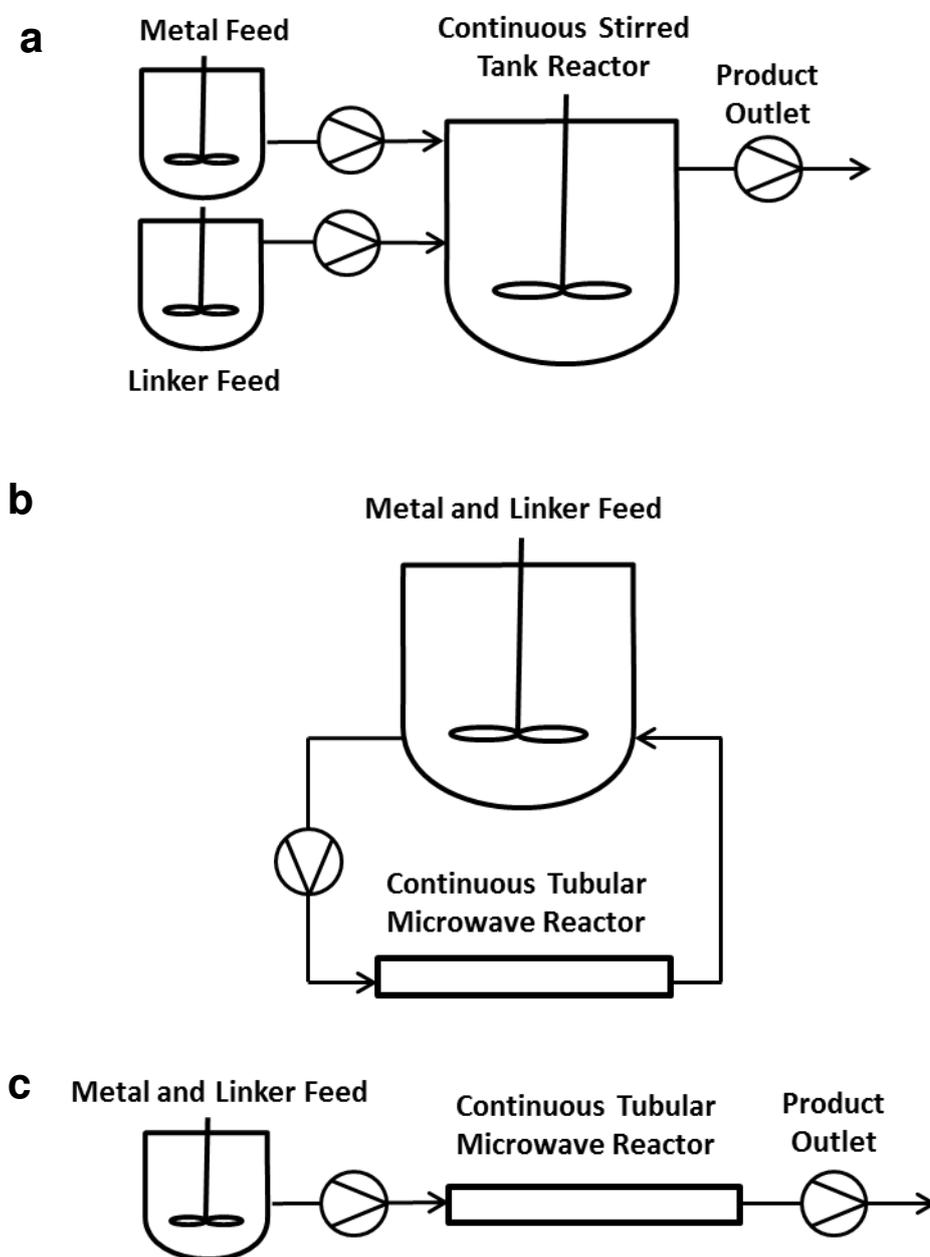

**Figure 1:** Layouts of the continuous HKUST-1 synthesis systems used in this study. a: A CSTR used with conventional heating. b: A multi-pass continuous microwave assisted synthesis. c: A single-pass continuous microwave assisted synthesis.

For the continuous flow system, the basic layout of the apparatus was as shown in Figure 1a.

The reactor vessel itself was equipped with a reflux condenser situated within an oil bath. A

thermocouple was used to monitor the temperature of the solution within the reactor. The reactor was initially loaded with 100 mL ethanol solvent and heated to the desired reaction temperature. At the time when the feed pumps were turned on, 4.62 g copper nitrate hemipentahydrate and 2.22 g trimesic acid were added to the reactor vessel as solid powders. The time when the pumps were initiated was recorded as the zero time for the reaction, thereby allowing observation of any start-up phases before steady state was achieved. The copper salt feed consisted of 13.86 g copper nitrate hemipentahydrate dissolved in 150 mL ethanol. The trimesic acid feed consisted of 6.66 g trimesic acid dissolved in 150 mL ethanol. Initially, the flow rates of the Watson Marlow 101-U calibrated pumps were set to deliver  $33 \text{ mL h}^{-1}$  of each of the feeds while the collection pump was set to remove  $66 \text{ mL h}^{-1}$ , giving an overall average residence time within the reactor of 1.5 h. Samples were collected over separate 15 min time intervals before filtration and washing with ethanol. The solid outputs were subsequently analysed as described in Section 2.3. This experiment was repeated with the volumes of feed increased by a factor of two, with all concentrations and flowrates kept constant, and was run for 9 h total, giving 6 full residence times for this reaction, in order to determine if the steady state yield had been reached.

In order to further probe the potential scalability of this system, we ran the reaction at 500 mL scale using a Radleys Reactor-Ready system, operating at a temperature of  $65 \text{ }^{\circ}\text{C}$ . The reaction temperature was maintained by passing heated fluid through the jacket of the vessel. The concentrations of all reactants were kept at the same values as described above for the smaller scale continuous syntheses. As with the smaller scale experiments, at the same time as the pumps were switched on, the reactor vessel starting conditions required the addition of 23.1 g copper nitrate hemipentahydrate and 11.1 g trimesic acid to the 500 mL of ethanol at  $65 \text{ }^{\circ}\text{C}$ . The copper salt feed consisted of 92.4 g copper nitrate hemipentahydrate dissolved in 1 L ethanol. The trimesic acid feed consisted of 44.4 g trimesic acid dissolved in 1 L ethanol.

Reactor feed and extraction rates were maintained via calibrated pumps operating to give an average residence time of 1.5 h. The experimental set up of the large scale system is shown in Supporting Information (Figure S1).

### 2.2.2 Continuous Microwave Assisted Synthesis of HKUST-1

For the microwave assisted HKUST-1 reaction system, a domestic microwave (Logik L20MS10 (800 W)) was used, where small bore PTFE tubing ( $d_i = 1\text{ mm}$ ) was fed through the side vents, in order to avoid any alterations to the cavity casing, out of safety considerations. Due to potential issues with hotspots forming in bulk solution under batch conditions, a tubular flow-through system was used for continuous operation, with the solution cycled through the microwave cavity multiple times, before removal of aliquots for analysis (see Figure 1b).

The feed vessel consisted of 13.86 g copper nitrate hemipentahydrate and 6.66 g trimesic acid dissolved in 300 mL of ethanol. This solution was kept at ambient temperature and stirred for 30 min to ensure complete dissolution of all reactants before the reaction was initiated by turning on the microwave. The resulting solution was pumped through the tubing within the microwave cavity at a rate of  $300\text{ mL h}^{-1}$ , giving a residence time of 5 min. The solution was then fed back into the original feed vessel which was stirred constantly. Samples were removed periodically, at preselected time intervals.

In order to investigate a single pass yield and find the highest space-time yield of materials, we used a single pass reactor system as shown in Figure 1c. The feed vessel consisted of 13.86 g copper nitrate hemipentahydrate and 6.66 g trimesic acid dissolved in 300 mL of ethanol. This solution was kept at ambient temperature and stirred for 30 min to ensure complete dissolution of all reactants. The resulting solution was pumped via peristaltic pump, set to deliver a flowrate of  $300\text{ mL h}^{-1}$  through a PTFE tube ( $d_i = 6\text{ mm}$ ) within the reactor

system, with 25 mL total volume, giving a residence time of 5 min. The microwave was operated on the lowest power setting (~80 W), with the output temperature maintained at approximately  $45 \pm 5$  °C. The output temperature was monitored by a thermocouple within the solution leaving the microwave cavity. This setup was repeated using a smaller reaction tube ( $d_i = 1$  mm), with 2 mL total volume and a flow rate of  $550 \text{ mL h}^{-1}$  in order to probe the minimum time required to produce HKUST-1 using continuous microwave assisted processing.

## **2.3 Characterisation**

The collected samples were dried by vacuum filtration before washing with a solution of equal volumes of ethanol and deionised water. Dry masses were determined by heating samples to 170 °C under vacuum. Samples were then characterised by Powder X-Ray Diffraction (PXRD), Fourier-Transform Infra-Red (FT-IR) spectroscopy and nitrogen sorption studies. PXRD results were collected using Cu K  $\alpha$  ( $\lambda = 1.54 \text{ \AA}$ ) radiation on aluminium plates. Nitrogen adsorption-desorption measurements were performed using a Micromeritics ASAP 2420 at  $-196$  °C; prior to analysis samples were degassed by heating at 170 °C for 12 h, under vacuum. FT-IR was carried out using an ABB MB-3000 with Attenuated Total Reflectance (ATR), and a resolution of 4 wavenumbers for 64 scans, before baseline correction and smoothing using GRAMS AI.


## **3. RESULTS AND DISCUSSION**

### **3.1 Selection of process conditions for scale-up**

Initially, we investigated various solvent systems and solid loadings for batch systems to understand their effects on HKUST-1 synthesis. The synthesis, and the solids obtained, were analysed by determining dry yield, space time yields (STY,  $\text{kg product/m}^3 \text{ reactor}$

volume/day), Langmuir specific surface area (SSA,  $\text{m}^2/\text{g}$ ) and crystallinity. The specific surface area was used as one of the key measures of product quality while STYs provided information on production rates. As it is known that increasing production rates often compromise product quality, in order to provide clear comparisons between experiments, we used surface area production rates (SAPRs), i.e. the amount of surface area of MOF produced per unit volume of the reactor per time ( $\text{m}^2/\text{m}^3/\text{day}$ ).

Figure 2a shows that, at  $60^\circ\text{C}$ , over the 5 h observation window, the DMF/ethanol/water system produced the highest overall yield, and also shows HKUST-1 forms faster in the mixed solvent system than in the ethanol only solutions (Table 1). Although using ethanol as the only solvent at  $60^\circ\text{C}$  appears to be very slow and produces poor yields, at a higher temperature ( $79^\circ\text{C}$ ), we see that the HKUST-1 yield reached a little over 40% by 5 h.

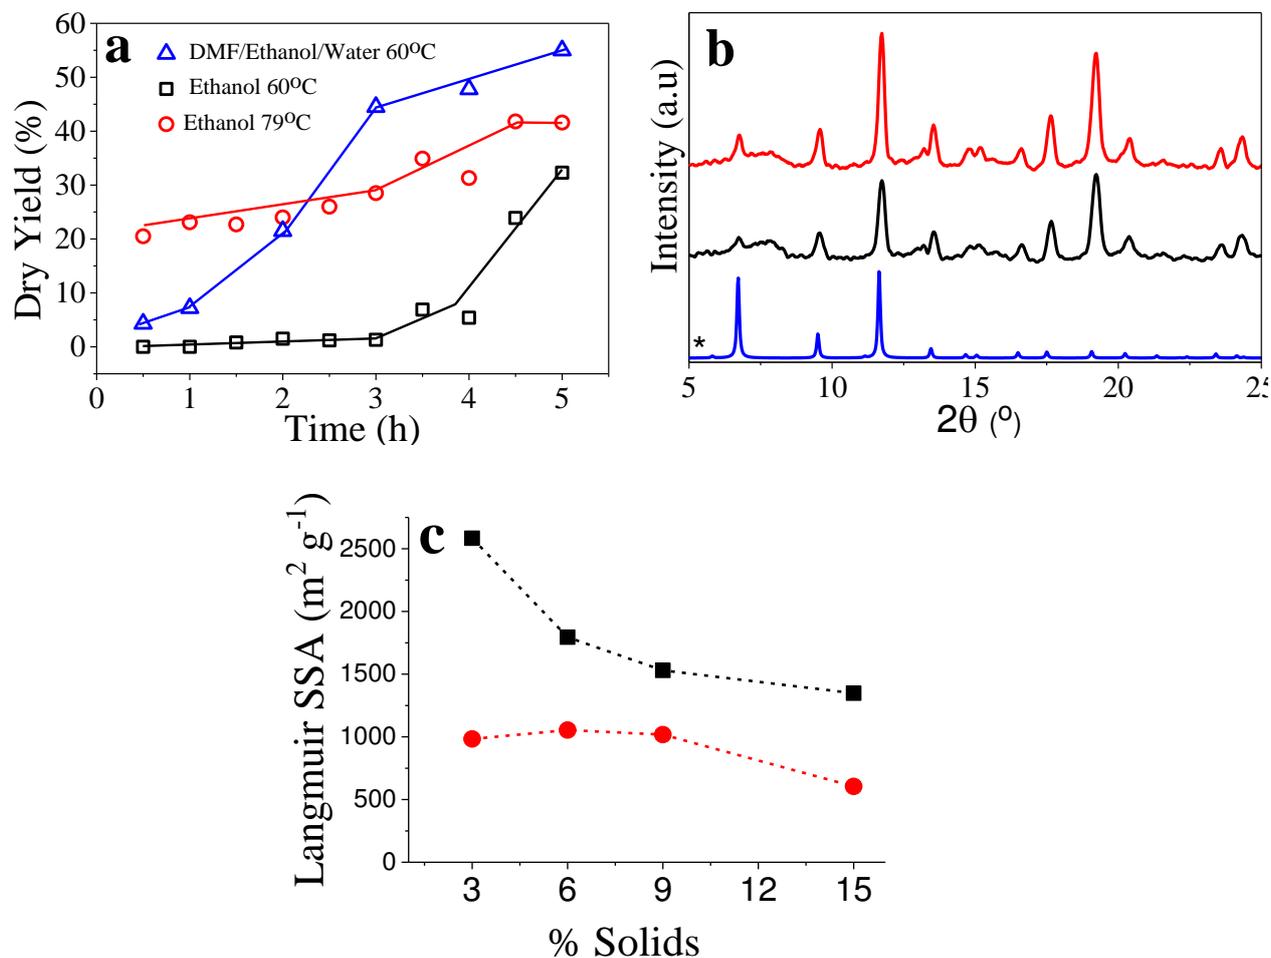

**Figure 2:** (a) Comparison of yields of batch systems as a function of time. (b) PXRD showing HKUST-1, as synthesized in 4 h at 60 °C, from DMF/ethanol/water (top line), ethanol only (middle line), \* indicates simulated PXRD data from single crystal data [8] (bottom line). (c) Comparison of Langmuir Specific Surface Area (SSA, filled symbols) as a function of % solids; circles: DMF/water/ethanol system (60°C), squares: ethanol only (60°C).

**Table 1:** Comparison of various batch synthesis routes for HKUST-1 synthesis\*

Solvent(s)		DMF/Water/Ethanol	Ethanol	Ethanol
Reaction Temperature (°C)		60	60	79
Dry Yield (%)	3h	45	1.3	28.5
	4h	47	5.4	31.3
	5h	55	32.3	41.6
Average Langmuir SSA m <sup>2</sup> g <sup>-1</sup>		1200	2200	2100
Solvent Cost (£/ g HKUST-1)		3.60	8.95	6.81
Highest STY (kg m <sup>-3</sup> day <sup>-1</sup> )		70	41	53
Surface Area Production Rate (m <sup>2</sup> m <sup>-3</sup> day <sup>-1</sup> )		84 × 10 <sup>6</sup>	91 × 10 <sup>6</sup>	112 × 10 <sup>6</sup>
Rough Cost*	(£/m <sup>2</sup> )	0.003273	0.0040	0.003243
	Relative Cost	0.804	1	0.797

\*For solids content of 3%. \*\*Cost estimations obtained from [31].

PXRD, FTIR and Langmuir SSA were measured and used to assess the quality of HKUST-1 produced. PXRD patterns (Figure 2b) show that both solvent systems produced HKUST-1, with locations of expected Bragg peaks matching the powder pattern generated from single crystal data. There were no significant differences observed with respect to the crystallinity of

the products from both systems. FT-IR spectra for the HKUST-1 produced (Figure S2) showed peaks at 1645, 1616, 1554 and 1455  $\text{cm}^{-1}$  indicating C=O and aromatic C=C, and 1375  $\text{cm}^{-1}$  indicating C-O from the BTC ligand, in good agreement with published sources [11, 32]. Gas adsorption confirmed the formation of a microporous material with pore diameters of  $< 1$  nm, and Type I isotherms [33] (Figure S3). The DMF/ethanol/water system produced crystals with a Langmuir SSA of  $1200 \pm 50 \text{ m}^2 \text{ g}^{-1}$  at 4 h synthesis time (Table 1), while both ethanol systems (60 and 79 °C) showed higher Langmuir SSAs ( $>2000 \pm 200 \text{ m}^2 \text{ g}^{-1}$ ).


In order to optimise yield by maximising the SAPRs, we increased the solids content from 3% to 6, 9, and 15%. The trade-off here is the potential reduction in MOF surface areas. While both solvent choices show a decrease in surface area with increasing % solid loading (Figure 2c), the ethanol system produced higher surface area MOFs when compared to those produced using DMF. When the SAPRs were calculated from the data in Figure 2c, and compared, the DMF system underperformed consistently by ~20% for all solid contents investigated.

As a determining factor in the decision of which system to use as the basis for a CSTR based synthesis; yield, cost, safety and availability of solvents, and the surface areas of the products obtained, were considered (see Table 1). Each synthesis process resulted in similar costs, based on initial estimates [31]. When scaling-up this process, it is important to consider that ethanol does not break down in the process, hence, it can be recycled. On the other hand, DMF is subject to breakdown when exposed to water and heat, therefore, it cannot be recycled and the amines produced from DMF decomposition present environmental risks. When economic analysis of this method was performed, it was reported that using ethanol and recycling the solvent can result in a profitable manufacturing process [31]. Our focus was

developing greener continuous processes for production of HKUST-1, by using ethanol instead of DMF and lower process temperatures. Unlike DMF, ethanol does not undergo decomposition and, thus, it can be recycled, resulting in a significant improvement of process economics [34]. We investigated temperatures below the boiling point of ethanol in order to avoid high pressure operation and/or boiling of solvent which cause additional safety issues as well as an increase in process costs. Thus, on the basis of production quality, cost, sustainability and safety, we selected to focus further syntheses on pure ethanolic systems.

Using the experimental findings from batch syntheses, we investigated continuous synthesis and scale-up. Figure 3 shows the results from the continuous synthesis systems at 100 mL and 500 mL scales. It is clear, from Figure 3a, that HKUST-1 can be produced continuously in ethanol using a CSTR. We note that this is the first report of the use of CSTR for continuous production of HKUST-1, and also the first study at 500 mL scale; all previous studies used tubular (micro)reactors [6]. PXRD confirmed the solid products were HKUST-1 (Figure S4). Although the system produces HKUST-1, product crystallinity does appear to vary over time, as evidenced by the relative intensities and widths of various Bragg peaks (Figure S4).

We observed that, at both scales, the yields from the continuous systems compare favourably to the equivalent batch syntheses. This is likely an effect of the system self-seeding, and being in a favourable state for the production of HKUST-1, highlighting one of the key benefits of using CSTR synthesis over tubular plug flow reactors. The dry yield of HKUST-1 collected varies almost linearly with time (Figure 3a) and the SAPRs increased to  $377 \times 10^6$   $\text{m}^2/\text{m}^3/\text{d}$  (Figure 3c and Table 2), which is an increase when compared with equivalent batch syntheses (see Table 1).

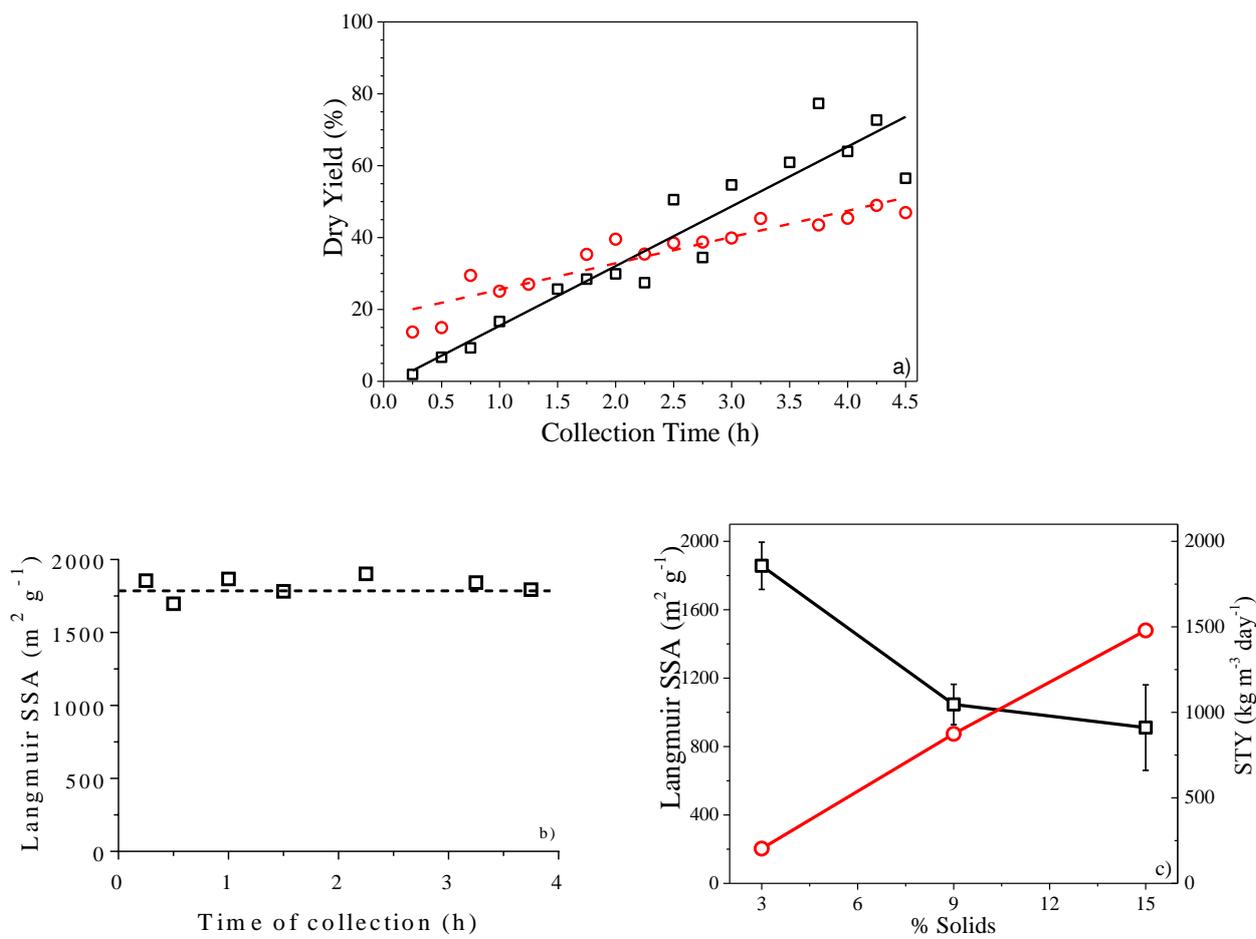

**Figure 3:** (a) Collected dry yield of HKUST-1; circles: 100 mL scale at 79 °C, dashed line indicating approximate trend, squares: 500 mL scale at 65 °C, solid line indicating approximate trend. Results show a lower yield at  $t < 2$  h, while showing scale-up gives significantly better production at  $t > 3$  h. (b) Langmuir Specific Surface Area (SSA) results from 4 repeats at various collection times. (c) squares: average Langmuir SSA ( $\text{m}^2 \text{g}^{-1}$ ), circles: calculated space time yield (STY,  $\text{kg m}^{-3} \text{day}^{-1}$ ).

**Table 2:** Comparison of reactor output at differing concentrations between 3 and 15% solids for continuous synthesis at 100 mL reactor volume and 79 °C (STY = Space-Time Yield; Langmuir SSA = Langmuir Specific Surface Area; SAPR = Surface Area Production Rate).

% Solids	STY ( $\text{kg m}^{-3} \text{day}^{-1}$ )	Langmuir SSA ( $\text{m}^2 \text{g}^{-1}$ )	SAPR ( $\text{m}^2 \text{m}^{-3} \text{day}^{-1}$ )

3	203	$1857 \pm 138$	$377 \times 10^6$
9	874	$1046 \pm 118$	$914 \times 10^6$
15	1479	$911 \pm 250$	$1347 \times 10^6$

Figure 3b shows the consistency of the high surface areas produced from this system, highlighting that we were able to reliably produce crystals with reasonably high surface areas. As increasing solid content showed benefits in batch operation, with respect to STY for MOF production, we decided to use the 100 mL scale system described above, operating at 79 °C, to study the effects of solids content (3% to 15% solids) in a continuous system. One of the most significant changes observed, when increasing reactant concentration, was the increase in yield, from ~40% at 3% solids to ~60% yield at 9 and 15% solids. The average surface areas of MOFs produced show a decrease with increasing solids content (Figure 3c), however, the total SAPR reached over  $1300 \times 10^6 \text{ m}^2$  per  $\text{m}^3$  of reactor volume per day for 15% solids content (Table 2). STY values for continuous systems were based on the outlet product flow rate (obtained from the overall flow rate, overall solid content and yield) divided by the reaction volume. As we have specified reaction volumes for each experiment, calculation of production rates in g/h from STY is also possible.

### 3.2 Microwave assisted synthesis and scale-up

Due to the potential benefits in heating efficiency and rate of formation of MOFs, we investigated the use of microwave heating. To identify operating conditions that can be used for continuous synthesis, we initially performed batch experiments; microwave power, residence time, and solids content were investigated. Under low microwave power (10%  $\approx$  80W), increasing the residence time increased the product specific surface area, and the yield

(Figure S5 and Table 3). Further, by increasing the microwave power, it was found that the surface area increased. Reaction time was not investigated at higher power levels due to the solution being close to the boiling point of the reaction mixture; therefore, operating at short times was required to prevent build-up of pressure within the vials. When the solids content were increased from 3% to 9%, the HKUST-1 produced exhibited moderate surface area but low yield.

PXRD data (Figure S5) shows phase pure HKUST-1 formed in all cases, however, the relative crystallinity varied between samples. Crystallinity appears to increase with reaction time (i, ii and iii) which is expected. Figure S5 (iv) shows the highest crystallinity of the 5 conditions analysed and also produced the highest average surface area, suggesting the increase in temperature, at the increased power level, is likely to produce higher quality crystals, even at relatively short time scales. The SAPRs for microwave assisted batch syntheses range between 1300 to 5900  $\times 10^6 \text{ m}^2 \text{ m}^{-3} \text{ d}^{-1}$  (Table 3), which are significantly higher when compared to conventional heating (see Table 1).

**Table 3:** Comparison of microwave assisted batch and continuous synthesis routes for HKUST-1 (Langmuir SSA = Langmuir Specific Surface Area; SAPR = Surface Area Production Rate).


<b>Reaction Time (s)</b>	<b>Power Level (%)</b>	<b>%Solids</b>	<b>STY</b> ( $\text{kg m}^{-3} \text{ day}^{-1}$ )	<b>Langmuir SSA</b> ( $\text{m}^2 \text{ g}^{-1}$ )	<b>SAPR</b> ( $\times 10^6 \text{ m}^2 \text{ m}^{-3} \text{ d}^{-1}$ )
<b>Batch synthesis</b>					
180	10	3	1970	1116 $\pm$ 680	2200
300	10	3	1560	1411 $\pm$ 393	2200
600	10	3	770	1685 $\pm$ 299	1300
180	20	3	1910	1880 $\pm$ 271	3600

300	10	9	3550	1664 ± 595	5900
<b>Continuous synthesis</b>					
300	10	3	2700	1930±90	5211
13	10	3	80000	1530±120	122400
13	10	15	400000	600±100	240000

Using the information obtained from batch synthesis, we performed continuous synthesis experiments in a single pass microwave system. Initially the residence time was set at 6 min, resulting in a reaction solution to be heated to a temperature of  $60 \pm 10$  °C, as measured at the outlet from the microwave cavity. The HKUST-1 produced had an average surface area of  $1930 \text{ m}^2 \text{ g}^{-1}$  (Table 3), with STY of  $2700 \text{ kg m}^{-3} \text{ d}^{-1}$  and SAPR of  $5.2 \times 10^9 \text{ m}^2 \text{ m}^{-3} \text{ d}^{-1}$ , which is an order of magnitude increase from the  $203 \text{ kg m}^{-3} \text{ d}^{-1}$  ( $0.377 \times 2 \times 10^9 \text{ m}^2 \text{ m}^{-3} \text{ d}^{-1}$ ) obtained for the conventionally heated continuous system. We note that this is the first report of the use of microwave heating for continuous production of HKUST-1 using only ethanol as the solvent. Previously reported microwave syntheses of HKUST-1 use DMF (with or without ethanol) [6]. The issues of overheating and boiling in the DMF systems even at pressures of up to 6 bars were reported by Ranocchiarri and co-workers [23]; our approach addresses these problems by achieving a robust control of microwave heating to avoid solvent overheating and undesirable side reactions. Given the economical and environmental benefits of avoiding the use of DMF, our results show significant improvements in HKUST-1 production.

When increasing the flowrate to  $550 \text{ mL h}^{-1}$ , from  $300 \text{ mL h}^{-1}$ , and decreasing the reactor volume to 2 mL from the original 25 mL, the residence time was reduced from 5 min to 13 s.

The output temperature was found to average  $45 \pm 5$  °C for this system. HKUST-1 was still found to form (Figure 4) with yields similar to the system operating with a residence time of 5 min (around 30%). This significant reduction in reaction duration results in an approximate STY of  $80,000 \text{ kg m}^{-3} \text{ day}^{-1}$ .

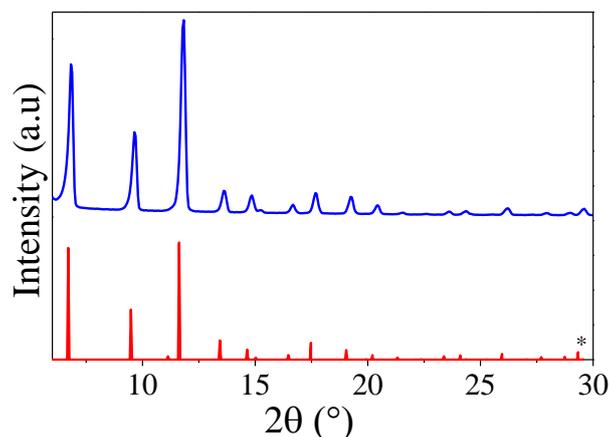

**Figure 4:** Powder X-ray diffraction data for HKUST-1 formed with 13 s residence time using continuous microwave assisted processing. Black lines show Bragg peak locations as generated by the crystallographic information for HKUST-1. \* indicates simulated PXRD data from single crystal data [8].

The product has an average Langmuir SSA of  $1550 \text{ m}^2 \text{ g}^{-1}$ , suggesting that the rapid formation of crystals within the microwave system may cause unreacted metal/ligand to be retained within the pores, thereby reducing the available surface area. We recognise that there may be multiple reasons for an observed reduction of the available surface area in the microwave system, including network interpenetration [35], occlusion of unreacted material [35] or partial network collapse upon characterisation [36], when synthesis conditions are changed. However, distinguishing between these effects is not trivial and sometimes not possible. In our experience, the use of TGA or FTIR is unable to accurately detect the presence of trapped (unbound) ligand. Thus, in order to avoid significant amount of ligand trapping in, we had thoroughly washed the solids. When increasing the concentration of the

feed to 15% solids, HKUST-1 was still formed, although the Langmuir SSA was reduced to  $600 \text{ m}^2 \text{ g}^{-1}$ , with STYs of  $400,000 \text{ kg m}^{-3} \text{ d}^{-1}$ . This STY is the highest ever STY reported for HKUST-1. The highest STY reported previously with any solvent was  $64,800 \text{ kg m}^{-3} \text{ d}^{-1}$  with DMF [23], while the highest STY reported with ethanol (without DMF) was  $4533 \text{ kg m}^{-3} \text{ d}^{-1}$  [22]. The resulting SAPR from our study is  $240 \times 10^9 \text{ m}^2 \text{ m}^{-3} \text{ d}^{-1}$ , which is also the highest reported to date and it is 2.4 times higher than any other reported so far [23].

#### 4. CONCLUSIONS

In our work, we demonstrated the first scalable continuous synthesis of HKUST-1 using ethanol only as the solvent, resulting in a greener and potentially much more economical process (as solvent does not decompose and thus can be recycled). We showed that either CSTR, single pass plug flow microwave assisted or a combined approach can be used effectively to produce high quality products at scale. We have shown that a conventionally heated continuous reaction system can be used to produce HKUST-1 in a relatively short time period, while maintaining high surface areas, increasing the potential output from a batch system (Table 4). Further, we demonstrated a novel approach to microwave assisted synthesis of HKUST-1, based on a recycle loop with microwave irradiation, which can be scalable under both batch and continuous conditions and allows an independent control of irradiation regime and the overall reaction time. We also showed that microwave heating can be used to significantly improve the STY of both batch and continuous systems while maintaining a surface area similar to conventionally heated processes. This represents the production of  $2.4 \times 10^{11} \text{ m}^2$  of Langmuir SSA for one  $\text{m}^3$  reactor volume per day. This is higher than any production rates reported to date, even when using DMF as the reaction solvent, and it is orders of magnitude more than the highest production rates reported for HKUST-1 in 'ethanol-only' systems.

**Table 4:** Summary of results discussed within main body of this work.

<b>System</b>	<b>% Solids</b>	<b>Langmuir SSA (m<sup>2</sup> g<sup>-1</sup>)</b>	<b>Surface Area Production Rate ×10<sup>6</sup> (m<sup>2</sup> m<sup>-3</sup> d<sup>-1</sup>)</b>
Continuous CSTR, (EtOH, 100 mL, 79 °C)	15	910 ± 250	1347
Continuous microwave system (EtOH, 13 s)	15	600 ± 100	240000
Commercially Available Product*	-	1680	378

\* Basolite C300, produced by BASF, reported STY = 225 kg/m<sup>3</sup>/d and Langmuir SSA of 1680 m<sup>2</sup>/g

## ACKNOWLEDGEMENTS

We thank the financial support provided by the EPSRC-DTG, the Department of Chemical and Process Engineering and the Department of Pure and Applied Chemistry. S.P. thanks the financial support provided by the EPSRC (EP/L017059/1 and EP/K031260/1).

## REFERENCES

- [1] A.U. Czaja, N. Trukhan, U. Muller, Industrial applications of metal-organic frameworks, *Chemical Society Reviews*, 38 (2009) 1284-1293.
- [2] O.K. Farha, I. Eryazici, N.C. Jeong, B.G. Hauser, C.E. Wilmer, A.A. Sarjeant, R.Q. Snurr, S.T. Nguyen, A.Ö. Yazaydin, J.T. Hupp, Metal–Organic Framework Materials with Ultrahigh Surface Areas: Is the Sky the Limit?, *Journal of the American Chemical Society*, 134 (2012) 15016-15021.
- [3] B. Li, H.L. Wang, B.L. Chen, Microporous Metal-Organic Frameworks for Gas Separation, *Chem.-Asian J.*, 9 (2014) 1474-1498.

- [4] A. Sachse, R. Ameloot, B. Coq, F. Fajula, B. Coasne, D. De Vos, A. Galarneau, In situ synthesis of Cu-BTC (HKUST-1) in macro-/mesoporous silica monoliths for continuous flow catalysis, *Chem. Commun.*, 48 (2012) 4749-4751.
- [5] H.S. Fogler, *Elements of chemical reaction engineering*, Prentice-Hall, 1986.
- [6] P.W. Dunne, E. Lester, R.I. Walton, Towards scalable and controlled synthesis of metal-organic framework materials using continuous flow reactors, *Reaction Chemistry & Engineering*, 1 (2016) 352-360.
- [7] M. Faustini, J. Kim, G.-Y. Jeong, J.Y. Kim, H.R. Moon, W.-S. Ahn, D.-P. Kim, Microfluidic Approach toward Continuous and Ultrafast Synthesis of Metal–Organic Framework Crystals and Hetero Structures in Confined Microdroplets, *Journal of the American Chemical Society*, 135 (2013) 14619-14626.
- [8] S.S.Y. Chui, S.M.F. Lo, J.P.H. Charmant, A.G. Orpen, I.D. Williams, A chemically functionalizable nanoporous material Cu-3(TMA)(2)(H<sub>2</sub>O)(3) (n), *Science*, 283 (1999) 1148-1150.
- [9] S.Y. Wang, Q.Y. Yang, C.L. Zhong, Adsorption and separation of binary mixtures in a metal-organic framework Cu-BTC: A computational study, *Sep. Purif. Technol.*, 60 (2008) 30-35.
- [10] J.S. Xiao, M. Hu, P. Benard, R. Chahine, Simulation of hydrogen storage tank packed with metal-organic framework, *Int. J. Hydrog. Energy*, 38 (2013) 13000-13010.
- [11] L.D. O'Neill, H. Zhang, D. Bradshaw, Macro-/microporous MOF composite beads, *Journal of Materials Chemistry*, 20 (2010) 5720-5726.
- [12] B. Silva, I. Solomon, A.M. Ribeiro, U.H. Lee, Y.K. Hwang, J.S. Chang, J.M. Loureiro, A.E. Rodrigues, H-2 purification by pressure swing adsorption using CuBTC, *Sep. Purif. Technol.*, 118 (2013) 744-756.
- [13] J.B. DeCoste, G.W. Peterson, Metal-Organic Frameworks for Air Purification of Toxic Chemicals, *Chem. Rev.*, 114 (2014) 5695-5727.
- [14] L.J. Murray, M. Dinca, J.R. Long, Hydrogen storage in metal-organic frameworks, *Chemical Society Reviews*, 38 (2009) 1294-1314.
- [15] T. Granato, F. Testa, R. Olivo, Catalytic activity of HKUST-1 coated on ceramic foam, *Microporous Mesoporous Mat.*, 153 (2012) 236-246.
- [16] E.V. Perez, K.J. Balkus, J.P. Ferraris, I.H. Musselman, Mixed-matrix membranes containing MOF-5 for gas separations, *J. Membr. Sci.*, 328 (2009) 165-173.
- [17] P. Kusgens, M. Rose, I. Senkowska, H. Frode, A. Henschel, S. Siegle, S. Kaskel, Characterization of metal-organic frameworks by water adsorption, *Microporous Mesoporous Mat.*, 120 (2009) 325-330.

- [18] S.S. Kaye, A. Dailly, O.M. Yaghi, J.R. Long, Impact of preparation and handling on the hydrogen storage properties of Zn<sub>4</sub>O(1,4-benzenedicarboxylate)<sub>3</sub> (MOF-5), *Journal of the American Chemical Society*, 129 (2007) 14176-+.
- [19] M. Gimeno-Fabra, A.S. Munn, L.A. Stevens, T.C. Drage, D.M. Grant, R.J. Kashtiban, J. Sloan, E. Lester, R.I. Walton, Instant MOFs: continuous synthesis of metal-organic frameworks by rapid solvent mixing, *Chem. Commun.*, 48 (2012) 10642-10644.
- [20] L. D'Arras, C. Sassoey, L. Rozes, C. Sanchez, J. Marrot, S. Marre, C. Aymonier, Fast and continuous processing of a new sub-micronic lanthanide-based metal-organic framework, *New Journal of Chemistry*, 38 (2014) 1477-1483.
- [21] K.-J. Kim, Y.J. Li, P.B. Kreider, C.-H. Chang, N. Wannemacher, P.K. Thallapally, H.-G. Ahn, High-rate synthesis of Cu-BTC metal-organic frameworks, *Chem. Commun.*, 49 (2013) 11518-11520.
- [22] M. Rubio-Martinez, M.P. Batten, A. Polyzos, K.-C. Carey, J.I. Mardel, K.-S. Lim, M.R. Hill, Versatile, High Quality and Scalable Continuous Flow Production of Metal-Organic Frameworks, *Sci. Rep.*, 4 (2014).
- [23] M. Taddei, D.A. Steitz, J.A. van Bokhoven, M. Ranocchiari, Continuous-Flow Microwave Synthesis of Metal-Organic Frameworks: A Highly Efficient Method for Large-Scale Production, *Chemistry – A European Journal*, 22 (2016) 3245-3249.
- [24] S. Hausdorf, J. Wagler, R. Mossig, F.O.R.L. Mertens, Proton and water activity-controlled structure formation in zinc carboxylate-based metal organic frameworks, *J Phys Chem A*, 112 (2008) 7567-7576.
- [25] C. McKinstry, R.J. Cathcart, E.J. Cussen, A.J. Fletcher, S.V. Patwardhan, J. Sefcik, Scalable continuous solvothermal synthesis of metal organic framework (MOF-5) crystals, *Chem Eng J*, 285 (2016) 718-725.
- [26] C. McKinstry, E.J. Cussen, A.J. Fletcher, S.V. Patwardhan, J. Sefcik, Effect of Synthesis Conditions on Formation Pathways of Metal Organic Framework (MOF-5) Crystals, *Cryst Growth Des*, 13 (2013) 5481-5486.
- [27] J.Y. Choi, J. Kim, S.H. Jung, H.K. Kim, J.S. Chang, H.K. Chae, Microwave synthesis of a porous metal-organic framework, zinc terephthalate MOF-5, *Bull. Korean Chem. Soc.*, 27 (2006) 1523-1524.
- [28] P. Chowdhury, C. Bikkina, D. Meister, F. Dreisbach, S. Gumma, Comparison of adsorption isotherms on Cu-BTC metal organic frameworks synthesized from different routes, *Microporous Mesoporous Mat.*, 117 (2009) 406-413.
- [29] F. Millange, R. El Osta, M.E. Medina, R.I. Walton, A time-resolved diffraction study of a window of stability in the synthesis of a copper carboxylate metal-organic framework, *Crystal Engineering Communications*, 13 (2011) 103-108.

- [30] K.B. Pitchai, S. L.; Jones, D.; Subbiah, J, Assessment of heating rate and non-uniform heating in domestic microwave ovens., *The Journal of Microwave Power and Electromagnetic Energy*, 46 (2012) 229-240.
- [31] C. McKinstry, Continuous production of two archetypal metal-organic frameworks using conventional and microwave heating, Ph. D. Thesis, University of Strathclyde, Glasgow, (2015)
- [32] E.M. Borfecchia, S.; Gianolio, D.; Groppo, E.; Chiesa, M.; Bonino, F.; Lamberti, C., Insights into Adsorption of NH<sub>3</sub> on HKUST-1 Metal–OrganicFramework: A Multitechnique Approach, *Journal of Physical Chemistry C*, 116 (2012) 19839-19850.
- [33] M. Thommes, K. Kaneko, A.V. Neimark, J.P. Olivier, F. Rodriguez-Reinoso, J. Rouquerol, K.S. Sing, Physisorption of gases, with special reference to the evaluation of surface area and pore size distribution (IUPAC Technical Report), *Pure and Applied Chemistry*, 87 (2015) 1051-1069.
- [34] E. Grimmond, T. Hadley, A. Monch, I. Harvey, J. Churchill, M. Rubio-Martinez, S. Lim, M. Hill, A techno-economic evaluation for industrial scale production of metal organic frameworks, in: *Asia Pacific Confederation of Chemical Engineering Congress 2015: APCCHE 2015, incorporating CHEMECA 2015, Engineers Australia, 2015*, pp. 691.
- [35] J. Hafizovic, M. Bjørgen, U. Olsbye, P.D. Dietzel, S. Bordiga, C. Prestipino, C. Lamberti, K.P. Lillerud, The inconsistency in adsorption properties and powder XRD data of MOF-5 is rationalized by framework interpenetration and the presence of organic and inorganic species in the nanocavities, *JACS*, 129 (2007) 3612.
- [36] V.V. Butova, M.A. Soldatov, A.A. Guda, K.A. Lomachenko, C. Lamberti, Metal-organic frameworks: structure, properties, methods of synthesis and characterization, *Russ. Chem. Rev.*, 85 (2016) 280.


## SUPPORTING INFORMATION

### High quality continuous production of metal organic framework

#### HKUST-1 via conventional and microwave heating




**Figure S1:** Experimental set-up of the scaled-up HKUST-1 system in operation in this work

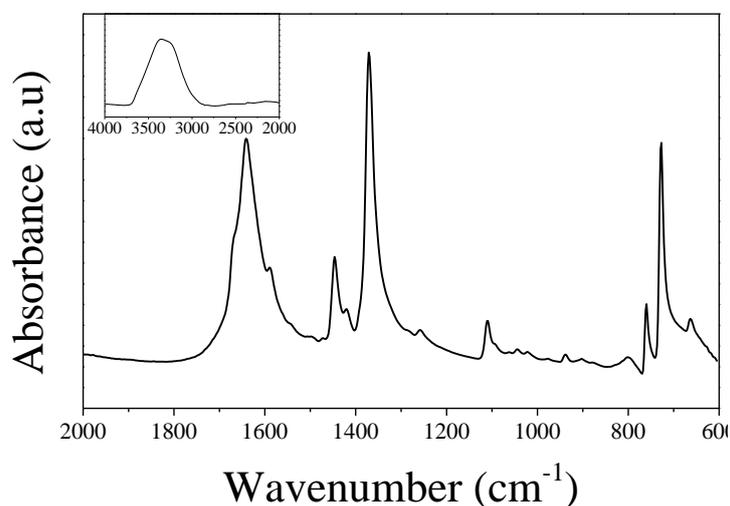


**Figure S2:** FT-IR spectra for a typical HKUST-1 sample. As HKUST-1 will quickly absorb water from the atmosphere, a large peak is present in the 3000-3600  $\text{cm}^{-1}$  region which is shown only in the inset image above and has generally otherwise been excluded from other FT-IR spectra shown for clarification of other peaks. We are unable to see the vibrational mode involving the Copper centre


which occurs at  $493\text{cm}^{-1}$ , [32] out with the range of our equipment. We see peaks at 1645, 1616, 1554 and  $1455\text{cm}^{-1}$  indicating C=O and aromatic C=C, and  $1375\text{cm}^{-1}$  indicating C-O from the BTC ligand, in good agreement with published sources [11, 32].

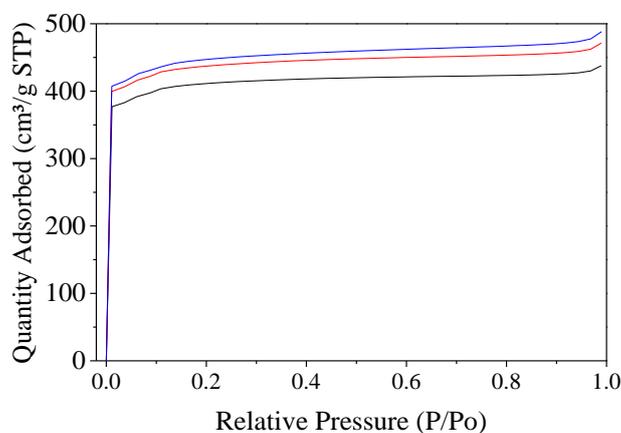

**Figure S3:** Nitrogen adsorption isotherms measured at  $-196\text{ }^{\circ}\text{C}$  for three samples of HKUST-1 produced using a continuous microwave reaction system. Samples were previously activated by heating to  $170\text{ }^{\circ}\text{C}$  under vacuum for 4 h. Samples show very similar gas uptakes; as expected for a structure with pore diameter  $< 1\text{nm}$ , we see clear Type I isotherms.

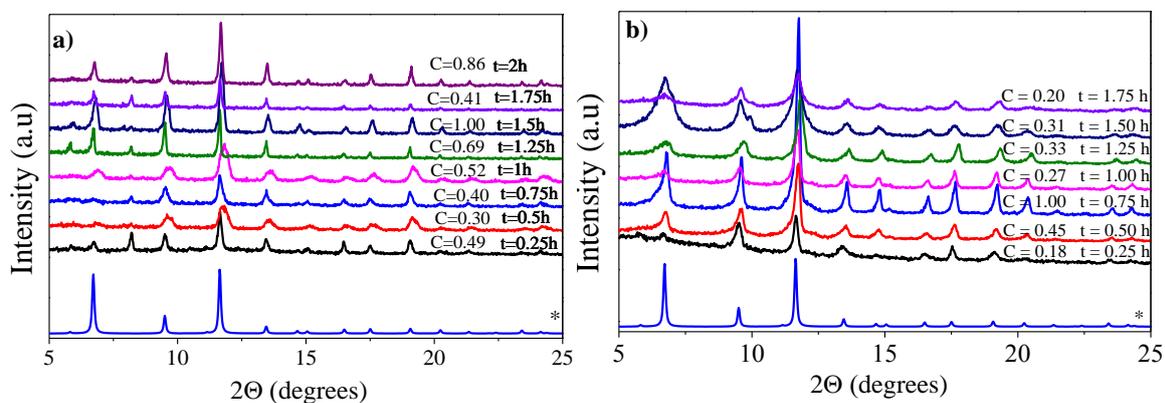

**Figure S4:** Powder X-ray diffraction results for HKUST-1 samples produced at a) 100 mL reaction scale at  $79\text{ }^{\circ}\text{C}$  and b) 500 mL reaction scale at  $65\text{ }^{\circ}\text{C}$ . As with batch experiments, the relative crystallinity of material produced appears to vary significantly. \* indicates simulated PXRD data from single crystal data [8].

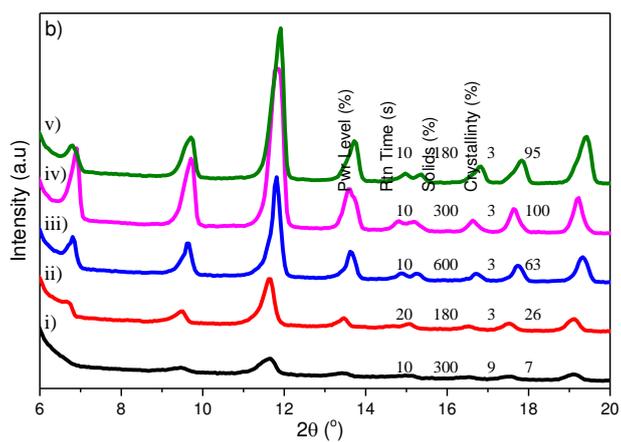

**Figure S5:** Example PXRDs of the 5 conditions analysed. All samples show PXRD patterns in agreement with HKUST-1, though i) is very low intensity. Relative crystallinity (%) of each sample, based on the intensity of Bragg peak at  $11.8^\circ 2\theta$ .