

This is a repository copy of *Synergistic chemo-enzymatic hydrolysis of poly(ethylene terephthalate) from textile waste*.

White Rose Research Online URL for this paper:

<https://eprints.whiterose.ac.uk/id/eprint/118366/>

Version: Published Version

---

**Article:**

Quartinello, Felice, Vajnhandl, S., Volmeijer Valh, Julija et al. (6 more authors) (2017)  
Synergistic chemo-enzymatic hydrolysis of poly(ethylene terephthalate) from textile waste.  
Microbial Biotechnology. ISSN: 1751-7915

<https://doi.org/10.1111/1751-7915.12734>

---

**Reuse**

This article is distributed under the terms of the Creative Commons Attribution (CC BY) licence. This licence allows you to distribute, remix, tweak, and build upon the work, even commercially, as long as you credit the authors for the original work. More information and the full terms of the licence here:

<https://creativecommons.org/licenses/>

**Takedown**

If you consider content in White Rose Research Online to be in breach of UK law, please notify us by emailing [eprints@whiterose.ac.uk](mailto:eprints@whiterose.ac.uk) including the URL of the record and the reason for the withdrawal request.

## Synergistic chemo-enzymatic hydrolysis of poly(ethylene terephthalate) from textile waste

Felice Quartinello,<sup>1</sup> Simona Vajnhandl,<sup>2</sup> Julija Volmajer Valh,<sup>2</sup> Thomas J. Farmer,<sup>3</sup> Bojana Vončina,<sup>2</sup> Alexandra Lobnik,<sup>2</sup> Enrique Herrero Acero,<sup>3</sup> Alessandro Pellis<sup>1,\*</sup> and Georg M. Guebitz<sup>1,4</sup>

<sup>1</sup>Department of Agrobiotechnology IFA-Tulln, University of Natural Resources and Life Sciences Vienna, Inst. of Environ. Biotech., Konrad Lorenz Strasse 20, 3430, Tulln a. d. Donau, Austria.

<sup>2</sup>Laboratory for Chemistry and Environmental Protection, Institute of Engineering Materials and Design, Faculty of Mechanical Engineering, University of Maribor, Smetanova ulica 17, 2000, Maribor, Slovenia.

<sup>3</sup>Green Chemistry Centre of Excellence, Department of Chemistry, University of York, Heslington, York YO10 5DD, UK.

<sup>4</sup>Austrian Centre of Industrial Biotechnology, Division Polymers & Enzymes, Konrad Lorenz Strasse 20, 3430, Tulln a. d. Donau, Austria.

### Summary

Due to the rising global environment protection awareness, recycling strategies that comply with the circular economy principles are needed. Polyesters are among the most used materials in the textile industry; therefore, achieving a complete poly(ethylene terephthalate) (PET) hydrolysis in an environmentally friendly way is a current challenge. In this work, a chemo-enzymatic treatment was developed to recover the PET building blocks, namely terephthalic acid (TA) and ethylene glycol. To monitor the monomer and oligomer content in solid samples, a Fourier-transformed Raman method was successfully developed. A shift of the free carboxylic groups ( $1632\text{ cm}^{-1}$ ) of TA into the deprotonated state ( $1604$  and  $1398\text{ cm}^{-1}$ ) was observed and bands at  $1728$  and  $1398\text{ cm}^{-1}$  were used to assess purity of TA after the chemo-enzymatic PET hydrolysis. The

chemical treatment, performed under neutral conditions ( $T = 250\text{ }^{\circ}\text{C}$ ,  $P = 40\text{ bar}$ ), led to conversion of PET into 85% TA and small oligomers. The latter were hydrolysed in a second step using the *Humicola insolens* cutinase (HiC) yielding 97% pure TA, therefore comparable with the commercial synthesis-grade TA (98%).

### Introduction

Global population and rising living standards are directly correlated to the continuous increase of textile waste (Allwood *et al.*, 2006). Overproduction of fabrics since 2010 is driven by the increased rate of replacement of products. In 2008, around 14 M tons of textile waste was generated in Europe, but only 5 M tons was recovered (Zamani, 2014). About 75% of the recovered fabrics were reused or recycled mainly in industrial applications (Jorgensen *et al.*, 2008). The remaining collected waste textiles are either landfilled or incinerated. However, the recycling of used textiles would lead to several environmental benefits such as energy saving, as this process requires less energy than the production of the same products from virgin materials and reduction of the carbon footprint of the overall process (Clark *et al.*, 2016).

The textile and clothing industry is a heterogeneous business which covers different types of fibres, with a consistent 54% that is represented by man-made synthetic materials. The consumption of these synthetic fibres increased by 77% between 2000 and 2012 (Harder *et al.*, 2017). On the other hand, the growth share of synthetic fibres in global consumption results in the rising demand for petroleum-based chemicals (Pellis *et al.*, 2016a). Among the synthetic textiles, poly(ethylene terephthalate) (PET) is one of the most widely used polymers in the global textile industry (Herrero Acero *et al.*, 2011). PET is a semi-crystalline thermoplastic polymer which shows excellent tensile strength, chemical resistance and high thermal stability. Two PET grades are dominating the global market: the fibre grade PET, with a  $M_w$  of  $15\text{--}20\text{ Kg mol}^{-1}$  and intrinsic viscosity between  $0.4$  and  $0.75\text{ dl g}^{-1}$ , and the bottle grade PET, which refers to a higher  $M_w$  polymer ( $> 20\text{ Kg mol}^{-1}$ ) with an intrinsic viscosity above  $0.95\text{ dl g}^{-1}$  (Tasca *et al.*, 2010; Al-Sabagh *et al.*, 2016).

Due to its wide production and utilization (Cavaco-Paulo and Guebitz, 2008), PET represents a broad

Received 14 February, 2017; revised 24 April, 2017; accepted 28 April, 2017.

\*For correspondence. E-mail alessandro.pellis@boku.ac.at; Tel. +43 1 47654-97447; Fax +43 1 47654-97409.

Microbial Biotechnology (2017) 0(0), 1–10  
doi:10.1111/1751-7915.12734

### Funding Information

No funding information provided.

disposal inert textile. The non-toxic nature, durability and crystal clear transparency of PET during use are the principal advantages of this polyester, while its rather slow biodegradability is the major cause of concern to the environmentalists. Recycling the textile waste-derived polyesters can significantly cut down the energy usage, resource depletion and greenhouse gas emissions. Unfortunately, different factors such as colouring dyes (Giannotta *et al.*, 1994) and other chemicals such as detergents, fuels and pesticides (Demertzis *et al.*, 1997) reduce the quality of recycled PET reducing the number of the possible applications. When compared to mechanical recycling and incineration, chemical hydrolysis could lead to higher value products (Paszun and Szychaj, 1997). The most common chemical-based PET hydrolysis processes are alkaline hydrolysis using 4–20% NaOH/KOH solutions (Karayannidis *et al.*, 2002), phase transfer catalysts and acidic hydrolysis using concentrated sulphuric acid or other mineral acids (Yoshioka *et al.*, 2001). All these processes are very costly and toxic because the chemicals required and laborious purification steps are needed. In recent years, more environmentally friendly PET recycling strategies based on neutral hydrolysis (carried out using water or steam at 1–4 MPa and temperatures of 200–300 °C) were reported (Launay *et al.*, 1994). In last decade, the interest of biotechnologies towards polyesters biodegradation and recycling is gaining a key role. Yoshida *et al.* (2016) showed a novel bacterium, *Ideonella sakaiensis* 201-F6, able to break down the plastic using two enzymes to hydrolyse PET and assimilate its building block for growth. Earlier, various studies demonstrated that a class of enzymes belonging to the  $\alpha/\beta$  hydrolase family, namely cutinases, are able to hydrolyse the ester bonds of PET and several other polyesters (Pellis *et al.*, 2015, 2016b; Barth *et al.*, 2016; Wei *et al.*, 2016). Among them, cutinase are currently under investigation for the bioprocessing of PET textiles on an industrial scale (Silva *et al.*, 2005). Earlier, it was reported that cutinases from *Thermobifida fusca* and *Humicola insolens* were able to hydrolyse low-crystallinity PET while complete hydrolysis by enzymes only seems to be difficult if not impossible for PET with higher crystallinity (Mueller, 2006; Nimchua *et al.*, 2007; Ronkvist *et al.*, 2009). In this work, we propose an innovative synergistic chemo-enzymatic hydrolysis of PET for the production of high-purity TA (97%) avoiding harsh chemical treatments.

## Results and discussion

### FT-Raman analysis

In the past, several methods, mainly HPLC-related, have been established to follow enzymatic hydrolysis of PET in aqueous solutions (Herrero Acero *et al.*, 2011; Pellis

*et al.*, 2016c). However, water-insoluble oligomers would obviously escape quantification of TA in the presence of insoluble oligomers; hence, a novel method based on FT-Raman and triethylamine was adapted for this study. TA,  $p\text{-C}_6\text{H}_4(\text{COOH})_2$ , has two carboxylic groups which are detectable using Fourier transform Raman spectroscopy. The analysis of benzene dicarboxylic acids such as isophthalate and terephthalate using FT-Raman was previously described by Arenas and Tellez (Arenas, 1979; Tellez *et al.*, 2001). According to these reports, the -COOH group of solid TA reveals a typic-centred band at  $1631\text{ cm}^{-1}$ , mainly given by the asymmetric stretching ( $\nu_{\text{as}}$ ) of C=O. As described by Tellez, a coupled vibrational mode is characteristic of the single band at  $1286\text{ cm}^{-1}$ . The discrimination of monomeric TA from esterified species was performed converting these functional groups into the corresponding anions. The simplest reaction of carboxylic acid is salification by a base. This reaction causes the shift of ( $\nu_{\text{as}}$ ) of the C=O group and appearance of new bands due to the in-phase and out of phase -COO<sup>(-)</sup> stretching vibration (Socrates, 2004). The shift of the acid peak of the carboxylic group from  $1720\text{ cm}^{-1}$  to  $1580\text{ cm}^{-1}$  after alkaline treatment was previously reported for the grafting of cotton with cyclodextrins (Voncina and Majcen, 2005) or for detection of end groups of fluoropolymers (Pianca *et al.*, 1999).


The conversion of the -COOH group into the carboxylate species was carried out using triethylamine (TEA) in chloroform solution (Di Robert *et al.*, 2015). The deprotonated anion obtained *via* incubation with tertiary aliphatic amine caused the shift of  $\nu_{\text{as}}\text{C=O}$  and the increase of the single band of the symmetric stretching ( $\nu_{\text{s}}$ ) of C=O at  $1400\text{ cm}^{-1}$  and an ammonium-related band in the  $2700\text{ cm}^{-1}$  region.

Figure 1 shows the shift of the acid peak of solid TA from  $1631$  to  $1604\text{ cm}^{-1}$  after deprotonation with TEA. Furthermore, the clear appearance of a peak at  $1398\text{ cm}^{-1}$  was observed due the symmetric stretching mode of the carboxylate moiety. On the other hand, the peak at  $1286\text{ cm}^{-1}$  was strongly reduced. The 1:5 TA/TEA ratio showed the clearest signal for the monomers due to a complete conversion of the desired groups (Fig. S2).

To assess the suitability of this method to quantify TA in the presence of oligomers, BHET, DMT and PET were incubated with the tertiary aliphatic amine (1:5 ratio). Expectedly, the shift of  $1632$  and  $1395\text{ cm}^{-1}$  typical for TA did not occur as all carboxylic groups of these oligomers are esterified (Figs S3–S5).

### Water-based PET hydrolysis

Preliminary experiments showed that water-based PET depolymerization was not achieved with ratio 1:4 PET/

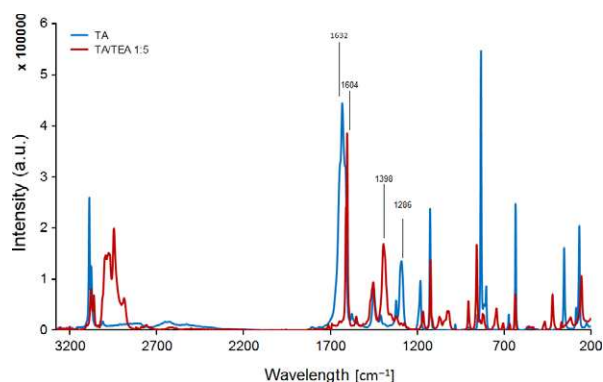

**Fig. 1.** FT-Raman analysis showing the deprotonation of the TA's carboxylic acid moieties (blue) via incubation with a 1:5 TA/TEA ratio (red). Spectra were normalized between the region 2000 and 2200  $\text{cm}^{-1}$ .

$\text{H}_2\text{O}$  and incubation for 90 min. Therefore, a series of experiments were performed, to define the appropriate depolymerization conditions (Table 1).

The incubation of PET fibre at 180 °C and 12 bar did not lead to any depolymerization of the sample, and hence, there was no difference of spectra. In Fig. S6, it is possible to observe how the spectra of raw PET fibre and Sample 2 are very similar with no remarkable differences that could be spotted, showing that reaction temperature and pressure were not optimal for the hydrolysis of the polymer. Finally, when temperature and pressure were increased to 250 °C and 39 bar, respectively, the polymer was completely reduced in a whitish powder (Fig. S7). In Fig. S8, it is possible to see that spectrum of PET depolymerization product for Sample 4 (blue) was similar to the spectrum of commercial TA. Using these conditions, a powder consisting of 85% TA was obtained from the water-based PET depolymerization according to HPLC and  $^1\text{H}$ -NMR analysis. Unfortunately, further variation of the reaction conditions

**Table 1.** Design of experiments strategy used for performing the water-based hydrolysis of PET.

Experiment	Initial MW (IV) range of PET	T [°C]	PET/ $\text{H}_2\text{O}$ ratio <sup>a</sup>	Steady-state time [min] <sup>b</sup>
1	0.62	180	1/4	0
2			1/10	30
3		250	1/4	
4			1/10	0
5		180	1/4	
6			1/10	30
7		250	1/4	
8			1/10	0

All reported conditions were also tested; zinc acetate was added to the reaction mixture.

a. 25 g of PET.


b. After the transient period (to reach the desired T).

including addition of zinc acetate did not lead to a higher yield of TA. Hence, enzymatic hydrolysis of the remaining oligomers was assessed in the next step. To note that experiments with various steady-state lengths were performed but did not lead to an improvement of the TA yield, therefore the enzymatic finishing step was critical in order to obtain high-purity TA.

### Enzymatic PET hydrolysis

The kinetics of the formation of degradation products via enzymatic treatment depends on various factors, including the chemical–physical structure of polyester substrate (Eberl *et al.*, 2008). Already, various authors have previously demonstrated that cutinase preferentially hydrolyze the amorphous region on PET (Donelli *et al.*, 2009; Gamerith *et al.*, 2017). On the other hand, it was shown that enzymatic hydrolysis of PET oligomers is way faster than of a long-chain polymer (Ribitsch *et al.*, 2011). Therefore, due to the high crystallinity of the PET fibres used in the textile industry, a chemical pre-hydrolysis was established in this work.

The sample from chemical pre-treatment with the highest degree of hydrolysis (Sample 4, 85% TA) was further incubated with different concentrations of *Humicola insolens* cutinase (HiC) to hydrolyse remaining oligomers (Fig. 2). The highest amount of soluble TA (6.5 mM) was obtained after 6 h of incubation both when 1 or 2  $\text{mg ml}^{-1}$  of HiC was applied without any further increase until 24 h of incubation. The lower concentrations of enzyme of 0.1 and 0.5  $\text{mg ml}^{-1}$  led to the release of 0.53 and 1.9 mM of TA respectively.

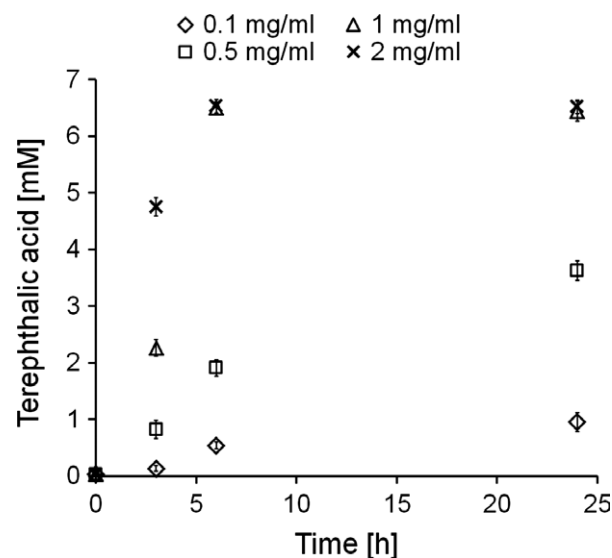

**Fig. 2.** Enzymatic hydrolysis of chemically pre-treated PET with different concentrations of *Humicola insolens* cutinase (HiC).


Terephthalic acid with 97% purity was obtained after enzymatic treatment of the chemical-treated PET which is comparable to synthesis-grade TA (98% pure). When chemical pre-hydrolysis of PET was performed in the presence of zinc acetate as a catalyst, a negative influence on enzymatic hydrolysis was observed (Fig. 3). In fact, there was no further increase in the amount of TA seen (Fig. 3).

Zinc and other metal ions are well known to be potential inhibitors of many enzymes, including cutinases as recently reported by Chen *et al.* that biochemically characterized *Thermobifida fusca* cutinases (Chen *et al.*, 2010).


#### FT-Raman detection of depolymerized PET

While in the chemically pre-treated sample oligomers were present, the peak at  $1728\text{ cm}^{-1}$  indicative of ester bond was considerably reduced after enzymatic hydrolysis (Fig. 4). In parallel, the increase in the band at  $1398\text{ cm}^{-1}$  indicated formation of TA. Finally, the signal at  $1286\text{ cm}^{-1}$ , as expected, had the opposite trend of the asymmetric stretching of CO, further confirming the reduction in the oligomers to TA (Fig. 5).

In addition to FT-Raman,  $^1\text{H-NMR}$  analysis was performed. Likewise,  $^1\text{H}$  spectra (recorded in  $\text{DMSO-d}_6$ )

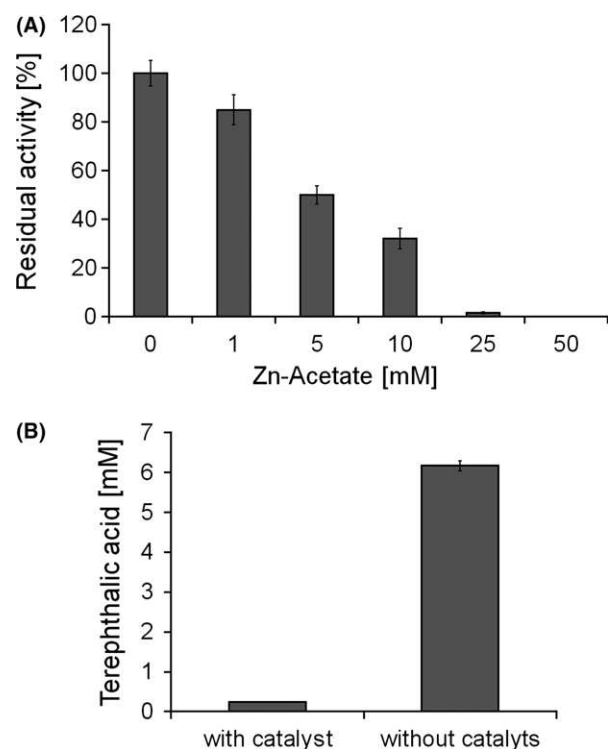

**Fig. 3.** Residual activity of HiC in the presence of Zn acetate (A) and enzymatic hydrolysis of PET chemically pre-treated in the presence of Zn acetate (B).

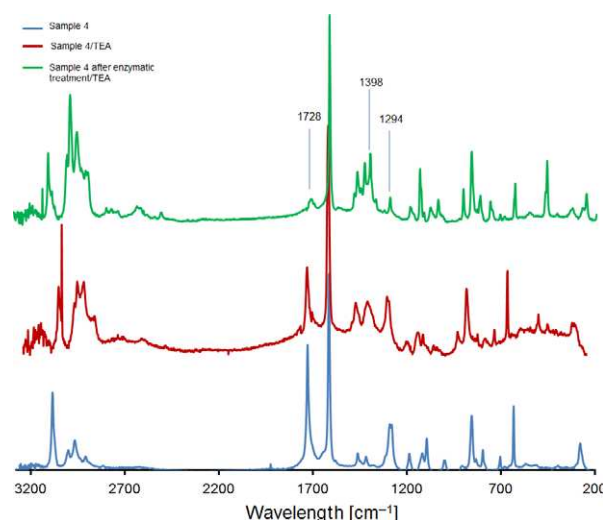

**Fig. 4.** FT-Raman analysis showing the incubation of Sample 4 with a 1:5 TEA ratio before (red) and after (green) enzymatic hydrolysis. Spectra were normalized between the 2000 and  $2200\text{ cm}^{-1}$  region.

indicate the presence of some longer oligomers in the chemically pre-treated sample while the spectra of the reaction product after subsequent enzymatic hydrolysis suggest their conversion into TA. Based on the  $^1\text{H-NMR}$ -performed calculations (see ESI for details), the oligomers are mostly comprised of less than four (but nearer two) constitutional repeat units, and TA end groups dominate over EG suggesting the oligomerization is more effective at releasing free EG than free TA, or that the purification steps involved preferentially remove EG.

#### Materials and Methods


##### Chemicals, substrates and enzymes

Buffer components, bovine serum albumin (BSA), *para*-nitrophenyl-butyrate (*p*-NPB), methanol, zinc acetate, TA and formic acid were purchased from Sigma-Aldrich (USA). All other chemicals and reagents used in this work were of analytical grade and used without further purification if not otherwise specified. *Humicola insolens* cutinase (HiC) was a gift from Novozymes (Beijing, China). All hydrolyses were performed using Wellman PET fibre with a viscosity of  $0.62\text{ dl g}^{-1}$ .

##### Water-based PET hydrolysis

Water-based PET hydrolysis was performed in 1 l stainless steel high-pressure and high-temperature reactor at different temperatures ( $180$  and  $250\text{ }^{\circ}\text{C}$ ) and with and without the addition of zinc acetate as catalyst. All experiments were carried out with 25 g of virgin PET fibre in 250 ml of deionized water. The reactions were stopped after 60 and 90 min, respectively (30 min after reaching



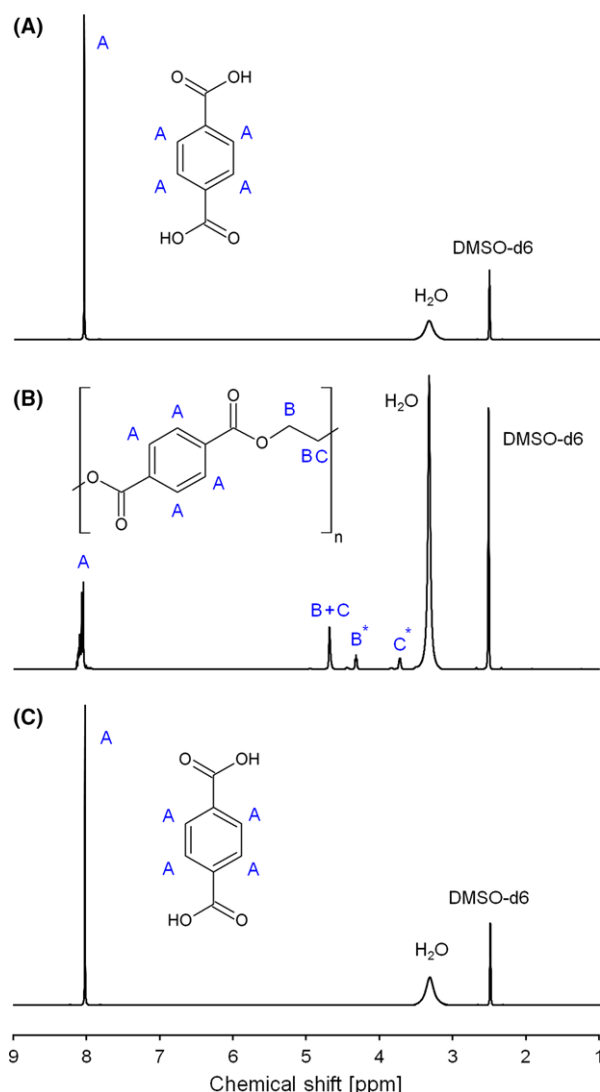

**Fig. 5.** <sup>1</sup>H-NMR of pure TA (A), PET degradation after the chemical treatment (Sample 4, B) and PET degradation after enzymatic finishing (C). All spectra were recorded in DMSO-d<sub>6</sub>. All samples were fully soluble in the selected solvent. For detailed proton assignments, please see ESI.

the steady state), and two different ratios PET/H<sub>2</sub>O were assessed. A temperature and pressure profile of a typical reaction is shown in Fig. S1. At the end of the process, H<sub>2</sub>O and EG were removed and a white powder was obtained (Fig. S7B). The EG stream can be further processed anaerobically due to the current low cost of the compound.

#### ATR FT-IR analysis

ATR FT-IR spectra were recorded on a Perkin-Elmer Spectrum GX spectrometer. The ATR accessory (supplied by Specac Ltd., UK) contained a diamond crystal. A total of 16 scans for each sample were taken with a resolution

of 4 cm<sup>-1</sup>. All spectra were recorded at 21 °C over the wavelength interval between 4000 and 650 cm<sup>-1</sup>.

#### FT-Raman analysis

To remove the water, terephthalic acid (TA), bis(2-hydroxyethyl) terephthalate (BHET), dimethyl terephthalate (DMT) and poly(ethylene terephthalate) PET as standards were lyophilized for 24 h; 50 mg of samples was incubated with different volumes of pure triethylamine in 10 ml of chloroform for 6 h. Afterwards, chloroform was removed by evaporation at 21 °C for 24 h. The virgin material and the powders obtained from the chemical process and after the enzymatic treatment were also incubated as described above. The FT-Raman spectra were recorded using a Perkin-Elmer Raman station 400, coupled with a 785 nm laser. Spectra were collected at a resolution of 2 cm<sup>-1</sup> for 25 scans and normalized in the region 2200–2400 cm<sup>-1</sup> before any data processing. The bands were assigned as follows: 3000–2700 cm<sup>-1</sup> ν(Et-NH<sub>4</sub><sup>+</sup>), 1728 cm<sup>-1</sup> ν(C=O, bended), 1632–1604 cm<sup>-1</sup> ν<sub>as</sub>(C=O), single band 1398 cm<sup>-1</sup> δ(C-O), single band 1286 cm<sup>-1</sup> coupled mode ν(C=O)+δ(COH).

#### Protein quantification and SDS-PAGE analysis

Protein concentration was measured using the Bio-Rad Protein Assay Kit (Bio-Rad, Vienna, Austria). BSA was used as protein standard; 10 μl of the sample was added into the wells of a 96-well plate. Afterwards, 200 μl of the prepared Bio-Rad reagent solution was added (Bio-Rad Reagent diluted 1:5 with MQ-water). The plate was incubated for 5 min at 21 °C and 400 rpm. Buffer (100 mM Tris-HCl pH 7) was used as blank. The absorption after 5 min was measured at λ = 595 nm in a plate reader (Tecan INFINITE M200) and the concentration calculated from the average of triplicates. Sodium dodecyl sulphate–polyacrylamide gel electrophoresis (SDS-PAGE) was performed according to Laemmli using 4% stacking gels and 15% separating gels and run at 150 V (Laemmli, 1970). Pre-stained protein marker IV (Peglab, Germany) was used as a molecular mass marker. Proteins were stained with Coomassie method.

#### Esterase activity assay

Esterase activity was measured at 25 °C using *p*-nitrophenyl-butyrate (*p*-NPB) as a substrate according to Biundo *et al.* (Biundo *et al.*, 2015). The final assay was carried out by mixing 200 μl of the substrate stock solution, in 100 mM Tris-HCl buffer pH 7, with 20 μl of enzyme solution. The increase in the absorbance at 405 nm due to the release of *p*-nitrophenol (ε 405 nm = 10.27 ml (μmol

cm)<sup>-1</sup>) was measured for 5 min, every 18 s with a plate reader. A blank was included using 20 µl of buffer instead of enzyme solution. The activity was calculated in units (U), where 1 unit is defined as the amount of enzyme required to hydrolyse 1 µmol of substrate per minute under the given assay conditions. The activity assay was also performed in the presence of 1, 5, 10, 25 or 50 mM of the chemical catalyst (zinc acetate). All the experiments were performed in triplicates.

#### Enzymatic hydrolysis of PET oligomers

The enzymatic hydrolysis of the PET powder resulting from the chemical treatments was performed as previously described with some modifications (Herrero Acero *et al.*, 2011; Pellis *et al.*, 2016a). Briefly, 10 mg of pre-treated PET powder and 2.0 ml of enzyme solution (diluted in 100 mM Tris-HCl buffer pH 7) were added in a test tube. The mixture was incubated for 24 h at 50 °C and 600 rpm in an orbital shaker. Different concentrations 0.1, 0.5, 1 and 2 mg ml<sup>-1</sup> of enzyme were used to understand the optimal concentration of HiC. All the experiments were performed in triplicates.

#### High-Performance Liquid Chromatography

Proteins were removed using a 1:1 (v v<sup>-1</sup>) ice-cold methanol precipitation. Therefore, samples were centrifuged at 14 000 rpm (Centrifuge Beckman JU-MI) at 0 °C for 15 min. The supernatant was acidified by adding 8 µl of 6 M HCl and then transferred into HPLC vials. The released products were analysed by high-performance liquid chromatography (HPLC) (Agilent Technologies, Palo Alto, CA) coupled with a UV detector, at 241 nm, using a water/methanol linear gradient (Table S1). To determine the TA percentage in the mixture, 10 mg of PET powder resulting from before and after the enzymatic hydrolysis was diluted in 100 ml of 100 mM Tris-HCl buffer pH 7 and analysed as described before.

#### <sup>1</sup>H-NMR analysis

<sup>1</sup>H nuclear magnetic resonance was performed on a Bruker Avance II 400 spectrometer (resonance frequency of 400.13 MHz for <sup>1</sup>H) equipped with a 5 mm observe broadband probe head (BBFO) with z-gradients. DMSO-*d*<sub>6</sub> was used as NMR solvent for all samples.

#### Conclusions

In this study, the synergism of chemical and enzymatic hydrolysis of PET was demonstrated on a multigram scale. To monitor the PET hydrolysis and formation of

TA, a FT-Raman method based on the deprotonation of the -COOH group was established. The chemical pre-treatment performed in an environmentally friendly way under neutral conditions, therefore avoiding harsh chemicals, leads to depolymerization of the polyester-composed waste textiles yielding about 85% TA. The enzymatic hydrolysis performed in a second reaction step leads to further hydrolysis of the remaining oligomers yielding TA with a purity of 97%. Future studies should consider the chemo-enzymatic treatment of different PET containing textiles wastes as well as studies on synthesis of PET based on the recovered TA.

#### Acknowledgements

This project received funding from the European Union's Horizon 2020 research and innovation programme under the grant agreement 641942 (Resyntex project).

#### Author contributions

The manuscript was written through contributions of all authors. All authors have given approval to the final version of the manuscript.

#### Conflict of interest

None declared.

#### References

- Allwood, J.M., Laursen, S.E., deRodriguez, C.M. and Bocken, N.M.P. (2006) Well dressed? The present and future sustainability of clothing and textiles in the United Kingdom. Technical annex. University of Cambridge.
- Al-Sabagh, A.M., Yehia, F.Z., Eshaq, Gh., Rabie, A.M. and ElMetwally, A.E. (2016) Greener routes for recycling of polyethylene terephthalate. *Egypt J Petrol* **25**: 53–64.
- Arenas, J.F. (1979) Infrared and Raman spectra of phthalate, isophthalate and terephthalate ions. *Spectrochim Acta, Part A* **35**: 355–363.
- Barth, M., Honak, A., Oeser, T., Wei, R., *et al.* (2016) A dual enzyme system composed of a polyester hydrolase and a carboxylesterase enhances the biocatalytic degradation of polyethylene terephthalate films. *Biotechnol J* **11**: 1082–1087.
- Biundo, A., Hromic, A., Pavkov-Keller, T., Gruber, K., *et al.* (2015) Characterization of a poly(butylene adipate-co-terephthalate)-hydrolyzing lipase from *Pelosinus fermentans*. *Appl Microbiol Biotechnol* **100**: 1753–1764.
- Cavaco-Paulo, A., and Guebitz, G.M. (2008) Enzymes go big: surface hydrolysis and functionalisation of synthetic polymers. *Trends Biotechnol* **26**: 32–38.
- Chen, S., Su, L., Billig, S., Zimmermann, W., Chen, J., and Wu, J. (2010) Biochemical characterization of the cutinases from *Thermobifida fusca*. *J Mol Catal B: Enzym* **63**: 121–127.

- Clark, J.H., Farmer, T.J., Herrero-Davila, L., and Sherwood, J. (2016) Circular economy design considerations for research and process development in the chemical sciences. *Green Chem* **14**: 3914–3934.
- Demertzis, P.G., Johansson, F., Lievens, C., and Franz, R. (1997) Studies on the development of a quick inertness test procedure for multi-use PET containers-sorption behaviour of bottle wall strips. *Packag Technol Sci* **10**: 45–58.
- Di Robert, M., Silverstein, F.W., David, J. and Bryce, D.L. (2015). Spectrometric Identification of Organic Compounds.
- Donelli, I., Taddei, P., Smet, P.F., Poelman, D., Nierstrasz, V.A., *et al.* (2009) Enzymatic surface modification and functionalization of PET: a water contact angle, FTIR, and fluorescence spectroscopy study. *Biotechnol Bioeng* **103**: 845–856.
- Eberl, A., Heumann, S., Kotek, R., Kaufmann, F., *et al.* (2008) Enzymatic hydrolysis of PTT polymers and oligomers. *J Biotechnol* **135**: 45–51.
- Gamerith, C., Zartl, B., Pellis, A., Guillaumot, F., *et al.* (2017) Enzymatic recovery of polyester building blocks from polymer blends. *Process Biochem* [In press] <https://doi.org/10.1016/j.procbio.2017.01.004>.
- Giannotta, G., Po, R., Cardi, N., Tampellini, E., *et al.* (1994) Processing effects on poly(ethylene terephthalate) from bottle scraps. *Polym Eng Sci* **34**: 1219–1223.
- Harder, R., Kalmykova, Y., Morrison, G.M., Feng, F., *et al.* (2017) Quantification of goods purchases and waste generation at the level of individual households. *J Ind Ecol* **18**: 227–241.
- Herrero Acero, E., Ribitsch, D., Steinkellner, G., Gruber, K., *et al.* (2011) Enzymatic surface hydrolysis of pet: effect of structural diversity on kinetic properties of cutinases from thermobifida. *Macromolecules* **44**: 4640.
- Jorgensen, A., Le Bocq, A., Nazarkina, L., *et al.* (2008) Methodologies for social life cycle assessment. *Int J LCA* **13**: 96–103.
- Karayannidis, G.P., Chatziavgoustis, F., Achillas, A.P., *et al.* (2002) Poly(ethylene terephthalate) recycling and recovery of pure terephthalic acid by alkaline hydrolysis. *Adv Polym Technol* **21**: 250–259.
- Laemmli, U.K. (1970) Cleavage of structural proteins during the assembly of the head of bacteriophage T4. *Nature* **227**: 680–685.
- Launay, A., Thominette, F., and Verdu, J. (1994) Hydrolysis of poly(ethylene terephthalate): a kinetic study. *Polym Degrad Stabil* **46**: 319–324.
- Mueller, R.-J. (2006) Biological degradation of synthetic polyesters-Enzymes as potential catalysts for polyester recycling. *Process Biochem* **41**: 2124–2128.
- Nimchua, T., Punnapayak, H., and Zimmermann, W. (2007) Comparison of the hydrolysis of polyethylene terephthalate fibers by a hydrolase from *Fusarium oxysporum* LCH I and *Fusarium solani* f. sp. pisi. *Biotechnol J* **2**: 361–364.
- Paszun, D., and Spychaj, T. (1997) Chemical recycling of Poly(ethylene terephthalate). *Ind Eng Chem Res* **36**: 1373–1383.
- Pellis, A., Herrero Acero, E., Weber, H., and Obersiebnig, M. (2015) Biocatalyzed approach for the surface functionalization of poly(L-lactic acid) films using hydrolytic enzyme. *Biotechnol J* **10**: 1739–1749.
- Pellis, A., Herrero Acero, E., Ferrario, V., Ribitsch, D., *et al.* (2016a) The closure of the cycle: enzymatic synthesis and functionalization of bio-based polyesters. *Trends Biotechnol* **34**: 316–328.
- Pellis, A., Gamerith, C., Ghazaryan, G., Ortner, A., *et al.* (2016b) Ultrasound-enhanced enzymatic hydrolysis of poly(ethylene terephthalate). *Biores Technol* **218**: 1298–1302.
- Pellis, A., Haernvall, K., Pichler, C.M., Ghazaryan, G., *et al.* (2016c) Enzymatic hydrolysis of poly(ethylene furanoate). *J Biotechnol* **235**: 47–53.
- Pianca, M., Esposto, G., and Radice, S. (1999) End groups in fluoropolymers. *J Fluorine Chem* **95**: 71–84.
- Ribitsch, D., Heumann, S., Trotscha, E., Herrero Acero, E., *et al.* (2011) Hydrolysis of polyethyleneterephthalate by p-nitrobenzylesterase from *Bacillus subtilis*. *Biotechnol Prog* **27**: 951–960.
- Ronkvist, A.M., Xie, W., Lu, W., and Gross, R.A. (2009) Cutinase-catalyzed hydrolysis of Poly(ethylene terephthalate). *Macromolecules* **42**: 5128–5138.
- Silva, C., Carneiro, F., O'Neill, A., Fonseca, L.P., Cabral, J.M.S., Guebitz, G. and Cavaco-Paulo, A. (2005) Cutinase- a new tool for biomodification of synthetic fibers. *J Polym Chem* **43**, 2448–2450.
- Socrates, G. (2004) *Infrared characteristic group frequencies tables and charts*, 3rd edn. John Wiley & Sons.
- Tasca, F., Gorton, L., Kujawa, M., Patel, I., *et al.* (2010) Increasing the coulombic efficiency of glucose biofuel cell anodes by combination of redox enzymes. *Biosens Bioelectron* **25**: 1710–1716.
- Téllez, A.C., Hollauer, E., Mondragon, M.A. and Castaño, V.M. (2001) Fourier transform infrared and Raman spectra, vibrational assignment and ab initio calculations of terephthalic acid and related compounds. *Spectrochim Acta Part A: Mol Biomol Spectrosc* **57**, 993–1007.
- Voncina, B. and Majcen, L. M.A. (2005) Grafting of cotton with  $\beta$ -cyclodextrin via poly(carboxylic acid). *J Appl Polym Sci* **96**, 1323–1328.
- Wei, R., Oeser, T., Schmidt, J., Meier, R., *et al.* (2016) Engineered bacterial polyester hydrolases efficiently degrade polyethylene terephthalate due to relieved product inhibition. *Biotechnol Bioeng* **113**: 1658–1665.
- Yoshida, S., Hiraga, K., Takehana, T., Taniguchi, I., Yamaji, H., Maeda, Y., *et al.* (2016) A bacterium that degrades and assimilates poly(ethylene terephthalate). *Science* **351**: 1196–1199.
- Yoshioka, T., Motoki, T., and Okuwaki, A. (2001) Kinetics of hydrolysis of Poly(ethylene terephthalate) powder in sulfuric acid by a modified shrinking-core model. *Ind Eng Chem Res* **40**: 75–79.
- Zamani, B. (2014) Towards Understanding Sustainable Textile Waste Management: Environmental impacts and social indicators. Thesis for the degree of licentiate of engineering: Chalmers University of Technology.

## Supporting information

Additional Supporting Information may be found online in the supporting information tab for this article:



**Fig. S1.** Temperature (blue, Y-axis left) and pressure (red, Y-axis right) increase according to the reaction time (X-axis).

**Fig. S2.** FT-Raman analysis showing the deprotonation of the TA's carboxylic acid moieties *via* incubation with different TA/TEA ratio.

**Fig. S3.** FT-Raman analysis showing the deprotonation of the BHET *via* incubation with TEA 1:5.

**Fig. S4.** FT-Raman analysis showing the deprotonation of the DMT *via* incubation with TEA 1:5.

**Fig. S5.** FT-Raman analysis showing the deprotonation of the PET *via* incubation with TEA 1:5.

**Fig. S6.** FT-IR spectrum of Sample 1 (black) and spectrum of untreated virgin PET.

**Fig. S7.** Samples obtained by three different depolymerisation operational conditions.

**Fig. S8.** FT-IR spectra of Sample 4 (blue), untreated virgin PET (black) and pure TA (red).

**Fig. S9.** SDS-PAGE of HiC. Lane 1 Protein Marker IV (bands 10-170 KDa). Lane 2 HiC (dilution 1:10), MW 24 KDa.

**Table S1.** Mobile phase gradient used for the HPLC-DAD analysis of the PET degradation release products.