



UNIVERSITY OF LEEDS

This is a repository copy of *Organically modified clay with potassium copper hexacyanoferrate for enhanced Cs + adsorption capacity and selective recovery by flotation*.

White Rose Research Online URL for this paper:

<https://eprints.whiterose.ac.uk/119519/>

Version: Accepted Version

---

**Article:**

Zhang, H [orcid.org/0000-0003-2438-788X](https://orcid.org/0000-0003-2438-788X), Kim, YK, Hunter, TN [orcid.org/0000-0003-3922-491X](https://orcid.org/0000-0003-3922-491X) et al. (3 more authors) (2017) Organically modified clay with potassium copper hexacyanoferrate for enhanced Cs + adsorption capacity and selective recovery by flotation. *Journal of Materials Chemistry A*, 5 (29). pp. 15130-15143. ISSN 2050-7488

<https://doi.org/10.1039/C7TA03873A>

---

© The Royal Society of Chemistry 2017. This is an author produced version of a paper published in *Journal of Materials Chemistry A*. Uploaded in accordance with the publisher's self-archiving policy.

**Reuse**

Items deposited in White Rose Research Online are protected by copyright, with all rights reserved unless indicated otherwise. They may be downloaded and/or printed for private study, or other acts as permitted by national copyright laws. The publisher or other rights holders may allow further reproduction and re-use of the full text version. This is indicated by the licence information on the White Rose Research Online record for the item.

**Takedown**

If you consider content in White Rose Research Online to be in breach of UK law, please notify us by emailing [eprints@whiterose.ac.uk](mailto:eprints@whiterose.ac.uk) including the URL of the record and the reason for the withdrawal request.



[eprints@whiterose.ac.uk](mailto:eprints@whiterose.ac.uk)  
<https://eprints.whiterose.ac.uk/>

# Organically modified clay with potassium copper hexacyanoferrate for enhanced Cs<sup>+</sup> adsorption capacity and selective recovery by flotation

Received 00th January 20xx,  
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

[www.rsc.org/](http://www.rsc.org/)

Huagui Zhang,<sup>\*a</sup> Yun Kon Kim,<sup>b</sup> Timothy N. Hunter,<sup>a</sup> Andrew P. Brown,<sup>a</sup> Jae W. Lee<sup>b</sup> and David Harbottle<sup>\*a</sup>

The selective capture of mobile radioactive nuclides, such as <sup>137</sup>Cs<sup>+</sup>, is crucial to the clean-up and remediation of contaminated environments. While remediation remains a challenging task, the current study considers novel organo-clay composites containing potassium copper hexacyanoferrate (KCuHCF) as a viable option for large-scale clean-up. A three-step synthesis has been demonstrated whereby pristine montmorillonite clay was readily modified to incorporate KCuHCF nanoparticles for enhanced and selective Cs<sup>+</sup> removal from aqueous environments. Alkyldiamine (DT) was used as an organic modifier to intercalate the clay and provided chelating sites to anchor copper onto the clay matrix, from which KCuHCF nanoparticles were subsequently grown *in-situ* via the coordination of hexacyanoferrate precursors with the immobilized copper ions. The organo-clay-HCF composite particles exhibited a superior Cs<sup>+</sup> adsorption capacity ( $q_m = 206$  mg/g), twice that of the pristine clay. The enhanced performance also extended to high Cs<sup>+</sup> selectivity in seawater, with the organo-clay-HCF composites demonstrating Cs<sup>+</sup> selectivity values in excess of 10<sup>5</sup> mL/g, two orders of magnitude greater than the pristine clay. Organo modification of the clay particles reduced the particle wettability, thus facilitating the separation of Cs-loaded composite particles from aqueous environments by collector-less flotation. Batch flotation experiments showed recovery efficiencies of the Cs-loaded composite particles of up to 90%, which was in great contrast to the low recovery of less than 15% for the Cs-loaded pristine montmorillonite. The current study provides a new concept for the treatment of contaminated aqueous environments.

## 1. Introduction

Nuclear power is seen as a viable option to address the global energy challenge due to efficient and clean energy production. While the industry is heavily regulated, risks of nuclear incident, such as that witnessed at the Fukushima Daiichi nuclear plant, must be planned for, as they can result in substantial environmental liability<sup>1</sup>. The release of radioactive isotopes, in particular <sup>134</sup>Cs<sup>+</sup> and <sup>137</sup>Cs<sup>+</sup>, can result in a significant biohazard with the long-lived radionuclides (half-life ~ 30 years) accumulating in the environment, and total depletion of radioactivity requiring approximately 1,000 years<sup>2</sup>. Additionally, a significant volume of contaminated effluent is produced from normal nuclear power operations (e.g. within fuel cooling plants) which must also be treated on an ongoing basis. Cs<sup>+</sup> is highly soluble in water and readily migrates with the potential to produce wide spread contamination of land and water systems.

Several remediation strategies have been deployed to recover Cs<sup>+</sup> from radioactive wastes; including chemical precipitation, membrane extraction, reverse osmosis, solvent extraction and ion exchange<sup>3</sup>. Ion exchange by selective adsorbent is a proven route to separate Cs<sup>+</sup> from aqueous environments, forming a concentrated waste more suitable for disposal. Accordingly, a series of inorganic Cs<sup>+</sup> adsorbents have been developed, among which zeolites<sup>4</sup>, crystalline silicotitanate<sup>5, 6</sup>, vanadosilicate<sup>7</sup> and chalcogenides<sup>2, 8, 9</sup>, have been studied in detail due to high Cs<sup>+</sup> selectivity and excellent removal efficiencies. Nevertheless, the complexity of synthesis and cost-inefficiency greatly limit application for large-scale nuclear waste clean-up and remediation. In contrast, natural clay minerals which have also been used as adsorbents for radionuclides (e.g. Cs<sup>+</sup>, Sr<sup>2+</sup>, Co<sup>2+</sup>)<sup>10, 11</sup> and other hazardous contaminants are readily available, low cost, and therefore suitable for scale-up. In particular, montmorillonite, a member of the smectite clays composed of two tetrahedral silica sheets surrounding a central octahedral sheet of alumina in a 2-1 layered structure, has been extensively adopted as a very efficient Cs<sup>+</sup> adsorbent with an adsorption capacity in the range 57-104 mg/g<sup>10-13</sup>. This relatively high adsorption capacity results from favourable structural properties including high cation exchange capacity (CEC), large surface area, high swelling capacity, good chemical and mechanical stability<sup>10, 14</sup>.

<sup>a</sup> School of Chemical and Process Engineering, University of Leeds, Leeds, United Kingdom, LS2 9JT. Email: d.harbottle@leeds.ac.uk (D.H.), prehz@leeds.ac.uk (H.Z.)

<sup>b</sup> Chemical and Biomolecular Engineering, Korean Advanced Institute of Science and Technology, Daejeon, Korea (the Republic of).

<sup>†</sup>Electronic Supplementary Information (ESI) available: [Flotation experimental setup, TGA data, adsorption isotherm of organo-clays, XPS analysis, EDX data and particle size distribution]. See DOI: 10.1039/x0xx00000x

An alternative group of adsorbents that are cost-effective and show high adsorption capacity are Prussian blue analogues (PBAs), namely the hexacyanoferrates (HCFs) of transition metals, wherein potassium copper hexacyanoferrate (KCuHCF) provides higher Cs<sup>+</sup> selectivity compared to other metal hexacyanoferrates<sup>15</sup>. Hexacyanoferrate(II) is an agent of high Cs<sup>+</sup> affinity and selectivity, with the small hydrated ions such as Cs<sup>+</sup> able to permeate through the cubic structure, while the larger competing ions are blocked from accessing the sorption sites<sup>15-18</sup>. However, the fine particle size of this type of adsorbent makes it difficult to separate from aqueous environments, so it is generally incorporated within supporting materials for effective Cs<sup>+</sup> adsorption and removal<sup>15, 19</sup>. The main supporting materials are either polymer composites or mesoporous silica, both of which show limited Cs<sup>+</sup> adsorption capacity. Even though both the smectite clay and HCF have demonstrated relatively high Cs<sup>+</sup> uptake ability, to the best of our knowledge, reports of nanocomposites immobilizing HCF onto clays remain surprisingly scarce<sup>20</sup>.

In the current study we report an original and facile synthesis route for organo-clay-KCuHCF composite adsorbents. Montmorillonite clay was organically intercalated with ethylhexadecyldimethylammonium-bromide and decorated with alkyldiamine, followed by the *in-situ* synthesis of KCuHCF. Cationic surfactant was firstly intercalated into the clay interlayer to immobilize the alkyldiamine, which acts as a metal chelator for a Cu<sup>2+</sup>-diamine complex, serving as an anchoring point for KCuHCF growth. This type of incorporation, with organo-clay being the supporting matrix, retains the high Cs<sup>+</sup> adsorption capacity of the clay and KCuHCF, along with modifying the surface of the clay to be hydrophobic and enable easy recovery of the composite particles by flotation. In the absence of clays the nano-sized KCuHCF particles remain dispersed in suspension and unrecoverable, but the apparent growth in particle size through incorporation with clays, and the increased surface hydrophobicity provide realization for a new concept in Cs<sup>+</sup> removal from contaminated aqueous environments. The structure and chemistry of the composite adsorbents were characterized using a series of techniques including powder X-ray diffraction (XRD), Fourier transform infrared spectroscopy (FTIR), X-ray photoelectron spectroscopy, scanning electron microscopy (SEM) and transmission electron microscopy (TEM). Component loadings were quantified by thermogravimetric analysis (TGA). Cs<sup>+</sup> adsorption was studied by measuring the kinetics and adsorption capacity in environments of varying pH and multi-component ionic solutions. Finally, the flotation performance of the Cs-loaded composites was studied using a laboratory batch flotation cell, with recovery performance measured as a function of the DT concentration.

## 2. Experimental

### 2.1 Chemicals

Montmorillonite clay (abbreviated as Mont., a naturally occurring mineral) of ~ 200 mesh (< 74 μm) was purchased from Alfa Aesar. Ethylhexadecyldimethylammonium-bromide (EHDA-Br; abbreviated as EH) with M<sub>w</sub> of 378.5 g/mol was purchased from Merck Millipore (purity > 98.0 %). The metal ligand of Alkyl-1,3-diaminopropane

(Duomen-T; abbreviated as DT) with M<sub>w</sub> of 350 g/mol, alkyl group (R) ranging from C<sub>12</sub> to C<sub>18</sub>, was supplied by Akzo Chemicals (Batch No. 1197752). Chemical structures of the EH and DT are given in Figure 1a. Potassium hexacyanoferrate(II) (K<sub>4</sub>[Fe(CN)]<sub>6</sub>·3H<sub>2</sub>O, ACS reagent, ≥ 99%), copper sulfate (CuSO<sub>4</sub>·5H<sub>2</sub>O, Reagent Plus, ≥ 99%) and cesium chloride (CsCl, analytical grade) were purchased from Sigma-Aldrich and used as received.

The cation exchange capacity (CEC) of the montmorillonite clay was found to be 90 meq/100g. The CEC was determined by the sorption of 0.01 M Cu(II)-triethylenetetramine complex [Cu Trien]<sup>2+</sup> following the procedure outlined by Honty *et al.*<sup>21</sup>. The concentration of [Cu Trien]<sup>2+</sup> was measured at 577 nm by UV spectroscopy (UV-1800 SHIMADZU). The BET specific surface area of the montmorillonite clay was determined to be 29.85 m<sup>2</sup>/g by N<sub>2</sub> adsorption isotherm using a Micromeritics TriStar 3000. The chemical composition of the montmorillonite clay was measured by X-ray fluorescence (XRF) spectrometry to be 2.20 wt% Na<sub>2</sub>O, 2.39 wt% MgO, 20.80 wt% Al<sub>2</sub>O<sub>3</sub>, 66.86 wt% SiO<sub>2</sub>, 0.06wt% P<sub>2</sub>O<sub>5</sub>, 0.40 wt% SO<sub>3</sub>, 0.70wt% K<sub>2</sub>O, 1.66 wt% CaO, 0.16wt% TiO<sub>2</sub>, 0.05wt% MnO, 4.57wt% Fe<sub>2</sub>O<sub>3</sub>, 0.03wt% CuO, 0.01wt% ZnO, 0.06 wt% SrO and 0.05wt% ZrO<sub>2</sub>.

### 2.2 Synthesis

**Preparation of organo-clays (Mont-EH-DT):** The montmorillonite clay particles were dispersed via stirring in ultrapure Milli-Q water (resistivity of 18.2 MΩ.cm) for 3 h at a solid-to-liquid ratio of 30 g/L, and left undisturbed for 12 h to separate out any quartz sand and heavy minerals. The remaining stable suspension (non-sedimented portion) was then decanted and the particle concentration was measured by drying and adjusting to 20 g/L before being stored as stock fractionated suspension.

To organically modify the clay particles and generate reacting sites for HCF growth, a cationic surfactant of alkylammonium salt (EHDA-Br) was first used to intercalate the clay particles. While the irreversible binding of the cationic surfactant to the clay interlayers has not been verified in the current study, this likely interaction was previously reported<sup>22</sup>. The intercalated EHDA molecules provided sites to anchor the metal ligand alkyldiamine (DT) through hydrophobic interactions. Without the inclusion of EHDA, DT molecules were unable to bind to the clay particles as evidenced by previous research<sup>23</sup>. Immobilization of DT onto clay particles promotes both the hydrophobic modification of the clay particles and generates binding sites for the chelation of transition metals via a metal-diamine coordination mechanism, see Figure 1a. 0.5 mL of 10 mM EHDA-Br solution was added dropwise to 20 mL of stock fractionated suspension (EH/Mont. ratio: 0.0125 mmol/g) in a 50 mL polypropylene centrifuge tube before agitating at 150 rpm in an orbital shaker for 2 h. The suspension was then centrifuged at 11,000 rpm for 15 min to separate the particles from any excess surfactant in the supernatant and washed a further 3 times in Milli-Q water. The particles were then re-dispersed in a series of 20 mL DT solutions, with concentrations varying from 0.1 mM to 50 mM, details of which are specified in Table 1. The DT solutions were obtained by a series of dilutions from 0.5 M DT, and the solution pH was fixed between 8.5-9.0 to deprotonate both amine groups and minimize the possible

displacement of pre-adsorbed EH, while ensuring that adsorption occurs through hydrophobic anchoring. The particle suspensions were shaken for 12 h before being rinsed in Milli-Q water a further 3 times, following the same procedure as outlined for removing excess DT.

**Preparation of organo-clay-HCF composites (Cu-Ferrocyanide-Mont-EH-DT):** To immobilize the hexacyanoferrate(II), the as-prepared organic-clay particles were re-dispersed in 10 mL Milli-Q water before adding 10 mL 0.5 M  $\text{CuSO}_4$  solution (solid content = 20 g/L). The suspension was shaken for 12 h to allow the metal receiving ligand anchored on the clay to chelate the  $\text{Cu}^{2+}$ . Then the as-obtained copper-chelated clays, of a light blue appearance (Figure 1c), were washed in Milli-Q water for 3 times. Thereafter, the particles were dispersed in 20 mL 0.25 M  $\text{K}_4\text{Fe}(\text{CN})_6$  and shaken for 12 h following the same procedure as outlined for the  $\text{Cu}^{2+}$  anchoring process. The resulting Cu-DT complex is believed to have a slightly distorted octahedral geometry with one of the diamine ligands being labile such that it can be displaced by the cyano group from the ferrocyanide anion<sup>19</sup>. Once associated to the copper, an insoluble copper-ferrocyanide nanoparticle was formed, being immobilized onto the clay matrix via the associated DT chain anchoring. The resultant reddish brown product is denoted as Cu-ferrocyanide-Mont-EH-DT with a shorter abbreviation of Mont-HCF. The modified clay particles were thoroughly washed with Milli-Q water to ensure that the particle suspension was free of dissolved salts. The modified clay particles were then divided into two groups; one fraction was oven dried at  $T = 85^\circ\text{C}$  and crushed into powder for characterization purposes, and a second fraction was re-dispersed in Milli-Q water to a solid concentration of 33.3 g/L, and kept wet for use in subsequent  $\text{Cs}^+$  adsorption experiments.

### 2.3 Particle Characterizations

Powder X-ray diffraction (XRD) patterns were obtained using a Bruker D8 X-ray diffractometer fitted with a LynxEye detector, using a  $\text{Cu K}\alpha$  (1.54 Å) radiation source operating at 40 kV and 40 mA, calibrated against a silica standard. Each sample was scanned over a  $2\theta$  angle range of  $4^\circ$  to  $49.98^\circ$  with a step size of  $0.03299^\circ$  at 2 s per step. Fourier transform infrared (FT-IR) spectra were collected using a Nicolet iS10 FT-IR spectrometer equipped with a deuterated triglycine sulphate (DTGS) KBr detector. A minimum of 36 scans were performed at a resolution  $4\text{ cm}^{-1}$  in the range of  $600\text{ cm}^{-1}$  to  $4,000\text{ cm}^{-1}$ . X-ray photoelectron spectroscopy (XPS) analysis was completed using a Thermo K-Alpha XPS system with a monochromated  $\text{Al K}\alpha$  X-ray source. An electron/ion gun was used to compensate for charge build-up on the sample during measurement. For morphological characterization, the as-prepared composite particles were deposited onto an SEM stub and dried in a desiccator before imaging using a Field Emission Gun Scanning Electron Microscope (FEG-SEM; LEO1530 GEMINI, Carl Zeiss Inc.). Transmission electron microscopy (TEM) measurements were completed using a FEI Tecnai TF20 FEG-TEM operated at 200 kV and fitted with a Gatan Orius SC600A CCD camera. Samples were prepared by depositing one drop of the particle suspension on an amorphous carbon film supported by a copper grid for TEM analysis (Agar Scientific Ltd). Elemental mapping of the modified clay particles

in both the FEG-TEM and FEG-SEM was completed using energy dispersive X-ray spectroscopy (EDX) with an Oxford Instruments 80  $\text{mm}^2$  X-Max SD detector and INCA 350 software. Thermogravimetric analysis (TGA) was performed using  $\sim 20$  mg samples in a Mettler-Toledo TGA-DSC1 instrument, with a heating profile from  $30^\circ\text{C}$  to  $1,000^\circ\text{C}$  using a heating rate of  $10^\circ\text{C}/\text{min}$  under steady  $\text{N}_2$  flow (50 mL/min). The collected data were blank subtracted.

**Contact angle:** The three phase (particle-air-water) contact angle of the pristine and modified clay particles was evaluated by the sessile drop technique (Attension Theta tensiometer, KSV). The clay particles were compressed using a 2-ton load applied over an area of  $13\text{ mm}^2$  to form compressed disc substrates. A  $\sim 10\ \mu\text{L}$  droplet of Milli-Q water was deposited on the surface of the compressed disc and the droplet contact angle was approximated using the Attension Software.

**Particle size:** Particle size was measured using a MasterSizer 2000 (Malvern Instruments Ltd., UK). Before each measurement the suspension was sonicated and then added drop-wise to the stirred measuring cell until the obscuration level was within a range of 5-10 %. The size distribution of each particle sample was repeated 10 times with an average particle size reported.

**Zeta potential:** The particle zeta potential was measured using the acoustic zeta probe analyser (Colloidal Dynamics, USA). The suspension concentration was fixed at 0.16 w/w% and the suspension was stirred at 300 rpm. The measurements were performed under neutral condition in the pH range of 7-8.

### 2.4 Batch adsorption experiments

The composite particles were stored wet at a solids concentration of 33.3 g/L. Wet storage avoided any issues of particle clumping and mitigated the need for high energy re-dispersion in water. All batch adsorption experiments were completed using plastic vials to prevent Si contamination from glassware, and potential  $\text{Cs}^+$  adsorption onto glassware, as previously discussed<sup>24</sup>. 19.4 mL cesium chloride (CsCl) solutions of varying electrolyte concentrations were prepared individually in polypropylene centrifuge tubes. 0.6 mL of the particle suspension was added to the electrolyte solutions and dispersed using mild sonication. The solid content was equal to 1 g/L (i.e. 20 mg solid in 20 mL liquid). The  $\text{Cs}^+$  concentration was varied from 0.05 mM (6.6 ppm  $\text{Cs}^+$ ) to 10 mM (1,329 ppm  $\text{Cs}^+$ ), with concentrations diluted from a stock solution of 100 mM CsCl. Particle suspensions were placed on an orbital shaker and shaken at 200 rpm for 48 h before centrifuging at 11,000 rpm for 15 min. The supernatant was decanted and passed through a  $0.45\ \mu\text{m}$  syringe filter before measuring the  $\text{Cs}^+$  concentration in the supernatant by Atomic Adsorption Spectrophotometry (AAS, Varian 240FS spectrometer). Adsorption wavelengths of 852.1 nm and 455.5 nm were used to cover the range of sample concentrations. Before each measurement, calibrations were performed based on five standards properly diluted from a 1,000 mg/L CsCl standard solution (Sigma-Aldrich).

The amount of caesium adsorbed by the particles,  $q$  (mg/g), was determined using the following equation:

$$q = \frac{(C_0 - C_e)V}{m} \quad (1)$$

where  $C_0$  and  $C_e$  (both in units of ppm) are the initial and equilibrium  $Cs^+$  concentrations, respectively (determined by AAS),  $V$  (L) is the volume of the suspension, and  $m$  (g) is the amount of adsorbent (clay or composite particles).

Adsorption kinetics were studied at a fixed initial  $Cs^+$  concentration ( $C_0$ ) of 1 mM, with the adsorption time varied from 10 min to 48 h. Adsorption experiments were conducted under neutral condition, except for the pH dependent study. The pH dependent  $Cs^+$  adsorption by the organo-clay-HCF composites was evaluated across the pH range 2 to 12, with  $C_0$  equal to 5 mM. The pH was adjusted using 1.0 M HCl and 1.0 M NaOH solutions for acidic and basic conditions, respectively. All other experimental procedures for adsorption testing remained consistent with those previously described (i.e. solid-to-liquid ratio = 1 g/L, shaking at 200 rpm for 48 h), with the equilibrium  $Cs^+$  concentration in the supernatant measured by AAS.  $Cs^+$  selectivity from other coexisting competitive ions was considered by dispersing 0.02 g adsorbent particles (pristine montmorillonite and Mont-HCF(DT0.1)) in 20 mL seawater (untreated;  $Na^+$ : ~12,500 ppm,  $Mg^{2+}$ : ~1,480 ppm,  $K^+$ : ~480 ppm,  $Ca^{2+}$ : ~150 ppm)<sup>16</sup>, and dosing the seawater with 10 ppm  $Cs^+$ . After shaking for 48 h and following the separation procedure previously described, the final  $Cs^+$  concentration in the supernatant was measured by inductively coupled plasma mass spectroscopy (ICP-MS, Perkin Elmer Elan DRCe).

## 2.5 Flotation experiments

$Cs^+$  contaminated ( $C_0 = 5$  mM) composite particles were extensively washed with Milli-Q water (minimum of 3 washes) before being re-dispersed, and the solids concentration adjusted to 2 g/L (stored as stock suspension). In the current study the  $Cs^+$  contaminated organo-clay-HCF particles were washed to remove excess electrolyte prior to flotation. While the washing step is not important in practice (i.e. following particle dispersion in the environment), the washing step was included to minimize the contribution from electrolyte-driven particle aggregation on the flotation performance. Flotation experiments were performed by pouring 100 mL stock suspension into the flotation cell, which is schematically shown in Figure S1 of the Supplementary Information. The flotation cell dimensions were 65 mm column diameter and 97 mm column height, with flotation bubbles generated at the base of the flotation column through a sintered glass plate. Milli-Q water was added to the particle suspension such that the total suspension volume equalled 210 mL (i.e. the initial solids concentration was fixed at 0.95 g/L). The air-suspension interface was ~5 mm below the froth collection outlet. Agitation of the particle suspension was provided by a  $\frac{3}{4}$  inch, 4-blade, 45° pitched impeller rotating at 300 rpm. During pre-treatment of the particle suspension the air flowrate was fixed at 1 sL/min. 20  $\mu$ L methyl isobutyl carbinol (MIBC) was added as the frother (i.e. 80 ppm based on the total mass), and the particle


suspension was mixed for 5 min. The impeller speed was then reduced to 100 rpm and the air flowrate increased to 8 sL/min to begin recovery of the organo-clays by flotation. (With no frother the launder foams were unstable, and recovery of the floated particles was compromised. In the environment addition of a frother may not be necessary due to the natural occurrence of organic species which will promote foam stabilization). The particle-laden foam was recovered via the side-arm of the flotation cell. Flotation experiments proceeded for 10 min and the foam was continuously collected. The collected foams were dried at 90 °C and weighed ( $m_d$  in g). The particle recovery ( $R\%$ ) was calculated using  $R\% = m_d/m_0 \times 100\%$ , where  $m_0$  is the initial particle mass in the suspension. Each flotation experiment was repeated a minimum of three times.

## 3. Results and Discussion

### 3.1 Synthesis and characterization of organo-clay-HCF composite adsorbents

Organo-modification of the clays can be realized via intercalation of various cationic surfactants into the clay, albeit often to the detriment of the cation exchange capacity, which greatly limits the clays adsorption capacity for radionuclides<sup>14</sup>. In the current study, to simultaneously enhance the clay particle hydrophobicity as well as maintain or even improve the particles selective adsorption capacity of  $Cs^+$ , organo-montmorillonite composites containing potassium copper hexacyanoferrate (KCuHCF) nanoparticles were prepared, taking advantage of the copper-alkyldiamine coordination.

The particle synthesis route is a simple *three-step* process, which is schematically illustrated in Figure 1b. i) *Organic modification of the clay particles with the cationic surfactant (EH) and alkyldiamine (DT)*. EH surfactant molecules were intercalated into the montmorillonite (as confirmed by TGA analysis, shown in Figure S2 of the Supporting Information), with the metal ligand DT anchored to the EH through hydrophobic interaction<sup>23</sup> to form an organo-clay of Mont-EH-DT. As is known, alkyldiamine chelates to a wide assortment of transition metal cations<sup>19</sup>, making the ligand a useful chelating agent to build different metal-ferrocyanides. Copper-ferrocyanide was chosen in the current study because of its high  $Cs^+$  recovery<sup>15</sup>. ii) *Copper chelation with the montmorillonite particles*. The anchored DT acts as a chelator to immobilize copper, forming a Cu-DT complex, known for irreversibly associating with ferrocyanide anions<sup>19</sup>. iii) *HCF immobilization*. The added hexacyanoferrate precursors coordinate with the copper ions at the amine (DT) sites, leading to efficient and selective *in-situ* growth of KCuHCF nanoparticles. By varying the DT concentration, both the hydrophobicity and the HCF concentration on the modified clays can be well-controlled, delivering high  $Cs^+$  adsorption capacity and good flotation performance. In the current study, the initial DT concentration was varied between 0.1 mM and 50 mM, including 0.8 mM and 8 mM, with the samples denoted as Mont-HCF(DT0.1), Mont-HCF(DT0.8), Mont-HCF(DT8) and Mont-HCF(DT50), respectively.

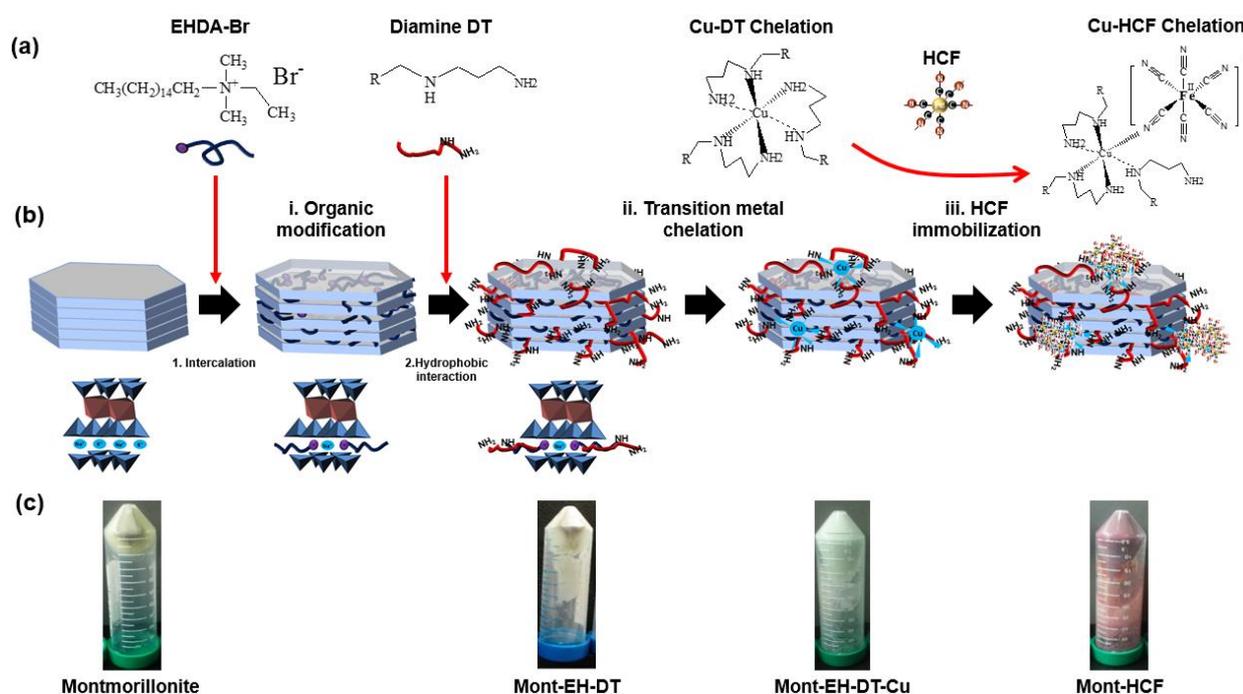

**Figure 1.** a) Structures of surfactant EHDA-Br, Diamine DT, along with its chelation of copper, and the association with (HCF). b) Schematic representation of the three stage preparation procedure to form-organo-clay-HCF composite adsorbent material: i) organic modification including EH intercalation and hydrophobic interaction; ii) chelation and iii) immobilization. c) Representative photos of wet samples at each stage of the preparation procedure. From left to right: Montmorillonite, Mont-EH-DT, Mont-EH-DT-Cu and Mont-EH-DT-KCuHCF (i.e. Mont-HCF).

Powder X-Ray diffraction (XRD) patterns of the Mont-HCF composites are shown in Figure 2 and compared to pristine montmorillonite and KCuHCF as references. The pristine montmorillonite has a basal plane spacing ( $d_{001}$ ) of 1.22 nm, which is in good agreement with previously reported data<sup>25</sup>. The d-spacing of the Mont-HCF composites expanded with increasing organic content to 1.27 nm and 1.34 nm for Mont-HCF(DT0.8) and Mont-HCF(DT8), respectively. The interlayer expansion suggests that the surfactant EH and ligand DT molecules are intercalated in the montmorillonite particles. The XRD patterns of the organo-clay-HCF composites, Mont-HCF(DT0.8) and Mont-HCF(DT8), have the characteristic diffraction peaks of montmorillonite, located at  $2\theta$  of  $19.9^\circ$  (111),  $26.7^\circ$  (103),  $35.1^\circ$  (211) (JCPDS card No. 60-0315), and additional peaks at  $2\theta$  values of  $17.9^\circ$ ,  $25.3^\circ$  and  $36.1^\circ$ , which can be assigned to the (200), (220) and (400) planes of the cubic crystal structure of KCuHCF (with a cell constant of 9.99 Å; JCPDS card No. 02-0383). Thus, the XRD data confirms the presence of KCuHCF on the clay matrix. Moreover, the average crystallite size of the KCuHCF particles can be approximated using the Scherrer equation:

$$L = \frac{K\lambda}{\beta \cos \theta} \quad (2)$$

where  $K$  is a dimensionless factor for crystal shape, taken to be 0.94<sup>18</sup>,  $\lambda$  is the X-ray wavelength (1.5406 Å for Cu  $K\alpha$ ),  $\theta$  is the diffraction angle at the peak (rad), and  $\beta$  is the full-width at half-maximum height (FWHM, rad). The average crystallite size for the KCuHCF complexes was determined from the major peaks (at  $17.9^\circ$ ,  $25.3^\circ$  and  $36.1^\circ$ ), and using Eq. 2 the crystallite size was found to be 10.5 nm and 15.7 nm for Mont-HCF(DT0.8) and Mont-HCF(DT8), respectively. In the current study XRD was used to qualitatively assess the composition of the novel adsorbent, with quantitative assessment of the particle composition provided by TGA, see Figure S2. The characteristic peaks observed at  $\sim 9^\circ$  and  $\sim 12^\circ$  for Mont-HCF(DT0.8) result from partial textural changes in the clay structure, most likely associated with the dehydration of interlayer cations during sample drying. Such behavior is consistent with the characteristic diffraction patterns of heated (and oriented) montmorillonite samples reported in the ICDD database (e.g. JCPDS card No. 00-007-0304 and 00-060-0321), and more recently

published data confirming a shift of the  $d_{001}$  plane from  $\sim 6^\circ$  to  $\sim 9^\circ$  following heat treatment<sup>26</sup>. These characteristic peaks were not observed for Mont-HCF(DT8) due to greater intercalation of organics, as evidenced by the reduction in the CEC (Table 1 and Figure S3). The relative intensities of the characteristic clay peaks were also affected by the change in clay texture, with stronger  $d_{001}$  and  $d_{111}$  peak intensities for the more exfoliated and therefore textured Mont-HCF(DT8) compared to Mont-HCF(DT0.8). Thus for Mont-HCF(DT0.8) the CuHCF peak intensities appeared more prominent.

FTIR spectra were collected for the initial reactants EH, DT and pristine montmorillonite; intermediate products of Step i) the organo-clay (Mont-EH-DT); and the final product of Step iii) the Mont-HCF composite, and are shown in Figure 3a (from top to bottom). For montmorillonite (Mont.) the strong broad adsorption band with a peak at  $\sim 1000\text{ cm}^{-1}$  corresponds to the Si-O vibration of the tetrahedral silica sheet<sup>27</sup>. In the sample of organo-clay (Mont-EH-DT), the C-H stretching vibration peaks between  $2750\text{ cm}^{-1}$  and  $3000\text{ cm}^{-1}$ , and the  $\text{CH}_2$  bending vibration at  $1470\text{ cm}^{-1}$  are assigned to the methylene moiety<sup>15, 23</sup> of the surfactant EH and the ligand DT, consistent with the reference spectra of EH and DT. In addition, the band in the range of  $1620 - 1640\text{ cm}^{-1}$  is characteristic of the  $-\text{NH}$  bending of the amine groups<sup>10, 15</sup> originating here from DT, therefore confirming the successful preparation of organo-clays (Mont-EH-DT) in Step i. For the Mont-HCF composite (i.e. Mont-EH-DT-KCuHCF), when compared to the intermediate product Mont-EH-DT (Step i), new peaks emerge at  $2073\text{ cm}^{-1}$  and  $2039\text{ cm}^{-1}$  and correspond to two closed CN stretching vibrations<sup>16, 18, 28</sup>, thus indicating the formation of the ferrocyanide (HCF) structure, and verifying the completion of Steps ii and iii. As previously reported, these two peaks have been attributed to the stretching of the CN ligand bridged between  $\text{Cu}^{2+}$  and  $\text{Fe}^{2+}$  in two different modes<sup>18</sup>. The success of Step ii which features the copper-amine chelation is also demonstrated in the subsequent XPS analysis (Figure 3 b-f).

To further validate the success of the multi-step synthesis, XPS measurements on the intermediate product (Step ii) of copper anchored organo-clay (Mont-EH-DT-Cu), and the final composite (Step iii) of Mont-HCF were analysed using the sample Mont-HCF(DT0.8) as shown in Figures 3b-f. Figures 3b and d-f clearly show the presence of N 1s from DT/EH, and Cu 2p peaks in the sample of Mont-EH-DT-Cu. Although only weakly visible in Figure 3b, these peaks are more pronounced in the high-resolution spectra shown in Figures 3d and e. In particular, the peaks centred at  $954\text{ eV}$  and  $933\text{ eV}$  (Figure 3e) were attributed to the Cu  $2p^{1/2}$  and Cu  $2p^{3/2}$  orbitals, respectively<sup>29</sup>. These peaks, together with the characteristic satellite peaks of  $\text{Cu}^{2+}$  at  $962\text{ eV}$  and  $943\text{ eV}$ , confirm the presence of copper ions in the intermediate and final composites. In addition, the XPS spectrum of Mont-HCF (Figure 3b) identifies the peaks of Fe ( $2p$ ) and K ( $2p$ ), which results from the *in-situ* growth of HCF (as confirmed from the reference spectrum of pure KCuHCF shown in Figure 3b). From the C 1s deconvolution spectrum in Figure 3c, two peaks centered at  $283.92\text{ eV}$  and  $285.69\text{ eV}$  were identifiable, which corresponded to the matrix C-C/C-H peaks and a  $\text{C}\equiv\text{N}$  group respectively<sup>28</sup>. In the N 1s spectra, the peak at  $398.71\text{ eV}$  is

characteristic of alkylammonium N, and the peak at  $401.08\text{ eV}$  was assigned to the protonated amino group due to chelation with  $\text{Cu}^{2+}$  ions<sup>30</sup>. These peaks were observed in both the Mont-EH-DT-Cu and the Mont-HCF. When compared to the intermediate of Step ii (Mont-EH-DT-Cu), a new strong peak at  $397.11\text{ eV}$  was observed in the Mont-HCF, signifying the existence of  $\text{N}\equiv\text{C}$  ( $[\text{Fe}(\text{CN})_6]^{4-}$ ) in the composites. The XPS observations were consistent with the FTIR data shown in Figure 3a. Moreover, the amino-copper chelation was confirmed from the Cu  $2p^{3/2}$  spectrum in Figure 3f, where peaks centered around  $932.0\text{ eV}$  were evident (i.e.  $932.46\text{ eV}$  for Mont-EH-DT-Cu and  $931.82\text{ eV}$  for Mont-HCF). This response, which is characteristic of  $\text{Cu}^+$  species ( $\sim 932\text{ eV}$ ), appears as a result of the redox reaction of the chelated  $\text{Cu}^{2+}$  with the amino groups<sup>31</sup>. This peak becomes even more pronounced in the case of Mont-HCF when the ferrocyanide ( $[\text{Fe}(\text{CN})_6]^{4-}$ ) is immobilized with the  $\text{C}\equiv\text{N}$  coordinating to the copper-DT complex.

From the FTIR and XPS analysis we can rationally conclude that Mont-HCF composites were successfully synthesized through the proposed copper-amine chelation mechanism. Depending on the amount of copper anchored by DT and subsequently reacted with an equivalent concentration of HCF precursor, the products of metal ferrocyanides prepared with different DT contents can be non-stoichiometric compounds. The relative atomic Cu/Fe ratios (Table S1 in Supplementary Information) calculated from peak areas of the Cu  $2p$  and Fe  $2p$  peaks in the XPS spectra, were used to propose an 'equivalent' structure for the complex according to the model structure  $\text{K}_{2x}\text{Cu}_{(2-x)}[\text{Fe}(\text{CN})_6]^{32}$ . Such an approach is reasonable since Fe was not found on the surface of pristine montmorillonite (Table S1), and can be considered to be a specific element originating from HCF. The measured compositions of the copper ferrocyanide immobilized on to the montmorillonite surface are presented in Table 1.


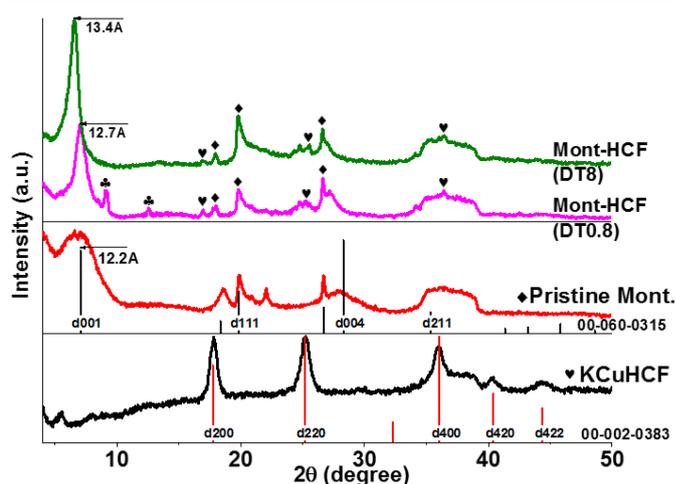


Figure 2. XRD patterns of Mont-HCF composite adsorbents with DT loadings of 0.8 mM and 8 mM. Pristine Mont. (pattern file JCPDS-ICDD 00-060-0315), and bulk KCuHCF nanoparticle (pattern file JCPDS-ICDD 02-0383) shown as reference. ♦ symbol: peaks associated with clay textural changes.

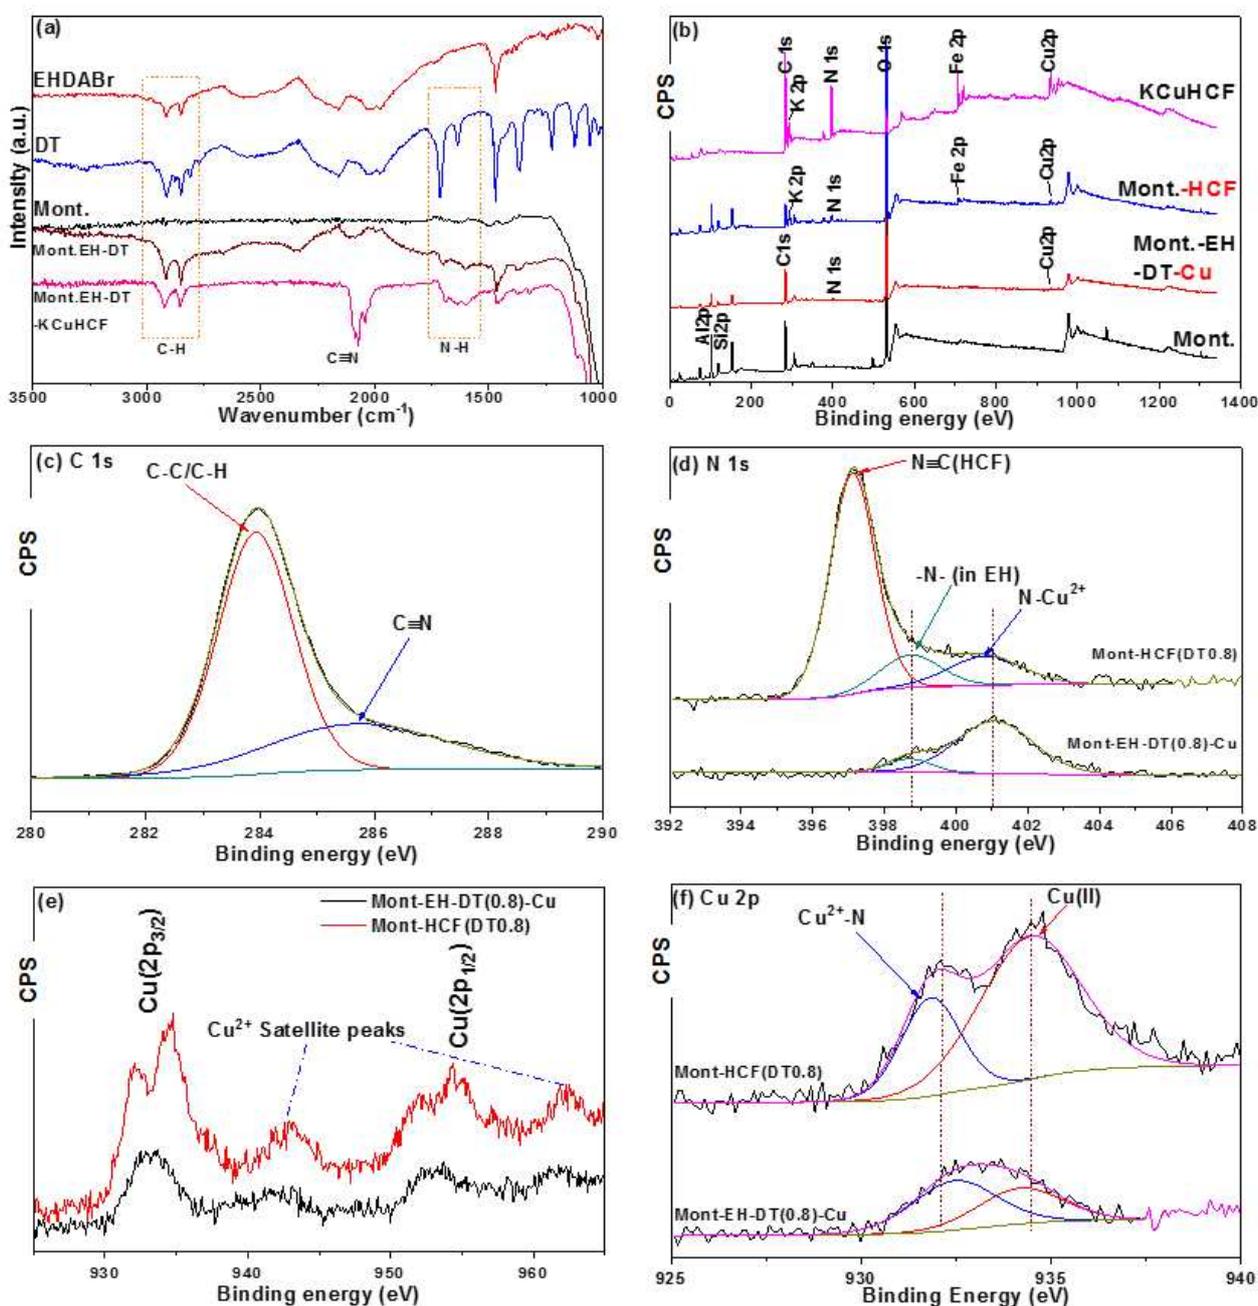

**Figure 3.** a) FTIR spectra of Mont-HCF composite and the intermediate product Mont-EH-DT of Step i, including the individual components Mont., EH, and DT as reference. b) XPS survey spectra (full range) of Mont-HCF composite and the intermediate product Mont-EH-DT-Cu of Step ii, with Mont. and KCuHCF shown as reference. c) High-resolution XPS spectrum on C 1s peak of Mont-HCF(DT0.8). d-f) High-resolution XPS spectra on N 1s and Cu 2p peaks of Mont-EH-(DT0.8)-Cu and Mont-HCF(DT0.8).

Figure 4 shows SEM images of pristine montmorillonite and the as-prepared Mont-HCF composites (DT0.8 and DT8), plus the N to Si atomic ratios of these compounds as determined by EDX

spectroscopy. The “plate-like” structure of pristine montmorillonite is clearly depicted in Figure 4a. For Mont-HCF(DT0.8) (Figure 4b), the silica basal plane becomes decorated with nano-sized particles,

suggesting the presence of the KCuHCF nanoparticles on the montmorillonite surface. For Mont-HCF(DT8) (Figure 4c), the inhomogeneous particle coverage appears to be replaced by a more uniform layer, forming a thin film and somewhat eliminating the sharp edge features of the pristine montmorillonite. The additional EDX data (Figure 4d) shows that N, a characteristic element of DT and HCF, is detected in significant levels for both composite particles but not for the pristine montmorillonite. There is an incremental increase in N with nominal DT content (Figure 4d). Both the SEM and EDX data further confirm the successful synthesis of organo-clay-KCuHCF composites.


The structure of the composite adsorbents was further characterized by TEM. Figures 5a-c and 5d-f show TEM images of Mont-HCF(DT0.8) and Mont-HCF(DT8) particles, respectively. The Mont-HCF(DT0.8) clay particles retain a plate-like structure of nanosheets, with the surface partially covered by nanoparticles (Figure 5a and b); the nanoparticles were identified to be KCuHCF by the crystal lattice spacings (Figure 5b). Moreover, by imaging the lattice fringe at the clay edges (Figure 5c), it was possible to estimate the clay interlayer spacing, which in the current study was measured to be 1.41 nm, consistent with the expansion due to intercalated organics; typical interlayer spacing for pristine montmorillonite was found to be  $\sim 1.0 - 1.2$  nm<sup>14, 25</sup>.

The TEM analysis is qualitatively consistent with the XRD data (Figure 2). As the DT concentration on the clay particles increased, more Cu was anchored and hence more KCuHCF nanoparticles and/or larger KCuHCF particles were formed. This was confirmed by the crystalline structures on the Mont-HCF(DT8), see Figures 5d and 5f. The Si, C, and N mass fractions on the particle surface were measured by XPS (Table S1), and show a general trend of decreasing Si and increasing C and N with increased DT concentration, thus validating the progressive coating of the clay particle surface by HCF nanoparticles. Figure 5e shows a selected area electron diffraction (SAED) pattern taken from the highlighted region (red circle) in Figure 5d. The SAED pattern for Mont-HCF(DT8) shows a strongly scattering clay lattice and weaker spots from the KCuHCF particles. Measurement of the latter leads to the labelled KCuHCF crystal, lattice planes (200) and (400) in Figure 5e (JCPDS-ICDD No. 02-0383). In addition, lattice fringes of interplanar spacing of 0.246 nm were clearly visible in the high magnification TEM image (Figure 5f), which corresponds to the (400) lattice plane of KCuHCF particles (JCPDS-ICDD No. 02-0383).

The organic content of the composite particles was determined by TGA, as shown in Figure S2. The pure organic components completely decomposed as the temperature increased from 200 to 400 °C. For pristine montmorillonite, a small but gradual weight loss is evident at  $\sim 700$  °C, and this can be attributed to the dihydroxylation of the

aluminium-silicate layer and the decomposition of any existing carbonate<sup>33, 34</sup>. For pure KCuHCF, the first significant weight loss occurs in the range of 160 to 350 °C, which can be ascribed to both the elimination of coordinating water, this has been widely reported to exist in Prussian blue (PB)-like molecules ( $< 250$  °C)<sup>15, 28</sup>, and also the decomposition of the cyano group which has been shown to occur in the range of 250 to 350 °C<sup>15, 35</sup>. At higher temperatures it is evident that the intermediate products undergo oxidative decomposition to iron oxides resulting in crystal growth, confirmed by the significant weight loss in the temperature range of 750-800 °C and the corresponding exothermic peak on the DSC curve (Figure S2b)<sup>36, 37</sup>.

For the organo-clays the thermal stability of the intercalated organics and the immobilized HCF was enhanced, as shown by the higher degradation temperatures across the temperature range 200 to 800 °C, with the two main weight losses observed around 400 °C and 600 °C. Considering the difference in mass loss between the intermediate organo-clay Mont-EH-DT and the final Mont-HCF composite product (Figure S2c), the mass fraction of KCuHCF nanoparticles in the composite particle can be estimated and is given in Table 1. Hence, a theoretical ion exchange capacity (TEC) can be calculated based on the potassium content of the immobilized HCF plus the maximum adsorption capacity ( $q_m$ ) of the organo- clay matrix.

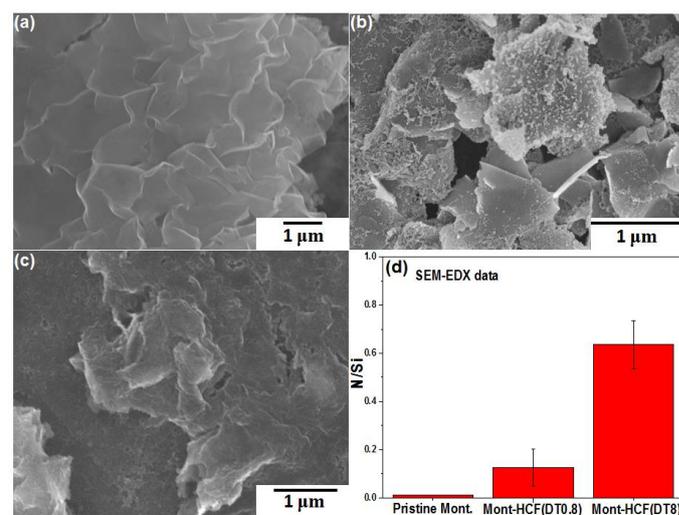

**Figure 4.** SEM images of a) pristine montmorillonite, b) Mont-HCF(DT0.8), c) Mont-HCF(DT8) composites, and d) N/Si ratio determined from SEM-EDX analysis.

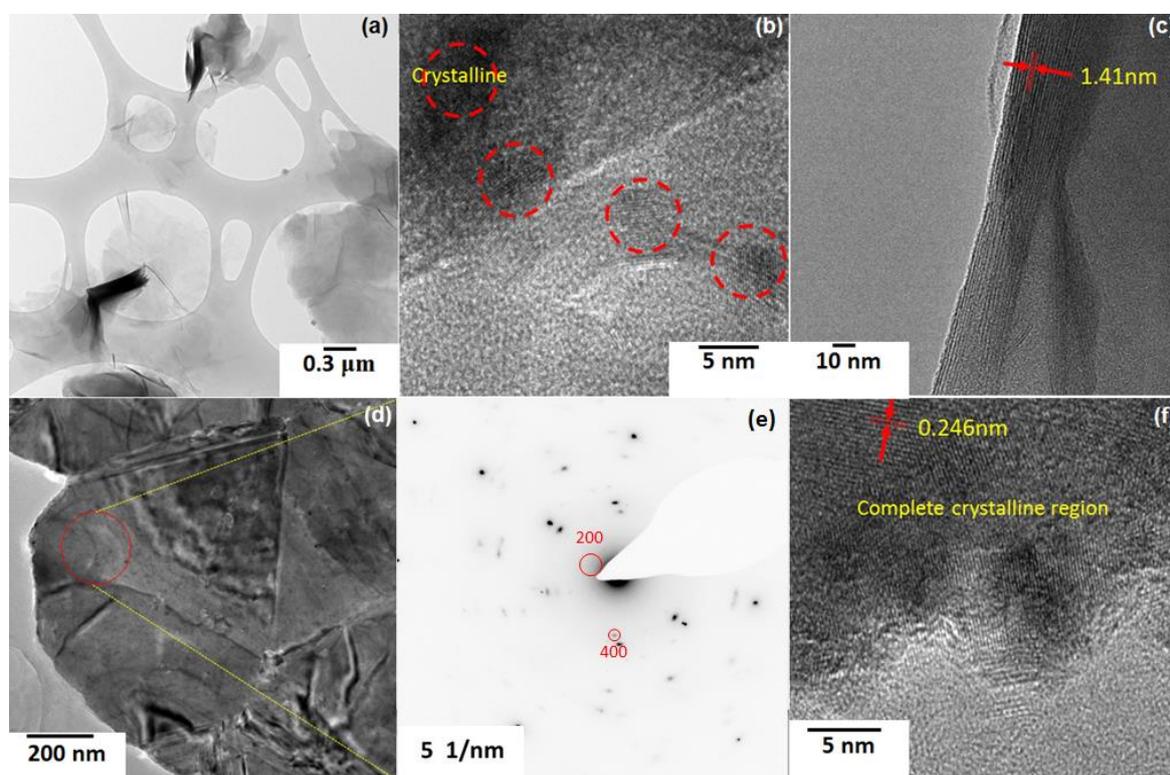


Figure 5. TEM images and electron diffraction pattern of composite adsorbents: a-c) Mont-HCF(DT0.8); d-f) Mont-HCF(DT8).

Table 1. Composition and theoretical adsorption capacity of Mont-HCF composite adsorbents.

Sample Label	Initial DT conc. (mM)	Organic loading <sup>a</sup> (% w/w)	Form of immobilized HCF <sup>b</sup>	HCF content <sup>a</sup> (% w/w)	$q_m$ of organo-clay (mg Cs g <sup>-1</sup> organo-clay) <sup>c</sup>	Theoretical exchange capacity <sup>d</sup> (mg Cs g <sup>-1</sup> composite)
Pristine Mont.	0	0	-	0	103	103
Mont-HCF(DT0.1)	0.1	1.2	K <sub>1.08</sub> Cu <sub>1.46</sub> Fe(CN) <sub>6</sub>	15.4	123	206
Mont-HCF(DT0.8)	0.8	1.8	K <sub>1.76</sub> Cu <sub>1.12</sub> Fe(CN) <sub>6</sub>	16.0	97	188
Mont-HCF(DT8)	8	11.8	K <sub>1.60</sub> Cu <sub>1.24</sub> Fe(CN) <sub>6</sub>	25.4	0	154
Mont-HCF(DT50)	50	40.4	K <sub>1.66</sub> Cu <sub>1.17</sub> Fe(CN) <sub>6</sub>	35.8	0	225

<sup>a</sup> estimated from the TGA data (Figure S2); <sup>b</sup> estimated from XPS analysis; <sup>c</sup> obtained from Langmuir isotherm fitting of the experimental data, see Figure S3; <sup>d</sup> based on K<sup>+</sup> content in the immobilized HCF and the  $q_m$  of organo-clay matrix.

### 3.2 Batch adsorption experiments

**Adsorption isotherm:** To evaluate Cs<sup>+</sup> effluent removal performance by the organo-clay-HCF composites, batch adsorption experiments were performed and the adsorption isotherm, given in terms of mass adsorbate (Cs<sup>+</sup>) to mass adsorbent,  $q$  in mg/g, was determined as a function of the equilibrium Cs<sup>+</sup> concentration ( $C_e$  in ppm) in solution.

As a first approximation, the well-known Langmuir model which assumes surface monolayer sorption, finite number of binding sites, uniform sorption energies, as well as no transmigration of sorbates in the plane of the surface, was employed to describe the adsorption behavior. The Langmuir isotherm is given by:

$$q = \frac{bq_m C_e}{1 + bC_e} \quad (3)$$

where  $b$  is the Langmuir constant related to the affinity coefficient of the binding sites ( $L\text{ mg}^{-1}$ ), and  $q_m$  is the maximum sorption capacity that describes the efficiency of  $\text{Cs}^+$  removal from solution at or near saturation. As shown in Figure 6a, the experimental data are in good agreement with the Langmuir isotherm. For each particle system the Langmuir fitting parameters  $q_m$  and  $b$ , and the correlation coefficients are listed in Table 2. Compared to the relatively low adsorption capacity of the pristine montmorillonite ( $q_m \sim 103\text{ mg/g}$ ), the organo-clay-HCF composites demonstrated a significant enhancement in  $q_m$ , particularly Mont-HCF(DT0.1) with an adsorption capacity of  $206.6\text{ mg/g}$ , twice that measured for the pristine montmorillonite. Such enhancement validates the successful immobilization of HCF onto the supporting montmorillonite particles given that both the clay particle and HCF can provide synergistic contributions for  $\text{Cs}^+$  adsorption. Moreover, while the pristine montmorillonite particles reach an adsorption plateau at  $C_e > 1,000\text{ ppm}$ , the adsorption of  $\text{Cs}^+$  by the organo-clay-HCF composites plateaus at a much lower concentration ( $C_e \sim 100\text{ ppm}$  to  $500\text{ ppm}$ ), thus demonstrating the higher affinity to adsorb  $\text{Cs}^+$ . This behavior is consistent with the  $b$  values reported in Table 2.

It is worth noting that the apparent poor performance of the Mont-HCF composites with higher DT contents (i.e. DT8, DT50), as shown in Figure 6b, resulted from a reduction in the adsorption capacity (CEC) of the clay matrix, brought about by the increased intercalation of DT. The reduced CEC with high DT concentration (i.e. DT8, DT50) was confirmed by measuring the  $\text{Cs}^+$  adsorption capacity of the organo-clay intermediates prior to HCF anchoring, which gave negligible values ( $q_m \sim 0\text{ mg/g}$ ) as shown in the Supplementary Information Figure S3. For the Mont-HCF composite adsorbents, a theoretical ion-exchange capacity (TEC) can be calculated based on the potassium content of the immobilized HCF and the  $q_m$  of the organo-clay matrix.


Since both parameters (HCF content,  $q_m$  of organo-clay matrix) vary for each composite, the TEC was calculated between 154 and 225

$\text{mg/g}$  for increasing DT concentration (see Table 1). As shown in Figure 6b, the TEC is in reasonable agreement with the experimentally determined maximum adsorption capacities ( $q_m$ ). The fluctuating performance of the organo-clay-HCF composites (i.e. maximum  $q_m$  at  $\text{DT} = 0.1\text{ mM}$  and minimum  $q_m$  at  $\text{DT} 0.8\text{ mM}$ ) can be attributed to the relative ion exchange capacities of both media (organo-clay and HCF content). At low DT concentrations ( $\text{DT} \leq 0.8\text{ mM}$ ) both the clay and bound HCF particles are active ion exchange sites, but with increasing DT concentration the organo-clay ion exchange capacity decreases (Table 1) and the HCF ion exchange capacity increases (directly related to the HCF content). Hence, the overall ion exchange capacity is a function of the relative contributions from both ion exchange sites. At higher DT concentrations the ion-exchange capacity of the organo-clay is effectively zero (Figure S3), hence  $q_m$  becomes a function of the HCF content only.

Such dependence has been validated by EDX mapping of the composite particles (see Supplementary Information Figure S5), where both the Cs and Fe peak intensities were higher for Mont-HCF(DT50) compared to Mont-HCF(DT8), confirming higher  $\text{Cs}^+$  adsorption when the HCF concentration was higher. Likewise from XPS analysis, the higher Cs/Si ratio (Figure S4) for Mont-HCF(DT50) than Mont-HCF(DT8) and Mont-HCF(DT0.8) further supports this conclusion. Based on the TEC data we should observe a 25% increase in  $q_m$  between Mont-HCF(DT0.1) and Mont-HCF(DT50). While this enhancement demonstrates the added capacity through incorporation of more HCF, the practicality of using Mont-HCF(DT50) particles is limited by the presence of many unbound HCF nanoparticles which results from HCF saturation of the clay matrix. Any unbound HCF particles remaining in the suspension (even though the particle suspension was washed several times), will result in an overestimation of  $\text{Cs}^+$  in the supernatant as measured by AAS (equivalent to an underestimation of  $\text{Cs}^+$  adsorption), thus contributing to the deviation between theory and experiment for Mont-HCF(DT50) particles. Such difficulties associated with the removal of unbound HCF particles has been reported<sup>15</sup>.

**Table 2.**  $\text{Cs}^+$  adsorption parameters obtained from Langmuir isotherm fittings.

Sample	Langmuir			Dual-site Langmuir				
	$q_m$ mg/g	$b$ L/mg	$R^2$	$q_{m1}$ mg/g	$b_1$ L/mg	$q_{m2}$ mg/g	$b_2$ L/mg	$R^2$
Pristine Mont.	103.00	0.005	0.91					
Mont-HCF(DT0.1)	206.64	0.188	0.94	70.02	0.019	144.09	0.019	0.95
Mont-HCF(DT0.8)	173.05	0.109	0.91	60.79	0.003	131.68	0.027	0.98
Mont-HCF(DT8)	139.29	0.020	0.93					
Mont-HCF(DT50)	153.09	0.030	0.90					

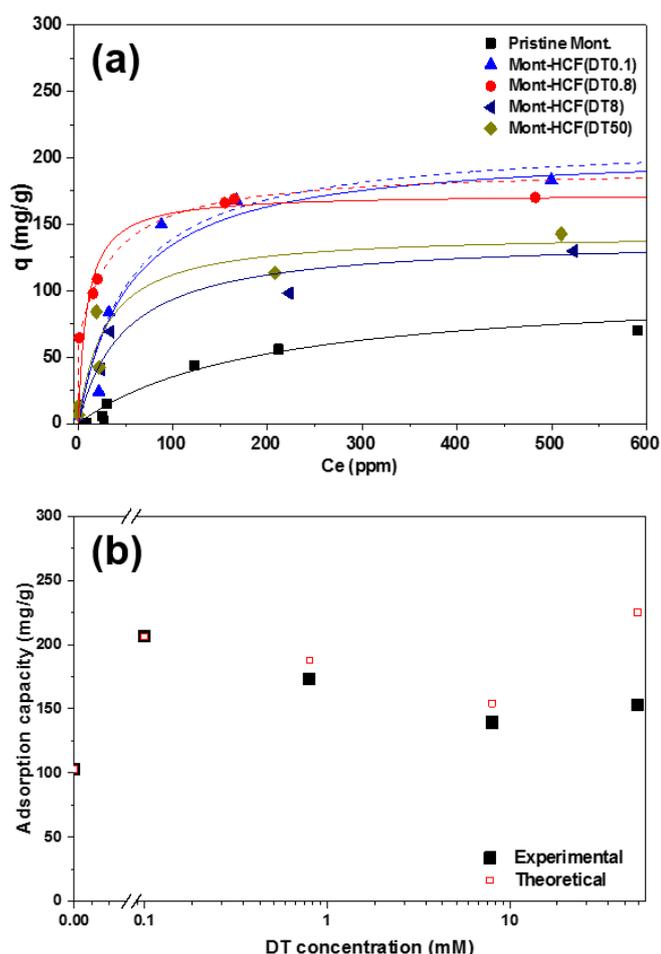

**Figure 6.** a) Cs<sup>+</sup> adsorption isotherm as a function of the equilibrium concentration ( $C_e$ ) for Mont-HCF composites and pristine montmorillonite. Solid and dashed lines represent fittings by the Langmuir model (solid) and Dual-site Langmuir model (dashed). b) Comparison between the experimental and theoretical maximum adsorption capacities,  $q_m$ , for Mont-HCF composite particles as a function of DT concentration.

In light of the fact that the Mont-HCF composites with DT0.1 and DT0.8 contain two possible active sites for ion sorption, the montmorillonite particle and the immobilized HCF, the dual-site Langmuir adsorption model was also considered, and describes sorption at two sites of different sorption energies. The dual-site Langmuir equation is given by:


$$q = \frac{b_1 q_{m1} C_e}{1 + b_1 C_e} + \frac{b_2 q_{m2} C_e}{1 + b_2 C_e} \quad (4)$$

where the fitting parameters  $b_1$ ,  $b_2$  and  $q_{m1}$ ,  $q_{m2}$  represent the affinity coefficients (L mg<sup>-1</sup>) and the maximum sorption capacity (mg g<sup>-1</sup>) for


the two types of sorption sites, respectively. As shown in Figure 6a, the dual-site Langmuir model (dashed line) describes the adsorption isotherm very well with the fitting parameters reported in Table 2. Such good agreement with distinct constants likely confirms that two binding sites, immobilized HCF and clay matrix, contribute to the adsorption of Cs<sup>+</sup>.

XPS spectra of the organo-clay-HCF composite particles saturated with Cs<sup>+</sup> ( $C_0 = 5$  mM) confirmed the significant displacement of K<sup>+</sup> by Cs<sup>+</sup>, see Figure S4. Following Cs<sup>+</sup> adsorption the XRD data shown in Figure 7 confirmed a reduction in the KCuHCF(200) peak height at 17.9° and a shift of the (220) and (400) planes to lower  $2\theta$  around 24.8° and 34.3°, confirming an effective crystal phase transition from KCuHCF to CsCuHCF (JCPDS card No. 24-0248). The XRD data suggest that the immobilized KCuHCF complex greatly contributes to Cs<sup>+</sup> adsorption via an ion-exchange mechanism, with these findings supported by the XPS data. In addition, a decrease in the clay (Mont-HCF(DT0.8)) d-spacing ( $d_{001}$ ) from 1.27 nm to 1.22 nm implies that Cs<sup>+</sup> adsorption also occurred via isomorphic ion-substitution, leading to a slight reduction in the clay interlayer spacing, mainly due to the unfavourable hydration of the Cs<sup>+</sup> existing in the interlayer<sup>38</sup>.

When compared to other clay-based adsorbents and KCuHCF adsorbents immobilized onto a range of different supporting materials, the Mont-HCF composites prepared in the current study are shown to be some of the most effective Cs<sup>+</sup> adsorbents in terms of  $q_m$ . Adsorption capacity data from a number of studies has been compared to Mont-HCF(DT0.1) and are shown in Table 3.

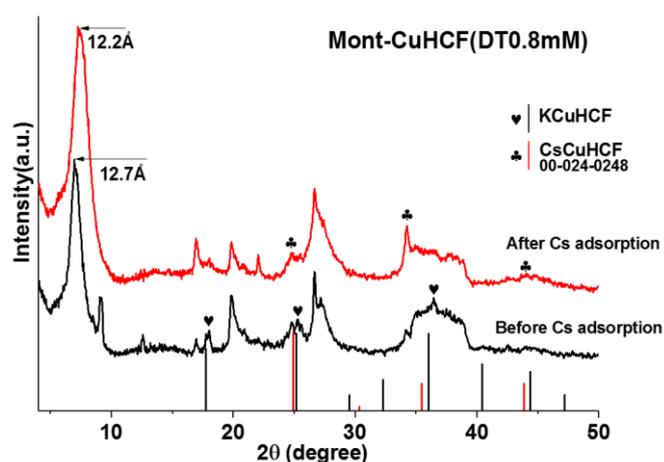

**Figure 7.** XRD patterns of Mont-HCF(DT0.8) before and after Cs<sup>+</sup> adsorption (pattern file 00-024-0248 for CsCuHCF).

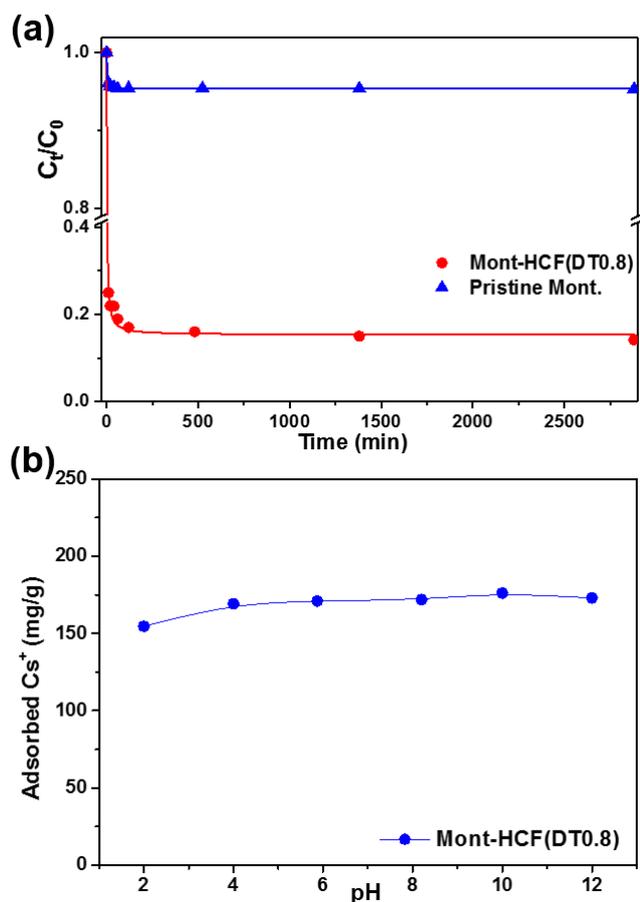

**Figure 8.** a)  $\text{Cs}^+$  uptake kinetics for organo-clay-HCF composites, and pristine montmorillonite ( $C_0 = 1 \text{ mM}$ ). b)  $\text{Cs}^+$  adsorption as a function of the solution pH ( $C_0 = 5 \text{ mM}$ ).

**Adsorption kinetics:**  $\text{Cs}^+$  adsorption kinetics have been considered to compare the performance of Mont-HCF(DT0.8) to that of pristine montmorillonite (Figure 8a). As shown,  $\text{Cs}^+$  adsorption by the pristine montmorillonite and the composite particle is reasonably fast, reaching equilibrium within a few hours. To quantitatively describe the adsorption kinetics the experimental data was fitted using a Pseudo-second order rate equation (PSORE):

$$\frac{t}{Q_t} = \frac{1}{k_2 Q_e^2} + \frac{t}{Q_e} \quad (5)$$

where  $Q_t$  is the adsorbed  $\text{Cs}^+$  quantity (mg/g) at time  $t$ ,  $Q_e$  is the adsorbed  $\text{Cs}^+$  quantity (mg/g) at equilibrium and  $k_2$  is a rate constant. For both particles, Mont-HCF(DT0.8) and pristine montmorillonite, the PSORE fits are very good with an  $R^2$  coefficient  $> 0.99$ , and the obtained fitting parameters reported in Table 4. Although the rate constant,  $k_2$ , for the composite adsorbent is lower than that for the pristine montmorillonite, the  $\text{Cs}^+$  uptake of the composite particle exceeds 80% within 30 min, compared to less than 5% for pristine montmorillonite under the same experimental conditions ( $C_0 = 1 \text{ mM}$ ). The  $k_2 \times 10^2$  for the composite adsorbent equals  $0.695 \text{ g mg}^{-1} \text{ min}^{-1}$  which is in good agreement with the previously published value of  $0.65 \text{ g mg}^{-1} \text{ min}^{-1}$  for KCuHCF immobilized on chitin beads<sup>15</sup>.

**pH effect:** The stability and  $\text{Cs}^+$  adsorption performance of the composite adsorbent was investigated as a function of pH (Figure 8b). In the pH range 4 to 12 ( $C_0 = 5 \text{ mM}$ ) the adsorption performance of the Mont-HCF(DT0.8) remained consistent, with the adsorption capacity,  $q_m$ , in the range of 169 to 176 mg/g. A small reduction in performance was observed in strongly acidic conditions (pH 2,  $q_m = 155 \text{ mg/g}$ ), which most likely resulted from the effect of competition between  $\text{H}^+$  and  $\text{Cs}^+$  ions. As reported elsewhere<sup>28</sup>, there is also a possibility that the Prussian-blue (PB) structure slightly denatures in strongly acidic conditions.

**Table 3.**  $\text{Cs}^+$  adsorption capacities using modified montmorillonite particles, and metal hexacyanoferrate immobilized on different supports.

Clay/Co-metal in HCF	Modifier/Support	$q_m^a$ (mg Cs/g composite)	Reference/ Publication year
Clay			
Montmorillonite	Pristine	57-104 <sup>b</sup>	10-12, 38/ 2013, 2011, 2002, 2009
Montmorillonite	Aluminum-pillared	83	39/2007
Montmorillonite	Phosphate	94	11/2011
Montmorillonite	Ethylamine	80	10/2013
Montmorillonite	Manganese oxide	90	40/2012
Montmorillonite	CuHCF(DT0.1)	206	Current study
Co-Metal in HCF			
Cu	Activated carbon	6	41/2009
Cu	Polyacrylonitrile (PAN)	26	42/2011
Cu	Chitin	118	15/2014
Cu	Mesoporous Silica	177	19/2001
Cu	Montmorillonite (DT0.1)	206	Current study

<sup>a</sup> maximum adsorption capacity determined from Langmuir model; <sup>b</sup> the relatively wide range depends on the CEC of the specific type of montmorillonite.

**Table 4.** Kinetic parameters of Cs<sup>+</sup> adsorption determined by a fit of the Pseudo-second order rate equation, Eq. 5.

Sample	k <sub>2</sub> (g mg <sup>-1</sup> min <sup>-1</sup> )	Q <sub>e</sub> (mg g <sup>-1</sup> )	R <sup>2</sup>
Pristine Mont.	0.09816	5.31	0.99
Mont-HCF(DT0.8)	0.00695	92.72	0.99

**Competitive ion effect:** The performance of the composite adsorbent was studied in more realistic aqueous environments, with the selectivity for Cs<sup>+</sup> in complex cationic solutions (seawater) determined by dosing the seawater with 10 ppm Cs<sup>+</sup>. The distribution coefficient  $K_d$  is given by:

$$K_d = \frac{(C_0 - C_e) V}{C_e m} \quad (6)$$

where  $C_0$  and  $C_e$  are the initial and equilibrium concentrations of Cs<sup>+</sup>,  $V$  is the volume (mL) of the solution, and  $m$  is the mass (g) of the sorbent. Using Eq. 6, pristine montmorillonite exhibited a relatively low Cs<sup>+</sup> selectivity,  $K_d = 1.81 \times 10^3$  mL/g, whereas Mont-HCF(DT0.1) resulted in very high Cs<sup>+</sup> selectivity,  $K_d = 1.10 \times 10^5$  mL/g. Such data confirmed that even in complex ionic environments composed of many competing cations, the composite adsorbent performs well in regards to Cs<sup>+</sup> adsorption, unlike pristine montmorillonite, which has previously been reported to perform poorly in competing cationic environments<sup>36, 41</sup>. The significant enhancement in  $K_d$  for Mont-HCF(DT0.1) compared to pristine montmorillonite relates to the high Cs<sup>+</sup> selectivity of the HCF cubic structure. The cubic lattice of HCF acts as an ion sieve and preferential ion exchange with the lattice ions (i.e. pre-existing K<sup>+</sup>) is governed by the size of the hydrated ion (Mg<sup>2+</sup> (0.428 nm) > Na<sup>+</sup> (0.358 nm) > K<sup>+</sup> (0.331 nm) > Cs<sup>+</sup> (0.329 nm))<sup>43</sup>. The smaller hydrated ions such as Cs<sup>+</sup> can easily permeate into the lattice whereas larger hydrated ions such as Na<sup>+</sup> become size-excluded from the sorption sites<sup>28</sup>. Hence, HCF has high selectivity for Cs<sup>+</sup>.


Moreover, the effect of DT content on the Cs<sup>+</sup> selectivity has been examined and was shown to be insignificant (data not shown), with  $K_d$  values within 2% over the DT concentration range studied.

### 3.3 Flotation selectivity

One of the objectives of this study was to synthesize organo-clays that exhibit high Cs<sup>+</sup> removal performance and can be easily recovered from the aqueous environment by flotation. Flotation performance of the Cs-loaded particles was studied using a laboratory flotation cell, as shown in Figure S1 of the Supplementary

Information. The particle (mass) recovery percentage (R%) and the particle contact angle are shown in Figure 9.

The flotation experiments were completed in the absence of any collector, i.e. collector-less flotation. As shown in Figure 9, the recovery performance of the Cs-loaded montmorillonite was very poor, less than 15%, in comparison to the Cs-loaded Mont-HCF composite (Mont-HCF(0.1)), which has a recovery efficiency in the range of 80-90%. This significant difference can be attributed to an increase in the particle hydrophobicity induced via the interlayer intercalation and surface decoration of the clay particles by the organic components of EH and DT. This is also consistent with the measured contact angle data (Figure 9) and the slight reduction in the particle zeta potential when the DT content increases (Table 5). These modifications to the particle surface properties promote slight aggregation of the composite particles and a broadening of the particle size distribution which may also contribute to the enhanced flotation performance, see Figure S6 in the Supplementary Information.

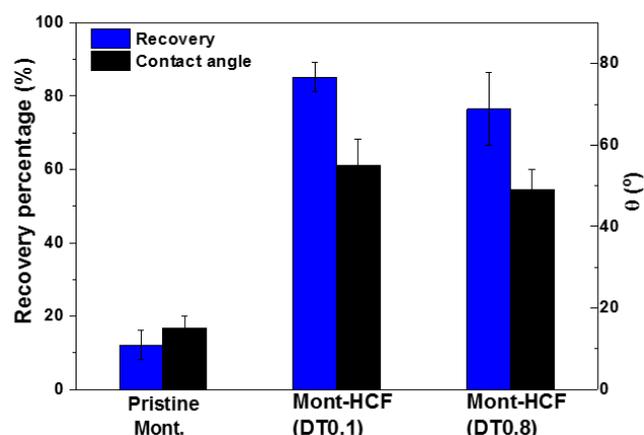

**Figure 9.** Flotation recovery percentages of Cs-loaded particles ( $C_0 = 5$  mM). The associated particle contact angles approximated by the sessile drop technique are shown on the second y-axis.

**Table 5.** Zeta potential and particle size of the composite and pristine montmorillonite particles.

Adsorbents	Zeta potential (mV) <sup>a</sup>	Particle size (μm)
Montmorillonite	-34.8±3.1	3.3
Mont-HCF (DT0.1 mM)	-24.7±8.9	2.9/22.9 <sup>b</sup>
Mont-HCF (DT0.8 mM)	-24.6±1.9	2.9/13.2 <sup>b</sup>

<sup>a</sup> measurements were performed using Cs-loaded particles ( $C_0 = 5$  mM); <sup>b</sup> refers to the bimodal particle distribution.

Together with the  $q_m$  data presented in Figure 6 it is reasonable to conclude that the as-prepared Mont-HCF based composite particles demonstrate both high Cs<sup>+</sup> uptake and selectivity, along with excellent recovery by collector-less flotation. Such a novel approach provides a cost-effective route to treat large volumes of aqueous wastes, reducing the environmental contamination, and minimizing the volume of waste for further treatment and ultimate disposal.

#### 4. Conclusions

A low cost and facile synthesis route has been demonstrated for organo-clay-HCF composites. The particle synthesis route included i) organic modification of montmorillonite with cationic surfactant (EH) and alkyldiamine (DT), ii) copper chelation with the anchored DT, and iii) growth of Cu<sup>2+</sup>/[Fe(CN)<sub>6</sub>]<sup>4-</sup>/2•K<sup>+</sup> nanoparticles (KCuHCF) via the coordination between hexacyanoferrate precursors and the immobilized copper ions. XRD analysis confirmed the expansion of the clay interlayer due to adsorption of organics, along with identifying the crystal structure of KCuHCF nanoparticles. FTIR analysis confirmed the formation of CN bonds in the composite adsorbents implying the successful immobilization of HCF on the clay, which was further supported by EDX and XPS analysis. XPS also demonstrated that the KCuHCF immobilization was realized via a copper-amine coordination mechanism. SEM and TEM confirmed the decoration of the clay particles with sub 15 nm KCuHCF particles.

The DT concentration was varied between 0.1 mM and 50 mM, with increasing DT concentration resulting in the formation of more KCuHCF nanoparticles. However, at DT concentrations greater than 0.8 mM, a significant excess of KCuHCF nanoparticles were produced that were not well attached to the clay particles. These unbound particles were mostly unrecoverable following a series of sample washes, leading to apparent errors in the Cs<sup>+</sup> adsorption experiments when measured by Atomic Adsorption Spectrophotometry. Such production of unbound KCuHCF nanoparticles prohibited the use of Mont-HCF(DT8) and Mont-HCF-(DT50) composite adsorbents. For Mont-HCF(DT0.1) the Cs<sup>+</sup> adsorption capacity ( $q_m$ ) was shown to be 206 mg/g, which was double the  $q_m$  for pristine montmorillonite particles. The excellent Cs<sup>+</sup> adsorption performance of the Mont-HCF composite was demonstrated over a wide pH range, as well as in seawater where the adsorption selectivity for Cs<sup>+</sup> in a complex solution of competing cations was shown to be superior compared to pristine montmorillonite, validating the robustness of the composite adsorbent.

The novel synthesis route not only enhanced the Cs<sup>+</sup> adsorption capacity of montmorillonite, but also increased the particle hydrophobicity. This effect allowed the Cs-loaded composite particles to be easily recovered by flotation, without the need for addition of flotation collectors. For the composite adsorbent, recovery efficiency was in the range of 80 to 90 %, compared to less than 15 % for Cs-loaded pristine montmorillonite.

The current study has demonstrated a new concept for Cs<sup>+</sup> removal from aqueous environments. Rather than filtration through packed-bed columns, where blockages and chemical incompatibility can hinder performance, the novel approach to clean-up relies on the

recovery of Cs-loaded clay particles by flotation, a technique that is suitable for remote deployment on any scale, facilitating the decontamination of environments, and minimizing the volume of waste for ultimate disposal.

#### Acknowledgements

This work was financially supported by Engineering and Physical Sciences Research Council (EPSRC) (grant number EP/M026426/1) and the National Research Foundation of Korea (NRF) (grant number NRF-2015M2A7A1000219). X-ray Photoelectron Spectroscopy was conducted at the National EPSRC XPS User's Service (NEXUS) at Newcastle University, an EPSRC mid-range facility.

#### Notes and References

1. D. H. Ding, Z. Y. Zhang, Z. F. Lei, Y. N. Yang and T. M. Cai, *Environ Sci Pollut R*, 2016, **23**, 2249-2263.
2. J. L. Mertz, Z. H. Fard, C. D. Malliakas, M. J. Manos and M. G. Kanatzidis, *Chem Mater*, 2013, **25**, 2116-2127.
3. M. A. Olatunji, M. U. Khandaker, H. N. M. E. Mahmud and Y. M. Amin, *Rsc Adv*, 2015, **5**, 71658-71683.
4. S. Komarneni and R. Roy, *Science*, 1988, **239**, 1286-1288.
5. A. J. Celestian, J. D. Kubicki, J. Hanson, A. Clearfield and J. B. Parise, *J Am Chem Soc*, 2008, **130**, 11689-11694.
6. H. M. Liu, A. Yonezawa, K. Kumagai, M. Sano and T. Miyake, *J Mater Chem A*, 2015, **3**, 1562-1568.
7. S. J. Datta, W. K. Moon, D. Y. Choi, I. C. Hwang and K. B. Yoon, *Angew Chem Int Edit*, 2014, **53**, 7203-7208.
8. N. Ding and M. G. Kanatzidis, *Nat Chem*, 2010, **2**, 187-191.
9. X. H. Qi, K. Z. Du, M. L. Feng, J. R. Li, C. F. Du, B. Zhang and X. Y. Huang, *J Mater Chem A*, 2015, **3**, 5665-5673.
10. H. Long, P. X. Wu and N. W. Zhu, *Chem Eng J*, 2013, **225**, 237-244.
11. B. Ma, S. Oh, W. S. Shin and S. J. Choi, *Desalination*, 2011, **276**, 336-346.
12. B. C. Bostick, M. A. Vairavamurthy, K. G. Karthikeyan and J. Chorover, *Environ Sci Technol*, 2002, **36**, 2670-2676.
13. J. Q. Jiang and Z. Q. Zeng, *Chemosphere*, 2003, **53**, 53-62.
14. T. H. Wang, C. J. Hsieh, S. M. Lin, D. C. Wu, M. H. Li and S. P. Teng, *Environ Sci Technol*, 2010, **44**, 5142-5147.
15. T. Vincent, C. Vincent, Y. Barre, Y. Guari, G. Le Saout and E. Guibal, *J Mater Chem A*, 2014, **2**, 10007-10021.
16. Y. Kim, Y. K. Kim, S. Kim, D. Harbottle and J. W. Lee, *Chem Eng J*, 2017, **313**, 1042-1050.
17. C. Loos-Neskovic, S. Ayrault, V. Badillo, B. Jimenez, E. Garnier, M. Fedoroff, D. J. Jones and B. Merinov, *J Solid State Chem*, 2004, **177**, 1817-1828.
18. R. Turgis, G. Arrachart, C. Delchet, C. Rey, Y. Barre, S. Pellet-Rostaing, Y. Guari, J. Larionova and A. Grandjean, *Chem Mater*, 2013, **25**, 4447-4453.
19. Y. H. Lin, G. E. Fryxell, H. Wu and M. Engelhard, *Environ Sci Technol*, 2001, **35**, 3962-3966.
20. V. V. Strelko, V. K. Mardanenko, V. V. Yatsenko and N. Patrilyak, *Russ J Appl Chem+*, 1998, **71**, 1746-1749.
21. M. Honty, M. De Craen, L. Wang, J. Madejova, A. Czimerova, M. Pentrak, I. Stricek and M. Van Geet, *Appl Geochem*, 2010, **25**, 825-840.
22. D. G. Devivo and B. L. Karger, *Separ Sci*, 1970, **5**, 145-&.

23. P. Malakul, K. R. Srinivasan and H. Y. Wang, *Ind Eng Chem Res*, 1998, **37**, 4296-4301.
24. J. Chorover, S. K. Choi, M. K. Amistadi, K. G. Karthikeyan, G. Crosson and K. T. Mueller, *Environ Sci Technol*, 2003, **37**, 2200-2208.
25. C. W. Chiu and J. J. Lin, *Prog Polym Sci*, 2012, **37**, 406-444.
26. M. S. Cavalcante, S. P. A. Paz, R. S. Angelica, E. N. Ito and R. F. Neves, *Clay Miner*, 2016, **51**, 39-54.
27. J. Madejova, *Vib Spectrosc*, 2003, **31**, 1-10.
28. H. J. Yang, L. Sun, J. L. Zhai, H. Y. Li, Y. Zhao and H. W. Yu, *J Mater Chem A*, 2014, **2**, 326-332.
29. Z. Y. Liu, Y. X. Hu, C. F. Liu and Z. Y. Zhou, *Chem Commun*, 2016, **52**, 12245-12248.
30. M. E. A. Ali, F. M. Hassan and X. S. Feng, *J Mater Chem A*, 2016, **4**, 6620-6629.
31. L. Y. Chai, T. Wang, L. Y. Zhang, H. Y. Wang, W. C. Yang, S. Dai, Y. Meng and X. R. Li, *Carbon*, 2015, **81**, 748-757.
32. C. Loosneskovic, M. Fedoroff, E. Garnier and P. Gravereau, *Talanta*, 1984, **31**, 1133-1147.
33. L. Cabedo, D. Plackett, E. Gimenez and J. M. Lagaron, *J Appl Polym Sci*, 2009, **112**, 3669-3676.
34. D. Eliche-Quesada, C. Martinez-Garcia, M. L. Martinez-Cartas, M. T. Cotes-Palomino, L. Perez-Villarejo, N. Cruz-Perez and F. A. Corpas-Iglesias, *Appl Clay Sci*, 2011, **52**, 270-276.
35. J. H. Her, P. W. Stephens, C. M. Kareis, J. G. Moore, K. S. Min, J. W. Park, G. Bali, B. S. Kennon and J. S. Miller, *Inorg Chem*, 2010, **49**, 1524-1534.
36. Z. F. Jiang, D. L. Jiang, A. M. S. Hossain, K. Qian and J. M. Xie, *Phys Chem Chem Phys*, 2015, **17**, 2550-2559.
37. Q. F. Wu, G. L. Wu, L. D. Wang, W. L. Hu and H. J. Wu, *Mat Sci Semicon Proc*, 2015, **30**, 476-481.
38. J. J. Wu, B. Li, J. L. Liao, Y. Feng, D. Zhang, J. Zhao, W. Wen, Y. Yang and N. Liu, *J Environ Radioactiv*, 2009, **100**, 914-920.
39. D. Karamanis and P. A. Assimakopoulos, *Water Res*, 2007, **41**, 1897-1906.
40. Y. Park, W. S. Shin and S. J. Choi, *J Radioanal Nucl Ch*, 2012, **292**, 837-852.
41. L. Wang, M. Feng, C. X. Liu, Y. S. Zhao, S. Q. Li, H. Wang, L. Yan, G. Tian and S. J. Li, *Separ Sci Technol*, 2009, **44**, 4023-4035.
42. A. Nilchi, R. Saberi, M. Moradi, H. Azizpour and R. Zarghami, *Chem Eng J*, 2011, **172**, 572-580.
43. S. B. Yang, N. Okada and M. Nagatsu, *J Hazard Mater*, 2016, **301**, 8-16.