

This is a repository copy of *Alginic acid-derived mesoporous carbon (Starbon®) as template and reducing agent for the hydrothermal synthesis of mesoporous LiMn<sub>2</sub>O<sub>4</sub> grafted by carbonaceous species.*

White Rose Research Online URL for this paper:

<https://eprints.whiterose.ac.uk/132964/>

Version: Accepted Version

---

**Article:**

MacQuarrie, Duncan James orcid.org/0000-0003-2017-7076, Stievano, Lorenzo, Kim, Sanghoon et al. (7 more authors) (2018) Alginic acid-derived mesoporous carbon (Starbon®) as template and reducing agent for the hydrothermal synthesis of mesoporous LiMn<sub>2</sub>O<sub>4</sub> grafted by carbonaceous species. *Journal of Materials Chemistry A*. pp. 14392-14399. ISSN 2050-7496

<https://doi.org/10.1039/C8TA04128H>

---

**Reuse**

Items deposited in White Rose Research Online are protected by copyright, with all rights reserved unless indicated otherwise. They may be downloaded and/or printed for private study, or other acts as permitted by national copyright laws. The publisher or other rights holders may allow further reproduction and re-use of the full text version. This is indicated by the licence information on the White Rose Research Online record for the item.

**Takedown**


If you consider content in White Rose Research Online to be in breach of UK law, please notify us by emailing [eprints@whiterose.ac.uk](mailto:eprints@whiterose.ac.uk) including the URL of the record and the reason for the withdrawal request.

# Journal of Materials Chemistry A

Accepted Manuscript



This article can be cited before page numbers have been issued, to do this please use: S. Kim, M. Debruyn, J. G. Alauzun, N. Louvain, N. Brun, D. J. Macquarrie, L. Stievano, B. Boury, L. Monconduit and P. H. Mutin, *J. Mater. Chem. A*, 2018, DOI: 10.1039/C8TA04128H.

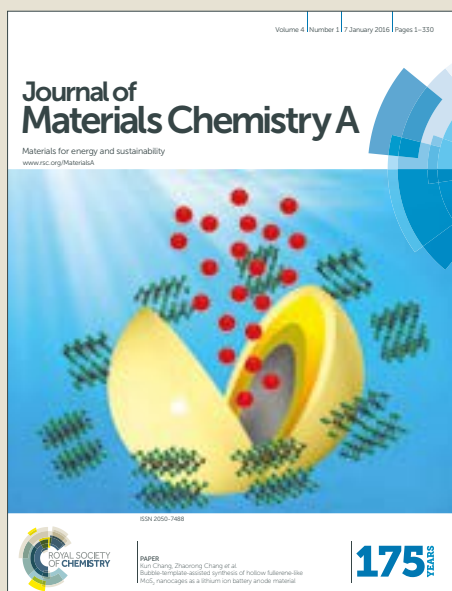

This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [author guidelines](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the ethical guidelines, outlined in our [author and reviewer resource centre](#), still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

## Alginate acid-derived mesoporous carbon (Starbon®) as template and reducing agent for the hydrothermal synthesis of mesoporous LiMn<sub>2</sub>O<sub>4</sub> grafted by carbonaceous species

Sanghoon Kim,<sup>a</sup> Mario De bruyn,<sup>b</sup> Johan G. Alauzun,<sup>a</sup> Nicolas Louvain,<sup>a,c</sup> Nicolas Brun,<sup>a</sup> Duncan J. Macquarrie,<sup>b</sup> Lorenzo Stievano,<sup>a,c</sup> Bruno Boury,<sup>a</sup> Laure Monconduit,<sup>a,c</sup> and P. Hubert Mutin<sup>a,\*</sup>

Received 00th January 20xx,  
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

www.rsc.org/

An alginate acid-derived mesoporous carbonaceous material (Starbon® A300) was used as a sacrificial porous template providing both a reducing environment and anchoring sites for LMO precursors, KMnO<sub>4</sub> and LiOH. After hydrothermal treatment at 180 °C for 24 h, the resulting nanocrystalline LMO particles (≈40 nm) spontaneously aggregated, generating a mesoporous structure with a relatively high mesopore volume (≈0.33 cm<sup>3</sup> g<sup>-1</sup>) and large pore size (≈30 nm). Moreover, a small amount (≈0.6 wt%) of residual carbon was present in mesoporous LMO. This carbon arises from carbonaceous species grafted at the surface of the LMO nanoparticles, which found to significantly enhance the rate capability of LMO by reducing internal electronic resistance. Finally, a "green" LMO electrode formulated using this Starbon-derived LMO as an active material, Starbon® A800 as a conductive additive and sodium alginate as a binder was tested, showing promising electrochemical performance.

### Introduction

Spinel LiMn<sub>2</sub>O<sub>4</sub> (LMO) has been considered as one of the most promising positive electrode materials in Li ion batteries for high power applications such as electric vehicles or portable electronic devices, owing to its low cost, low toxicity and to the high abundance of manganese.<sup>1-6</sup> However, practical implementation of LMO technology is hampered by a low rate capability and fading of its capacity during cycling, mainly due to the dissolution of manganese in the electrolyte<sup>7-9</sup> and to the phase transition from the cubic spinel to a tetragonal crystal structure caused by Jahn-Teller distortion.<sup>10,11</sup> Over the years, many efforts have been made to address these problems, including doping,<sup>12-14</sup> carbon coating,<sup>15,16</sup> and nanostructuring LMO.<sup>17-22</sup> Nano-structuration leading to mesoporous LMO materials has been shown to enhance the battery performance, due to the large surface area favoring better interfacial contact between electrode and electrolyte,<sup>23-27</sup> and to the fast lithium ion diffusion through the mesopores. The mesoporous LMO materials can be generally synthesized via solid-state reaction of pre-synthesized porous magnesium oxide with a lithium precursor, which implies a heat treatment at temperatures

generally above 500 °C,<sup>23,28</sup> or reduction of KMnO<sub>4</sub> to manganese oxide in aqueous solution, followed by lithiation under mild hydrothermal conditions (< 200 °C).<sup>29,30</sup> The latter method has been widely investigated using various reducing agents, of essentially two types i) molecular or polymeric organic reducing agent such as glucose<sup>31</sup> or ii) conductive carbon materials such as carbon nanotube or graphene to obtain a carbon/LMO hybrid electrode. Even though the hydrothermal synthesis seems versatile for the synthesis of mesoporous LMO, it bears also a few disadvantages, the main ones lying in the difficulty of controlling morphology and porosity of LMO for the first type of reducing agent, and in the high cost of carbon nanotubes or graphene for the second type.<sup>32-34</sup> The use of a low-cost porous carbon as both structure directing and reducing agent for KMnO<sub>4</sub> might offer an interesting alternative for the synthesis of porous LMO. However, to the best of our knowledge, this strategy remains nearly unexplored, with the exception of one paper in which carbon fiber paper was used as a structure directing template.<sup>35</sup> Environmental issues being of increasing concern, the green synthesis of porous carbonaceous materials has intensively been investigated, for example, using sustainable or biomass materials such as wheat flour,<sup>36</sup> sugar from Coca Cola®,<sup>37</sup> or soft templating method using polymeric species.<sup>38,39</sup> Among various 'green' carbonaceous materials, Starbon® are a unique class of bio-derived mesoporous carbonaceous materials, which can be derived from a range of polysaccharides by means of a template-free pyrolysis.<sup>40-42</sup> The physicochemical properties of Starbon®, including its porosity, the hydrophobicity/hydrophilicity ratio of the surface and their

<sup>a</sup> Institut Charles Gerhardt Montpellier, Université de Montpellier, CNRS, Montpellier, France. \*E-mail: hubert.mutin@umontpellier.fr

<sup>b</sup> Green Chemistry Centre of Excellence, University of York, York, North Yorkshire, YO10 5DD, UK.

<sup>c</sup> Réseau sur le Stockage Electrochimique de l'Energie (RS2E), CNRS FR3459, 33 Rue Saint Leu, 80039 Amiens Cedex, France.

† Electronic Supplementary Information (ESI) available: Additional characterization data of mesoporous LMO. See DOI: 10.1039/x0xx00000x

conductivity, can be easily tuned by varying the parameters of said thermal transformation, and most notably the type of polysaccharide involved and the pyrolysis temperature. Starbon® materials have been applied as catalysts,<sup>43,44</sup> sorbents for pollutant removal<sup>45-47</sup> and as catalyst supports.<sup>48</sup> In the field of electrochemistry, Starbon® materials have found use as an alternative carbon additive in Li-ion batteries, significantly improving battery performance compared to conventional carbon additives.<sup>49</sup>

We report here the hydrothermal synthesis of mesoporous nanocrystalline LMO using an alginic acid-derived mesoporous carbonaceous materials (Starbon®) as both a sacrificial porous template and a reducing environment that also provides anchoring sites for the precursors of LMO,  $\text{KMnO}_4$  and  $\text{LiOH}$ . The resulting well-crystallized LMO nanoparticles of 30-50 nm in size spontaneously aggregate, generating a mesoporous network. Interestingly, a small amount of residual carbonaceous species ( $\approx 0.6$  wt% C) remains grafted at the surface of the LMO nanoparticles, and this residual carbon significantly enhances the rate capability of mesoporous LMO by reducing its internal electronic resistance.

Finally, as a proof of concept of a "green" electrode derived from seaweed, an electrode formulated with this mesoporous LMO as active material, alginic acid derived Starbon® as a conductive additive and alginic acid sodium salt as a binder was tested, showing an electrochemical performance comparable to conventional LMO electrodes.

## Experimental

### Materials

Alginic acid and potassium permanganate ( $\text{KMnO}_4$ , > 99 %) were purchased from Sigma-Aldrich (France). Alginic acid sodium salt was purchased from Acros (France). Super P (> 99 %) and lithium hydroxide ( $\text{LiOH}$ , anhydrous, 99 %) were purchased from Alfa Aesar (France). S300 was prepared at the University of York and is similar to the mesoporous carbon Starbon® 300 commercialized by Sigma-Aldrich (reference number: 702110). A commercial bulk lithium manganese oxide ( $\text{LiMn}_2\text{O}_4$ ) with particle size around 200-400 nm was purchased from Targray (Canada). All reagents were used without further purification.

### Synthesis of alginic acid-derived mesoporous carbon materials.

First, a dried expanded mesoporous gel of alginic acid was prepared as described previously.<sup>50</sup> Briefly, an alginic acid solution (4.8 wt.% in water) was gelled by heating at 90 °C for 2.5 h, and then kept at 4 °C for 24 h. Afterwards, *tert*-butyl alcohol (TBA) was added to the gel, to reach the eutectic composition (30 wt% TBA, 70 wt% water). The mixture was stirred for 1h at RT and then kept for 24 h without stirring and finally freeze-dried (-55°C). The so-obtained dried expanded gel of alginic acid obtained in this way was then pyrolyzed at 300 °C for 3 h (argon flow: 50 mL min<sup>-1</sup>, heating rate: 1 °C min<sup>-1</sup>) giving the mesoporous carbonaceous material A300 (A stands for Alginic acid, 300 for the carbonization temperature in °C) with a

yield of ca. 40 wt%. The specific surface area and total pore volume of A300 determined by  $\text{N}_2$  physisorption experiments were 222 m<sup>2</sup> g<sup>-1</sup> and 1.04 cm<sup>3</sup> g<sup>-1</sup>, respectively.

Other Starbon® materials such as A450 and A800 were obtained by carbonization for 3 hours of the expanded gel of alginic acid at 450 °C and 800 °C, respectively.

### Synthesis of mesoporous nanocrystalline $\text{LiMn}_2\text{O}_4$ using A300

Briefly,  $\text{KMnO}_4$  (316 mg, 2 mmol) was dissolved in a suspension of A300 (50 mg, 36 mg as carbon, 3 mmol) dispersed in 21 mL of water and stirred for 2 h at RT. Then, a 1M aqueous solution of  $\text{LiOH}$  (4 ml, 4 mmol) was added and the suspension was stirred for 1 h at RT. The resulting mixture was transferred into an autoclave with polytetrafluoroethylene (PTFE) lining (100 mL). The sealed autoclave was heated at 180 °C in an oven for 24 h under autogenous pressure. After cooling the resulting powder was centrifuged, then washed 3 times with water (50 mL), dried under vacuum at 120 °C for 15 h, yielding mesoporous  $\text{LiMn}_2\text{O}_4$  (labeled LMO-HT) with the molar yield of 77 % calculated from the amount of  $\text{KMnO}_4$  initially introduced. Several fractions of LMO-HT were then calcined at 350, 500, or 700 °C in a muffle furnace (heating rate: 1 °C min<sup>-1</sup>) giving respectively LMO-350, LMO-500, or LMO-700.

### Characterization

Powder XRD patterns were measured using a PANalytical X'Pert Pro MPD diffractometer, equipped with the  $\text{K}\alpha$  radiation of Cu ( $\lambda = 1.5418 \text{ \AA}$ ) and a step size of 0.033° in the 10°-80° 2 $\theta$  range.  $\text{N}_2$  physisorption experiments were carried out at -196 °C on a Micromeritics 3Flex; all materials were degassed at 120°C for 15 h at 5·10<sup>-2</sup> mbar before the physisorption measurements. ICP-OES analysis was performed using an iCAP 6000 Series. Scanning electron microscopy (SEM) images were acquired with a Hitachi S-4800 electron microscope. EDX analyses were acquired with a JEOL CENTURIO detector. Transmission electron microscopy (TEM) images were acquired using JEOL FX2200 microscope. Raman spectra were obtained on a Horiba Jobin-Yvon LabRAM ARAMIS microspectrometer. The excitation wavelength was 633 nm.

Galvanostatic electrochemical characterizations were performed at room temperature on a BTS3000 instrument from Neware Battery. Electrochemical impedance spectroscopy (EIS) studies were done on a BioLogic VSP instrument, from 100 kHz to 20 mHz, with a 10 mV amplitude in potentiostatic mode. LMO electrodes are composed of the active material (82 wt.%), Super P (12 wt.%), and polyvinylidene fluoride (PVDF, 6 wt.%, Solef 5130). After stirring in *N*-methyl-2-pyrrolidone (NMP), the slurry was mixed using an agate grinding jar (1 h at 500 rpm), then tape casted uniformly at 150  $\mu\text{m}$  onto an aluminum current collector (0.018 mm, 99.0 %, Goodfellow) using a 3540 bird film applicator from Elcometer. In case of the green LMO electrode formulated with Starbon® A800 as alternative carbon additive and alginic acid sodium salt as alternative binder, the weight ratio is 78 : 12 : 10 for active material : A800 : alginic acid sodium salt, respectively. For the slurry preparation of the green LMO electrode, water was used instead of NMP for the

preparation of the slurry. Electrodes (diameter 12.7 mm) were then cut out with a disk cutter and dried under vacuum at 90 °C for 15 h. The loading weight per electrode disk was approximately 2.2 mg. CR2032 coin-type cells were assembled in a glove box under Ar atmosphere ( $O_2 < 0.5$  ppm,  $H_2O < 0.5$  ppm), using lithium metal as both reference and counter electrode. The electrolyte was LP30 (1M  $LiPF_6$  dissolved in a mixture of ethylene carbonate (EC) and dimethyl carbonate (DMC) (ratio EC : DMC = 1 : 1). Whatman glass fibre disks were used as separators. The electrochemical galvanostatic measurements were taken in the voltage range of 3.4-4.3 V versus  $Li^+/Li$  at different current densities.

## Results and discussion

### Synthesis of mesoporous nanocrystalline LMO materials

The Starbon A300 template was prepared by pyrolysis at 300 °C of a mesoporous expanded cryogel of alginic acid, as previously reported.<sup>37</sup> The key synthetic step to maintain the mesoporous structure of alginic acid gel during solvent removal by freeze-drying is adding *tert*-butyl alcohol to form a water/*tert*-butyl alcohol eutectic.<sup>50</sup> As shown in Fig. S1, direct freeze-drying without addition of *tert*-butyl alcohol yields a cryogel with only 0.36 cm<sup>3</sup> g<sup>-1</sup> as mesopores volume, 3 times lower than the cryogel obtained with the water/*tert*-butyl alcohol eutectic.

This mesoporous carbonaceous material A300 was used successfully as sacrificial template and reducing agent in the hydrothermal synthesis of mesoporous nanocrystalline  $LiMn_2O_4$  (LMO-HT). The method is simple: in a first step, an aqueous dispersion of A300 is reacted for 2 h at room temperature with  $KMnO_4$  to form  $MnO_2$  then  $LiOH$  is added and the mixture heated at 180 °C for 24 h under autogenous pressure to perform the lithiation of  $MnO_2$ .

Controlling the phase purity is a recurrent issue in the hydrothermal synthesis of LMO and a precise control of both Li/Mn and C/Mn molar ratio is essential to obtain pure LMO. As shown in Fig. S2, the ratio of  $LiOH/KMnO_4$  was systematically varied, and a 2:1 ratio was found to lead to pure LMO. As detailed in Fig. S3, the optimum amount of A300 is 50 mg for 2 mmol of  $KMnO_4$ , corresponding to a C/Mn molar ratio of 1.5. The nature of the carbonaceous material was also found to be important: interestingly, pure LMO could be obtained only using A300, while additional phases are detected when the synthesis is performed under the same conditions but using different carbon materials (Fig. S3): alginic acid, expanded alginic acid calcined at higher temperatures (A450, A800), expanded starch carbonized at 300 °C (S300), or carbon black (Super P). These results suggest that both the mesoporous texture and the numerous residual carboxylic acid groups found in A300 play an important role in our synthesis.

According to CHNS elemental analysis, LMO-HT contains only 0.6 wt% of carbon. This value is significantly lower than the theoretical value of 9 wt% which can be calculated from the stoichiometry of the reduction of  $KMnO_4$  with carbon to form  $MnO_2$ :



When the reaction of A300 with  $KMnO_4$  was stopped after 2 h (*i.e.*, before the hydrothermal treatment) the violet colour of the suspension had vanished, indicating complete reduction of  $KMnO_4$ . Characterization of the dried resulting powder shows the formation of a poorly crystalline, mesoporous manganese oxide with a carbon content close to 9 wt% (Fig. S4). Hence, it can be concluded that A300 served during the first step as both the reducing agent and the mesoporous template, and that most of the A300 was then removed during the hydrothermal lithiation treatment. The low stability of A300 under hydrothermal conditions in the presence of  $LiOH$  is not surprising as this material is only very partially carbonized, with a C:O molar ratio of 4:1.<sup>41</sup>

The optimized LMO material (LMO-HT) was then calcined at 350, 500 or 700 °C in air, giving LMO-350, LMO-500 or LMO-700, respectively, allowing the investigation of the influence of carbon content and texture on the electrochemical performance. Calcination at 500 °C led to a virtually complete removal of residual organics (0.04 wt% C in LMO-500 sample). Fig. 1 shows the XRD patterns of LMO-HT and of the calcined samples compared with a commercial bulk LMO (LMO-Comm). All XRD patterns show only diffraction peaks characteristic of the cubic spinel structure of  $LiMn_2O_4$  (JCPDS no. 49-0207) at  $2\theta = 18.6^\circ, 36.1^\circ, 37.7^\circ, 43.9^\circ, 48.1^\circ, 58.3^\circ, 64.0^\circ$  and  $67.4^\circ$  corresponding to the (111), (311), (222), (400), (331), (333), (440) and (531) reflections, respectively. The chemical composition of LMO-HT was found to be  $Li_{0.99}Mn_{1.00}O_4$  by ICP analysis, thus, LMO-HT can be considered as a virtually stoichiometric  $LiMn_2O_4$ . Upon calcination, the peak corresponding to (111) plane slightly shifts towards lower  $2\theta$ , indicating an increase of the cell parameter  $a$ . (Fig. S5, Table S1). This increase of cell parameter can be explained considering that at low calcination temperatures the manganese ions in LMO are more stable as  $Mn^{4+}$  (0.054 nm), which is smaller than  $Mn^{3+}$  (0.064 nm).<sup>51,52</sup> No other diffraction peaks characteristic of impurities such as  $\alpha$ - or  $\beta$ - $MnO_2$  (*i.e.*, intense peak at  $2\theta = 28^\circ$  for (310) or (110) plane of  $\alpha$  or  $\beta$ - $MnO_2$ , respectively<sup>53</sup>) are observed. The LMO crystallite size, estimated using the Scherrer equation, increase slightly with the calcination temperature (Table 1).

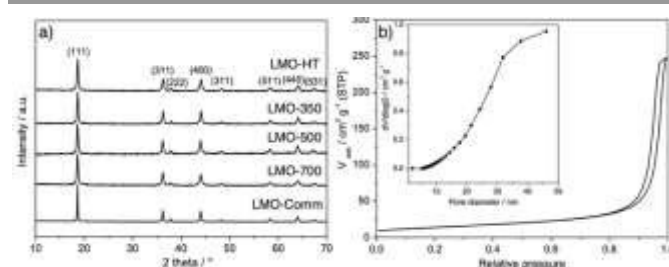


Fig. 1. a) Powder X-ray diffraction (XRD) patterns of LMO-HT, LMO-350, LMO-500, LMO-700 and LMO-Comm. b)  $N_2$  adsorption-desorption isotherms and pore size distribution (inset) of LMO-HT.

The textural properties of LMO materials were evaluated by  $N_2$  physisorption (Fig. 1b for LMO-HT and Fig. S6 for the others). As shown in Table 1, LMO-HT is mesoporous, with a specific surface area of 49 m<sup>2</sup> g<sup>-1</sup> and a pore volume of 0.33 cm<sup>3</sup> g<sup>-1</sup>. Both

specific surface area and pore volume slightly decrease upon calcination up to 500 °C, owing to the growth of the LMO crystallites. Upon calcination at 700 °C, the strong decrease of surface area and pore volume can be ascribed mostly to the sintering of LMO particles.

Table 1. Textural properties of LMO samples investigated in this study. N<sub>2</sub> adsorption-desorption isotherms and pore size distributions are given in Fig. S5.

	S <sub>BET</sub> <sup>a</sup> (m <sup>2</sup> g <sup>-1</sup> )	PV <sub>total</sub> <sup>b</sup> (cm <sup>3</sup> g <sup>-1</sup> )	PV <sub>meso</sub> <sup>c</sup> (cm <sup>3</sup> g <sup>-1</sup> )	D <sub>B</sub> <sup>d</sup> (nm)	Crystallite size <sup>e</sup> (nm)
LMO-HT	49	0.37	0.33	24	25
LMO-350	50	0.32	0.28	23	28
LMO-500	41	0.28	0.26	23	30
LMO-700	17	0.11	0.11	23	33
LMO-Comm	< 1	< 0.01	< 0.01	-	60

<sup>a</sup>: specific area determined by BET method; <sup>b</sup>: total pore volume at P/P<sub>0</sub> = 0.99; <sup>c</sup>: BJH mesopore volume between 2 and 50 nm; <sup>d</sup>: BJH average mesopore diameter (desorption branch); <sup>e</sup>: derived from (111) reflection using the Scherrer equation.

Fig. 2 shows SEM images of samples LMO-HT, LMO-350, LMO-500, LMO-700 and commercial LMO. LMO-HT (Fig. 2a and b) is composed of aggregated nanoparticles giving rise to interparticle mesoporosity. The size of the LMO nanoparticles does not vary significantly upon calcination. However, sintering of LMO nanoparticles leading to a collapse of the mesoporosity was evidenced for LMO-700 (Fig. S7).

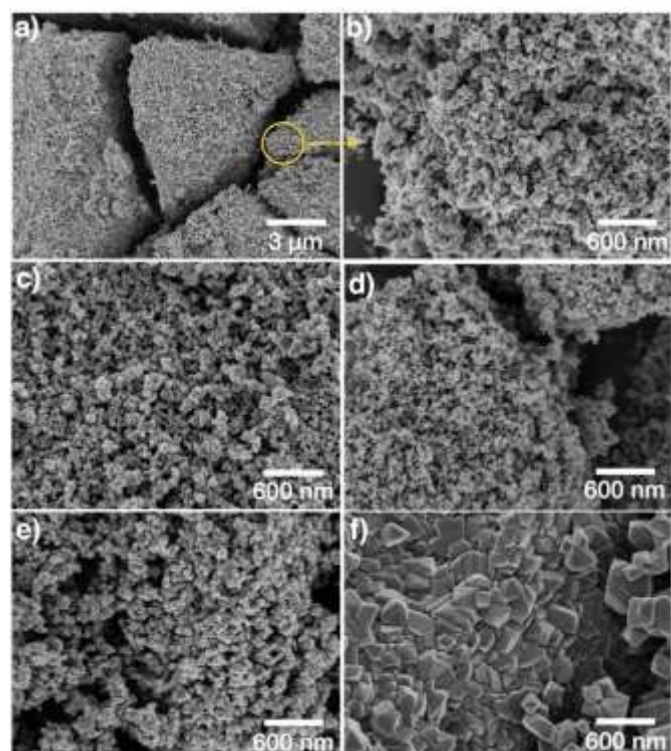
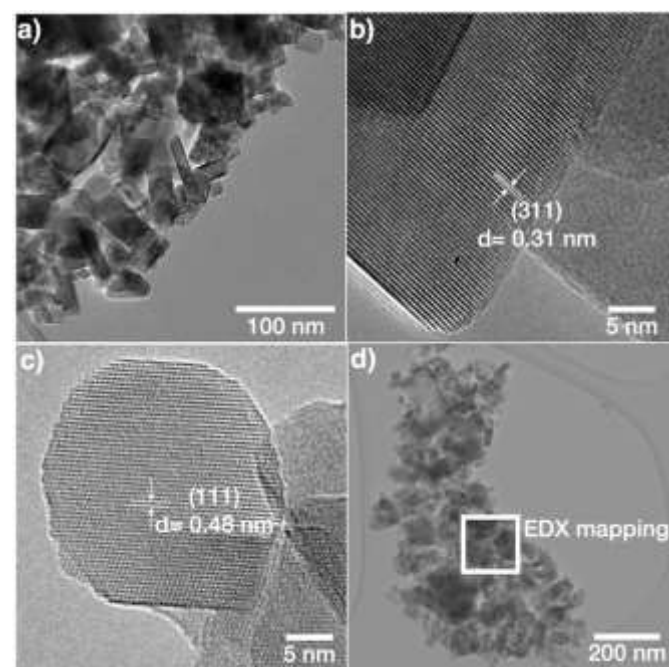


Fig. 2. SEM images of a), b) LMO-HT, c) LMO-350, d) LMO-500, e) LMO-700 and f) LMO-Comm. More SEM images in Fig. S7

TEM images of LMO-HT (Fig. 3) confirm that the mesoporosity derives from the random packing of well-crystallized primary

LMO nanoparticles. In the case of LMO-HT (0.6 wt% C), TEM-EDX mapping reveals that the carbon is homogeneously distributed over the surface of the LMO particles. The average thickness of a carbon coating (estimated from the specific surface area of LMO-HT assuming a density of 1 for the coating) would be only ≈0.112 nm. Accordingly, the decomposition of A300 during the hydrothermal treatment does not lead to a "thick" carbon coating but rather to grafted molecular or macromolecular carbonaceous species which could not be removed by washing. The Raman spectrum of LMO-HT suggests the absence of graphitic structures in the residual organic species found in this sample (Fig. S8), which is not surprising considering the low temperature used in the hydrothermal treatment (180 °C).

Even though the amount of these carbonaceous species is quite low, their role seems particularly important since they are found to significantly improve the electrochemical performance of mesoporous LMO (*vide infra*).



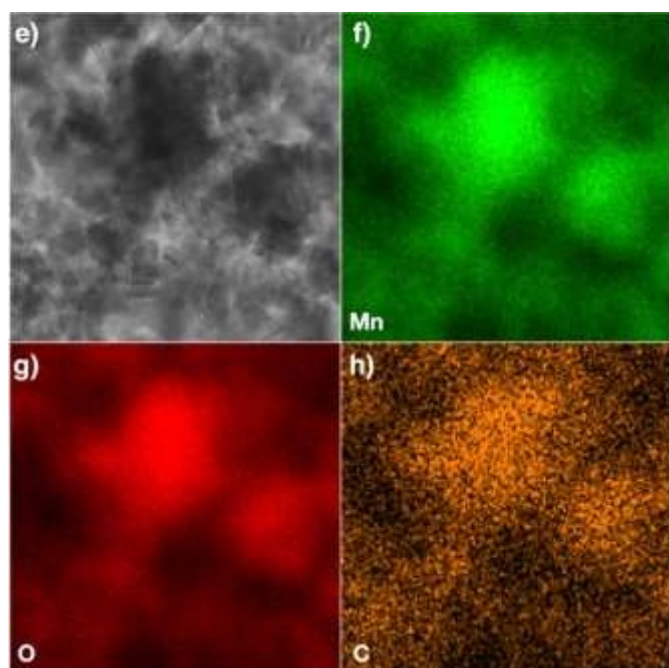


Fig. 3. TEM images (a-d) and EDX mapping images for Mn, O and C (e-h) of LMO-HT.

### Electrochemical performance of mesoporous LMO materials

The electrochemical performance of LMO materials was evaluated in CR2032 coin-type half-cells using Li metal as counter and reference electrode. Fig. 4a shows a representative charge/discharge galvanostatic curves of mesoporous LMO-HT at C-rate of C/10 (1 C = 148 mA g<sup>-1</sup> for LMO) over the voltage range of 3.4 – 4.3 V. The double plateau signature typical of LMO is observed, corresponding to a two-step process during both charge and discharge: the biphasic reaction between LiMn<sub>2</sub>O<sub>4</sub> and Li<sub>0.5</sub>Mn<sub>2</sub>O<sub>4</sub> at ≈4.0 V vs Li/Li<sup>+</sup> is followed by the biphasic reaction between Li<sub>0.5</sub>Mn<sub>2</sub>O<sub>4</sub> and γ-MnO<sub>2</sub> at ≈4.1 vs Li/Li<sup>+</sup>.<sup>6</sup> The initial charge and discharge capacities of mesoporous LMO-HT are 151 and 133 mAh g<sup>-1</sup>, respectively, with a low coulombic efficiency of 87%. This irreversible capacity at the 1<sup>st</sup> cycle is most probably due to the decomposition of the electrolyte at the surface of the electrode at high potential, leading to the formation of a solid electrolyte interphase (SEI).<sup>54</sup> When higher C-rates are applied (from 0.5 C to 10 C), the characteristic double plateau becomes less visible along with a decrease of discharge capacity and an increase of the polarization (Fig. 4b).

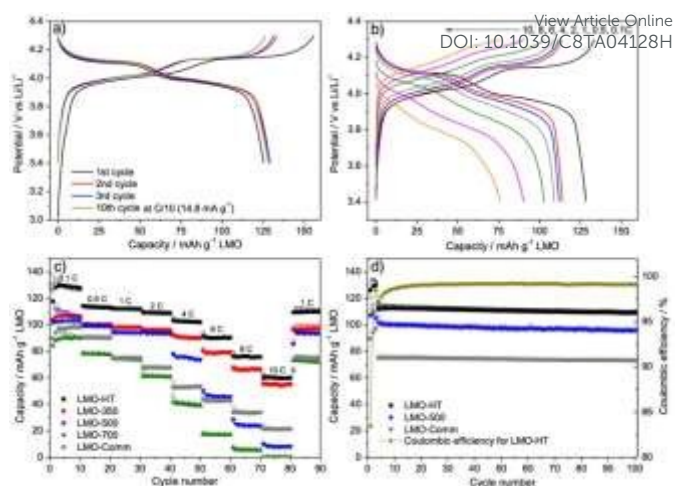


Fig. 4. Galvanostatic charge–discharge curves for LMO-HT cycled a) at C/10 (1<sup>st</sup> to 10<sup>th</sup> cycle), b) at various C-rates (0.1–10 C); c) Rate-capability and cycling performance of different LMO electrodes; d) Long term cyclability of different LMO electrodes at 1 C for 100 cycles. First 3 cycles were tested at 0.1 C. See Fig. S9 for galvanostatic charge–discharge curves for LMO-350, LMO-500, LMO-700 and LMO-Comm.

LMO-HT delivers a much higher capacity than LMO-500, LMO-700 or LMO-Comm samples, particularly at high C rates, as shown in Fig. 4c. Calcination of LMO-HT at 500 °C leading to LMO-500 does not induce a significant modification of the crystallinity or of the texture, but mainly results in the removal of the residual carbonaceous species (<0.05 wt% C in LMO-500). Thus, it can be assumed that the presence of the carbonaceous species in LMO-HT are responsible for its remarkably improved electrochemical performance compared to LMO-500, probably by ensuring a good conductivity *via* interconnection of the LMO nanoparticles. Besides, the poor performance of LMO-700 can be ascribed to the sintering of the LMO particles upon calcination at 700 °C. The initial coulombic efficiency for LMO-350, 500, 700 and LMO-Comm were 80, 79, 66 and 64 %, significantly lower than that of LMO-HT (89 %).

Comparison between LMO-500 and LMO-Comm electrodes allows us to evaluate the role of the texture and particle size in the electrochemical behavior. At low to moderate C-rates (up to 4C), the mesoporous LMO-500 active material shows a much higher capacity than bulk LMO-Comm. This can be ascribed to the much higher specific surface area of LMO-500 leading to a better interfacial contact between electrode and electrolyte and to the fast lithium ion diffusion through the mesopores.<sup>23–27</sup> On the other hand, at very high C-rates (above 4C), the situation is reversed and the LMO-Comm material displays a higher capacity than LMO-500. This behavior suggests that at very high C-rates the limiting factor becomes the electronic conductivity and that the small crystallite size in LMO-500 lead to a lower electronic conductivity than in LMO-Comm, possibly due to the drastic increase in the number of contacts between LMO nanoparticles (Fig. S10).

Electrochemical impedance spectroscopy (EIS) was used to comfort this hypothesis. As shown in Fig. 5, the Nyquist plot for the different electrodes exhibits a single semicircle in the middle to high frequency range, which is attributed to the charge transfer resistance ( $R_{ct}$ ) between electrolyte and LMO.

Before cycling,  $R_{ct}$  for LMO-HT (76  $\Omega$ ) and LMO-500 (93  $\Omega$ ) is significantly lower than for LMO-Comm (163  $\Omega$ ). After the first cycle, these values increase for all electrodes, most probably due to the formation of a solid electrolyte interphase (SEI) at the surface of the LMO particles. Upon further cycling this resistance remains then almost constant, indicating that the SEI layer of both electrodes is relatively stable over cycling, allowing stable electrode processes and good cycling performance.

The diffusion coefficient of Li ions ( $D_{Li^+}$ ) was estimated by fitting the different plots on low frequency range. Interestingly, the  $D_{Li^+}$  values for LMO-HT ( $3.2 \cdot 10^{-12} \text{ cm}^2 \text{ s}^{-1}$ ) and LMO-500 ( $2.3 \cdot 10^{-12} \text{ cm}^2 \text{ s}^{-1}$ ) are similar, while the value found for LMO-Comm ( $1.6 \cdot 10^{-13} \text{ cm}^2 \text{ s}^{-1}$ ) is significantly lower. The slower diffusion of Li ions in the non-porous commercial sample can be ascribed to the larger particle size.

Thus, the better performance at high C rate of LMO-Comm compared to LMO-500 cannot be attributed to improved Li ion diffusion or better charge transfer, but probably depends upon the higher electronic conductivity of LMO-Comm, due to the larger particle size in this sample.

Similarly, the superior behavior of LMO-HT compared to LMO-Comm can be ascribed at moderate C rates to its mesoporosity and at high C rates to the low amount of grafted carbonaceous species which efficiently increases electronic conductivity by bridging LMO nanoparticles.

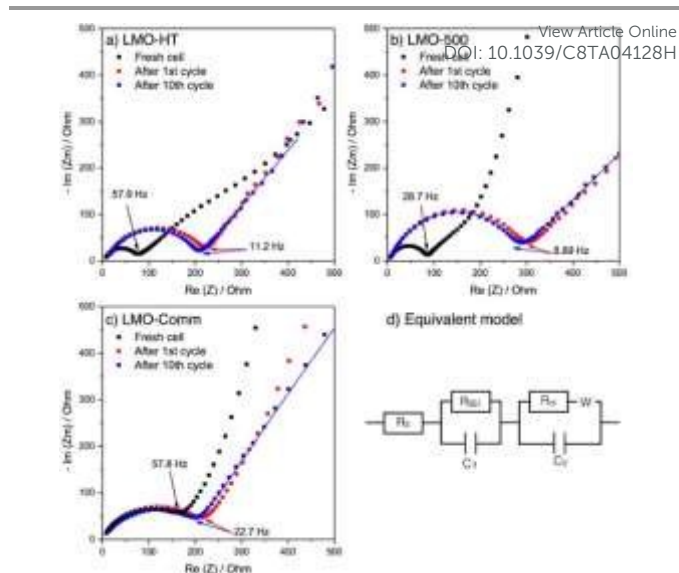


Fig. 5. Nyquist plots of a) LMO-HT electrode, b) LMO-500 electrode, c) LMO-Comm electrode during cycling at C/10, and d) equivalent circuit model used. Fitting was performed on the Nyquist plots after 10<sup>th</sup> cycle and presented as solid line.

The cycling performance of mesoporous LMO-HT, LMO-500 and LMO-Comm electrodes are compared in Fig. 4d. After 100 cycles at 1C, LMO-HT shows a discharge capacity of 112  $\text{mAh g}^{-1}$ , corresponding to 98.5 % of the initial discharge capacity, thus demonstrating an excellent cycling stability (0.015 % of fading per cycle). A coulombic efficiency of 99.2 % is found after 100 cycles. Despite their decent electrochemical performance LMO-500 and LMO-Comm exhibit significantly lower capacities (94 and 77  $\text{mAh g}^{-1}$  respectively) and lower capacity retentions after 100 cycles (96.2 % and 94.5, respectively). Moreover, LMO-HT shows a remarkable cycling robustness at high C-rate, retaining 98.1 % of its initial discharge capacity after 500 cycles at 4 C (592  $\text{mAh g}^{-1}$ ), with a coulombic efficiency of > 99.0 % (Fig. S11).

As shown in Table 2, the electrochemical performance of LMO-HT compares well with that of other mesoporous LMO materials reported in the literature. Unfortunately, specific surface area and pore volume data are not always mentioned and the presence of mesopores is mainly deduced from SEM or TEM images. It is thus difficult to compare LMO-HT with the other published materials and correlate the electrochemical performance with the mesoporosity.

Table 2. Performance of selected porous LMO materials as anode in Li ion batteries.<sup>a</sup>

Type of material	Synthetic method	$S_{BET}$ ( $\text{m}^2 \text{ g}^{-1}$ )	$PV_{\text{meso}}$ ( $\text{cm}^3 \text{ g}^{-1}$ ) <sup>b</sup>	Specific capacity ( $\text{mAh g}^{-1}$ )	Specific capacity at high rate ( $\text{mAh g}^{-1}$ )	Cyclability (Capacity retention %)	refs
Mesoporous LMO (LMO-HT)	Hydrothermal synthesis using Starbon	49	0.33	131 $\text{mAh g}^{-1}$ at 0.1 C	104 $\text{mAh g}^{-1}$ at 4C	98.5 % at 1 C after 100 cycles, 98.1 % at 4C after 500 cycles	This work
Mesoporous LMO	Impregnation using mesoporous carbon (KIT-6)	55	N/A	100 $\text{mAh g}^{-1}$ at 1 C	80 $\text{mAh g}^{-1}$ at 5 C	94 % at 1 C after 500 cycles	23



Mesoporous LMO	Sol-gel synthesis using P123 surfactant	42	N/A	140 mAh g <sup>-1</sup> at 0.2 C	87 mAh g <sup>-1</sup> at 4 C	82 % at 0.5 C after 100 cycles	24 DOI: 10.1039/C8TA04128H
Carbon coated mesoporous LMO	Hydrothermal synthesis using mesoporous manganese oxide	N/A	N/A	130 mAh g <sup>-1</sup> at 0.5 C	115 mAh g <sup>-1</sup> at 4 C	91 % at 30 C after 1500 cycles	26
Porous LMO	Solid state synthesis using manganese oxide	26	N/A	128 mAh g <sup>-1</sup> at 0.2 C	100 mAh g <sup>-1</sup> at 5 C	94 % at 1 C after 100 cycles	55
Hollow mesoporous microspheres	Solid state synthesis using MnCO <sub>3</sub> microspheres	N/A	N/A	119 mAh g <sup>-1</sup> at 0.1 C	106 mAh g <sup>-1</sup> at 5 C	96 % at 1 C after 100 cycles	21
Macroporous LMO microspheres	Solid state synthesis using microsphere of MnO <sub>2</sub>	N/A	N/A	132 mAh g <sup>-1</sup> at 0.1 C	115 mAh g <sup>-1</sup> at 5 C	80 % at 20 C after 100 cycles	56
Porous LMO-C composite	Hydrothermal synthesis using carbon fiber paper	N/A	N/A	131 mAh g <sup>-1</sup> at 0.2 C	98 mAh g <sup>-1</sup> at 5 C	78 % at 1 C after 100 cycles	35

<sup>a</sup> The electrode formulation, thickness, loading weight and cell fabrication can vary, and thus, this comparison may only be approximate. <sup>b</sup> In most papers, no detailed data about pore volume was provided. Only the presence of (meso)pores was visualized by TEM or SEM analysis. The current density corresponding to 1 C for LiMn<sub>2</sub>O<sub>4</sub> is 148 mA g<sup>-1</sup>.

Finally, as a proof of concept of a seaweed-derived green electrode, an electrode was formulated using LMO-HT, alginic acid-derived mesoporous carbon Starbon® A800 (instead of Super P conductive additive) and alginic acid sodium salt (instead of PVDF binder). As shown in Fig. 6a, this green electrode exhibited an electrochemical performance similar to that of the electrode prepared from LMO-HT using Super P and PVDF (Fig. 4), with a reversible discharge capacity of ≈115 mAh g<sup>-1</sup> at 0.1 C. In terms of long-term cycling performance (Fig. 6b), after 100 cycles at 1 C, this "green" LMO electrode showed a discharge capacity of 93 mAh g<sup>-1</sup>, with a capacity retention of 96 % with respect to the initial capacity at 1 C. Interestingly, an electrode formulated with LMO-HT, mesoporous carbon additive Starbon® A800 and PVDF gave only 10 mAh g<sup>-1</sup> without any characteristic galvanostatic curve of LMO (Fig. S12), which suggest that the working mechanism of the green LMO electrode might be different from conventional electrodes using carbon black and PVDF. Indeed, the sodium salt of alginic acid was found to be stiffer than PVDF in carbonate-based electrolytes,<sup>57</sup> and thus Li ion transfer can occur via an hopping mechanism through the carboxylate group of alginate.<sup>58</sup> Moreover, since Starbon® A800 is slightly less hydrophobic (C:O ratio = 17) than the conventional carbon black (e.g. Super P, C:O ratio > 200), the interaction between alginic acid sodium salt and Starbon® A800 might be also different. A more detailed investigation on the green electrode processing (e.g. using different binders or carbon additives) is underway, and the result will be reported elsewhere.

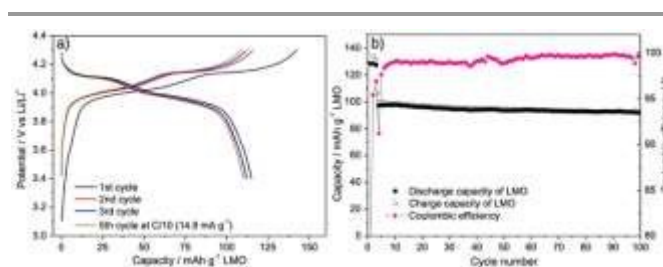


Fig. 6. a) Representative galvanostatic charge–discharge curves of the green LMO-HT electrode at C/10 (1st to 5th cycle), b) Long term cyclability of the green LMO-HT electrode at 1 C for 100 cycles. First 3 cycles were tested at 0.1 C.

## Conclusions

In summary, well-crystallized mesoporous LMO was successfully synthesized by a one-pot hydrothermal method from KMnO<sub>4</sub> and LiOH in the presence of an alginic acid-derived mesoporous carbonaceous materials (Starbon® A300) as sacrificial template and reducing agent. A post-synthesis annealing or calcination step is not needed in this synthesis. The resulting mesoporous LMO (LMO-HT) contains a small amount of carbon arising from carbonaceous species grafted at the surface of the LMO nanoparticles. The excellent electrochemical performance at low and high C-rates of LMO-HT compared to calcined (carbon-free) mesoporous LMO or commercial (non-porous) LMO are ascribed to i) its mesoporous structure, which might favour fast Li<sup>+</sup> diffusion from the electrolyte to the surface of the LMO particles, but also to ii) the presence of the grafted carbonaceous species, which apparently decrease the resistance in the mesoporous LMO electrode by enhancing the electronical interconnection between the LMO nanoparticles, as confirmed by electrochemical impedance spectroscopy (EIS).

Moreover, as a proof of concept of a seaweed-derived green electrode, an electrode formulated from LMO-HT using Starbon® A800 as a conductive additive and sodium alginate as a binder was tested, showing promising electrochemical performance comparable to that of conventional LMO electrodes.

### Author contributions

S.K. designed the study, synthesized mesoporous LMO and carried out electrochemical testing and analysis. M.D. synthesized the dried expanded gel of alginic acid, carbonaceous materials with advice from D.J.M. J.G.A., N.L., N.B., L.S. and B.B. supervised data analysis. S.K. and P.H.M. wrote the manuscript with advice from M. D. B.B., N.B., L.S. and L.M. L.M. and P.H.M. oversaw the study. All authors discussed the results and commented on the manuscript.

### Conflicts of interest

There are no conflicts to declare.

### Acknowledgements

Financial support was received from the European Commission in the framework of POROUS4APP project (H2020 GA no. 666157). The authors would like to thank Didier Cot (IEM, France) for SEM analysis. Lea Daenens (ICGM, France) is gratefully acknowledged for technical help in the collection of the Raman spectra. The authors acknowledge Eun Jeong Kim, Gavin Peters and A. Robert Armstrong (School of Chemistry, University of St Andrews, UK) for ICP measurements.


### Notes and references

- M. M. Thackeray, P. J. Johnson, L. A. de Picciotto, P. G. Bruce and J. B. Goodenough, *Mater. Res. Bull.*, 1984, **19**, 179–187.
- G. Amatucci and J. M. Tarascon, *J. Electrochem. Soc.*, 2002, **149**, K31–K46.
- K. M. Shaju and P. G. Bruce, *Chem. Mater.*, 2008, **20**, 5557–5562.
- H. Xia, Z. Luo and J. Xie, *Prog. Nat. Sci.: Mater. Int.*, 2012, **22**, 572–584.
- F. Mao, W. Guo and J. Ma, *RSC Adv.*, 2015, **5**, 105248–105258.
- A. V. Potapenko and S. A. Kirillov, *J. Energy Chem.*, 2014, **23**, 543–558.
- L.-F. Wang, C.-C. Ou, K. A. Striebel and J.-S. Chen, *J. Electrochem. Soc.*, 2003, **150**, A905–A911.
- J. Cho, T.-J. Kim, Y. J. Kim and B. Park, *Chem. Commun.*, 2001, **0**, 1074–1075.
- J. Lu, C. Zhan, T. Wu, J. Wen, Y. Lei, A. J. Kropf, H. Wu, D. J. Miller, J. W. Elam, Y.-K. Sun, X. Qiu and K. Amine, *Nat. Commun.*, 2014, **5**, 5693.
- L. Cai, Y. Dai, M. Nicholson, R. E. White, K. Jagannathan and G. Bhatia, *J. Power Sources*, 2013, **221**, 191–200.
- J. Darul, C. Lathe and P. Piszora, *RSC Adv.*, 2014, **4**, 65205–65212.

- Z. Zhang, Z. Chen, G. Wang, H. Ren, M. Pan, L. Xiao, K. Wu, L. Zhao, J. Yang, Q. Wu, J. Shu, D. Wang, H. Zhang, N. Huo and J. Li, *Phys. Chem. Chem. Phys.*, 2016, **18**, 6893–6900.
- Y. Fu, H. Jiang, Y. Hu, Y. Dai, L. Zhang and C. Li, *Ind. Eng. Chem. Res.*, 2015, **54**, 3800–3805.
- C.-G. Han, C. Zhu, G. Saito and T. Akiyama, *RSC Adv.*, 2015, **5**, 73315–73322.
- W. Sun, H. Liu, Y. Liu, G. Bai, W. Liu, S. Guo and X.-Z. Zhao, *Nanoscale*, 2015, **7**, 13173–13180.
- S. Lee, Y. Cho, H.-K. Song, K. T. Lee and J. Cho, *Angew. Chem. Int. Ed.*, 2012, **51**, 8748–8752.
- P. G. Bruce, B. Scrosati and J.-M. Tarascon, *Angew. Chem. Int. Ed.*, 2008, **47**, 2930–2946.
- W. Sun, H. Liu, T. Peng, Y. Liu, G. Bai, Sen Kong, S. Guo, M. Li and X.-Z. Zhao, *J. Mater. Chem. A*, 2015, **3**, 8165–8170.
- J. Wang, W. Liu, S. Liu, J. Chen, H. Wang and S. Zhao, *Electrochim. Acta*, 2016, **188**, 645–652.
- J. Deng, J. Pan, Q. Yao, Z. Wang, H. Zhou and G. Rao, *J. Power Sources*, 2015, **278**, 370–374.
- Y. Deng, Y. Zhou, Z. Shi, X. Zhou, X. Quan and G. Chen, *J. Mater. Chem. A*, 2013, **1**, 8170–8.
- F. Cheng, H. Wang, Z. Zhu, Y. Wang, T. Zhang, Z. Tao and J. Chen, *Energy Environ. Sci.*, 2011, **4**, 3668–8.
- J.-Y. Luo, Y.-G. Wang, H.-M. Xiong and Y.-Y. Xia, *Chem. Mater.*, 2007, **19**, 4791–4795.
- S. Chen, Z. Chen and C. Cao, *Electrochim. Acta*, 2016, **199**, 51–58.
- F. Jiao, J. Bao, A. H. Hill and P. G. Bruce, *Angew. Chem. Int. Ed.*, 2008, **47**, 9711–9716.
- C. Jiang, Z. Tang, S. Deng, Y. Hong, S. Wang and Z. Zhang, *RSC Adv.*, 2017, **7**, 3746–3751.
- J. M. Kim, G. Lee, B. H. Kim, Y. S. Huh, G. -W. Lee and H. J. Kim, *Ultrason. Sonochem.* 2012, **19**, 627–631.
- J. Cabana, T. Valdés-Solís, M. R. Palacín, J. Oró-Solé, A. Fuertes, G. Marbán and A. B. Fuertes, *J. Power Sources*, 2007, **166**, 492–498.
- B. J. Liddle, S. M. Collins and B. M. Bartlett, *Energy Environ. Sci.*, 2010, **3**, 1339–8.
- X. Lv, S. Chen, C. Chen, L. Liu, F. Liu and G. Qiu, *Solid State Sci.*, 2014, **31**, 16–23.
- Y.-Y. Liang, S.-J. Bao, B.-L. He, W.-J. Zhou and H.-L. Li, *J. Electrochem. Soc.*, 2005, **152**, A2030–1.
- X. Jia, C. Yan, Z. Chen, R. Wang, Q. Zhang, L. Guo, F. Wei and Y. Lu, *Chem. Commun.*, 2011, **47**, 9669–3.
- B. Lin, Q. Yin, H. Hu, F. Lu and H. Xia, *J. Solid State Chem.*, 2014, **209**, 23–28.
- M. Tang, A. Yuan and J. Xu, *Electrochim. Acta*, 2015, **166**, 244–252.
- G. H. Waller, S. Y. Lai, Ben Harris Rainwater and M. Liu, *J. Power Sources*, 2014, **251**, 411–416.
- G. Lan, Y. Wang, Y. Qiu, X. Wang, J. Liang, W. Han, H. Tang, H. Liu, J. Liu and Y. Li, *Chem. Commun.*, 2018, **54**, 623–626.
- Y. Boyjoo, Y. Cheng, H. Zhong, H. Tian, J. Pan, V. K. Pareek, S. P. Jiang, J.-F. Lamonier, M. Jaroniec and J. Liu, *Carbon*, 2017, **116**, 490–499.
- J. Liu, T. Yang, D.-W. Wang, G. Q. Lu, D. Zhao and S. Z. Qiao, *Nat. Commun.*, 2013, **4**, 2798.
- H. Tian, H. Liu, T. Yang, J.-P. Veder, G. Wang, M. Hu, S. Wang, M. Jaroniec and J. Liu, *Mater. Chem. Front.*, 2017, **1**, 823–830.
- V. Budarin, J. H. Clark, J. J. E. Hardy, R. Luque, K. Milkowski, S. J. Tavener and A. J. Wilson, *Angew. Chem. Int. Ed.*, 2006, **45**, 3782–3786.
- R. J. White, C. Antonio, V. L. Budarin, E. Bergström, J. Thomas-Oates and J. H. Clark, *Adv. Funct. Mater.*, 2010, **20**, 1834–1841.
- R. J. White, V. L. Budarin and J. H. Clark, *Chem. Eur. J.*, 2010, **16**, 1326–1335.

- 43 R. Luque, J. H. Clark, K. Yoshida and P. L. Gai, *Chem. Commun.*, 2009, **0**, 5305–5307.
- 44 R. Luque, V. Budarin, J. H. Clark and D. J. Macquarrie, *Appl. Catal., B*, 2008, **82**, 157–162.
- 45 H. L. Parker, A. J. Hunt, V. L. Budarin, P. S. Shuttleworth, K. L. Miller and J. H. Clark, *RSC Adv.*, 2012, **2**, 8992–8997.
- 46 A. Muñoz García, A. J. Hunt, V. L. Budarin, H. L. Parker, P. S. Shuttleworth, G. J. Ellis and J. H. Clark, *Green Chemistry*, 2015, **17**, 2146–2149.
- 47 H. L. P. A. M. G. A. H. K. A. T. J. F. H. H. J. H. C. A. J. H. Jennifer R Dodson, *Green Chem.*, 2015, **17**, 1951–1965.
- 48 J. C. Colmenares, P. Lisowski and D. Łomot, *RSC Adv.*, 2013, **3**, 20186–7.
- 49 S. Kim, A. M. Escamilla-Pérez, M. De Bruyn, J. G. Alauzun, N. Louvain, N. Brun, D. Macquarrie, L. Stievano, B. Boury, L. Monconduit and P. H. Mutin, *J. Mater. Chem. A*, 2017, **5**, 24380–24387.
- 50 A. Borisova, M. De Bruyn, V. L. Budarin, P. S. Shuttleworth, J. R. Dodson, M. L. Segatto and J. H. Clark, *Macromol. Rapid Commun.*, 2015, **36**, 774–779.
- 51 C. Masquelier, M. Tabuchi, K. Ado, R. Kanno, Y. Kobayashi, Y. Maki, O. Nakamura and J. B. Goodenough, *J. Solid State Chem.*, 1996, **123**, 255–266.
- 52 P. Cui, Y. Liang, D. Zhan, Y. Zhao and R. Peng, *RSC Adv.*, 2014, **4**, 43821–43827.
- 53 X. Li, J. Liu, Y. Zhao, H. Zhang, F. Du, C. Lin, T. Zhao and Y. Sun, *ChemCatChem*, 2015, **7**, 1848–1856.
- 54 D. K. Kim, P. Muralidharan, H.-W. Lee, R. Ruffo, Y. Yang, C. K. Chan, H. Peng, R. A. Huggins and Y. Cui, *Nano Lett.*, 2008, **8**, 3948–3952.
- 55 Y. Wang, X. Shao, H. Xu, M. Xie, S. Deng, H. Wang, J. Liu and H. Yan, *J. Power Sources*, 2013, **226**, 140–148.
- 56 C. Zhou, Z. Liu, K. S. Lee and L. Lu, *Electrochim. Acta*, 2016, **212**, 553–560.
- 57 J. Xu, L. Zhang, Y. Wang, T. Chen, M. Al-Shroofy and Y.-T. Cheng, *ACS Appl. Mater. Interfaces*, 2017, **9**, 3562–3569.
- 58 I. Kovalenko, B. Zdyrko, A. Magasinski, B. Hertzberg, Z. Milicev, R. Burtovyy, I. Luzinov and G. Yushin, *Science*, 2011, **334**, 75–79.

View Article Online  
DOI: 10.1039/C8TA04128H

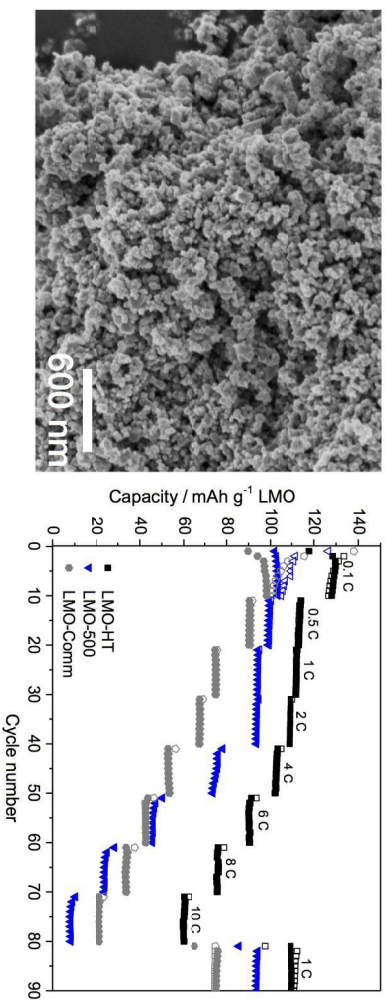

177x68mm (300 x 300 DPI)