



Deposited via The University of Leeds.

White Rose Research Online URL for this paper:

<https://eprints.whiterose.ac.uk/id/eprint/135917/>

Version: Accepted Version

Article:

Saxey, DW, Moser, DE, Piazzolo, S et al. (2018) Atomic worlds: Current state and future of atom probe tomography in geoscience. *Scripta Materialia*, 148. pp. 115-121. ISSN: 1359-6462

<https://doi.org/10.1016/j.scriptamat.2017.11.014>

© 2017 Acta Materialia Inc. Published by Elsevier Ltd. Licensed under the Creative Commons Attribution-Non Commercial No Derivatives 4.0 International License (<https://creativecommons.org/licenses/by-nc-nd/4.0/>).

Reuse

This article is distributed under the terms of the Creative Commons Attribution-NonCommercial-NoDerivs (CC BY-NC-ND) licence. This licence only allows you to download this work and share it with others as long as you credit the authors, but you can't change the article in any way or use it commercially. More information and the full terms of the licence here: <https://creativecommons.org/licenses/>

Takedown

If you consider content in White Rose Research Online to be in breach of UK law, please notify us by emailing eprints@whiterose.ac.uk including the URL of the record and the reason for the withdrawal request.



Atomic worlds: current state and future of atom probe microscopy in geoscience

D.W. Saxey^{*1}, D.E. Moser², S. Piazzolo^{3,4}, S.M. Reddy^{1,5}, J.W. Valley⁶

¹*Geoscience Atom Probe Facility, Advanced Resource Characterisation Facility, John de Laeter Centre, Curtin University, Perth, WA 6102, Australia.*

²*Department of Earth Sciences, University of Western Ontario, London, Canada N6A 5B7.*

³*Department of Earth and Planetary Science, Macquarie University, Sydney, NSW 2109, Australia.*

⁴*School of Earth and Environment, University of Leeds, Leeds LS2 9JT, UK.*

⁵*Department of Applied Geology, Curtin University, Perth, WA 6102, Australia.*

⁶*Department of Geoscience, University of Wisconsin, Madison, WI 53706, USA.*

*Corresponding author: david.saxey@curtin.edu.au

Abstract

Atom Probe Microscopy (APM) is rapidly finding new applications within the geosciences. Historically connected with materials science and semiconductor device applications, recent years have seen an exciting trend as APM has proved a useful tool for nanoscale geochemistry, as it offers unique capabilities when compared with the current suite of conventional geoanalytical techniques. The ability to characterize 3D nanoscale chemistry with isotopic sensitivity, and correlate these results with other analytical techniques, has uncovered intricate details of complex trace element distributions within a variety of minerals and has opened the door to nanoscale isotope geochemistry. Already these advances are having an impact on long-standing questions within geochronology, planetary science and many other fields of research. As this trend gathers pace, we present here a brief summary of the current status of APM geoscience applications and discuss the likely future directions in this developing research space.

Keywords: atom probe tomography; three-dimensional atom probe (3DAP);

Introduction

Earth's diverse range of rock types represents different mixtures of >5000 minerals, the diversity of which has grown over the past 4.4 billion years [1]. Each of these minerals has differing composition and/or crystal structure that reflects the conditions of formation and the subsequent geological evolution that has modified them. Over several hundred years, geoscientists have developed a broad range of analytical techniques to characterise mineral compositions and structures, to shed light on the geological evolution of the planet. However, at a fundamental level, geological processes are governed by the mechanisms that control the nanoscale distribution and mobility of atoms within minerals and their boundaries. Nanoscale analytical techniques thereby underpin our ability to observe, measure and understand such mechanisms. At the sub-nanometer scale, transmission electron microscopy has commonly been used to investigate nanoscale processes in minerals [2–4]. However, this approach is limited to the compositional analysis of major elements and cannot identify individual atoms, or provide trace elements or isotopic compositions that are widely used by geochemists. In recent years, atom probe microscopy (APM) has been increasingly applied to geological minerals to address this shortfall and to investigate a diverse and growing range of nanoscale features and processes. This contribution gives the authors' assessment of pioneering developments over the last few years, reviews the current state of APM in relation to geoscience applications, and forecasts the future developments and exciting possible applications in this rapidly growing field.

Atom Probe Microscopy: A short overview

Atom probe microscopy, or atom probe tomography (APT), is unique among materials analysis techniques in its ability to provide three-dimensional chemical and isotopic information at the atomic scale [5]. Such detailed analysis can be achieved over regions of interest of up to 100s of nm in size, carefully positioned at the apex of a needle-shaped specimen (Fig 1a). In its application to geological samples, which are commonly electrically insulating, the atom probe is usually operated in a 'pulsed-laser' mode, combining a very high electric field at the needle tip with a short laser pulse focused in the same region [6]. Thermal energy from the laser pulse is

1
2
3
4 sufficient to initiate field-evaporation of atoms from the specimen apex, ideally one atom at a
5 time. The specimen is thereby slowly eroded away as the evaporated ions are accelerated from
6 the tip and impact upon a position-sensitive detector (Fig. 1b). Data from the detector are used
7
8 to infer the original 3-D location of each atom within the sample, by applying a reverse-
9
10 projection algorithm to the ion trajectories to generate a three-dimensional point-cloud, or
11
12 'atom map' (Fig. 1c). Importantly for geochemical studies, the detector arrival time can be used
13
14 in time-of-flight mass spectrometry to determine the mass-to-charge ratio of each ion, which
15
16 usually allows all isotopes to be identified with confidence.
17
18

19
20
21 The mass-to-charge ratios are typically presented as a histogram, or 'mass spectrum'
22
23 (Fig. 2). Interpretation of the data requires the association of intervals, or 'ranges', within the
24
25 mass spectrum with particular ionic species [7], which may be elemental or molecular. Multiple
26
27 charge states may also be present for a single species. No pre-selection of elements or isotopes
28
29 is required as the entire spectrum is recorded for each laser pulse, and every atom may be
30
31 considered to be ionized and detected with equal probability.
32

33
34 The ability to confidently interpret APM data requires both site-specific targeting from
35
36 well-characterised locations and non-destructive, correlative imaging of the atom probe
37
38 specimen. The workflow to identify critical locations commonly involves multiple techniques. In
39
40 identifying regions of interest, geoscience atom probe studies have so far utilized SEM-based
41
42 cathodoluminescence (CL) and imaging [8–10], secondary ion mass spectrometry (SIMS) [9],
43
44 electron backscatter diffraction (EBSD) [10–12], x-ray fluorescence microscopy (XFM) [13], and
45
46 backscatter electron (BSE) imaging [9,10,14]. Characterisation of atom probe specimens by
47
48 Transmission Kikuchi Diffraction (TKD) [15] in the SEM has been developed over recent years
49
50 [16,17], and has been used to confirm lattice homogeneity of zircon and baddeleyite reference
51
52 materials [18], and to identify subgrain boundaries and lattice distortions in zircon [11,12].
53
54

55 56 **Geoscience applications of APM**

57
58 Early work on geological materials was performed with voltage-pulsed atom probes,
59
60 which require electrically conductive samples for efficient field-evaporation. This limited the
61
62
63
64
65

1
2
3
4 quantity of data and the variety of materials that could be analysed [19,20]. The advent of
5 commercial laser atom probe systems in the mid-2000s opened the APM technique to non-
6 conducting samples [21–24], including geological materials such as sulphides, carbonates and
7 silicates. Combined with the ability to prepare site-specific samples using focussed ion beam
8 (FIB) techniques [25], this has resulted in a marked increase in the APM analysis of geological
9 materials.

10
11 Over the last decade, a wide variety of mineral phases and multiphase samples have
12 been analysed by APM. Although the majority of the Earth’s accessible minerals are silicates,
13 such as zircon (discussed below), much of the early use of atom probe samples for geomaterials
14 is in the application to non-silicate phases such as oxides, sulphides, sulphates and metals. The
15 earliest reported application to geomaterials is the analysis of a Ni-rich meteoritic alloy [20],
16 with the first terrestrial study focusing on metamorphic magnetite [19].

17
18 Other mineral systems targeted by APM include triuranium octoxide (U_3O_8), an isotope
19 standard, analysed with the aim of distinguishing natural and anthropogenic sources of
20 uranium [26]. Weber and co-workers [27] studied nanoscale structures in barite ($BaSO_4$), with
21 implications for radium contamination. Analysis of a platinum group alloy [28] illustrated the
22 applicability of APM in the study of metallic geomaterials, helping to decipher their origin.

23
24 Several researches have studied carbonate minerals via APM [29–32]. McMurray et al.
25 [31], for example, investigated precipitation mechanisms of calcium carbonate in seawater.
26 However, the application of APM to quantitative chemistry of carbonates still necessitates
27 further development of the APM technique itself as carbonates, especially biominerals, are
28 extremely beam sensitive making it difficult to obtain reliable data [32].

29
30 In recent years, the application of APM on meteoritic materials has seen investigations
31 of meteoritic nanodiamonds [33,34] and interfaces in kamacite-taenite, Fe-Ni alloys from the
32 early solar system [35]. Several recent works have used APM to address planetary or proto-
33 planetary processes [14,36–39].

34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1
2
3
4 The work to date on silicate minerals has focused on the application of atom probe
5 microscopy to understanding nanoscale trace element and isotopic variations in the common
6 accessory mineral zircon ($ZrSiO_4$, Fig. 3a,b). So far, the majority of studies have focused on
7 understanding the mechanisms of Pb mobility and Pb loss, which have fundamental
8 implications for the interpretation of U-Pb geochronological data.
9

10
11
12
13
14
15 The potential for APM to contribute to this field was first highlighted by Valley et al.
16 [9,10], who analyzed a 4.4 billion year old zircon grain and showed that, despite Pb mobility and
17 clustering at the nanoscale, the mineral remained a closed system for Pb at micron length
18 scales and over geological timescales (Fig. 3a). Incompatible elements, including radiogenic Pb
19 and rare earth elements have been shown to diffuse to amorphous domains created by
20 radiation damage in zircons with complex histories [9,10]. Analysis of Pb isotope ratios in these
21 5-10nm clusters solve the Pb-mobility question at an atomic scale, confirm the age of the oldest
22 known zircon from Earth, and represent the first application of nano-geochronology. Analysis of
23 zircon that has lost Pb from its lattice has since shown that Pb distribution in zircon can be
24 represented by isotopically-distinct Pb reservoirs, with nanoscale Pb-clusters being linked to
25 dislocation loops formed during the annealing of U-induced radiation damage [8]. In these
26 studies, the different Pb reservoirs yield different, but geologically-meaningful, age information
27 that can be used to characterize different aspects of the minerals geological evolution.
28
29
30
31
32
33
34
35
36
37
38
39
40

41 In deformed and deforming zircon, mineral defects are shown to control mobility of U
42 and Pb [11] (Fig. 3b). Likewise, a study of zircon from the Stac Fada impactite showed mobility
43 of coupled interstitial and substitutional trace elements linked to defect formation and
44 migration over geologically-instantaneous timescales [12]. Similar approaches are starting to be
45 applied to other U-bearing accessory minerals such as baddeleyite (ZrO_2) [39], where nano-
46 clustering of trace elements, notably Fe, due to a meteorite impact shock wave has created
47 distinctive nanostructures (Fig. 3c). These serve as spatial proxies for crystal volumes that
48 experienced Pb diffusion and record the crater age. In summary, the studies have shown the
49 importance of radiation damage and mineral defects in controlling element mobility, and that
50 the recognition and quantification of different Pb isotopic ratios in nanoscale features has the
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1
2
3
4 potential to both advance our understanding of the controls on this mobility, and to yield new
5 geochronological applications in a broad range of minerals.
6
7

8
9 Other work on silicate minerals includes early studies by several research groups on
10 olivine [40–42], while Bachhav et al. were successful in targeting the chemical make-up of grain
11 boundary structures in natural olivine and orthopyroxene [42].
12
13
14

15
16
17 Research with relevance to the resource industry includes the investigation of nanoscale
18 gold clusters in arsenopyrite [13], which showed that the formation of nanoparticles of gold in
19 arsenopyrite from the Obuasi gold mine of W. Africa was dependent upon crystal growth rates.
20 This ability to characterize precious metal deportment at the nanoscale has fundamental
21 implications for process mineralogy and the optimization of recovery efficiency.
22
23
24
25
26

27 **Reference materials and standardisation**

28
29 The novelty of APM as an analytical tool for geochemistry has prompted investigation of
30 its performance and accuracy. In particular, zircon and badelleyite reference materials have
31 been used to confirm chemical quantification and to optimise acquisition conditions for these
32 minerals [18,43–46]. Conversely, APM has been employed to test the nanoscale homogeneity
33 of existing geostandards [47]. Others have also reported comparisons between APM chemical
34 and isotopic compositions with those from standard materials or other well-characterised
35 samples [26,28,32]. Initiatives have also been undertaken to develop standard approaches to
36 the application of APM within the geosciences, including the proposed standardisation of data
37 reporting [48].
38
39
40
41
42
43
44
45
46
47
48

49 **Future Developments**

50 **Technique development**

51
52 Of central importance to geoscience applications of APM is the ability to correctly
53 identify and quantify elemental and isotopic signatures of interest. Natural metals and minerals
54 tend to have complex compositions in major, minor and trace elements and therefore yield
55 mass spectra that have numerous peaks associated with both elemental species and a
56
57
58
59
60
61
62
63
64
65

1
2
3
4 bewildering array of molecular species (Fig. 2). As well as issues relating to peak identification,
5 this leads to interferences, which are difficult to resolve, and the dilution of low concentration
6 trace elements over multiple, often immeasurable peaks. Consequently, many current
7 challenges relate to optimization of the desired signal, and correct interpretation of these
8 complex mass spectra. Other areas of development include improvements in the accuracy of
9 the spatial three-dimensional reconstruction. In addition, the optimization of sample
10 preparation will be crucial to open up APM to the general geoscience community, enabling
11 routine, cost-effective, and well-constrained data production.
12
13
14
15
16
17
18
19
20

21 Several potential technical advances in APM hardware may bring significant
22 improvements in the future. A modest increase in the mass resolving power, beyond the range
23 of 1000 – 1200 typically attainable at present, could improve discrimination of overlapping
24 mass peaks (Table 1). Improvements in detector efficiency will lead to direct improvements in
25 the quantification of nanoscale chemistry, as uncertainties are very often determined by
26 fundamental limitations arising from the number of atom counts (counting statistics). Similarly,
27 a reduction in detector dead-time could improve efficiency and quantification accuracy by
28 ensuring that all ions are detected equally, even for closely-spaced isotopes. Continued
29 advances in spatial reconstruction accuracy will also play a role, though for the geosciences this
30 aspect of APM data quality may not be as critical as in other applications [49–51]. However,
31 accommodating large evaporation field differences associated with polyphase samples remains
32 important [13,52], and advances in this area will be significant for geoscience studies.
33
34
35
36
37
38
39
40
41
42
43
44
45

46 A particularly exciting prospect for geological applications is the potential development
47 of an energy-sensitive APM detector [53]. This would allow the mass spectra to be filtered for
48 specific charge states, resulting in separation of mass peak overlaps and interferences [54], and
49 a reduction in background noise (Fig 4). This would enable, for example, quantification of ^{208}Pb
50 in zircon, as the $^{208}\text{Pb}^{++}$ and $^{28}\text{Si}_2^{16}\text{O}_3^+$ ions have different charge states. However, increased
51 mass resolving power would still be required to separate ions having the same charge, such as
52 the geologically important $^{40}\text{Ca}^{++}$ and $^{24}\text{Mg}^{16}\text{O}^{++}$ (Table 1).
53
54
55
56
57
58
59
60
61
62
63
64
65

1
2
3
4 Other potential hardware developments include the reduction of residual hydrogen gas
5 in the ultra-high vacuum analysis chamber [55]. This could allow the quantification of water and
6 other volatiles of importance within geological materials, including biologically mediated
7 minerals, as well as reducing peak interferences due to hydride ion formation.
8
9

10
11
12
13 Advances are also likely to arise from improvements and innovations in methodology,
14 particularly as APM is applied to a broader variety of mineral phases and their chemical
15 variants. Progress has been made toward optimization of acquisition conditions and specimen
16 preparation for some specific geological materials, such as zircon, baddeleyite, and magnetite
17 [18,44,46,56,57], but many more sample types require similar attention and technique
18 development. Suitable acquisition conditions may reduce detection limits for particular species,
19 lower the background noise, simplify the mass spectrum, and eliminate peak overlaps by
20 reducing complex molecular ion (e.g. hydride) formation [46]. Likewise, specimen preparation
21 may be optimized to increase specimen yield, and also to reduce ‘thermal tails’ and improve
22 the reproducibility of mass peak shapes. Such repeatability in mass peaks will be of critical
23 importance in applying curve fitting techniques necessary to achieve robust background
24 subtraction and mass peak deconvolution. As a wider variety of geological APM data becomes
25 available, improvements in peak identification and the accurate quantification of peak
26 interferences, particularly hydrides, will provide valuable information required to completely
27 separate and quantify isotopic concentrations.
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42

43 Developments in correlative microscopy, particularly the use of combined physical and
44 chemical characterization techniques such as TEM, TKD, and EBSD [58], along with Nano-
45 Computed Tomography (CT), to identify and characterize regions of interest prior to APM
46 analysis are also likely to play an important part in an advanced methodology for nanoscale
47 geoscience. There is also potential for the integration of high spatial resolution compositional
48 mapping tools such as sub-micron SIMS (nanoSIMS) [59,60] and SEM-based time-of-flight
49 secondary ion mass spectrometry (TOF-SIMS) [61] to identify regions of interest at the sub-
50 micrometre scale. In the geoscience field, characterization of needle-shaped specimens by
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1
2
3
4 transmission electron microscopy has not yet been undertaken [62,63], but is likely to become
5
6 a critical part of the work flow for robust interpretation of atom probe data.
7
8

9 Further developments in specimen preparation will also enable a wider range of
10 geological samples to be targeted, by providing robust methods for the analysis of
11 nanoparticulate materials [33,64], or specimen preparation and coating methods to allow nano-
12 porous or weakly-bonded materials to be analysed [64].
13
14
15
16
17

18 **Applications: Examples and Outlook**

19 **Nanoscale geochemistry: from atomic-scale phenomena to large scale processes**

20 The ability to analyse compositional information in 3D at close to atomic scales has the
21 potential to revolutionise our understanding of the fundamental mechanisms that underpin
22 many geological processes. Primary composition and compositional zoning of major and trace
23 elements provides constraints on igneous [65], metamorphic [66] and sedimentary processes
24 [67] in the Earth's crust and mantle [68], yet very few observations have been made at the
25 nanoscale. Such observations have the potential to yield previously unobtainable information.
26 Secondary processes that can alter elemental distributions in minerals, for example diffusion,
27 will be modified by the presence and distribution of nanoscale defects and interfaces.
28 Segregation of elements at the nanoscale has been shown to control the properties of non-
29 geological materials [69], particularly their rheological behavior [70]. Yet there are currently
30 very few studies investigating the role of such features in geomaterials. The study of these
31 features is clearly possible by APM and has the potential to change our understanding of mass
32 transfer processes throughout geoscience, from biominerals to the formation of ore deposits.
33 Such studies are not limited to Earth's crustal rocks. Volcanic activity may bring mantle samples
34 to the surface, and meteorites represent accessible samples that formed early in the solar
35 system's evolution. One potential challenge with such an approach is that the conditions by
36 which nanoscale features form are often unknown in geological samples. One avenue to
37 address this is in the analysis of minerals formed experimentally, where all extrinsic conditions
38 are constrained. A combination of experimental and empirical approaches therefore seems to
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1
2
3
4 be a clear way forward. Such studies will be strengthened by simulations, utilizing molecular
5 dynamics techniques to underpin observations with theoretical understanding [71].
6
7

9 **Isotopic analysis: tracers and chronometers**

10 Application of APM to radiogenic isotope geochemistry has been demonstrated using
11 the U-Pb system [8–10]. And other radiogenic systems, such as Sm-Nd and Re-Os, also appear
12 amenable to the technique, where concentrations permit [72]. Within this field, the atom probe
13 is an ideal tool for determining the origin and history of geological materials from sub-micron
14 isotopic signatures, which are often not resolvable using other techniques. Central to this
15 application is the ability to accurately determine isotopic ratios from APM data. The highest
16 accuracy is expected for single-element isotope ratios (e.g. $^{207}\text{Pb}/^{206}\text{Pb}$), which are aided by the
17 absence of chemical-dependent effects on charge-state, molecular ion formation and mass
18 peak shape [8,9,43]. For isotopic ratios between different elements (e.g. $^{206}\text{Pb}/^{238}\text{U}$) absolute
19 quantification of each element is required with high accuracy. In these cases, optimization of
20 acquisition conditions and developments in mass spectral data analysis will be essential for
21 further advances.
22
23
24
25
26
27
28
29
30
31
32
33
34
35

36 Isotopic fractionation in stable isotope systems is also expected to be accessible to APM,
37 though fractionations are typically smaller than for radiogenic systems. As an indicator of
38 potential applications, Table 2 compares a model uncertainty for fractionation data derived
39 from APM measurements with the range of natural fractionation observed for each element
40 [73], assuming that isobaric interferences can be resolved. For many light element isotopes,
41 which tend to exhibit significant fractionations due to their large relative mass difference
42 between isotopes, the sensitivity of APM over reasonable length scales is sufficient to detect
43 meaningful levels of fractionation. The values are calculated for one million detected atoms and
44 the uncertainty will reduce as more atoms are collected for a particular element. Depending on
45 the atomic density of the sample and element composition, one million detected atoms
46 corresponds to a 3-dimensional feature as small as 40 – 50nm. A significant challenge to
47 development of stable isotope analysis via APM will be the avoidance or correction of mass
48 interferences, particularly hydrides [33].
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1
2
3
4 The aforementioned advances in mass spectrum peak shape determination and
5 modelling would provide a step advance in the ability to quantify both chemical compositions
6 and isotopic ratios by APM, and would open the possibility of analysing stable isotope systems
7 at sub-micron scales. It is important to note that there is a fundamental limit to nanoscale
8 chemical and isotopic measurements due to the granularity of atomic matter and the
9 corresponding limitations imposed by Poissonian counting statistics that govern such sampling
10 methods. However, APM is well-suited for approaching the limits of such measurements
11 because of its relatively high ionization and detection efficiency (~80% in the CAMECA LEAP
12 5000X atom probe). Future technical advances, such as the reduction of detector dead-time,
13 optimizations aimed at lowering background noise and peak tails, as well as increases in
14 detector efficiency, will yield further incremental improvements in accuracy and sensitivity
15 relevant to isotope geochemistry. Furthermore, a wide range of new experiments can be
16 designed using synthetically enriched isotope ratios to investigate processes such as mineral-
17 growth, unmixing, or diffusion at single-nanometer scale. Isotopic labels offer the advantage
18 that different isotopes behave the same chemically yet can be distinguished by APM. If high
19 concentrations of a trace isotope are added to an experiment, the contrast is identifiable at
20 nanometer scales, allowing studies ranging from rate and process for diffusion and
21 crystallization kinetics, to subcellular chemistry in microfossils.

22 **Deformation and Defect Analysis**

23
24 So far, the effect of deformation structures and dislocation movement on chemical
25 variations at the nanometer scale has been shown only for zircon [11,12] and baddeleyite
26 [38,39]. However, many other minerals may behave similarly. Importantly, the selectivity of the
27 process of deformation induced elemental mobility will affect the elemental ratios, which are
28 used for geobarometry (garnet, pyroxenes) and for determination of igneous and metasomatic
29 history (e.g. olivine, [68]). Therefore, knowledge of deformation enhanced diffusion and
30 elemental redistribution will be important across a variety of minerals, and not only those
31 commonly used in geochronology (e.g. zircon, baddeleyite, apatite, titanite and rutile). In these
32 cases, local changes to chemical composition significantly affect the geological interpretation of
33 the rock from which the mineral stems.

1
2
3
4 Furthermore, it has been shown that incorporation of hydrogen in the crystal lattice has
5 a marked effect on the rheology and slip system activation in geologically important minerals,
6 such as olivine [74–76] and quartz [77]. For example, changes in hydrogen content in olivine will
7 influence the seismic signal of deformed mantle rocks, which is used to infer mantle flow and
8 large scale plate tectonic processes such as subduction zone behavior [78]. Consequently, in-
9 depth understanding of the effect of deformation and deformation structures on hydrogen
10 uptake and expulsion is of pivotal interest to the geoscience community.
11
12
13
14
15
16
17
18
19

20 **Reaction interfaces and diffusion**

21 The mechanisms by which reactions occur between individual mineral grains or
22 between a mineral and a fluid (i.e. free water-rich fluid or melt) govern the progression of
23 reactions, and with that the physiochemical behavior of geomaterials. The surface chemistry of
24 the interface at the atomic scale plays a major role in these reactions [79], and APM is perfectly
25 suited to investigate such interfaces, as evidenced by extensive applications within materials
26 science [7,80–82]. APM is therefore likely to become an emerging technique for interface
27 chemistry analysis of geomaterials.
28
29
30
31
32
33
34
35
36

37 Some related fields for which APM will be important include, leaching of contaminants
38 from waste materials [83], weathering of surfaces (e.g. [79]), preservation of cultural heritage,
39 and metamorphic geology. In metamorphic geology, the rate of reaction progress is
40 traditionally thought to depend on diffusion both within grains and at grain boundaries (e.g.
41 [84]). A competing theory suggests that many reactions occur through fluid-mediated
42 dissolution and precipitation [85], with much faster kinetics. With APM, this still unresolved
43 question may be answered. In diffusion dominated reactions, the area right next to the
44 interface of the reacting minerals should show a diffusion profile with elemental gradients;
45 however, in the case of dissolution-precipitation reaction, a sharp, atomic-scale interface is
46 expected [79,81,85].
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1
2
3
4
5 Another application of APM is foreseen for diffusion studies [86–89], where the
6
7 elemental diffusion profile at mineral interfaces is used to derive time-scales of volcanic-
8
9 eruptions (e.g. [90,91]). For such studies, the spatial resolution offered by APM opens new
10
11 avenues of diffusion profile modelling and verification against data from natural samples.
12
13

14 **Standardisation of analytical procedure and data analysis**

15 Finally, further studies are required to systematically investigate the influence of
16
17 specimen preparation and the conditions of analysis on the accuracy of APM analyses across a
18
19 variety of minerals. Recent work has shown that chemical values derived from APM of zircon,
20
21 at length scales of the specimen needle and below, are precise and reasonably accurate, though
22
23 minor artefacts may arise depending on the analysis conditions [44,46]. A current effort from
24
25 eight APM laboratories around the world is investigating these effects systematically using a
26
27 reference material used in zircon geochronology [47], which has been shown to be chemically
28
29 homogeneous at the nanometer scale. In the future, such rigorous evaluation of the accuracy of
30
31 APM data will be necessary for other minerals.
32
33

34 While reference materials, or standards, are widely used in ion- and electron-
35
36 microprobe techniques, they are expected to be of limited use within APM. Although small
37
38 systematic errors are often present in the analysis [46], the technique does not lend itself to
39
40 correction using standards, as the analysis conditions cannot be reliably replicated between the
41
42 standard and the specimen of interest. In particular, the voltage applied to the specimen, the
43
44 heating from the laser pulse and the shape of the specimen tip cannot be tightly controlled
45
46 between acquisitions from two separate specimens.
47
48

49 **Conclusions**

50
51 The reconstruction of the nature and sequence of the processes that have created our
52
53 planet and its resources is a major component of Earth and planetary science research, and is
54
55 part of a discipline going back hundreds of years when ideas on the atomic makeup of minerals
56
57 were just crystallizing. Atom probe microscopy, in conjunction with other micro- and nano-
58
59 analysis techniques, is thus opening up a broad new world of discovery in this vein. Even though
60
61
62
63
64
65

1
2
3
4 a relatively small number of minerals has so far been explored, a diverse range of nano-features
5
6 has already been revealed, corresponding to the formation of the solar system, early
7
8 continents, giant craters, precious metals, and flowing deep crust. Dozens of important rock-
9
10 forming minerals from Earth and space remain to be analysed using current techniques, and
11
12 studies of many diffusion phenomena in cool near-surface and deep, high-temperature
13
14 environments have yet to be carried out. Promising developments in instrumentation to
15
16 increase mass and spatial resolution, together with improved work flow through interfacing
17
18 with reference and experimental samples, will amplify an already rapid pace of discovery with
19
20 regard to atom probe microscopy in geoscience.
21
22

23 **Acknowledgements**

24
25 The Geoscience Atom Probe at Curtin University is part of the Advanced Resource
26
27 Characterisation Facility under the auspices of the National Resource Sciences Precinct—a
28
29 collaboration between the Commonwealth Scientific and Industrial Research Organization,
30
31 Curtin University, and the University of Western Australia—and is supported by the Science and
32
33 Industry Endowment Fund (SIEF RI13-01). SP thanks the Australian Research Council for
34
35 financial support (FT1101100070). DEM gratefully acknowledges research support through a
36
37 Canadian NSERC-Discovery Grant. JWV is supported by the U.S. National Science Foundation
38
39 (EAR-1524336), the Department of Energy (DE-FG02-93ER14389) and the NASA Astrobiology
40
41 Institute. The authors shared many fruitful discussions with Drs. David Larson, Tom Kelly, Dave
42
43 Reinhard and other CAMECA-AMETEK scientists at the Madison, WI laboratory.
44

45 **References**

- 46
47
48 [1] R.M. Hazen, D. Papineau, W. Bleeker, R.T. Downs, J.M. Ferry, T.J. McCoy, D.A. Sverjensky, H.
49
50 Yang, *Am. Mineral.* 93 (2008) 1693–1720.
51
52 [2] P. Buseck, J. Cowley, L. Eyring, *High-Resolution Transmission Electron Microscopy: And*
53
54 *Associated Techniques*, Oxford University Press, 1989.
55
56 [3] M.R. Lee, *Mineral. Mag.* 74 (2010) 1–27.
57
58 [4] A.C. McLaren, *Transmission Electron Microscopy of Minerals and Rocks*, Cambridge
59
60 University Press, 2005.
61
62 [5] T.F. Kelly, D.J. Larson, *Annu. Rev. Mater. Res.* 42 (2012) 1–31.
63
64
65

- 1
2
3
4 [6] D.J. Larson, T.J. Prosa, R.M. Ulfig, B.P. Geiser, T.F. Kelly, Local Electrode Atom Probe
5 Tomography, Springer New York, New York, NY, 2013.
6
7 [7] B. Gault, M.P. Moody, J.M. Cairney, S.P. Ringer, Atom Probe Microscopy, Springer New
8 York, New York, NY, 2012.
9
10 [8] E.M. Peterman, S.M. Reddy, D.W. Saxey, D.R. Snoeyenbos, W.D.A. Rickard, D. Fougereuse,
11 A.R.C. Kylander-Clark, *Sci. Adv.* 2 (2016) e1601318.
12
13 [9] J.W. Valley, D.A. Reinhard, A.J. Cavosie, T. Ushikubo, D.F. Lawrence, D.J. Larson, T.F. Kelly,
14 D.R. Snoeyenbos, A. Strickland, *Am. Mineral.* 100 (2015) 1355–1377.
15
16 [10] J.W. Valley, A.J. Cavosie, T. Ushikubo, D.A. Reinhard, D.F. Lawrence, D.J. Larson, P.H.
17 Clifton, T.F. Kelly, S.A. Wilde, D.E. Moser, M.J. Spicuzza, *Nat. Geosci.* 7 (2014) 219–223.
18
19 [11] S. Piazzolo, A. La Fontaine, P. Trimby, S. Harley, L. Yang, R. Armstrong, J.M. Cairney, *Nat.*
20 *Commun.* 7 (2016) 10490.
21
22 [12] S.M. Reddy, A. van Riessen, D.W. Saxey, T.E. Johnson, W.D.A. Rickard, D. Fougereuse, S.
23 Fischer, T.J. Prosa, K.P. Rice, D.A. Reinhard, Y. Chen, D. Olson, *Geochim. Cosmochim. Acta*
24 195 (2016) 158–170.
25
26 [13] D. Fougereuse, S.M. Reddy, D.W. Saxey, W.D.A. Rickard, A. van Riessen, S. Micklethwaite,
27 *Am. Mineral.* 101 (2016) 1916–1919.
28
29 [14] L. Daly, P.A. Bland, D.W. Saxey, S.M. Reddy, D. Fougereuse, W.D. Rickard, L.V. Forman,
30 *Geology* 45 (2017) 847–850.
31
32 [15] P.W. Trimby, *Ultramicroscopy* 120 (2012) 16–24.
33
34 [16] K. Babinsky, R. De Kloe, H. Clemens, S. Primig, *Ultramicroscopy* 144 (2014) 9–18.
35
36 [17] A.J. Breen, K. Babinsky, A.C. Day, K. Eder, C.J. Oakman, P.W. Trimby, S. Primig, J.M.
37 Cairney, S.P. Ringer, *Microsc. Microanal.* (2017) 1–12.
38
39 [18] D.A. Reinhard, D.E. Moser, I. Martin, K.P. Rice, Y. Chen, D. Olson, D.F. Lawrence, T.J. Prosa,
40 D.J. Larson, in: D.E. Moser, F. Corfu, J.R. Darling, S.M. Reddy, K.T. Tait (Eds.), *Microstruct.*
41 *Geochronol.*, AGU/Wiley Publishing, 2017.
42
43 [19] K.R. Kuhlman, R.L. Martens, T.F. Kelly, N.D. Evans, M.K. Miller, *Ultramicroscopy* 89 (2001)
44 169–176.
45
46 [20] M.K. Miller, K.F. Russell, *Surf. Sci.* 266 (1992) 441–445.
47
48 [21] J.H. Bunton, J.D. Olson, D.R. Lenz, T.F. Kelly, *Microsc. Microanal.* 13 (2007) 418–427.
49
50 [22] B. Deconihout, F. Vurpillot, B. Gault, G. Da Costa, M. Bouet, A. Bostel, D. Blavette, A.
51 Hideur, G. Martel, M. Brunel, *Surf. Interface Anal.* 39 (2007) 278–282.
52
53 [23] B. Gault, F. Vurpillot, A. Vella, M. Gilbert, A. Menand, D. Blavette, B. Deconihout, *Rev. Sci.*
54 *Instrum.* 77 (2006) 043705.
55
56 [24] K. Hono, T. Ohkubo, Y.M. Chen, M. Kodzuka, K. Oh-ishi, H. Sepehri-Amin, F. Li, T. Kinno, S.
57 Tomiya, Y. Kanitani, *Ultramicroscopy* 111 (2011) 576–583.
58
59 [25] M.K. Miller, K.F. Russell, K. Thompson, R. Alvis, D.J. Larson, *Microsc. Microanal.* 13 (2007)
60 428–436.
61
62
63
64
65

- 1
2
3
4 [26] A.J. Fahey, D.E. Perea, J. Bartrand, B.W. Arey, S. Thevuthasan, *J. Environ. Radioact.* 153
5 (2016) 206–213.
6
7 [27] J. Weber, J. Barthel, F. Brandt, M. Klinkenberg, U. Breuer, M. Kruth, D. Bosbach, *Chem.*
8 *Geol.* 424 (2016) 51–59.
9
10 [28] S.W. Parman, D.R. Diercks, B.P. Gorman, R.F. Cooper, *Am. Mineral.* 100 (2015) 852–860.
11
12 [29] O. Branson, E.A. Bonnin, D.E. Perea, H.J. Spero, Z. Zhu, M. Winters, B. Hönisch, A.D.
13 Russell, J.S. Fehrenbacher, A.C. Gagnon, *Proc. Natl. Acad. Sci.* (2016) 201522864.
14 [30] A.R. Felmy, O. Qafoku, B.W. Arey, L. Kovarik, J. Liu, D. Perea, E.S. Ilton, *Chem. Geol.* 395
15 (2015) 119–125.
16
17 [31] S. McMurray, B. Gorman, D. Diercks, *Microsc. Microanal.* 17 (2011) 758–759.
18
19 [32] A. Pérez-Huerta, F. Laiginhas, D.A. Reinhard, T.J. Prosa, R.L. Martens, *Micron* 80 (2016) 83–
20 89.
21
22 [33] P.R. Heck, F.J. Stadermann, D. Isheim, O. Auciello, T.L. Daulton, A.M. Davis, J.W. Elam, C.
23 Floss, J. Hiller, D.J. Larson, J.B. Lewis, A. Mane, M.J. Pellin, M.R. Savina, D.N. Seidman, T.
24 Stephan, *Meteorit. Planet. Sci.* 49 (2014) 453–467.
25
26 [34] J.B. Lewis, D. Isheim, C. Floss, D.N. Seidman, *Ultramicroscopy* 159 (2015) 248–254.
27
28 [35] S.S. Rout, P.R. Heck, D. Isheim, T. Stephan, A.M. Davis, D.N. Seidman, *Microsc. Microanal.*
29 21 (2015) 1313–1314.
30
31 [36] P. Gopon, M.J. Spicuzza, T.F. Kelly, D. Reinhard, T.J. Prosa, J. Fournelle, *Meteorit. Planet.*
32 *Sci.* 52 (2017) 1941–1962.
33
34 [37] B.P. Gorman, D.R. Diercks, S. Parman, R. Cooper, *Microsc. Microanal.* 21 (2015) 1311–
35 1312.
36
37 [38] L.F. White, J.R. Darling, D.E. Moser, D.A. Reinhard, J. Dunlop, D.J. Larson, in: D.E. Moser, F.
38 Corfu, J.R. Darling, S.M. Reddy, K.T. Tait (Eds.), *Microstruct. Geochronol.*, AGU/Wiley
39 Publishing, 2017.
40
41 [39] L.F. White, J.R. Darling, D.E. Moser, D.A. Reinhard, T.J. Prosa, D. Bullen, D. Olson, D.J.
42 Larson, D. Lawrence, I. Martin, *Nat. Commun.* 8 (2017) 15597.
43
44 [40] B.W. Arey, D.E. Perea, L. Kovarik, R.J. Colby, J. Liu, O. Qafoku, A.R. Felmy, *Microsc.*
45 *Microanal.* 20 (2014) 998–999.
46
47 [41] B.W. Arey, D. Perera, L. Kovarik, O. Qafoku, A. Felmy, B. Gorman, *Microsc. Microanal.* 18
48 (2012) 658–659.
49
50 [42] M. Bachhav, Y. Dong, P. Skemer, E.A. Marquis, *Microsc. Microanal.* 21 (2015) 1315–1316.
51
52 [43] T. Blum, D.A. Reinhard, Y. Chen, T.J. Prosa, J.W. Valley, in: D.E. Moser, F. Corfu, J.R.
53 Darling, S.M. Reddy, K.T. Tait (Eds.), *Microstruct. Geochronol.*, AGU/Wiley Publishing,
54 2017.
55
56 [44] A. La Fontaine, S. Piazzolo, P. Trimby, L. Yang, J.M. Cairney, *Microsc. Microanal.* (2017) 1–
57 10.
58
59
60
61
62
63
64
65

- 1
2
3
4 [45] D.A. Reinhard, D.E. Moser, I.R. Barker, D. Olson, I. Martin, K.P. Rice, Y. Chen, D. Lawrence,
5 T.J. Prosa, D.J. Larson, *Microsc. Microanal.* 21 (2015) 851–852.
- 6 [46] D.W. Saxey, S.M. Reddy, D. Fougerouse, W.D.A. Rickard, in: D.E. Moser, F. Corfu, J.R.
7 Darling, S.M. Reddy, K.T. Tait (Eds.), *Microstruct. Geochronol.*, AGU/Wiley Publishing,
8 2017.
- 9 [47] S. Piazzolo, E. Belousova, A. La Fontaine, C. Corcoran, J.M. Cairney, *Chem. Geol.* 456 (2017)
10 10–18.
- 11 [48] T. Blum, J. Darling, T.F. Kelly, D.J. Larson, D.E. Moser, A. Perez-Huerta, T.J. Prosa, S. Reddy,
12 D.A. Reinhard, D. Saxey, R. Ulfig, J.W. Valley, in: D.E. Moser, F. Corfu, J.R. Darling, S.M.
13 Reddy, K.T. Tait (Eds.), *Microstruct. Geochronol.*, AGU/Wiley Publishing, 2017.
- 14 [49] T.F. Kelly, D.J. Larson, K. Thompson, R.L. Alvis, J.H. Bunton, J.D. Olson, B.P. Gorman, *Annu.*
15 *Rev. Mater. Res.* 37 (2007) 681–727.
- 16 [50] D.J. Larson, B. Gault, B.P. Geiser, F. De Geuser, F. Vurpillot, *Curr. Opin. Solid State Mater.*
17 *Sci.* 17 (2013) 236–247.
- 18 [51] F. Vurpillot, N. Rolland, R. Estivill, S. Duguay, D. Blavette, *Semicond. Sci. Technol.* 31 (2016)
19 074002.
- 20 [52] N. Rolland, D.J. Larson, B.P. Geiser, S. Duguay, F. Vurpillot, D. Blavette, *Ultramicroscopy*
21 159 (2015) 195–201.
- 22 [53] T.F. Kelly, *Microsc. Microanal.* 17 (2011) 1–14.
- 23 [54] S.R. Broderick, A. Bryden, S.K. Suram, K. Rajan, *Ultramicroscopy* 132 (2013) 121–128.
- 24 [55] Y. Ishikawa, V. Nemanič, *Vacuum* 69 (2003) 501–512.
- 25 [56] L.M. Gordon, D. Joester, *Nature* 469 (2011) 194–197.
- 26 [57] D.K. Schreiber, A.N. Chiaramonti, L.M. Gordon, K. Kruska, *Appl. Phys. Lett.* 105 (2014)
27 244106.
- 28 [58] S.M. Reddy, D.W. Saxey, W.D.A. Rickard, D. Fougerouse, A. van Riessen, in: *Conf. Proc.*
29 *EMAS 2017 IUMAS-7*, Konstanz, Germany, 2017, pp. 150–158.
- 30 [59] D.K. Schreiber, M.J. Olszta, D.W. Saxey, K. Kruska, K.L. Moore, S. Lozano-Perez, S.M.
31 Bruemmer, *Microsc. Microanal.* 19 (2013) 676–687.
- 32 [60] J.B. Seol, N.S. Lim, B.H. Lee, L. Renaud, C.G. Park, *Met. Mater. Int.* 17 (2011) 413–416.
- 33 [61] W.D.A. Rickard, S.M. Reddy, D.W. Saxey, D. Fourgerouse, A. van Riessen, in: *Proc. Microsc.*
34 *Microanal. 2016*, Microscopy Society of America, Columbus, Ohio, 2016, pp. 684–685.
- 35 [62] M. Herbig, *Scr. Mater.* In Press (2017).
- 36 [63] W. Lefebvre-Ulrikson, in: W. Lefebvre, F. Vurpillot, X. Sauvage (Eds.), *At. Probe Tomogr.*
37 *Put Theory Pract.*, 1st ed., Academic Press, 2016.
- 38 [64] P. Felfer, T. Li, K. Eder, H. Galinski, A.P. Magyar, D.C. Bell, G.D.W. Smith, N. Kruse, S.P.
39 Ringer, J.M. Cairney, *Ultramicroscopy* 159 (2015) 413–419.
- 40 [65] C. Ginibre, G. Wörner, A. Kronz, *Elements* 3 (2007) 261–266.
- 41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

- 1
2
3
4
5 [66] M.J. Kohn, S.L. Corrie, *Earth Planet. Sci. Lett.* 311 (2011) 136–143.
- 6
7 [67] T. Götte, T. Pettke, K. Ramseyer, M. Koch-Muller, J. Mullis, *Am. Mineral.* 96 (2011) 802–
8 813.
- 9
10 [68] S.F. Foley, D. Prelevic, T. Rehfeldt, D.E. Jacob, *Earth Planet. Sci. Lett.* 363 (2013) 181–191.
- 11 [69] E.A. Marquis, M. Bachhav, Y. Chen, Y. Dong, L.M. Gordon, A. McFarland, *Curr. Opin. Solid*
12 *State Mater. Sci.* 17 (2013) 217–223.
- 13
14 [70] S. Floreen, J. Westbrook, *Acta Metall.* 17 (1969) 1175–1181.
- 15
16 [71] R. Skelton, A.M. Walker, *Phys. Chem. Miner.* 42 (2015) 677–691.
- 17
18 [72] L. Daly, P.A. Bland, L.V. Forman, D.W. Saxey, S.M. Reddy, W.D.A. Rickard, D. Fougereuse, S.
19 Tessalina, A.L. Fontaine, L. Yang, P.W. Trimby, J. Cairney, S.P. Ringer, B.F. Schaefer, in:
20 80th Annu. Meet. Meteorit. Soc., 2017.
- 21 [73] J. Hoefs, *Stable Isotope Geochemistry*, Springer International Publishing, Cham, 2015.
- 22 [74] S.-I. Karato, M.S. Paterson, J.D. FitzGerald, *J. Geophys. Res. Solid Earth* 91 (1986) 8151–
23 8176.
- 24 [75] I. Katayama, H. Jung, S. Karato, *Geology* 32 (2004) 1045–1048.
- 25 [76] J. Korenaga, S.-I. Karato, *J. Geophys. Res.* 113 (2008) B02403.
- 26 [77] A.K. Kronenberg, J. Tullis, *J. Geophys. Res. Solid Earth* 89 (1984) 4281–4297.
- 27 [78] I. Katayama, S. Karato, *Phys. Earth Planet. Inter.* 157 (2006) 33–45.
- 28 [79] R. Hellmann, R. Wirth, D. Daval, J.-P. Barnes, J.-M. Penisson, D. Tisserand, T. Epicier, B.
29 Florin, R.L. Hervig, *Chem. Geol.* 294–295 (2012) 203–216.
- 30 [80] A. Devaraj, D.E. Perea, J. Liu, L.M. Gordon, T.J. Prosa, P. Parikh, D.R. Diercks, S. Meher, R.P.
31 Kolli, Y.S. Meng, S. Thevuthasan, *Int. Mater. Rev.* (2017) 1–34.
- 32 [81] R. Hellmann, S. Cotte, E. Cadel, S. Malladi, L.S. Karlsson, S. Lozano-Perez, M. Cabié, A.
33 Seyeux, *Nat. Mater.* 14 (2015) 307–311.
- 34 [82] M.K. Miller, *J. Mater. Sci.* 41 (2006) 7808–7813.
- 35 [83] C.S. Kirby, J.D. Rimstidt, *Environ. Sci. Technol.* 28 (1994) 443–451.
- 36 [84] R.H. Vernon, G.L. Clarke, *Principles of Metamorphic Petrology*, Cambridge University Press,
37 2008.
- 38 [85] A. Putnis, *Rev. Mineral. Geochem.* 70 (2009) 87–124.
- 39 [86] O. Cojocaru-Mirédin, C. Perrin-Pellegrino, D. Mangelinck, D. Blavette, *Microelectron. Eng.*
40 87 (2010) 271–273.
- 41 [87] D. Mangelinck, K. Hoummada, A. Portavoce, C. Perrin, R. Daineche, M. Descoins, D.J.
42 Larson, P.H. Clifton, *Scr. Mater.* 62 (2010) 568–571.
- 43 [88] S. Park, W. Jung, C. Park, *Met. Mater. Int.* 19 (2013) 1117–1121.
- 44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

[89] G. Schmitz, C.-B. Ene, C. Nowak, *Acta Mater.* 57 (2009) 2673–2683.

[90] G.N. Kilgour, K.E. Saunders, J.D. Blundy, K.V. Cashman, B.J. Scott, C.A. Miller, *J. Volcanol. Geotherm. Res.* 288 (2014) 62–75.

[91] D.J. Morgan, S. Blake, N.W. Rogers, B. DeVivo, G. Rolandi, R. Macdonald, C.J. Hawkesworth, *Earth Planet. Sci. Lett.* 222 (2004) 933–946.

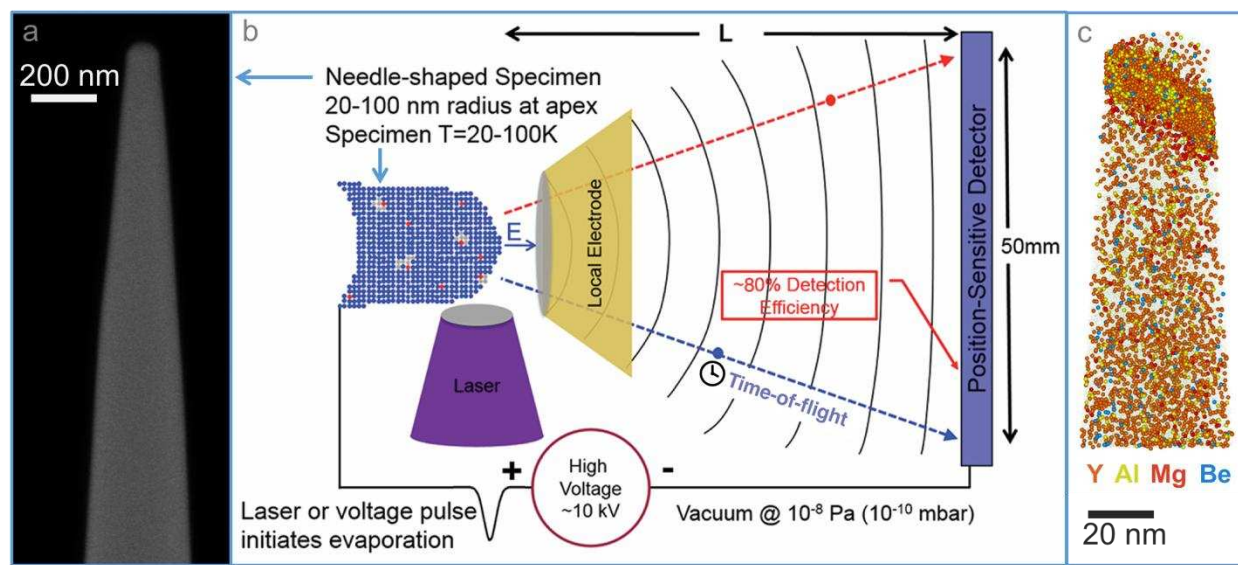


Figure 1: a) Scanning electron microscope image of an APM specimen needle. b) Schematic view of the atom probe microscope from Valley et al. [9]. The laser pulse incident on the specimen apex initiates field-evaporation of ions from the surface. Ions are projected by the strong electrostatic field on to the position-sensitive detector, creating a highly magnified 'image' of the specimen surface. Measurement of the ion flight times, from laser pulse to detector impact, allows the ion identities to be determined by time-of-flight mass spectrometry. c) The detector data can be used to reconstruct the original three-dimensional location of each detected atom within the specimen. The atom map here shows the distribution of trace elements within a sample of shocked zircon [12].

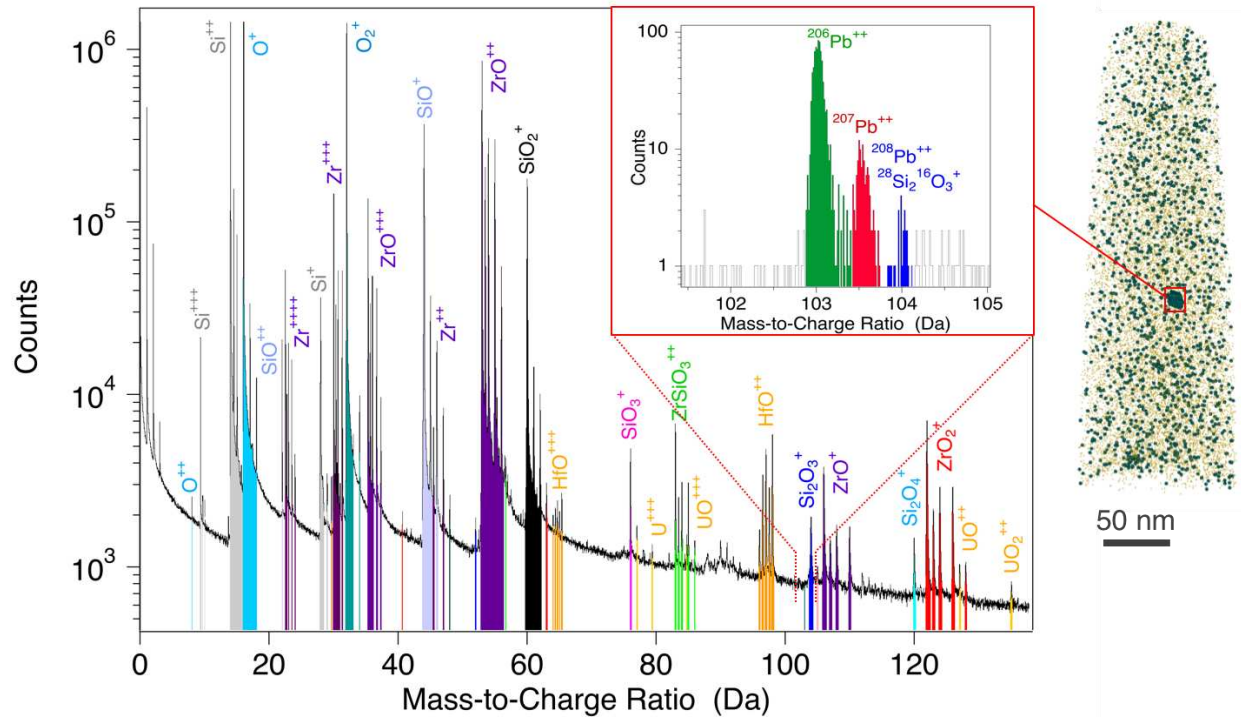


Figure 2: An APM mass spectrum obtained from a zircon sample, showing the ranges (coloured bands) used to identify each atomic or molecular ion species. The atom map (right side) shows the distribution of Pb atoms within the grain. Selecting only the atoms in close proximity to a ~10 nm Pb-rich cluster allows the Pb isotopes to be clearly identified in the reduced mass spectrum (inset). From Peterman et al. [8].

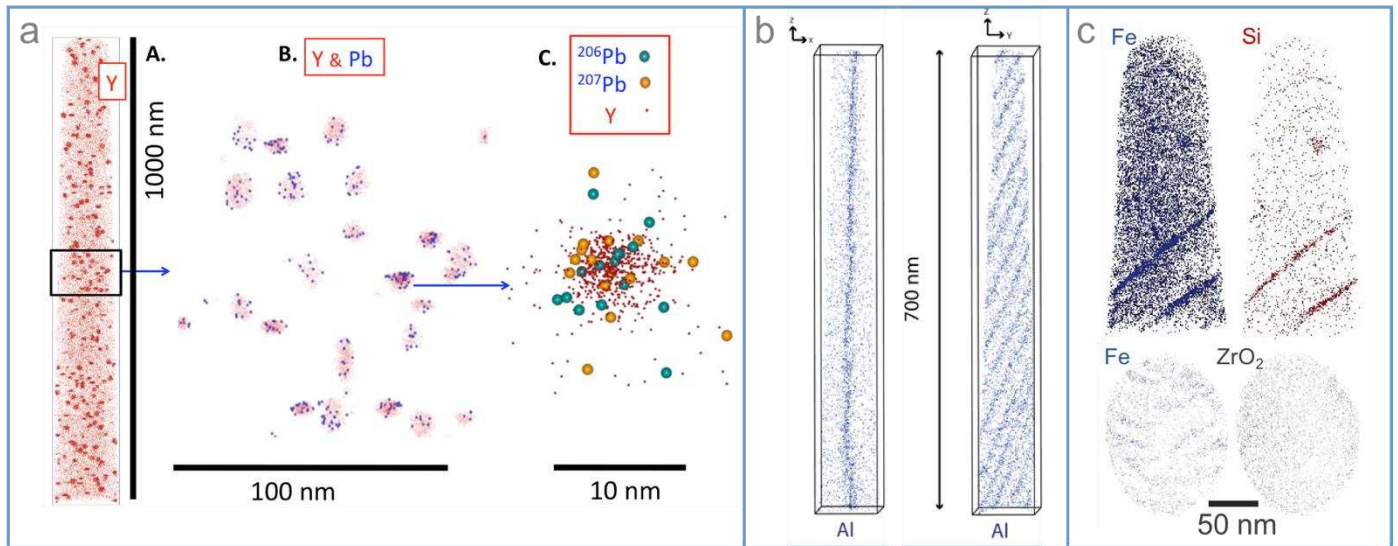


Figure 3:

a) APM of zircons ($ZrSiO_4$). A: Full specimen 3D atom map ($\sim 1000 \times 100$ nm) from a 4.4 billion year old zircon showing the distribution of Y atoms. Darker domains are clusters of 100's of atoms. B: Clusters from A are isolated and enlarged, showing atoms of Y (orange) and Pb (blue) co-localized in clusters. C: Single cluster from B: Y (orange), ^{206}Pb (green), ^{207}Pb (yellow). Y and rare earth elements are concentrated by a factor of 60 in clusters, which have average diameters of 5-10 nm and closest-neighbor spacing averaging 25 nm. The ratios of $^{207}Pb/^{206}Pb$ show that Pb is radiogenic and that clusters formed ca 1 billion years later than the zircon. Clusters are interpreted to form by diffusion of Pb and rare earth elements to amorphous domains formed by alpha-recoil of daughter atoms on emission of α -particles. These results confirm the age of the oldest known solid material from Earth and are interpreted to indicate that conditions habitable for life existed on Earth over 800 million years before the earliest known microfossils. From Valley et al. [9,10].

b) Distribution of aluminium atoms on a low angle grain boundary in a 2.5 billion year old deformed zircon grain. Note the 90 degrees rotation between the two atom maps. The Al atoms decorate a regularly spaced array of dislocation cores that form the boundary. The authors interpret that this decoration is a consequence of trace element attraction and accumulation during dislocation movement. Consequently, crystal plastic deformation can significantly change the local elemental make up of a mineral. From Piazzolo et al. [11].

c) APM atom maps from a 2.5 billion year old baddeleyite (monoclinic zirconia (ZrO_2)) grain from the edge of the 1.85 billion year old Sudbury meteorite-impact structure, Canada. The data illustrate the clustering and re-distribution of trace elements such as Fe and Si to form planar features attributed to the shock wave and deformation that accompanied crater and massive Cu-Ni ore deposit formation. Note the crescent shaped nano-structures apparent in plan views of the planar sub-volumes. From White et al. [39].

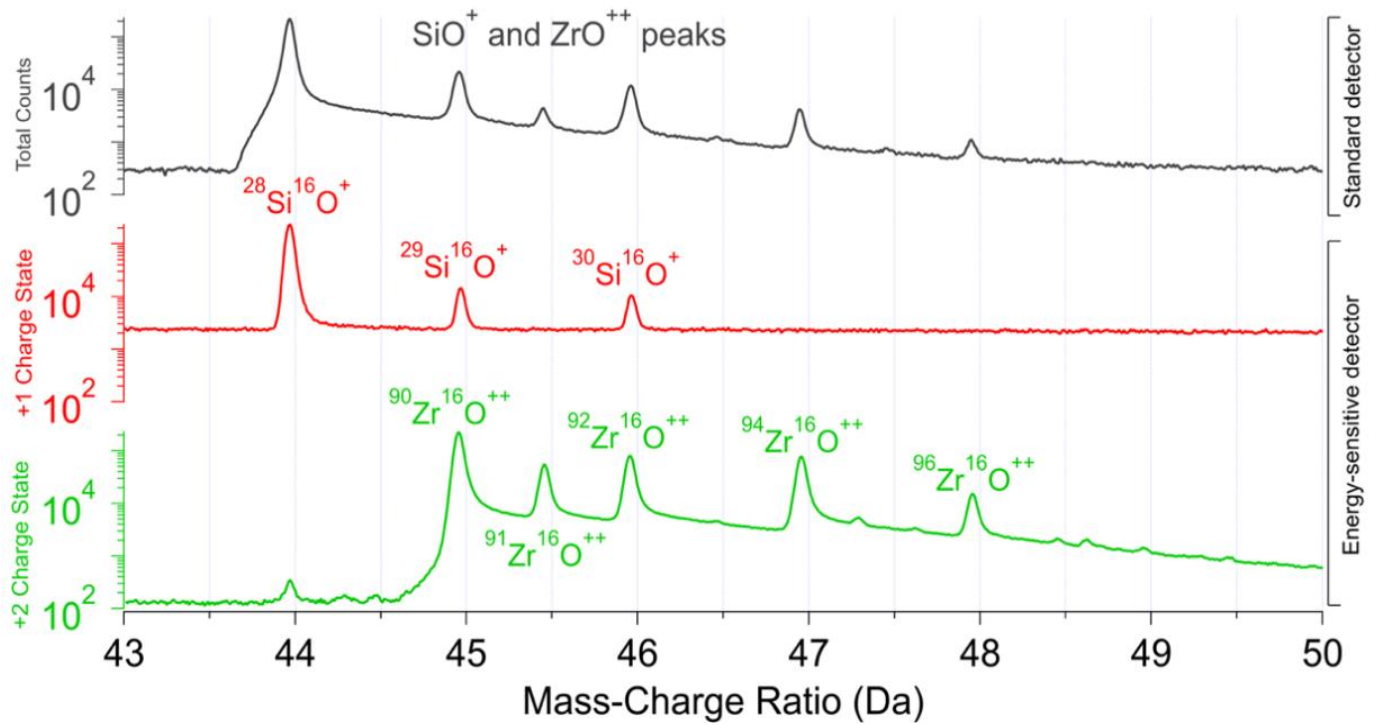


Figure 4: Indicative spectra showing the expected peak decomposition achievable with an energy-sensitive detector having sufficient resolution to separate +1 and +2 charge states (i.e. a factor of 2 in energy). Data shows part of a zircon mass spectrum.

Ion peak interferences		m/ Δm
⁵¹ V ⁺	²⁷ Al ₂ ¹⁶ O ₃ ⁺⁺	1702
⁴⁸ Ti ¹⁶ O ⁺⁺	¹⁶ O ₂ ⁺	1740
²⁰⁸ Pb ⁺⁺	²⁸ Si ₂ ¹⁶ O ₃ ⁺	2090
⁴⁰ Ca ⁺⁺	²⁴ Mg ¹⁶ O ⁺⁺	2300
¹³ C ⁺	¹² C ¹ H ⁺	2910

Table 1: The mass resolving power ($m/\Delta m$) required to separate various mass peak interferences.

Element, Stable isotopes	Minor isotope abundance (%)	Estimated APM measurement uncertainty in isotope ratio (1 std dev ‰)	Approximate range of ratios in terrestrial isotope geochemistry (‰)
H (2/1)	0.016%	79	400
Li (7/6)	7.59%	3.6	50
B (11/10)	19.90%	2.2	40
C (13/12)	1.07%	9.7	30
N (15/14)	0.36%	16.6	20
O (18/16)	0.21%	22.1	100
S (34/32)	4.20%	4.9	100

Table 2: Model uncertainties (1 SD) for stable isotope ratios, as determined by APM, are compared with the approximate range of isotope ratios that are observed in natural samples [73]. The APM uncertainty estimate is derived from the counting statistics of the least abundant isotope in the ratio, based on the detection of one million atoms across all isotopes of each element, and assuming no unresolved interferences.