



UNIVERSITY OF LEEDS

This is a repository copy of *Antimicrobial Dye-Conjugated Polyglobalide-Based Organogels*.

White Rose Research Online URL for this paper:
<https://eprints.whiterose.ac.uk/161680/>

Version: Accepted Version

Article:

Rowley, JV orcid.org/0000-0001-6646-1676, Wall, P, Yu, H et al. (4 more authors) (2020) Antimicrobial Dye-Conjugated Polyglobalide-Based Organogels. *ACS Applied Polymer Materials*, 2 (7). pp. 2927-2933. ISSN 2637-6105

<https://doi.org/10.1021/acsapm.0c00422>

This document is the Accepted Manuscript version of a Published Work that appeared in final form in *ACS Applied Polymer Materials* copyright © 2020 American Chemical Society after peer review and technical editing by the publisher. To access the final edited and published work see <https://doi.org/10.1021/acsapm.0c00422>.

Reuse

Items deposited in White Rose Research Online are protected by copyright, with all rights reserved unless indicated otherwise. They may be downloaded and/or printed for private study, or other acts as permitted by national copyright laws. The publisher or other rights holders may allow further reproduction and re-use of the full text version. This is indicated by the licence information on the White Rose Research Online record for the item.

Takedown

If you consider content in White Rose Research Online to be in breach of UK law, please notify us by emailing eprints@whiterose.ac.uk including the URL of the record and the reason for the withdrawal request.



eprints@whiterose.ac.uk
<https://eprints.whiterose.ac.uk/>

Antimicrobial Dye-Conjugated Polyglobalide-Based Organogels

*Jason V. Rowley,[†] Patrick Wall,[†] Huayang Yu,[†] Giuseppe Tronci,^{‡,§} Deirdre A. Devine,^{||} Jonathan J. Vernon^{||}
and Paul D. Thornton^{†*}*

[†]School of Chemistry, [§]Clothworkers' Centre for Textile Materials Innovation for Healthcare, School of Design, ^{||}Division of Oral Biology, School of Dentistry, University of Leeds, Leeds LS2 9JT, U.K.

[‡]Biomaterials and Tissue Engineering Research Group, School of Dentistry, St. James's University Hospital, University of Leeds, Leeds LS9 7TF, U.K.

ABSTRACT

The straightforward coloration of polyglobalide by the covalent grafting of thiol-modified disperse dyes to afford a colored polyester is reported. The colored polymer could form physical organogels, and upon covalent crosslinking chemical organogels in a range of food-grade oils, and the fragrant and antimicrobial molecule 2-phenylethanol. Antimicrobial testing of the 2-phenylethanol-swollen chemical organogels revealed considerable antimicrobial activity against both *Staphylococcus aureus* and *Escherichia coli*. The materials reported offer a range of potential applications, particularly as simple and cost-effective antimicrobial gels.

KEYWORDS

Antimicrobial organogels, natural oil-based gels, polyester coloration, fragrance release, polyglobalide.

INTRODUCTION

Commodity plastics commonly originate from a non-renewable source and are non-biodegradable. Globally, approximately 8.3 billion metric tons of plastic have been manufactured since the commencement of mass production in the 1950s.¹ In 2017, approximately 40% of plastic produced was classified as being non-biodegradable and from a non-renewable source.^{2,3} Consequently, there is an urgent demand for the creation of renewable and biodegradable polymers that can be readily applied commercially.

Aliphatic polyesters have significant potential for use in numerous artefacts in sectors ranging from packaging to personal care products owing to their degradability⁴ and biocompatibility.⁵⁻⁸ Additionally, many aliphatic polyesters can be created from renewable sources, for instance sweetcorn harvested to produce poly(lactic acid).⁹ However, such polyesters lack chemical functionality to enable chemical conjugation to the repeat units of the polymer backbone, restricting post-polymerization functionalization that may add value to the polymer. One such functionalization is effective polymer coloration, which cannot be achieved using reactive dyes if the polymer lacks the appropriate functionality to permit dye conjugation.

Polyglobalide (PGI) is a non-cytotoxic, potentially biodegradable, aliphatic polyester that has potential use within a biomedical setting.¹⁰⁻¹³ Polymer synthesis is achieved by the enzymatic ring-opening polymerization (ROP) of globalide, a 16-membered cyclic lactone which is widely used in the fragrance industry. Similar unsaturated cyclic macrolactones can be obtained from a renewable source, for instance the essential oil from *Angelica archangelica*.^{16,17} Crucially, globalide contains a C=C double bond

within its molecular structure that is transferred to the polymer, and may be used for post-polymerization modification.^{14,15} Consequently, it may be envisaged that reactive dye molecules that possess suitable functionality may be covalently conjugated to the C=C double bond of the PGI backbone to yield a polymer that boasts likely enhanced color fastness compared to polyesters colored by a non-reactive dye.

Reactive dyes that present thiol functionality are highly desirable owing to their capability to covalently couple to materials that present reactive C=C double bonds via efficient thiol-ene click chemistry reactions.¹⁸ For instance, thermosets that originate from plant oils and possess C=C double bonds may be permanently colored by a thiol-bearing reactive dye. Previous research within our group has disclosed both the modification of linseed oil by thiol-ene coupling to yield an oil that C. I. Disperse Red 1 (DR1) can be covalently attached to by 1-ethyl-3-(3-dimethylaminopropyl)carbodiimide hydrochloride (EDC) coupling in water,¹⁹ and the creation of thiol-bearing DR1, thereby converting a disperse dye to a reactive dye.²⁰ The latter holds promise as a reactive dye for the efficient coloration of (macro)molecules that present C=C double bonds.

The C=C double bond of PGI may also be exploited for covalent crosslinking to yield a non-soluble material. Chemically crosslinked PGI may readily swell, but not dissolve, in a range of organic solvents, enabling the creation of organogels. Such materials have been cited for use in dye effluent removal,²¹ oil spillage clean-up,²² cosmetics²³ and fluorescent displays.²⁴ Organogels are increasingly being employed as biomaterials due to their inherent stability, ease of preparation and capability to deliver guest molecules in a controlled manner.²⁵⁻³¹ Organogels that aid the treatment of ailments caused or exacerbated by bacterial infection are extremely promising, and organogels with antimicrobial activity against *Escherichia coli*,³²⁻³⁴ *Bacillus subtilis*,^{33,35-37} *Staphylococcus aureus*³⁸ and *Candida albicans*³⁹ have been reported.

In this paper we describe the straightforward synthesis and coloration of PGI using thiol-modified DR1 and C. I. Disperse Blue 3 (DB3) to yield two permanently colored polyesters. DR1 and DB3 were selected as two reactive dyes commonly used industrially, whilst the thiol-ene reaction was pursued to achieve colored polymers and colored covalently crosslinked polymer networks in one-step. The resultant thermoset polymers were able to form organogels when independently dispersed in a range of food-grade oils and the antimicrobial compound 2-phenylethanol. The antimicrobial activity of 2-phenylethanol-swollen organogels was tested against *S. aureus* and *E. coli*. It is envisaged that such materials hold great promise as potential biomaterials, rheology modifiers for personal care products, and antimicrobial gels.

EXPRIMENTAL

Synthesis of PGI. Globalide was polymerized as previously described.⁴⁰ Briefly, globalide (2.11 g, 8.81 mmol) and CALB (recombinant Lipase B from *Candida antarctica* immobilized on Immobead 150, recombinant from yeast) (0.44 g, ≥ 2000 U g⁻¹) were dissolved in anhydrous toluene (4.6 mL) in a Schlenk tube and stirred at 60 °C for four hours under a N₂ flow. To quench the reaction, dichloromethane (DCM) (10 mL) was added and CALB removed by vacuum filtration. The filtrate was added dropwise to ice-cold methanol (30 mL) to precipitate PGI, which was collected by vacuum filtration, washed with methanol, and dried *in vacuo* to yield an off-white crystalline polymer (yield 69%).

Synthesis of DR1 3-mercaptopropionate (1) and DB3 3-mercaptopropionate (2). DR1 3-mercaptopropionate (1) was synthesized as reported previously.¹⁹ Briefly, DR1 (1.04 g, 3.30 mmol), 4-dimethylaminopyridine (DMAP) (3 mg, 0.03 mmol) and 3-mercaptopropionic acid (1.49 mL, 16.50 mmol) were mixed in anhydrous DCM (100 mL) and stirred at 0 °C under a N₂ flow. Over a ten-minute period, a solution of dicyclohexylcarbodiimide (DCC) (3.41 g, 16.50 mmol) in anhydrous DCM (30 mL) was added dropwise to the DR1 mixture and the reaction allowed to stir at 0 °C for two hours. HCl (0.5 M, 300 mL)

was then added, forming a white precipitate which was removed by filtration. The organic layer was washed with NaHCO₃ and then water, whilst the aqueous layer was washed with DCM before the organic layers were combined and dried over MgSO₄. The solution was concentrated by rotary evaporator and purified by column chromatography (DCM) monitored by thin layer chromatography (TLC, DCM). The eluents collected were precipitated in ice-cold hexane and collected by centrifugation (4,500 r.p.m., 15 minutes) as a red crystalline product (yield 68.1%).

An analogous method was used to synthesize DB3 3-mercaptopropionate (**2**). DB3 (978 mg, 3.30 mmol), DMAP (3 mg, 0.03 mmol) and 3-mercaptopropionic acid (1.50 mL, 16.50 mmol) were combined with anhydrous DCM (80 mL). To this stirring DB3 mixture, a solution of DCC (3.41 g, 16.50 mmol) in anhydrous DCM (30 mL) was added dropwise over a ten-minute period at 0 °C under N₂ flow. After a further two hours of stirring at 0 °C, HCl (0.5 M, 200 mL) was added and the white precipitate that formed removed by filtration. The filtrate was washed and purified as per the procedure above, yielding a fine blue powder (yield 9.1%).

PGI gelation. To PGI (50 mg), a collection of food-grade solvents (2-phenylethanol, safflower oil, linseed oil, olive oil and corn oil) were independently added, and the suspensions sonicated to ensure thorough mixing. The mixtures were taken to and just beyond the point of maximum gelation, and the maximum point of gelation for each solvent recorded.

Dyeing of PGI with **1 and with **2**.** PGI (120 mg, 0.01 mmol), **1** or **2** (12 mg, 0.04 mmol) and 2,2'-azobis(2-methylpropionitrile) (AIBN) (30 mg, 0.18 mmol) were dissolved in anhydrous THF (5 mL) and stirred at 60 °C under a N₂ flow. After ~46 hours, DCM (8 mL) was added and the solution added dropwise to ice-cold methanol (40 mL) to precipitate a colored product (red for **1** or blue for **2**) which was collected by centrifugation (4,500 r.p.m., 15 minutes). The dyed polymer was then washed with methanol until the washings became colorless (yield 75%).

Crosslinking PGI. Various PGI organogels were synthesized that contained various amounts of 2,2'-(ethylenedioxy)diethanethiol (EDT) crosslinker. As a representative example, PGI (300 mg, 0.01 mmol), EDT (0.5 mL, 3.07 mmol) and AIBN (50 mg, 0.30 mmol) were dissolved in anhydrous THF (10 mL) in a 15 mL sample vial. After being left to gently stir with a magnetic stirrer bar at 60 °C and under a flow of N₂ for ~26 hours, a colorless gel had formed. The crosslinked polymer was dialyzed against deionized water (2,000 Da molecular weight cut-off) and lyophilized.

Colored PGI organogel was synthesized in a one-pot procedure. For example, PGI (290 mg, 0.01 mmol), **2** (1 mg, 0.003 mmol) and AIBN (50 mg, 0.30 mmol) were dissolved in anhydrous THF (8 mL). EDT (0.5 mL, 3.07 mmol) was then added to the blue colored THF solution at which point simultaneous cross-linking and dye conjugation reactions occurred by stirring at 60 °C under a flow of N₂. The colored crosslinked PGI was dialyzed against deionized water (2,000 Da molecular weight cut-off) and lyophilized.

Crosslinked PGI gelation. Colored, crosslinked PGI (122 mg) was weighed into a small glass vial and 2-phenylethanol added until it no longer caused the crosslinked PGI to swell. The point before turning the vial upside down and the solvent could be decanted was taken to be the maximum amount of solvent required to gel (730 mg). Degree of swelling was calculated ($100\% \times (607.8/122.3)$) to be 497.0 %.

Antimicrobial activity testing of the crosslinked organogels. The antimicrobial activity of the 2-phenylethanol-swollen organogel was tested against *E. coli* National Collection of Type Cultures (NCTC) 11954 and *S. aureus* NCTC 8532 strains. Organogels with polymer concentrations of 84, 72, 60 and 48 mg mL⁻¹ in 2-phenylethanol were generated in both a colorless and blue-dyed formulation by casting in 24-well plates (Corning). Crosslinked polymer (10 mg) in the absence of a solvent was tested as a control. The polymer-containing plates were UV sterilized for 30 minutes at 254 nm prior to antimicrobial testing. Polymer-free bacterial cultures acted as positive (growth) controls, whilst sterile broths functioned as negative controls.

Bacteria were cultured on Colombia Blood Agar (CBA; Oxoid) plates supplemented with 5% oxalated horse blood (Oxoid) in 5% (v/v) CO₂ at 37°C for 18 hours. Single colonies were inoculated into 5 mL brain heart infusion (BHI; Oxoid) broths, which were incubated at 37°C whilst agitated at 150 rpm (MaxQ 4450; Thermo Scientific). Optical densities (OD₆₀₀) of overnight cultures were measured with a Jenway 6305 spectrophotometer to estimate viable count of the undiluted suspension (based on calibration curve data). Inocula were prepared by diluting these suspensions in sterile BHI broth to a concentration of 1x10⁶ colony forming units (CFU). Inocula (500 µL) were added to polymer-containing wells and incubated overnight at 37°C with gentle agitation (70 rpm). Samples from these cultures were serially diluted in phosphate buffered saline (PBS; Oxoid) and viable bacterial populations enumerated on CBA incubated as previously. All experiments were performed in biological triplicate, with plate enumerations implemented on four separate occasions.

Statistical analysis. Statistical analysis was performed using IBM SPSS Statistics 25, groups were compared by Kruskal-Wallis test with Bonferonni adjustment; * p<0.05, ** p<0.01.

RESULTS AND DISCUSSION

Synthesis of Polyglobalide (PGI), DR1 3-Mercaptopropionate (1) and DB3 3-mercaptopropionate (2).

PGI was synthesized by the enzyme-initiated ROP of globalide using CALB to initiate the polymerization.⁴⁰ To maintain the activity of lipase B, the temperature of the reaction was limited to 70 °C. An off-white crystalline solid was produced that was confirmed to be PGI by ¹H NMR spectroscopy (Figure S1), and ¹³C NMR spectroscopy (Figure S2). The PGI produced was analyzed by advanced polymer chromatography, a form of size exclusion chromatography that enables relatively quick polymer analysis compared to gel permeation chromatography, which revealed a number average molecular weight of

30,727 g mol⁻¹ and \bar{M}_n of 1.38 (Figure S3). PGI was also analyzed by differential scanning calorimetry (DSC) and found to have a melting point of 45 °C (Figure S4).

Thiol-bearing DR1 (DR1 3-mercaptopropionate) (**1**) and thiol-bearing DB3 (DB3 3-mercaptopropionate) (**2**) were synthesized by Steglich esterification. The products, which possess pendant thiol groups for subsequent covalent conjugation to PGI, were analyzed by FTIR and ¹H NMR spectroscopy. The synthesis of **1** was confirmed by FTIR (Figure S5), and two further products that may be used for the coloration of PGI were also obtained from the reaction, DR1 bis(3-mercaptopropionate) and DR1 tris(3-mercaptopropionate) (Figures S6-S7). All spectra reveal peaks corresponding to a S-H thiol stretch at 2563 cm⁻¹ and a C=O ester stretch at 1721 cm⁻¹. The formation of the thioester in DR1 bis(3-mercaptopropionate) and DR1 tris(3-mercaptopropionate) is further confirmed in the ¹H NMR spectra (Figures S8-S9). Figure S9 is particularly informative; the integration values of the peaks at 3.09 ppm and 3.05 ppm have increased by a factor of two, confirming the formation of DR1 tris(3-mercaptopropionate). Yields of 41.4%, 20.1% and 6.6% were obtained for **1**, DR1 bis(3-mercaptopropionate) and DR1 tris(3-mercaptopropionate), respectively (68.1% yield of colored material overall). All three products are suitable for use as a reactive dye in thiol-ene coupling reactions with PGI as they each contain a terminal thiol group and azobenzene chromophore. The UV-vis absorption spectrum of DR1 (Figure S10) was near identical to those of **1**, DR1 bis(3-mercaptopropionate) and DR1 tris(3-mercaptopropionate) (Figures S10-S12); DR1 revealed a maximum absorption at 486 nm, whereas the functionalized DR1 variants had maximum absorptions at 476 nm.

¹H NMR spectroscopy confirmed the successful formation of **2** (Figure S13). Notably, the peak at 1.60 ppm that appears in the spectrum of **2** and which corresponds to the thiol proton, is absent from the ¹H NMR spectrum of unmodified DB3. In addition, peaks at 2.73 ppm and 3.13 ppm that originate from conjugated 3-mercaptopropionate are present in the spectrum of **2** but are lacking in the spectrum of DB3. FTIR analysis of **2** revealed a weak peak corresponding to the S-H thiol stretch at 2567 cm⁻¹ and a

strong peak representing the C=O ester stretch at 1739 cm^{-1} (Figure S14). UV-vis spectroscopy analysis of **2** revealed maximum absorbance values of 554 nm, 594 nm and 641 nm that are comparable to the spectrum of DB3, which has maximum absorbance values of 559 nm, 599 nm and 646 nm (Figure 1).

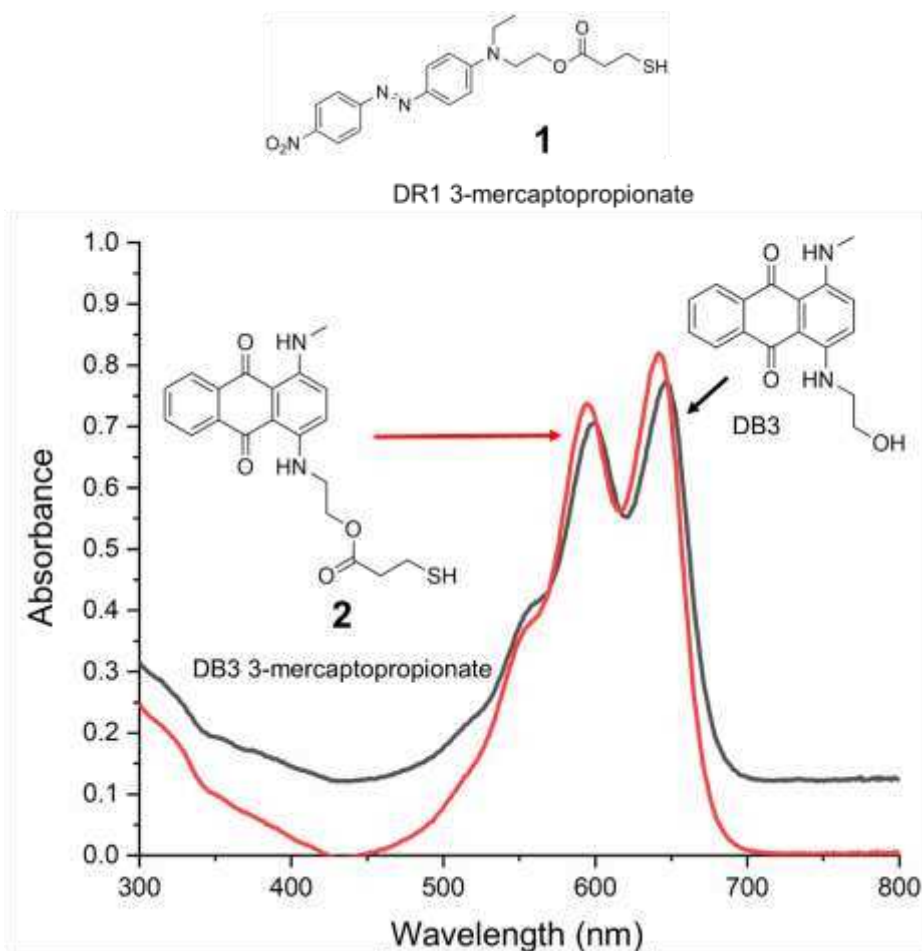


Figure 1. The UV-vis spectra corresponding to DB3 and DB3 3-mercaptopropionate (**2**).

Covalent Coloration of PGI with DR1 3-Mercaptopropionate (1**) and DB3 3-Mercaptopropionate (**2**).**

1 and **2** were used to covalently dye PGI via thiol-ene coupling (Figure 2). After dyeing, the colored polymer was washed thoroughly with methanol, a solvent that readily solubilizes both modified dye

molecules, until the washings were colorless to ensure that any dye remaining was covalently bound to PGI.

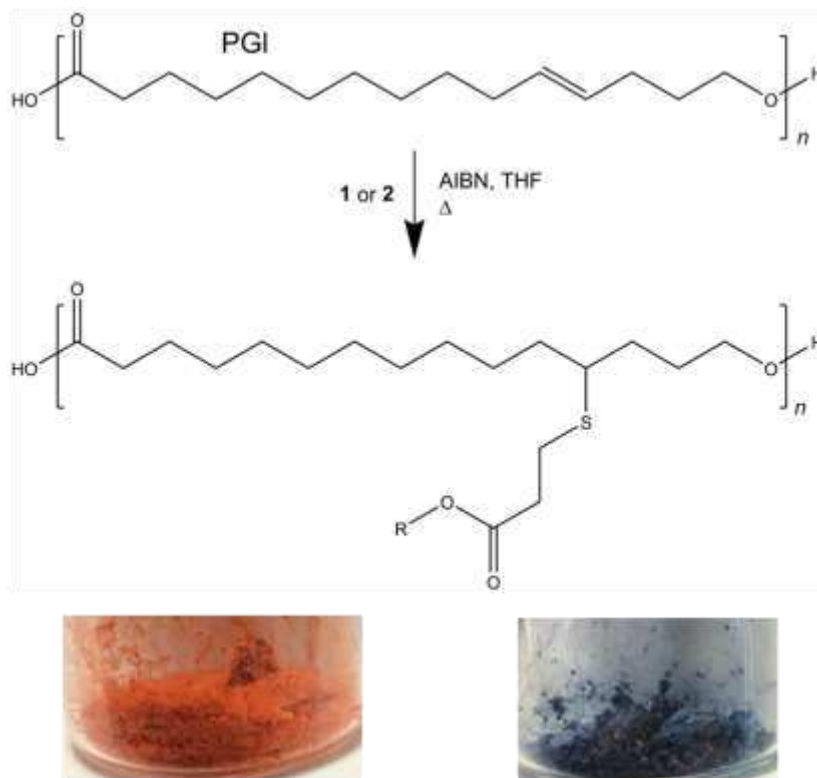


Figure 2. Thiol-ene coupling of PGI with **1** or **2** to yield PGI that is dyed red (left inset = photo of collected red PGI) or blue (right inset = photo of collected blue PGI).

FTIR analysis of the polymer dyed with **1** revealed peaks that are attributed to PGI, and additional peaks at 1604 cm^{-1} , which corresponds to the azobenzene group of **1**, and 1520 cm^{-1} , which represents the NO_2 asymmetric stretch of **1** (Figure S15). The FTIR spectrum of PGI dyed with **2** contains the peaks that are attributed to PGI, plus an additional peak at 1677 cm^{-1} , which corresponds to the aromatic ketone of **2** (Figure S16). ^1H NMR analysis confirmed the successful conjugation of **1** (Figure 3a) and **2** (Figure 3b) to PGI. Based on comparing the integrals of peaks corresponding to the methylene group adjacent to the terminal hydroxyl group of PGI with peaks corresponding to the aromatic groups of **1**

and **2**, dye conjugation to PGI was found to be approximately 2% for both dyes. It was also found that the melting transition of PGI increased slightly from 45 °C for linear PGI (Figure S4) to ~51 °C for dyed PGI (Figures S17-S18). This increase in melting point is likely due to restricted polymer flexibility as a result of the conjugated pendant groups.

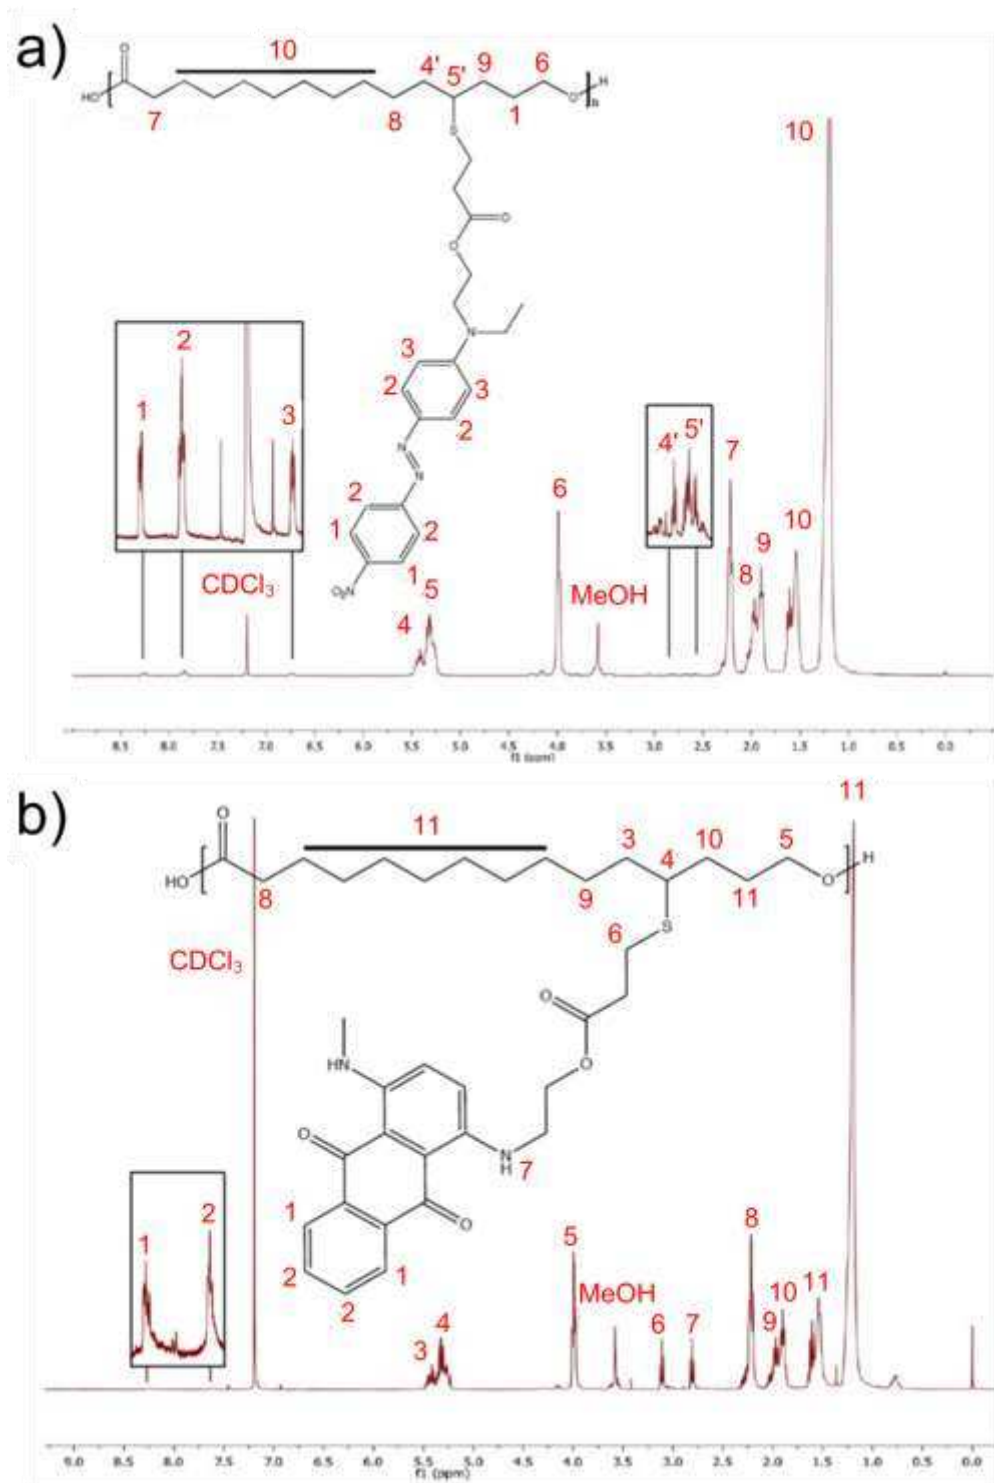


Figure 3. ^1H NMR (400 MHz, CDCl_3 , δ ppm) spectra of a) 1-dyed PGI and b) 2-dyed PGI.

The Creation of PGI-Based Organogels. The capability of linear PGI to form physical organogels via organic solvent uptake was assessed using various non-aqueous solvents as the continuous phase (Table 1). 2-Phenylethanol was selected as it is a fragrant and antimicrobial molecule, and so any gel formed has potential application as a perfumed, antimicrobial, gel.⁴¹ The gel swollen in 2-phenylethanol was a physical gel whereby the elastic modulus (G') exceeds the viscous modulus (G'') at higher angular frequency owing to relative freedom of the polymer chains within the physically crosslinked network (Figure S19). The other oils tested are certified food grade and so gels formed have potential *in vivo* application. In all cases, self-supporting materials were formed, with the lowest and highest quantity of polymer (disperse phase) required for organogel formation being when corn oil (11.3% PGI) and 2-phenylethanol (24.8% PGI) were used as the continuous phase, respectively (Table 1).

Table 1. The minimum weight percentage of PGI required to form a self-supporting organogel in various continuous phases.

Weight % of Polymer Required for Gel Formation				
2-phenylethanol	Safflower Oil	Linseed Oil	Olive Oil	Corn Oil
24.8	15.5	20.8	21.1	11.3

Covalently crosslinking PGI with EDT using thiol-ene coupling was then performed. Successful PGI crosslinking was confirmed by DSC analysis; the thermogram produced revealed an exothermic peak at 123 °C that is attributed to crosslinker degradation and lacked the sizeable endothermic melting point peak at 42 °C that linear PGI possesses (Figure S20). Such thermal stability is advantageous for using materials in applications in which it must retain structural integrity at elevated temperatures, for instance as a recyclable polymer that undergoes washing in hot liquids between uses. The crosslinked polymer was robust when handled.

The crosslinked polymer also holds great potential to form an organogel with increased mechanical properties when swollen in an organic continuous phase. Once more, 2-phenylethanol was probed to determine if it can form a chemical organogel that includes a fragrant antimicrobial molecule as the continuous phase (Table 2). Figure S21 demonstrates the solid-like behavior of the covalent gel whereby values of the storage modulus are significantly increased with respect to values of the loss modulus, regardless of the angular frequency. The rheogram also shows the significantly increased storage modulus of this organogel compared with the non-crosslinked organogel. THF was also used to create organogels owing to its ability to readily solubilize linear PGI, rendering it ideal to demonstrate PGI crosslinking by organogel formation as linear PGI dissolves in THF, whereas crosslinked PGI should swell in THF.

Table 2. The PGI : EDT ratio, weight percentage of PGI in the organogels formed, and the solvent loss rate (mL/h) of the organogels created in THF or 2-phenylethanol.

Sample	Polymer : Crosslinker Ratio	THF		2-Phenylethanol	
		% PGI	Solvent loss	% PGI	Solvent loss (mL/h)
1	1 : 0.11	15	0.3	11	0.07
2	1 : 0.22	19	0.29	16	0.06
3	1 : 0.44	21	0.24	22	0.05
4	1 : 0.85	23	0.24	20	0.04

In general, as the PGI : EDT ratio converges to parity, the weight percentage of PGI in the organogels formed increases. This was anticipated as reduced gel swelling typically corresponds to increased crosslink density. Organogels formed using 2-phenylethanol had a solvent loss rate, determined by organogel mass, of 0.07 mL h⁻¹ over 24 h, which proved to be much reduced compared with that of THF. 2-Phenylethanol retention capability provides the material with potential use as an antimicrobial gel that provides prolonged fragrance release; control over solvent loss ensures the material does not dry prematurely. SEM analysis revealed that such structures possessed a porous morphology and so may

also be feasibly deployed as scaffolds for three-dimensional cell culture owing to the non-cytotoxic components of the material (Figure 4a). The porous morphology is also relevant when aiming to achieve uptake of antibacterial compound within the pores rather than only in the polymer free volume.

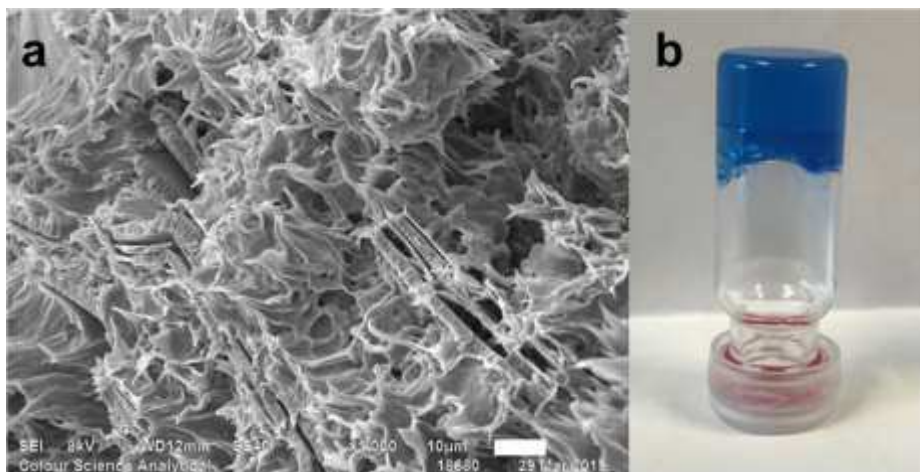


Figure 4. (a) SEM image of PGI crosslinked with EDT. The scale bar represents 10 μm . (b) DB3-dyed PGI crosslinked with EDT and dispersed in 2-phenylethanol.

PGI was simultaneously dyed with **2** and crosslinked with EDT to yield a polymer that may form a blue organogel (Figure 4b). DB3-dyed and EDT-crosslinked PGI expanded to 497% the original polymer mass, when dispersed in 2-phenylethanol. Figure S22 demonstrates this dyed organogel is stronger than the non-crosslinked organogel (Figure S19) as the G' value is much greater than the G'' value. However, the G' value is less than that of the non-dyed organogel (Figure S21) (G' of $\sim 17,000$ Pa and $\sim 10,250$ Pa for the non-dyed and dyed organogels, respectively).

Finally, the antimicrobial activity of the blue colored and uncolored chemically-crosslinked 2-phenylethanol-swollen PGI-based organogels was assessed versus *S. aureus* and *E. coli*. Preliminary testing revealed comparable antimicrobial activity for gels at all concentrations (data not shown),

therefore subsequent experiments focused only on the gel with the lowest solvent concentration, 84 mg mL⁻¹. Figure 5 shows the bacterial viability following incubations of *S. aureus* and *E. coli* in the positive growth control, with the 2-phenylethanol-free PGI control and the colored/non-colored organogels. The antimicrobial effect of colored and non-colored PGI in the absence of 2-phenylethanol was minimal, but when swollen to form an organogel the material displayed clear antimicrobial capabilities. As expected, there was no marked difference in the antimicrobial activity between crosslinked PGI dyed with **2** or not, although some difference was found when assessed against *S. aureus*. Additionally, OD₆₀₀ readings were made of the suspensions incubated with the organogels. For *S. aureus*, the OD₆₀₀ values for both the colorless and dyed 84 mg mL⁻¹ organogel were reduced by >95% compared with the positive growth control. Similarly, the OD₆₀₀ values for both *E. coli* organogels decreased by >97% from the positive growth control, further demonstrating the pronounced antimicrobial capabilities of the reported organogels.

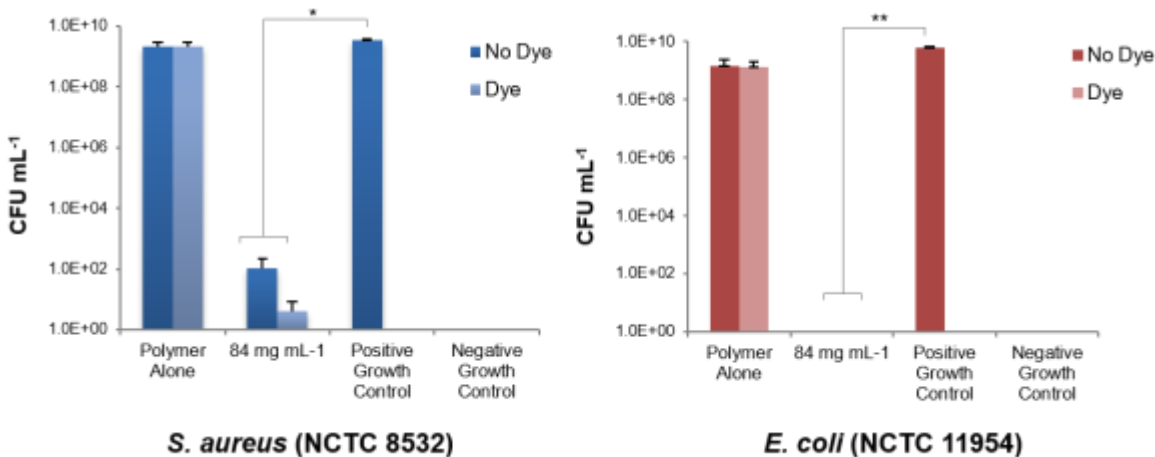


Figure 5. Bacterial viability of *S. aureus* (left) and *E. coli* (right) following incubation with DB3-conjugated and DB-3 crosslinked PGI samples, and respective 2-phenylethanol-swollen PGI organogel.

CONCLUSIONS

The thiol modification of DR1 and DB3 was carried out to yield two reactive dyes that are able to color (macro)molecules that possess C=C double bonds, through covalent coupling. PGI, a biocompatible and potentially biodegradable polyester, was both colored by such dyes, and crosslinked via a one-step thiol-ene reaction to yield a non-soluble polymer that lacks a melting point. Crosslinked PGI was used as the gelating component for various food-grade solvents, including the fragrant, food-grade, molecule 2-phenylethanol. Chemically crosslinked PGI-based organogels that have 2-phenylethanol as the continuous phase demonstrate a predominantly elastic behavior with increased storage modulus with respect to both the loss modulus and the storage modulus of the 2-phenylethanol-swollen linear polymer. Such organogels display excellent antimicrobial activity against both *S. aureus* and *E. coli* regardless of dye conjugation to the crosslinked network. Consequently, the PGI-based, 2-phenylethanol-containing, organogels reported are highly promising candidates to be employed for the prolonged release of a fragrant molecule, and as antimicrobial gels.

ASSOCIATED CONTENT

Supporting information. The following supporting information is available free of charge: materials, equipment and settings; NMR spectra of the PGIs and thiol-modified dyes; advanced polymer chromatography chromatogram of the PGI; DSC thermograms of the PGI, dyed PGI and crosslinked PGI; FTIR spectra of the dyes and the dyed PGI; UV-vis absorbance spectra and rheological graphs.

AUTHOR INFORMATION

Corresponding author. Paul D. Thornton – *School of Chemistry, University of Leeds, Leeds, LS2 9JT, U.K.*; Email: p.d.thornton@leeds.ac.uk.

Authors

Jason V. Rowley – *School of Chemistry, University of Leeds, Leeds, LS2 9JT, U.K.*

Patrick Wall – *School of Chemistry, University of Leeds, Leeds, LS2 9JT, U.K.*

Huayang Yu – *School of Chemistry, University of Leeds, Leeds, LS2 9JT, U.K.*

Giuseppe Tronci – *Clothworkers' Centre for Textile Materials Innovation for Healthcare, School of Design, University of Leeds, Leeds LS2 9JT, U.K. and Biomaterials and Tissue Engineering Research Group, School of Dentistry, St James's University Hospital, University of Leeds, Leeds, LS9 7TF, U.K.*

Deirdre A. Devine – *Division of Oral Biology, School of Dentistry, University of Leeds, Leeds, LS2 9JT, U.K.*

Jonathan J. Vernon – *Division of Oral Biology, School of Dentistry, University of Leeds, Leeds, LS2 9JT, U.K.*

Author Contributions. J.V.R. and P.W. synthesized the polymers, crosslinked polymers and organogels. J.V.R., P.W. and H.Y. carried out characterization. J.J.V. tested the antimicrobial activity. All authors contributed to the writing of the paper.

Funding Sources. University of Leeds via the Gunnell and Matthews Scholarship.

Acknowledgements. The authors would like to thank The University of Leeds for funding through the Gunnell and Matthews Scholarship. The authors would also like to thank Algy Kazlauciusas for help with SEM, DSC and rheological analysis.

Notes. The authors declare no competing financial interests.

REFERENCES

1. Wright, S. L.; Kelly, F. J., Threat to human health from environmental plastics. *BMJ* **2017**, 358, j4334.

2. Gibb, B. C., Plastics are forever. *Nat. Chem.* **2019**, 11, (5), 394-395.
3. Geyer, R.; Jambeck, J. R.; Law, K. L., Production, use, and fate of all plastics ever made. *Sci. Adv.* **2017**, 3, (7), e1700782.
4. Grizzi, I.; Garreau, H.; Li, S.; Vert, M., Hydrolytic degradation of devices based on poly(dl-lactic acid) size-dependence. *Biomaterials* **1995**, 16, (4), 305-311.
5. da Silva, D.; Kaduri, M.; Poley, M.; Adir, O.; Krinsky, N.; Shainsky-Roitman, J.; Schroeder, A., Biocompatibility, biodegradation and excretion of polylactic acid (PLA) in medical implants and theranostic systems. *Chem. Eng. J.* **2018**, 340, 9-14.
6. Bi, S.; Tan, B.; Soule, J. L.; Sobkowicz, M. J., Enzymatic degradation of poly (butylene succinate-co-hexamethylene succinate). *Polym. Degrad. Stab.* **2018**, 155, 9-14.
7. Guidotti, G.; Soccio, M.; Siracusa, V.; Gazzano, M.; Salatelli, E.; Munari, A.; Lotti, N., Novel Random PBS-Based Copolymers Containing Aliphatic Side Chains for Sustainable Flexible Food Packaging. *Polymers* **2017**, 9, (12), 724.
8. Becker, G.; Wurm, F. R., Functional biodegradable polymers via ring-opening polymerization of monomers without protective groups. *Chem. Soc. Rev.* **2018**, 47, (20), 7739-7782.
9. Auras, R.; Harte, B.; Selke, S., An Overview of Polylactides as Packaging Materials. *Macromol. Biosci.* **2004**, 4, (9), 835-864.
10. Polloni, A. E.; Chiaradia, V.; Figura, E. M.; De Paoli, J. P.; de Oliveira, D.; de Oliveira, J. V.; de Araujo, P. H. H.; Sayer, C. J. A. B.; Biotechnology, Polyesters from Macrolactones Using Commercial Lipase NS 88011 and Novozym 435 as Biocatalysts. *Appl. Biochem. Biotechnol.* **2018**, 184, (2), 659-672.

11. van der Meulen, I.; Li, Y.; Deumens, R.; Joosten, E. A. J.; Koning, C. E.; Heise, A., Copolymers from Unsaturated Macrolactones: Toward the Design of Cross-Linked Biodegradable Polyesters. *Biomacromol.* **2011**, *12*, (3), 837-843.
12. van der Meulen, I.; de Geus, M.; Antheunis, H.; Deumens, R.; Joosten, E. A. J.; Koning, C. E.; Heise, A., Polymers from Functional Macrolactones as Potential Biomaterials: Enzymatic Ring Opening Polymerization, Biodegradation, and Biocompatibility. *Biomacromol.* **2008**, *9*, (12), 3404-3410.
13. de Oliveira, F. C. S.; Olvera, D.; Sawkins, M. J.; Cryan, S.-A.; Kimmins, S. D.; da Silva, T. E.; Kelly, D. J.; Duffy, G. P.; Kearney, C.; Heise, A., Direct UV-Triggered Thiol–ene Cross-Linking of Electrospun Polyester Fibers from Unsaturated Poly(macrolactone)s and Their Drug Loading by Solvent Swelling. *Biomacromol.* **2017**, *18*, (12), 4292-4298.
14. Ates, Z.; Thornton, P. D.; Heise, A., Side-chain functionalisation of unsaturated polyesters from ring-opening polymerisation of macrolactones by thiol–ene click chemistry. *Polym. Chem.* **2011**, *2*, (2), 309-312.
15. Savin, C. L.; Peptu, C.; Kroneková, Z.; Sedlačík, M.; Mrlik, M.; Sasinková, V.; Peptu, C. A.; Popa, M.; Mosnáček, J., Polyglobalide-Based Porous Networks Containing Poly(ethylene glycol) Structures Prepared by Photoinitiated Thiol–Ene Coupling. *Biomacromol.* **2018**, *19*, (8), 3331-3342.
16. Williams, A. S., The Synthesis of Macrocyclic Musks. *Synthesis* **1999**, 1999, (10), 1707-1723.
17. Claudino, M.; van der Meulen, I.; Trey, S.; Jonsson, M.; Heise, A.; Johansson, M., Photoinduced thiol–ene crosslinking of globalide/ ϵ -caprolactone copolymers: Curing performance and resulting thermoset properties. *J. Polym. Sci., Part A: Polym. Chem.* **2012**, *50*, (1), 16-24.

18. Fuoco, T.; Finne-Wistrand, A., Synthetic Approaches to Combine the Versatility of the Thiol Chemistry with the Degradability of Aliphatic Polyesters. *Polym. Rev.* **2020**, 60, (1), 86-113.
19. Hayashi, T.; Thornton, P. D., The synthesis and characterisation of thiol-bearing C. I. Disperse Red 1. *Dyes Pigm.* **2015**, 121, 235-237.
20. Hayashi, T.; Kazlauciuonas, A.; Thornton, P. D., Dye conjugation to linseed oil by highly-effective thiol-ene coupling and subsequent esterification reactions. *Dyes Pigm.* **2015**, 123, 304-316.
21. Chetia, M.; Debnath, S.; Chowdhury, S.; Chatterjee, S., Self-assembly and multifunctionality of peptide organogels: oil spill recovery, dye absorption and synthesis of conducting biomaterials. *RSC Adv.* **2020**, 10, (9), 5220-5233.
22. Khayat, Z.; Zali-Boeini, H., Phase selective amphiphilic supergelators for oil spill solidification and dye removal. *Soft Mater.* **2019**, 17, (2), 150-158.
23. Kirilov, P.; Rum, S.; Gilbert, E.; Roussel, L.; Salmon, D.; Abdayem, R.; Serre, C.; Villa, C.; Haftek, M.; Falson, F.; Pirot, F., Aqueous dispersions of organogel nanoparticles – potential systems for cosmetic and dermo-cosmetic applications. *Int. J. Cosmet. Sci.* **2014**, 36, (4), 336-346.
24. Zhang, Y.-M.; Zhu, W.; Qu, W.-J.; Zhong, K.-P.; Chen, X.-P.; Yao, H.; Wei, T.-B.; Lin, Q., Competition of cation- π and exo-wall π - π interactions: a novel approach to achieve ultrasensitive response. *Chem. Comm.* **2018**, 54, (36), 4549-4552.
25. Murdan, S.; Gregoriadis, G.; Florence, A. T., Sorbitan monostearate/polysorbate 20 organogels containing niosomes: a delivery vehicle for antigens? *Eur. J. Pharma. Sci.* **1999**, 8, (3), 177-185.
26. Vintiloiu, A.; Leroux, J.-C., Organogels and their use in drug delivery — A review. *J. Controlled Release* **2008**, 125, (3), 179-192.

27. Zheng, H.; Deng, L.; Que, F.; Feng, F.; Zhang, H., Physical characterization and antimicrobial evaluation of glycerol monolaurate organogels. *Colloids Surf., A* **2016**, 502, 19-25.
28. Khuphe, M.; Mukonoweshuro, B.; Kazlauciusas, A.; Thornton, P. D., A vegetable oil-based organogel for use in pH-mediated drug delivery. *Soft Matter*. **2015**, 11, (47), 9160-9167.
29. Dai, M.; Bai, L.; Zhang, H.; Ma, Q.; Luo, R.; Lei, F.; Fei, Q.; He, N., A novel flunarizine hydrochloride-loaded organogel for intraocular drug delivery in situ: Design, physicochemical characteristics and inspection. *Int. J. Pharmaceutics* **2020**, 576, 119027.
30. Uzan, S.; Barış, D.; Çolak, M.; Aydın, H.; Hoşgören, H., Organogels as novel carriers for dermal and topical drug delivery vehicles. *Tetrahedron* **2016**, 72, (47), 7517-7525.
31. Esposito, C. L.; Kirilov, P.; Roullin, V. G., Organogels, promising drug delivery systems: an update of state-of-the-art and recent applications. *J. Controlled Release* **2018**, 271, 1-20.
32. Singh, V. K.; Anis, A.; Banerjee, I.; Pramanik, K.; Bhattacharya, M. K.; Pal, K., Preparation and characterization of novel carbopol based bigels for topical delivery of metronidazole for the treatment of bacterial vaginosis. *Mater. Sci. Eng., C* **2014**, 44, 151-158.
33. Singh, V. K.; Pal, K.; Pradhan, D. K.; Pramanik, K., Castor oil and sorbitan monopalmitate based organogel as a probable matrix for controlled drug delivery. *J. App. Polym. Sci.* **2013**, 130, (3), 1503-1515.
34. Singh, V. K.; Pal, K.; Banerjee, I.; Pramanik, K.; Anis, A.; Al-Zahrani, S. M., Novel organogel based lyotropic liquid crystal physical gels for controlled delivery applications. *Eur. Polym. J.* **2015**, 68, 326-337.

35. Singh, V. K.; Banerjee, I.; Agarwal, T.; Pramanik, K.; Bhattacharya, M. K.; Pal, K., Guar gum and sesame oil based novel bigels for controlled drug delivery. *Colloids Surf., B* **2014**, 123, 582-592.
36. Satapathy, D.; Biswas, D.; Behera, B.; Sagiri, S. S.; Pal, K.; Pramanik, K., Sunflower-oil-based lecithin organogels as matrices for controlled drug delivery. *J. Appl. Polym. Sci.* **2013**, 129, (2), 585-594.
37. Behera, B.; Sagiri, S. S.; Pal, K.; Srivastava, A., Modulating the physical properties of sunflower oil and sorbitan monopalmitate-based organogels. *J. Appl. Polym. Sci.* **2013**, 127, (6), 4910-4917.
38. Yu, H.; Zeng, P.; Liang, Y.; Chen, X.; Hu, H.; Wen, L.; Chen, G., A Tanshinone IIA loaded hybrid nanocomposite with enhanced therapeutic effect for otitis media. *Int. J. of Pharma.* **2020**, 574, 118846.
39. Querobino, S. M.; de Faria, N. C.; Vigato, A. A.; da Silva, B. G. M.; Machado, I. P.; Costa, M. S.; Costa, F. N.; de Araujo, D. R.; Alberto-Silva, C., Sodium alginate in oil-poloxamer organogels for intravaginal drug delivery: Influence on structural parameters, drug release mechanisms, cytotoxicity and in vitro antifungal activity. *Mater. Sci. Eng., C* **2019**, 99, 1350-1361.
40. Ates, Z.; Heise, A., Functional films from unsaturated poly(macrolactones) by thiol-ene cross-linking and functionalisation. *Polym. Chem.* **2014**, 5, (8), 2936-2941.
41. Zhu, Y.-J.; Zhou, H.-T.; Hu, Y.-H.; Tang, J.-Y.; Su, M.-X.; Guo, Y.-J.; Chen, Q.-X.; Liu, B., Antityrosinase and antimicrobial activities of 2-phenylethanol, 2-phenylacetaldehyde and 2-phenylacetic acid. *Food Chem.* **2011**, 124, (1), 298-302.

Table of Contents Graphic

