

This is a repository copy of *Tailored design of graphitic biochar for high-efficiency and chemical-free microwave-assisted removal of refractory organic contaminants*.

White Rose Research Online URL for this paper:

<https://eprints.whiterose.ac.uk/161991/>

Version: Accepted Version

---

**Article:**

Sun, Yuqing, Yu, Iris K.M., Tsang, Daniel C.W. et al. (6 more authors) (2020) Tailored design of graphitic biochar for high-efficiency and chemical-free microwave-assisted removal of refractory organic contaminants. CHEMICAL ENGINEERING JOURNAL. 125505. ISSN 1385-8947

<https://doi.org/10.1016/j.cej.2020.125505>

---

**Reuse**

This article is distributed under the terms of the Creative Commons Attribution-NonCommercial-NoDerivs (CC BY-NC-ND) licence. This licence only allows you to download this work and share it with others as long as you credit the authors, but you can't change the article in any way or use it commercially. More information and the full terms of the licence here: <https://creativecommons.org/licenses/>

**Takedown**

If you consider content in White Rose Research Online to be in breach of UK law, please notify us by emailing [eprints@whiterose.ac.uk](mailto:eprints@whiterose.ac.uk) including the URL of the record and the reason for the withdrawal request.

# Chemical Engineering Journal

## Tailored design of graphitic biochar for high-efficiency and chemical-free microwave-assisted removal of refractory organic contaminants --Manuscript Draft--

<b>Manuscript Number:</b>	CEJ-D-20-06099R1
<b>Article Type:</b>	Research Paper
<b>Keywords:</b>	Microwave irradiation; Engineered biochar; Graphitic carbon; Sustainable waste management; Advanced wastewater treatment.
<b>Corresponding Author:</b>	Daniel CW Tsang, PhD Hong Kong Polytechnic University Hong Kong, HONG KONG
<b>First Author:</b>	Yuqing Sun, PhD
<b>Order of Authors:</b>	Yuqing Sun, PhD Iris KM Yu, PhD Daniel CW Tsang, PhD Jiajun Fan, PhD James H Clark, PhD Gang Luo, PhD Shicheng Zhang, PhD Eakalak Khan, PhD Nigel JD Graham, PhD
<b>Abstract:</b>	<p>Energy-saving, chemical-free, and high-efficiency microwave (MW)-assisted water treatment can be greatly facilitated via tailored design of an economical, sustainable, and 'green' carbonaceous catalyst. Various biochars (BC) were pyrolyzed from two lignocellulosic waste biomasses, oak (O) and apple tree (A), at high temperature (900 °C) and under different gases (N<sub>2</sub> and CO<sub>2</sub>). The holistic characterization by advanced spectroscopic techniques demonstrated that CO<sub>2</sub> pyrolysis of feedstock with more lignin (i.e., oak), produced biochar with increased aromaticity and degree of carbonization. CO<sub>2</sub> modification created a hierarchical porous structure, improved surface hydrophilicity, polarity, and acidity, and provided higher densities of near-surface functionalities of the biochar. Without MW irradiation, ABC-900C (1 g L<sup>-1</sup>) provided the highest adsorption (52.6%, 1 min) of 2,4-dichlorophenoxy acetic acid (2,4-D) ascribed to large specific surface area, high micropore content, appropriate pore size, and abundant active groups. OBC-900C (1 g L<sup>-1</sup>) enabled significantly increased 2,4-D removal (81.6%, 1 min) under MW irradiation (90 °C) in contrast with an oil bath (55.7%, 90 °C, 1 min) and room temperature (33.9%, 1 min) conditions, due to its highest graphitization degree and medium-developed microporous structure. The MW-induced thermal effect formed "hotspots" on the biochar surface as evidenced by elevated temperature of the bulk solution and lowered energy consumption of the MW reactor in the presence of OBC-900C, compared to those of the other biochars. The scavenging tests suggested that the generation of highly oxidative hydroxyl (•OH), anionic superoxide (O<sub>2</sub><sup>•-</sup>), and singlet oxygen (1O<sub>2</sub>) radicals contributed to the removal of 2,4-D. This study demonstrated that biochar with customized structure and high organic adsorption capacity can act as an effective MW absorber suitable for rapid and improved removal of toxic organics.</p>
<b>Response to Reviewers:</b>	<p>Dear Prof. Gao,</p> <p>We sincerely appreciate the reviewers' and your constructive comments on our manuscript (CEJ-D-20-06099). The comments and suggestions have helped us to improve our manuscript and stimulate new thoughts for our ongoing studies. You can find the point-by-point list of our responses to the comments and the corresponding changes in this document. The revisions of our manuscript are highlighted in red colour</p>

for your reference. We confirm that the figures and tables in this revised manuscript are the original work of the authors.

We hope the revised manuscript meets the criteria for publication in Chemical Engineering Journal. Thank you very much again and we look forward to hearing from you soon.

Best Wishes,  
Dan (on behalf of co-authors)



THE HONG KONG  
POLYTECHNIC UNIVERSITY  
香港理工大學

Department of Civil and Environmental Engineering  
土木及環境工程學系

香港 九龍 紅磡  
Hung Hom, Kowloon, Hong Kong  
Tel (852) 2766 6045 Fax (852) 2334 6389  
Website [www.polyu.edu.hk](http://www.polyu.edu.hk)

16 April 2020

Dear Editor,

Attached please find our manuscript entitled “Tailored design of graphitic biochar for high-efficiency and chemical-free microwave-assisted removal of refractory organic contaminants”, which is submitted for publication as an original research paper. This manuscript contains 4872 words, 8 figures, and 1 table in the text excluding references. We believe that the scientific merits and environmental significance of our manuscript fit well into the scope of *Chemical Engineering Journal*.

Significance and Novelty:

- In this study, we demonstrated that CO<sub>2</sub> pyrolysis of feedstock (oak tree) with higher lignin content produced biochar (OBC-900C) with a hierarchical porous structure, improved surface hydrophilicity, polarity, and surface functionalities.
- The OBC-900C (1 g L<sup>-1</sup>) enabled significantly increased 2,4-dichlorophenoxy acetic acid (2,4-D) removal (81.6%, 1 min) under microwave (MW) irradiation in contrast with an oil bath (55.7%, 1 min) and room temperature (33.9%, 1 min) conditions, owing to its high MW absorption and 2,4-D adsorption capacities ascribed to high graphitization degree and medium-developed microporous structure.
- The MW-induced thermal effect formed “hot spots” on the biochar surface and generated highly oxidative hydroxyl (<sup>•</sup>OH), anionic superoxide (O<sub>2</sub><sup>•-</sup>), and singlet oxygen (<sup>1</sup>O<sub>2</sub>) radicals contributing to the removal of 2,4-D.

Neither the entire paper nor any part of its content has been published elsewhere, and it is not being submitted to any other journal. This submission is approved by all authors, and we declare that there is no conflict of interest regarding its publication. We sincerely appreciate your kind consideration and look forward to hearing from you.

Best Wishes,

Dan Tsang, PhD, CEnv, BEng, PG Dip (Tert Tchg)  
Associate Professor, Programme Leader (EOSH)  
Department of Civil and Environmental Engineering,  
Hong Kong Polytechnic University,  
Hung Hom, Kowloon, Hong Kong

<https://www.scopus.com/authid/detail.uri?authorId=12760921200>  
[http://www.polyu.edu.hk/cee/~dan\\_tsang/](http://www.polyu.edu.hk/cee/~dan_tsang/)



**THE HONG KONG  
POLYTECHNIC UNIVERSITY**  
香港理工大學

**Department of Civil and Environmental Engineering**  
土木及環境工程學系

香港 九龍 紅磡  
Hung Hom, Kowloon, Hong Kong  
Tel (852) 2766 6045 Fax (852) 2334 6389  
Website [www.polyu.edu.hk](http://www.polyu.edu.hk)

### **Suggested Reviewers:**

<b>First Name*</b>	Bingcai
Middle Initial	
<b>Last Name*</b>	Pan
Academic Degree(s)	PhD
Position	Professor
<b>Department*</b>	Research Center for Environmental Nanotechnology
<b>Institution*</b>	Nanjing University
<b>E-mail Address*</b>	bcpan@nju.edu.cn
<b>Reason*</b>	Expert at solid catalyst

<b>First Name*</b>	Kevin
Middle Initial	
<b>Last Name*</b>	Wu
Academic Degree(s)	PhD
Position	Professor
<b>Department*</b>	Department of Chemical Engineering
<b>Institution*</b>	National Taiwan University
<b>E-mail Address*</b>	kevinwu@ntu.edu.tw
<b>Reason*</b>	Expert at solid catalyst

<b>First Name*</b>	Bin
Middle Initial	
<b>Last Name*</b>	Gao
Academic Degree(s)	PhD
Position	Professor
<b>Department*</b>	Department of Agricultural and Biological Engineering
<b>Institution*</b>	University of Florida
<b>E-mail Address*</b>	bg55@ufl.edu
<b>Reason*</b>	Expert at engineered biochar

Dear Prof. Gao,

We sincerely appreciate the reviewers' and your constructive comments on our manuscript (CEJ-D-20-06099). The comments and suggestions have helped us to improve our manuscript and stimulate new thoughts for our ongoing studies. You can find the point-by-point list of our responses to the comments and the corresponding changes in this document. The revisions of our manuscript are highlighted in red colour for your reference. We confirm that the figures and tables in this revised manuscript are the original work of the authors.

We hope the revised manuscript meets the criteria for publication in *Chemical Engineering Journal*. Thank you very much again and we look forward to hearing from you soon.

Best Wishes,  
Dan (on behalf of co-authors)

### Reviewer # 1

Sun and co-authors test the efficacy of high temperature (900 C) biochars for the sorption and degradation of 2,4-dichlorophenoxy acetic acid (2,4-D) - a model organic contaminant - by microwave-assisted treatment. The authors find that a char produced from oak wood in the presence of CO<sub>2</sub> during pyrolysis markedly enhances 2,4-D removal from aqueous solution, and propose that biochar may be a cost-effective alternative to other catalysts (such as metal-based catalysts) in the treatment of organic contaminants in water. I find the manuscript to be scientifically sound, generally well-written, and a good fit for publication in *Chemical Engineering Journal*.

*Response:* Many thanks for your kind support. We revised the manuscript according to your constructive suggestions and thoughtful comments as follows.

Following are some thoughts and recommendations that I hope will help the authors in revising their manuscript:

1. Page 2, Line 4: "...more near-surface functionalities of the biochar." The language is vague here - do you mean higher surface functional group densities/concentrations, or a more diverse group of functionalities at the surface?

*Response:* We revised this sentence for clarity as suggested (Page 2, line 1).

2. Page 2, Line 7: The authors give a reasonable explanation (Page 5, Lines 4-14) about why 2,4-D was used - that it is common and has a non-trivial toxicity. However, with only testing one model organic compound, how applicable are the general results of this study, the use of MW assisted degradation for organics? I would have liked to have seen a few more tests of a broader range of model organic contaminants, to confirm that the approach the authors propose is widely useful.

*Response:* As suggested, we acknowledged the need of testing with different organic compounds as a future research direction of MW-assisted biochar-catalyzed degradation in the revised manuscript (Page 17, line 19), because we had limited access to the laboratory and could not conduct a large amount of additional experiments due to the COVID-19 pandemic.

3. Page 4, Line 58: Are the trace amounts of transition metals in the biochars a concern in terms of leachability / toxicity? It would have been interesting to see the results of a sequential extraction for metals (e.g., Tessier et al., 1979).

*Response:* In view of your comments, we clarified in the revised manuscript (Page 7, line 20-21) that only one type of transition metal (*i.e.*, Fe) with trace amount (*i.e.*, 1-2 wt.%) was tested

in all the four types of biochars (Table 1) and that no leaching of metals, organics, or nutrients was detected under all the experimental conditions of this study.

**4. Page 7, Lines 12-19: Why was a loading of 20 mg biochar in 20 mL of solution chosen? The efficiency of removal depends on this loading, and a test as a function of loading would have been helpful to optimize the system.**

*Response:* As suggested, we explained the reason for choosing this biochar loading in the revised manuscript (Page 7, line 8-10).

**5. Page 7, Lines 31-34: Perhaps tell the reader here that 2,4-D is being quantified using HPLC.**

*Response:* Revised as suggested (Page 7, line 15).

**6. Page 8, Lines 4-49: There is not a citation for these methods of extraction and quantification. Did the authors develop this method themselves, or based on existing or similar extraction / quantification methods for 2,4-D. Later it is discussed that potential degradation compounds of 2,4-D are not detected, which could be an artifact of the HPLC method used (mobile phase, column temperature, time of elution, etc.).**

*Response:* As suggested, references were provided for the methods used for extraction and quantification of 2,4-D in the revised manuscript (Page 8, line 7, 9, 13, 15).

**7. Page 9, Lines 43-46: "CO<sub>2</sub> may have acidified the biochars via the creation of more near-surface oxygen-containing functional groups." Do your XPS data (and to some extent, FTIR data) support this conclusion? If so, I'd be firmer on this point (e.g., Page 10, Lines 48-53).**

*Response:* XPS data were used to support this conclusion and we clarified this in the revised manuscript (Page 9, line 22-23).

**8. Page 11, Lines 53-56: FTIR does not identify "oxygen-containing functional groups...on the biochar surface". IR penetrates the sample significantly, and is more of a bulk technique that shows the average bonding environment (for example, of C in this case). IR analyses can be done as a function of solution pH to identify proton-active functional groups - and even their pK<sub>a</sub>'s in some instances - but this is rarely done. Change the language here.**

*Response:* Thanks again and we revised the discussion accordingly (Page 12, line 3, 5-7).

**9. Page 12, Lines 55-58: Perhaps soften to "...by biochar was LIKELY a result of electrostatic..." The authors propose reasonable hypotheses about the mechanisms of adsorption, but these are not tested.**

*Response:* We agree with you and revised the text as suggested (Page 13, line 10).

**10. Pages 13-14: The authors provide a clear comparison of how the two different feedstock biomasses, N<sub>2</sub> vs. CO<sub>2</sub>, and even pyrolysis temperature impact the efficiency of a biochar using MW for 2,4-D treatment. To make this paper more useful, can the authors provide a few sentences in the discussion and/or conclusions about feedstocks and/or pyrolysis conditions that might be most promising in MW applications? I realize that there is more optimization work to be done (a fact the authors might also mention), but some "take home" guidance would be helpful.**

*Response:* As suggested, in view of the promising results of this proof-of-concept study, we considered optimization of feedstock type and pyrolytic conditions as a future research

direction and revised the text as suggested (Page 17, line 20-21).

**11. Page 15, Lines 19-22: I assume the 10% 2,4-D recovery was measured using HPLC. In case the HPLC method was not capturing all of the degradation products, was the bulk TOC concentration at all helpful? That is, was the TOC recovery on par with the initial 2,4-D concentration in the experiment?**

*Response:* The extraction/desorption of the reacted biochars was conducted using different organic solvents, we attempted to compare the TOC concentrations as suggested but the minor differences in the bulk solutions (especially after dilution) could not accurately demonstrate the existence of 2,4-D or its degradation products.

**12. Page 15, Lines 54-56: Do the authors have any suggestions about how to regenerate OBC-900C (or more generally, a biochar) for reuse in MW applications?**

*Response:* We proposed two regeneration methods as suggested (Page 16, line 20-22).

### Reviewer #2

In this paper, the authors fabricated a series of biochars produced from two feedstock under N<sub>2</sub>/CO<sub>2</sub> atmosphere, and used them for the microwave-assisted removal of 2,4-D. This paper is well designed with detailed characterization of materials and adequate study for the underlying mechanisms. The only doubt is how to confirm the existence of degradation process with microwave, and more experiments might be needed to clarify the main results.

*Response:* Many thanks for your constructive suggestions. We added more experimental results and additional discussion on our coherent findings to further improve our manuscript based on your valuable comments and thoughtful suggestions as follows.

#### **Specific comment:**

**1. In my opinion, it was important to study the degradation process of 2,4-D during its removal, although it might be hard due to the strong entrapment of possible by-products. Enlarging the concentration of 2,4-D or using some other extraction reagents for the spent biochars might be helpful to identify the possible by-products. If there is no direct evidence, it is hard to conclude that the degradation process happened due to the similar TOC and pollutant removal rate. It is possible that merely sorption process occurred and the microwave only facilitated the dispersion process or the formation of surface sorption sites on the biochars?**

*Response:* In our preliminary experiments, much higher (500 mg L<sup>-1</sup>) or lower (10 mg L<sup>-1</sup>) initial 2,4-D concentrations and different biochar loadings (1 and 2.5 g L<sup>-1</sup>) were also tested for adsorption-desorption of 2,4-D by different organic solvents (methanol, ethanol, hexane, acetonitrile, and DMSO). However, it was noteworthy that the 2,4-D recoveries were all below 50%. Furthermore, we affirmed that radicals were generated only in the MW system (Page 15, line 2-5) and that these radicals were able to degrade 2,4-D. In our upcoming studies after the COVID-19 pandemic, we will design more comprehensive experiments and go about other experimental-computational approaches to further prove and quantify the degradation of 2,4-D in the MW/biochar system (Page 16, line 8-13).

**2. If the organic pollutant is completely degraded to CO<sub>2</sub> and H<sub>2</sub>O, there might be some Cl<sup>-</sup> left in the solution. It might be helpful to detect the soluble Cl<sup>-</sup> concentration to confirm the degradation process?**

*Response:* As suggested, according to the latest report (Li et al., 2020, [56]), the dechlorination



rate of 2,4-D was correlated to the degradation efficiency of 2,4-D when 2,4-D was completely mineralized into CO<sub>2</sub> and H<sub>2</sub>O (*viz.* radical + 2,4-D → intermediates → CO<sub>2</sub> + H<sub>2</sub>O + Cl<sup>-</sup>). We revised the manuscript accordingly (Page 16, line 8-13) and would detect the released Cl<sup>-</sup> concentration after reaction in our future studies after the COVID-19 pandemic.

**3. EPR analysis can be added to determine the free radicals during the removal process in order to further confirm the degradation process. It might also be necessary to provide the control experiment for the organic scavengers, which means only mixing organic scavenger with biochar and organic pollutants at 90°C. This can help to confirm the roles of radicals for the degradation instead of competing the sorption sites on biochar since these scavengers was organic compounds, which might change the sorption process of biochar.**

*Response:* The EPR analysis of radicals requires sample testing immediately after reaction, yet we cannot have an immediate access to EPR (in a commercial lab) right after conducting the MW experiments in our lab. Nevertheless, we added more experimental results and explanation (Page 15, line 2-5) reaffirming that these additional organic scavengers did not affect 2,4-D adsorption by the biochars and that the radicals were only generated in the MW system.

**4. The characterization of biochars is detailed and sufficient, but some conclusions need further consideration. E.g., OBC had higher aromatic peaks than ABC, but the difference between N<sub>2</sub> and CO<sub>2</sub> was hard to be identified in the FTIR analysis, especially considering the FTIR analysis might not be a suitable quantitative approach?**

*Response:* The difference in contents of oxygen-containing functional groups was identified by XPS analysis (Page 12, line 3-4; Fig.4). The limitation of FTIR analysis was clarified in the revised manuscript (Page 12, line 5-7) thanks to your comments.

**5. Similar to comment 4, XPS results showed the change of aromatic C=C and aromatic  $\Pi$ - $\Pi^*$  of different biochars, but the alternation is limited. It might not be precise to demonstrate the difference between biochars of two feedstock with such little gap, especially when it comes from peak-fitting. Besides, if aromatic C=C and aromatic  $\Pi$ - $\Pi^*$  both represented the degrees of aromatic rings, why it showed contrasting transition with two feedstock (i.e. oak tree had higher C=C but lower  $\Pi$ - $\Pi^*$  comparing with apple tree)?**

*Response:* The limitation of XPS analysis was clarified in the revised manuscript (Page 12, line 11-13), and the areas of these two peaks corresponded to the content of aromatic C=C on biochar surface and the density of  $\pi$ - $\pi^*$  transition in aromatic rings of biochar, respectively. The text was revised for clarity as suggested (Page 12, line 8).


**6. The reusability of biochars declined noticeably after each cycle and "popcorn effect" might be the main reason according to the author's words, which was possible, but another possible explanation of this result is the occupation of sorption sites after each cycle. So, the author can evaluate the reusability of biochar at 90°C with oil bath without microwave to exclude this possibility.**

*Response:* We agree with you and added this possibility in the revised manuscript (Page 16, line 16-18). However, the 2,4-D adsorption capacity of biochar under MW condition might not be equivalent to that of oil bath [21], limiting the relevance of reusability test with oil bath.

**7. 90 oC in the Fig.5 needs revise.**

*Response:* Revised as suggested (Fig.5).

## Graphical abstract

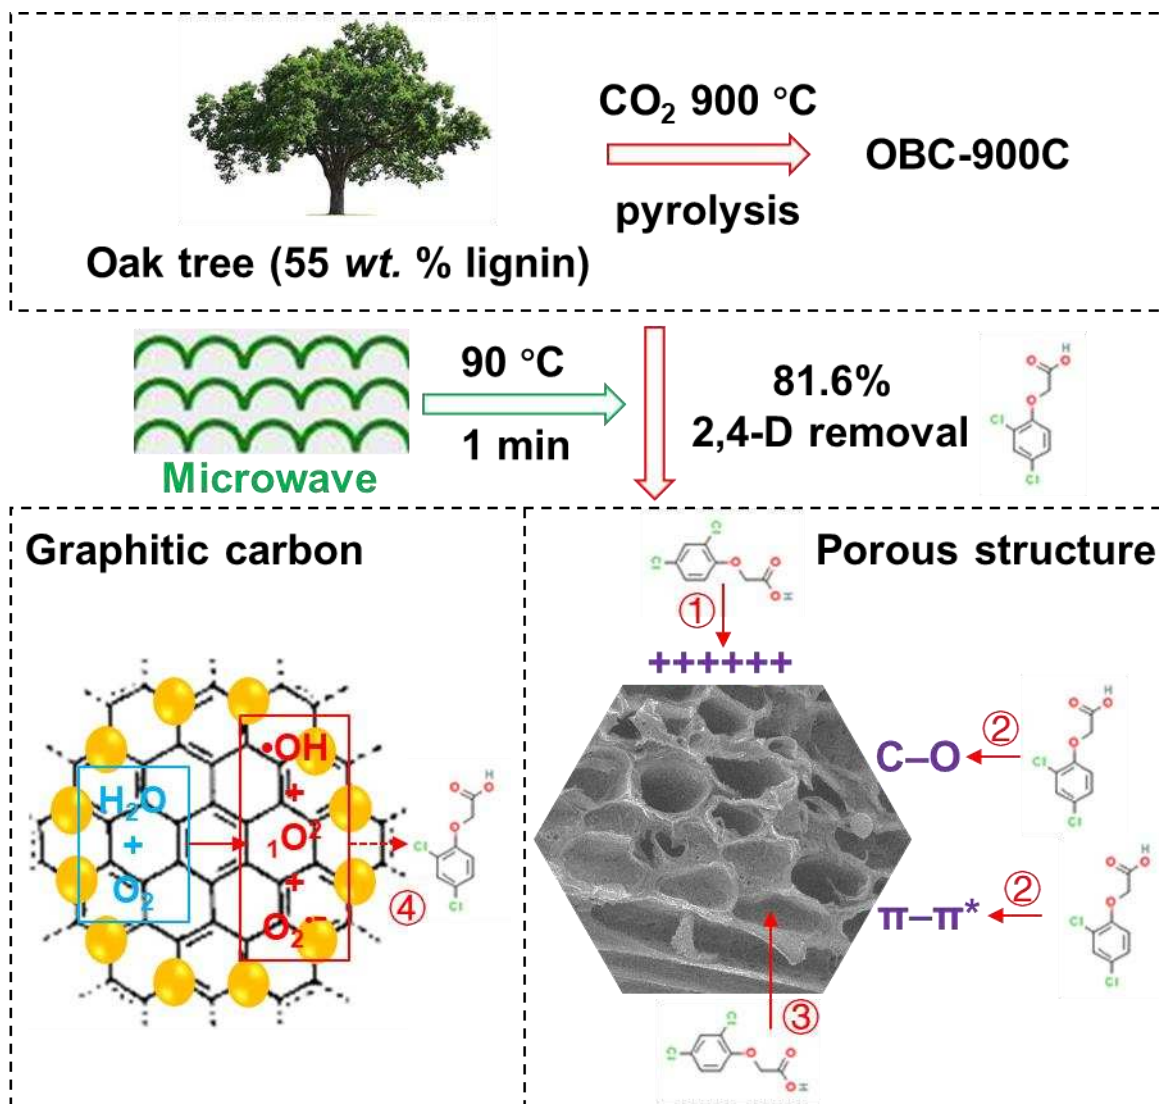

① Electrostatic interaction ③ Diffusion into inner pores

② Chemical adsorption ④ Possible degradation

● "Hot spots"

## Highlights

- CO<sub>2</sub>-pyrolyzed lignin-rich oak at 900 °C produced highly graphitic, porous OBC-900C
- OBC-900C exhibited high microwave (MW) absorption and 2,4-D adsorption capacities
- MW irradiation at 90 °C significantly promoted 2,4-D removal by OBC-900C
- MW-induced thermal effect generated “hot spots” and various radicals for pollutant degradation

# Tailored design of graphitic biochar for high-efficiency and chemical-free microwave-assisted removal of refractory organic contaminants

Yuqing Sun<sup>a</sup>, Iris K.M. Yu<sup>b,c</sup>, Daniel C.W. Tsang<sup>a,\*</sup>, Jiajun Fan<sup>b</sup>, James H. Clark<sup>b,d</sup>, Gang Luo<sup>d</sup>, Shicheng Zhang<sup>d</sup>, Eakalak Khan<sup>e</sup>, Nigel J.D. Graham<sup>f</sup>

<sup>a</sup> Department of Civil and Environmental Engineering, The Hong Kong Polytechnic University, Hung Hom, Kowloon, Hong Kong, China.

<sup>b</sup> Green Chemistry Centre of Excellence, Department of Chemistry, University of York, York, YO10 5DD, UK.

<sup>c</sup> Department of Chemistry and Catalysis Research Center, Technische Universität München, Lichtenbergstrasse 4, Garching, 85748, Germany.

<sup>d</sup> Shanghai Key Laboratory of Atmospheric Particle Pollution and Prevention (LAP3), Department of Environmental Science and Engineering, Fudan University, Shanghai 200438, China.

<sup>e</sup> Department of Civil and Environmental Engineering and Construction, University of Nevada, Las Vegas, NV 89154, USA.

<sup>f</sup> Department of Civil and Environmental Engineering, Imperial College London, South Kensington Campus, London SW7 2AZ, UK.

\* Corresponding author email: [dan.tsang@polyu.edu.hk](mailto:dan.tsang@polyu.edu.hk)

## Abstract

Energy-saving, chemical-free, and high-efficiency microwave (MW)-assisted water treatment can be greatly facilitated *via* tailored design of an economical, sustainable, and ‘green’ carbonaceous catalyst. In this study, various biochars (BC) were pyrolyzed from two lignocellulosic waste biomasses, oak (O) and apple tree (A), at high temperature (900 °C) and under different gases (N<sub>2</sub> and CO<sub>2</sub>). The holistic characterization by advanced spectroscopic techniques demonstrated that CO<sub>2</sub> pyrolysis of feedstock with more lignin (*i.e.*, oak), produced biochar with increased aromaticity and degree of carbonization. CO<sub>2</sub> modification created a hierarchical porous structure, improved surface hydrophilicity, polarity, and acidity, and provided higher

1  
2  
3  
4 densities of near-surface functionalities of the biochar. Without MW irradiation, ABC-900C (1 g L<sup>-1</sup>)  
5  
6 provided the highest adsorption (52.6%, 1 min) of 2,4-dichlorophenoxy acetic acid (2,4-D) ascribed to large  
7  
8 specific surface area, high micropore content, appropriate pore size, and abundant active groups. OBC-900C  
9  
10 (1 g L<sup>-1</sup>) enabled significantly increased 2,4-D removal (81.6%, 1 min) under MW irradiation (90 °C) in  
11  
12 contrast with an oil bath (55.7%, 90 °C, 1 min) and room temperature (33.9%, 1 min) conditions, due to its  
13  
14 highest graphitization degree and medium-developed microporous structure. The MW-induced thermal effect  
15  
16 formed “hot spots” on the biochar surface as evidenced by elevated temperature of the bulk solution and  
17  
18 lowered energy consumption of the MW reactor in the presence of OBC-900C, compared to those of the  
19  
20 other biochars. The scavenging tests suggested that the generation of highly oxidative hydroxyl (<sup>•</sup>OH), anionic  
21  
22 superoxide (O<sub>2</sub><sup>•-</sup>), and singlet oxygen (<sup>1</sup>O<sub>2</sub>) radicals contributed to the removal of 2,4-D. This study has  
23  
24 demonstrated that biochar with customized structure and high organic adsorption capacity can act as an  
25  
26 effective MW absorber suitable for rapid and improved removal of toxic organics.  
27  
28  
29  
30  
31  
32

33 **Keywords:** Microwave irradiation; Engineered biochar; Graphitic carbon; Sustainable waste management;  
34  
35  
36 Advanced wastewater treatment.  
37  
38  
39

## 40 41 **1. Introduction**

42  
43 With the rapid economic development, continuous industrialization, and increasing expectations of quality  
44  
45 of life, large volumes of diverse chemicals have been discharging into aquatic ecosystems and causing severe  
46  
47 water pollution [1]. Conventional wastewater treatment has become less efficient, and even advanced  
48  
49 oxidation processes (AOPs) exhibit limitations including high demand of energy and need for additional  
50  
51 chemicals, incomplete removal of refractory organic pollutants, and generation of more toxic intermediates  
52  
53 derived from their parent compounds [2]. In recent years, microwave (MW)-assisted water treatment has  
54  
55 emerged as a promising technology [3,4]. MW irradiation, which has a wide range of frequency (0.3–300  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1  
2  
3  
4 GHz) and wavelength (1–0.001 m) [3], provides selective, volumetric, uniform, and non-contact heating for  
5  
6 MW-absorbing materials (*i.e.*, MW catalysts) [4,5], and induces rapid and non-gradient temperature ramping.  
7  
8 The thermal effect of MW irradiation may produce “hot spots” or micro-plasmas that ionize the surrounding  
9  
10 atmosphere [6], which can accelerate organic decomposition and generate highly oxidative hydroxyl radicals  
11  
12 (\*OH) [4,6]. MW irradiation treatment presents advantages compared to other heating techniques of easy  
13  
14 operation, improved processing efficiency, reduced energy and chemical consumption, shortened reaction  
15  
16 time, and complete mineralization of organic contaminants [3,7].  
17  
18  
19  
20

21 MW catalysts usually consist of a single (or binary/ternary) metallic phase (*e.g.*, Fe [8], Cu [9], Mn [10],  
22  
23 Ni [11], Ti [12], Co [13], and Bi [14]), supported on porous, conductive materials (*e.g.*, activated carbon (AC)  
24  
25 [15], mesoporous carbon [16], reduced graphene oxide (rGO) [17], and minerals [18]), which favour  
26  
27 dispersion of metals/metal oxides and accelerate recycling of metal redox pairs [17]. Nonetheless, these  
28  
29 catalysts are prone to deactivation *via* metal leaching/detachment creating a new environmental problem [6].  
30  
31 In contrast, metal-free carbon materials display strong thermal stability and robust anti-oxidation abilities that  
32  
33 maintain good catalytic performance upon repeated use [4]. Carbonaceous materials with high dielectric loss  
34  
35 tangent values ( $\tan \delta$ ) are powerful MW absorbers [16], but seldom explored so far as MW catalysts for  
36  
37 organics removal. Zhang et al. reported a MW-induced complete (97.9%) degradation of congo red (50 mg  
38  
39 L<sup>-1</sup>, 25 mL) catalyzed by commercial granular AC powder (2.0 g L<sup>-1</sup>) in 2.5 min; however, no direct evidence  
40  
41 was provided for the generation of reactive oxidative species (ROSs) and “hot spots” [20]. Veksha et al.  
42  
43 claimed that MW irradiation on woodchip-derived AC (600 °C pyrolysis for 30 min followed by 10-min CO<sub>2</sub>  
44  
45 activation at 780 °C) could not initiate the formation of “hot spots” or radicals for methyl orange (MO)  
46  
47 decomposition [21]. Chen et al. reported MW-enhanced removal (100% within 7 min) of MO (25 mg L<sup>-1</sup>, 25  
48  
49 mL) due to the formation of \*OH over commercial multi-walled carbon nanotubes (CNTs) [22], yet did not  
50  
51 discuss the existence of “hot spots” and differentiate organic adsorption from degradation [22]. In addition to  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1  
2  
3  
4 a lack of conclusive findings or solid evidence of MW-directed organic removal, the reported materials (AC  
5  
6 and CNTs) were produced or purchased without science-informed design for high-performance  
7  
8 functionalities under MW irradiation. Thus, there is a need for tailoring economical, sustainable, and ‘green’  
9  
10 carbon catalysts with favourable physicochemical characteristics, to achieve efficient MW absorption and fast  
11  
12 removal of refractory organic pollutants.  
13  
14

15  
16 Biochar is a carbon-rich solid material with aromatic surfaces produced *via* cost-effective thermal  
17  
18 decomposition of various biomasses [23,24], including lignocellulosic wastes or residues from agricultural  
19  
20 and forestry activities as the renewable feedstocks, under inert conditions [23,25]. Biochar finds wide  
21  
22 applications in soil remediation [26,27], carbon dioxide (CO<sub>2</sub>) sequestration [28,29], decontamination of  
23  
24 heavy metals [30,31], degradation of organic pollutants [32,33], biorefinery [34,35], and energy storage [36].  
25  
26 Its outstanding performance is attributed to the hierarchical porous structure and abundant surface  
27  
28 functionalities, which are primarily dependent on the synthesis conditions including biomass composition  
29  
30 (*e.g.*, cellulose, hemicellulose, and lignin), pyrolysis temperature, and atmosphere (*e.g.*, N<sub>2</sub> and CO<sub>2</sub>) [37].  
31  
32 Our recent studies revealed that high-temperature pyrolysis and CO<sub>2</sub> modification induced carbon reforming  
33  
34 to improve the porous structure, increase carbonization level, and facilitate interface chemical interaction of  
35  
36 biochar [38,39]. Herein, we hypothesize that: (i) MW-assisted organic compound removal is a combined  
37  
38 process of simultaneous adsorption and degradation by biochar; (ii) highly porous and graphitic biochar with  
39  
40 high MW absorption and organic adsorption capacities could act as effective MW-catalysts; and (iii) enhanced  
41  
42 organic sequestration under MW irradiation catalyzed by biochar is attributed to the MW-induced thermal  
43  
44 effect on the biochar surface.  
45  
46  
47  
48  
49  
50  
51  
52

53 In this study, two common lignocellulosic biomasses, oak tree (22 *wt.%* cellulose, 23 *wt.%* hemicellulose,  
54  
55 and 55 *wt.%* lignin) and apple tree (43 *wt.%* cellulose, 22 *wt.%* hemicellulose, and 35 *wt.%* lignin) [23], with  
56  
57 trace amounts of transition metals were selected as biochar feedstocks. Various biochars were prepared under  
58  
59  
60  
61  
62  
63  
64  
65

1  
2  
3  
4 a high temperature (900 °C) and different purging gases (N<sub>2</sub> and CO<sub>2</sub>). The easily mobilized 2,4-  
5  
6 dichlorophenoxy acetic acid (2,4-D) was selected as a target refractory organic contaminant, as it has a high  
7  
8 water solubility (900 mg L<sup>-1</sup>), anionic nature ( $pK_a = 2.7$ ), recalcitrant chemical structure, and low  
9  
10 biodegradability, and is one of the most widely used herbicides and possible human carcinogens with  
11  
12 moderate toxicity [40]. The objectives of this study were to: (i) articulate the interactions of several pyrolysis  
13  
14 parameters (*i.e.*, feedstock type and gaseous medium) for tailoring the biochar physicochemical properties,  
15  
16 surface structure, and interfacial chemical behaviour; and (ii) capitalize on the evolution of MW-induced  
17  
18 thermal effect for biochar-catalyzed organic removal *via* generation of “hot spots” and various ROSs. The  
19  
20 results of this study are conducive to improving the future design of high-efficiency, sustainable, and ‘green’  
21  
22 engineered carbon catalysts for application of MW irradiation in wastewater treatment.  
23  
24  
25  
26  
27  
28  
29  
30

## 31 **2. Materials and methods**

### 32 *2.1. Biomass and chemicals*

33  
34 Waste wood biomasses of oak tree and apple tree were collected from Wuxi city (Jiangsu province, China)  
35  
36 and Guiyang city (Guizhou province, China), respectively, and were applied as biochar feedstocks without  
37  
38 further treatment. All chemicals used in this study (*viz.* 2,4-dichlorophenoxyacetic acid (C<sub>8</sub>H<sub>6</sub>Cl<sub>2</sub>O<sub>3</sub>, 2,4-D),  
39  
40 *tert*-butanol (C<sub>4</sub>H<sub>10</sub>O, TBA), chloroform (CHCl<sub>3</sub>, CF), furfuryl alcohol (C<sub>5</sub>H<sub>6</sub>O<sub>2</sub>, FFA), methanol (CH<sub>3</sub>OH),  
41  
42 ethanol (C<sub>2</sub>H<sub>5</sub>OH), hexane (C<sub>6</sub>H<sub>14</sub>), acetonitrile (CH<sub>3</sub>CN), dimethylsulfoxide ((CH<sub>3</sub>)<sub>2</sub>SO, DMSO), and acetic  
43  
44 acid (CH<sub>3</sub>COOH)) were of analytical reagent grade and solvents were of high-performance liquid  
45  
46 chromatography (HPLC) grade from Sigma-Aldrich Co. Lit. (St. Louis, USA). Ultrapure water (UW, 18.2  
47  
48 MΩ cm), obtained from a Millipore Milli-Q Water Purification System (Milford, USA), was employed for  
49  
50 all experimental aqueous solutions.  
51  
52  
53  
54  
55  
56

### 57 *2.2. Preparation of the biochars*



1  
2  
3  
4 Wood waste (oak tree and apple tree) were cut into small pieces (< 1 cm), crushed and sieved through a  
5  
6 120-mesh (particle size < 0.125 mm), and then pyrolyzed in a tube furnace that was heated to 900 °C at a  
7  
8 heating rate of 10 °C min<sup>-1</sup>, and lasted for 2 h after reaching the target temperature with continuous N<sub>2</sub> or CO<sub>2</sub>  
9  
10 purging at a flow rate of 200 mL min<sup>-1</sup>. After being cooled down to room temperature (23 ±2 °C) inside the  
11  
12 furnace, the samples were taken out, ground and passed through a 200-mesh sieve (particle size < 0.075 mm),  
13  
14 and stored in airtight containers before use. The obtained oak and apple tree biochars were denoted as OBC-  
15  
16 900N, OBC-900C, ABC-900N, and ABC-900C, respectively, where N/C corresponded to N<sub>2</sub>/CO<sub>2</sub> purging.  
17  
18  
19  
20

### 21 *2.3. Characterization of the biochars*

22  
23 The ultimate elemental analysis (EA, Vario EL cube, Germany) was used to estimate the CHONS  
24  
25 elemental ratio in the biochar samples. The surface morphology and approximate surface elemental analysis  
26  
27 of the obtained biochar samples were observed using scanning electron microscopy coupled with energy-  
28  
29 dispersive X-ray spectroscopy (SEM-EDS, JSM-IT300, JXA-8230, Hitachi, Japan). The textural  
30  
31 characteristics were determined using N<sub>2</sub> adsorption-desorption isotherms obtained from a surface area  
32  
33 analyzer (Quantachrome Autosorb, USA) at 77 K for Brunauer-Emmett-Teller (BET) surface area and  
34  
35 Barrett-Joyner-Halenda (BJH) porosity analyses. The Fourier transform infrared (FTIR, Nicolet 6700  
36  
37 spectrometer, USA) spectroscopy was used to observe the near-surface functionalities on biochars with the  
38  
39 wavelength range at 400–4000 cm<sup>-1</sup>. The micro-Raman spectrometer (Raman spectra, Renishwa Invia Fellex,  
40  
41 UK) equipped with a Diode-Pumped Solid State (DPSS) at 532 nm excitation was used to record the defective  
42  
43 level and graphitization degree of the biochars. The X-ray photoelectron spectroscopy (XPS, Thermo Fisher  
44  
45 Scientific, USA) with Al K $\alpha$  radiation was used to investigate the composition and chemical state of the  
46  
47 elements on the sample surfaces. The binding energy of all characteristic peaks were calibrated with carbon  
48  
49 C1s core level at 284.8 eV. Devolution of XPS data was conducted using Shirley background associated with  
50  
51 Gaussian-Lorentzian model in XPSPEAK41, and the component peaks were identified by comparison of  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1  
2  
3  
4 their binding energies (BEs) with the reported values in the literature.  
5

#### 6 7 2.4. MW-assisted removal of 2,4-D by the biochars 8

9 The 2,4-D solution was prepared at an initial concentration of 100 mg L<sup>-1</sup> (in accordance with the average  
10 concentration reported in 2,4-D manufacturing wastewaters [41,42]) by dissolving a certain amount of  
11 C<sub>8</sub>H<sub>6</sub>Cl<sub>2</sub>O<sub>3</sub> in 1 L UW under magnetic stirring at 200 rpm for 6 h. To initiate the reaction, 20 mL of the 2,4-D  
12 solution and 20 mg of the biochars (OBC-900N, OBC-900C, ABC-900N, and ABC-900C, respectively)  
13 were added in 100 mL Teflon reaction vessels without pH adjustment and heated in the Ethos UP MW Reactor  
14 (Milestone, 2450 MHz, maximum power of 1900 W) under continuous magnetic stirring. The biochar  
15 loading (*i.e.*, 1 g L<sup>-1</sup>) was determined according to preliminary experiments (data not shown) for obtaining  
16 relatively high 2,4-D removal by the four biochars with distinguishable differences. The MW temperature  
17 was ramped from room temperature to 90 °C within 2 min, held for 1 min, and gradually cooled down to  
18 below 60 °C by continuous mechanical ventilation in the MW reactor. The adopted reaction temperature and  
19 duration were comparable to previous studies on MW-assisted organic removal [20-22]. After reaction, an  
20 aliquot of 1 mL solution was withdrawn from the vessels, filtered into HPLC sample vials through 0.45 µm  
21 pore-size mixed cellulose ester membrane filters (MCE, Millipore), and tested for 2,4-D concentration by  
22 HPLC. The spent biochars were recovered by vacuum filtration, rinsed with UW, and oven dried at 60 °C  
23 overnight. The reusability of biochars was investigated by reacting spent samples (1 g L<sup>-1</sup>) with 20 mL  
24 solution of 2,4-D (100 mg L<sup>-1</sup>) in the MW reactor. A control experiment with only MW and no biochar was  
25 conducted. A comparative experiment using oil bath as the heating source was also performed under the same  
26 reaction conditions. The adsorption of 2,4-D by biochars was investigated at room temperature. No leaching  
27 of metals, organics, or nutrients was detected from the four biochars under the studied experimental conditions.  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54

55 To verify the *in-situ* formation of radicals, such as •OH, anionic superoxide radical (O<sub>2</sub><sup>•-</sup>), and singlet  
56 oxygen (<sup>1</sup>O<sub>2</sub>), during MW-assisted removal of 2,4-D, certain quantities of different organic scavengers (TBA  
57  
58  
59  
60  
61  
62  
63  
64  
65

1  
2  
3  
4 ( $k_{OH} = (3.2-7.6) \times 10^8 \text{ M}^{-1} \text{ s}^{-1}$ ), CF ( $k_{O_2^-} = (1.1-3.2) \times 10^9 \text{ M}^{-1} \text{ s}^{-1}$ ), and FFA ( $k'_{O_2} = 1.2 \times 10^8 \text{ M}^{-1} \text{ s}^{-1}$ ),  
5  
6 respectively) were doped into the MW vessels to reach the target concentration of 45.2 mmol (at molar ratio  
7  
8 to 2,4-D of 100:1) [39,43], respectively. The radical quenching experiment was conducted under the same  
9  
10 MW/oil bath/room temperature conditions.  
11

12  
13 To extract adsorbed 2,4-D and possible degradation intermediates, after 1-min reaction in the three systems,  
14  
15 the spent samples were: (i) transferred into 20 mL solution of organic solvent (methanol, ethanol, hexane,  
16  
17 acetonitrile, and DMSO, respectively) under 8-h end-over-end shaking at 30 rpm [40]; or (ii) added into 20  
18  
19 mL mixed solution of water and different organic solvents (50%, v/v) under 1-min reaction in MW reactors  
20  
21 at 90 °C [21]. The above solutions were then analyzed for the extracted 2,4-D.  
22  
23

## 24 25 26 *2.5. Analytical methods*

27  
28 The samples were analyzed for 2,4-D by a HPLC (Hitachi Chromaster 5420, Japan, limit of detection  
29  
30 (LOD) of 0.1 mg L<sup>-1</sup>) equipped with an ODS-2 chromatography column (150 mm × 4.6 mm, 5 μm) and an  
31  
32 ultraviolet and visible spectrophotometry (UV-VIS) detector with UV wavelength set at 280 nm [44]. A  
33  
34 mixture of 60% (v/v %) acetonitrile, 38% (v/v %) UW, and 2% (v/v %) acetic acid was used as the mobile  
35  
36 phase at a flow rate of 0.5 mL min<sup>-1</sup> [44]. The peak for 2,4-D was detected at a retention time of 5.6 min [44].  
37  
38 The total organic carbon (TOC) concentration was measured by a TOC analyzer (Shimadzu, SSM-5000A,  
39  
40 Japan, LOD of 0.1 mg L<sup>-1</sup>). The 2,4-D or TOC removal efficiency was calculated using **Eq. 1** as follows.  
41  
42

$$43 \text{ Removal efficiency} = (C_{\text{initial}} - C_{\text{final}}) / C_{\text{initial}} \times 100\% \quad \text{(Eq.1)}$$

44  
45  
46 Standard calibration was carried out prior to each analysis. Standards were analyzed every 10 samples for  
47  
48 quality assurance and quality control. All experiments were performed in at least triplicate, and the results are  
49  
50 presented as mean ± standard deviations. One-way analysis of variance (ANOVA) by the Duncan test was  
51  
52 applied to analyze the significance of differences between data (SPSS version 22.0). The lower-case letters in  
53  
54 the figures represent data grouping based on the significance level of 0.05 ( $p < 0.05$ ).  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

### 3. Results and discussion

#### 3.1. Characterization of the biochars

The distinctive physicochemical properties of the various biochars prepared from different feedstocks under N<sub>2</sub>/CO<sub>2</sub> purging are summarized in **Table 1**. Pyrolysis of the lignin-rich biomass (*i.e.*, oak wood) produced biochars (OBC-900N and OBC-900C) with higher yield (20.8 and 19.8%) and carbon content (92.1 and 88.6 wt.%). Switching the purging gas from N<sub>2</sub> to CO<sub>2</sub> noticeably lowered the yield (from 19.8 to 17.0%) and carbon content (from 88.8 to 78.9 wt.%) of the resultant ABC-900s. These indicated that thermal decomposition of biomass in a CO<sub>2</sub> environment is more significant than that in a N<sub>2</sub> atmosphere, probably due to accelerated consumption of carbon matrix by CO<sub>2</sub> and other active gases produced during pyrolysis [45,46]. The elemental analysis revealed that the OBC-900s exhibited much lower molar ratios of H/C (0.010 of the OBC-900C and 0.011 of the OBC-900N) than the ABC-900s (0.025 of the ABC-900C and 0.079 of the ABC-900N), suggesting an increased biochar aromaticity with higher lignin content in the feedstocks and using CO<sub>2</sub> pyrolysis. The higher molar ratio of (O+N)/C of the ABC-900C (0.200) compared to ABC-900N (0.096) indicated an improved hydrophilicity and polarity in CO<sub>2</sub>. In particular, the ABC-900C contained a much higher oxygen content (20.3 wt.%) than the other three biochars, probably because of CO<sub>2</sub> induced carbon oxidation during cooling inside the tube furnace after pyrolysis [47]. The zeta potential of the OBC-900s was negative (-18.8 – -12.6 mV) in contrast to the positively charged surfaces of the ABC-900s (2.64 – 6.73 mV), which can be ascribed to the higher metal (*i.e.*, Ca, K, Mg, Na, Fe, and Al) content in the former (**Table 1**). The pH values of the CO<sub>2</sub> pyrolyzed biochars (10.8–10.9) were lower than those of the N<sub>2</sub> pyrolyzed biochars (11.2–12.4), despite their similar ash contents (**Table 1**). CO<sub>2</sub> may have acidified the biochars *via* the creation of more near-surface oxygen-containing functionalities [45,48], which could be verified by the XPS analysis in the subsequent discussion.

1  
2  
3  
4 The SEM images clearly depict the morphological and structural differences in the biochars dependent on  
5  
6 different feedstocks and purging gases (**Fig. 1**). The OBC-900s presented rougher surfaces because of their  
7  
8 higher ash content (**Table 1**), while the ABC-900s exhibited more porous structures due to the hierarchical  
9  
10 spatial structure of softwood (*e.g.*, apple tree) [23]. As shown in **Fig. 1**, micro- and meso-pores were highly  
11  
12 developed inside the carbon matrix of the CO<sub>2</sub> biochars (*i.e.*, OBC-900C and ABC-900C). These were also  
13  
14 evidenced by the surface area and pore size distribution of the biochars in **Table 1**. The BET surface area  
15  
16 ( $S_{\text{BET}}$ , 479.9 or 510.5 m<sup>2</sup> g<sup>-1</sup>) and total pore volume ( $V_{\text{total}}$ , 0.325 or 0.349 cm<sup>3</sup> g<sup>-1</sup>) of biochars fabricated in a  
17  
18 CO<sub>2</sub> environment (OBC-900C or ABC-900C) were significantly higher than those generated in a N<sub>2</sub>  
19  
20 environment. The CO<sub>2</sub> medium promoted the formation of micropores (377.5 or 384.4 m<sup>2</sup> g<sup>-1</sup>) of the OBC-  
21  
22 900C (or ABC-900C). The micropore volume also increased from 0.164 (ABC-900N, 46.8% of  $V_{\text{total}}$ ) to  
23  
24 0.235 (ABC-900C, 67.4% of  $V_{\text{total}}$ ) cm<sup>3</sup> g<sup>-1</sup>. The average pore diameter ( $D_p$ ) increased from 2.53 nm for the  
25  
26 OBC-900N to 2.90 nm for the OBC-900C, indicating that CO<sub>2</sub> acted as a pore-enlarging agent. Tar and  
27  
28 volatile organics generated from an incomplete thermal degradation of lignin could block the pores in biochars  
29  
30 [49]. Such pore blocking was suppressed in CO<sub>2</sub>, which could expedite tar cracking/reforming *via* the thermo-  
31  
32 dynamically favourable Boudouard reaction between the CO<sub>2</sub> and lignin-C (*viz.*  $C + \text{CO}_2 \rightarrow \text{CO}$ ) at  $\geq 720$  °C  
33  
34 [50], resulting in highly porous biochars [45].

35  
36  
37  
38 The near-surface chemical functionalities of the biochars were characterized by FTIR analysis, as shown  
39  
40 in **Fig. 2**. The small peak at  $\sim 3760$  cm<sup>-1</sup> ascribed to the -OH group was present in the spectra of all the biochars  
41  
42 except the ABC-900N [51]. The peaks between 1360 and 1450 cm<sup>-1</sup> are due to the aromatic C=C rings  
43  
44 [52,53], whereas the aromatic C-C rings appeared at  $\sim 760$  cm<sup>-1</sup> [54]. The high-temperature (900 °C)  
45  
46 pyrolysis eliminated the O-containing functional groups from the biochar surface and increased the content  
47  
48 of condensed aromatic rings [38,39] as a result of intensive decomposition of the aliphatic and phenolic  
49  
50 organic compounds *via* dehydration of cellulosic and ligneous components [39]. Biomass with higher lignin  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1  
2  
3  
4 content in a CO<sub>2</sub> atmosphere can provide biochars with a higher level of carbonization, as evidenced by the  
5  
6 increasing intensity of aromatic peaks in the order of ABC-900N < ABC-900C < OBC-900N < OBC-900C  
7  
8  
9 (Fig. 2), in accordance with the elemental analysis (Table 1).

10  
11 The graphitization degree of the biochars was further investigated by Raman analysis (Fig. 3). The Raman  
12  
13 spectra of the biochar samples were deconvoluted into five characteristics peaks that were assigned to *sp*<sup>2</sup> C–  
14  
15 H of aromatic rings (S<sup>1</sup>) at 1060 cm<sup>-1</sup>, defect bands and small ordered fused benzene rings (D) at 1310 cm<sup>-1</sup>,  
16  
17 methyl group and amorphous carbon (V<sup>1</sup>) at 1380 cm<sup>-1</sup>, aromatics with 3–5 rings (G<sup>1</sup>) at 1540 cm<sup>-1</sup>, and  
18  
19 highly ordered *sp*<sup>2</sup> graphitic carbon (G) at 1590 cm<sup>-1</sup>, respectively [39]. The area ratio of the D peak to the G  
20  
21 peak (*A<sub>D</sub>/A<sub>G</sub>*) of the CO<sub>2</sub> pyrolyzed composites (1.94–2.56) was smaller than that produced in N<sub>2</sub> (2.26–3.52),  
22  
23 suggesting that a CO<sub>2</sub> medium induced higher aromaticity and graphitization within the carbon matrix during  
24  
25 pyrolysis [45,50]. Higher proportions of the G (11.5–13.0%) and G<sup>1</sup> (2.58–6.72%) bands were formed in the  
26  
27 OBC-900s. The ratio of *A<sub>D</sub>/A<sub>G</sub>* decreased when there was a larger lignin content in the feedstocks. The  
28  
29 cellulose and hemicellulose with branched polymer structure and short side chains form volatile products  
30  
31 during pyrolysis of wood biomass, whereas the lignin with complex crosslinking phenolic polymer structure  
32  
33 contributes mainly to the biochar production [23]. At pyrolysis temperatures higher than 700 °C, the  
34  
35 fragmentation and repolymerization of lignin monomers favour the biochar formation, which could be  
36  
37 accelerated in the presence of CO<sub>2</sub> [23]. Thus, the CO<sub>2</sub> enhanced aromaticity could be attributed to accelerated  
38  
39 conversion of lignin monomers [44].  
40  
41  
42  
43  
44  
45  
46  
47

48 XPS analysis was conducted to investigate the transformation of near-surface functional groups in various  
49  
50 biochars (Fig. 4). For all the samples, the C 1s spectra consisted of three distinctive peaks that were attributed  
51  
52 to the presence of aromatic C–C/C=C at 284.8 eV, C–O at 285.8 eV, and π–π\* transition in aromatic rings at  
53  
54 288.3 eV, respectively [38]. As shown in Fig. 4, the ratio of aromatic C–C/C=C increased from 65.4–66.9%,  
55  
56 for ABC-900s to 68.4–68.7% for OBC-900s. This observation reaffirmed the idea of an enhanced conversion  
57  
58  
59  
60  
61  
62  
63  
64  
65

1  
2  
3  
4 of the crosslinking C structure to condensed aromatic nature of biochars derived from lignin-rich feedstocks  
5  
6 [23,39], agreeing with the elemental composition (**Table 1**), FTIR spectra (**Fig. 2**), and Raman spectra (**Fig.**  
7  
8 **3**). Moreover, by means of XPS analysis, oxygen-containing functional groups (C–O) were identifiable on  
9  
10 the biochar surface, the ratio of which increased from 16.1% (ABC-900N) to 17.5% (ABC-900C) after CO<sub>2</sub>  
11  
12 activation. This contradictory observation compared with FTIR analysis (**Fig. 2**) might be due to the effect of  
13  
14 solution pH and pK<sub>a</sub> of biochar on the sensitivity of FTIR, which is a bulk technique that reflects the average  
15  
16 bonding environment. The C–O might result from the interaction of CO<sub>2</sub> with organic/inorganic compounds  
17  
18 in the biochar [49]. Moreover, the density of  $\pi$ – $\pi^*$  transition in aromatic rings increased from 14.7–15.1% in  
19  
20 the OBC-900s to 17.0–17.1% in the ABC-900s (**Fig. 4**). According to a previous study [55], these  
21  
22 functionalities (C–O and  $\pi$ – $\pi^*$  transition) on biochar could contribute to effective adsorption of 2,4-D.  
23  
24 However, it should be acknowledged that the above discussion was mainly based on the peak fitting of XPS  
25  
26 spectra, which might be complicated by the small differences between different biochars. More accurate  
27  
28 analysis using advanced and computational techniques should also be pursued in future studies.  
29  
30  
31  
32  
33  
34  
35  
36  
37

### 38 *3.2. MW-assisted removal of 2,4-D by the biochars*

39  
40  
41 Removal efficiencies of 2,4-D by various biochars under three reaction conditions (*i.e.*, room temperature,  
42  
43 oil bath, and MW irradiation) are presented and compared in **Fig. 5**. CO<sub>2</sub> activated biochars (ABC-900C and  
44  
45 OBC-900C) with increased S<sub>BET</sub> (479.9 and 510.5 m<sup>2</sup> g<sup>-1</sup>) and D<sub>p</sub> (2.90 and 2.99 nm) gave better 2,4-D  
46  
47 adsorption performance than the N<sub>2</sub>-produced biochars. CO<sub>2</sub> modification significantly promoted 2,4-D  
48  
49 adsorption on OBC-900 and ABC-900, with the equilibrium removal efficiency improved from 40.9 ± 0.7 to  
50  
51 49.4 ± 7.3% and from 41.8 ± 1.5 to 69.8 ± 7.0% (**Fig. S1 (Supporting Information)**) after 30-min reaction,  
52  
53  
54 respectively, at room temperature without heating. A previous study also discovered a positive correlation  
55  
56 between the specific surface area of biochar (400–600 m<sup>2</sup> g<sup>-1</sup>) and its 2,4-D adsorption capacity [40],  
57  
58  
59  
60  
61  
62  
63  
64  
65

1  
2  
3  
4 indicating that the progressive widening of micropores into mesopores accommodated more 2,4-D molecules  
5  
6 with polar surface area of  $47 \text{ \AA}^2$  [40]. Apart from a porous structure, other physicochemical properties of  
7  
8 biochar also determined its capacity for 2,4-D adsorption. Our study suggested ABC-900C as the best-  
9  
10 performing adsorbent of 2,4-D at room temperature. It had a zeta potential of 2.64 mV (**Table 1**) and thus a  
11  
12 positively charged surface that favoured electrostatic interaction with the anionic form of 2,4-D at solution  
13  
14 pH > 2.7 [55]. In addition, biochars with higher content of the  $\pi$ - $\pi^*$  transition (17.1% of the ABC-900C, **Fig.**  
15  
16  
17 **4**) as electron acceptor could strengthen attraction with the electron-rich benzene ring of 2,4-D as electron  
18  
19 donor *via*  $\pi$ - $\pi$  interaction [55]. Moreover, the abundant oxygen-containing functional groups (17.5% C-O,  
20  
21  
22 **Fig. 4**) in the ABC-900C could contribute more active sites for 2,4-D adsorption [55]. Thus, adsorption of  
23  
24 2,4-D by biochar was likely a result of electrostatic interaction, electron conjugation, and chemisorption [55].  
25  
26  
27

28  
29 The significantly promoted removal of 2,4-D under MW irradiation is clearly illustrated in **Fig. 5**. After 1-  
30  
31 min reaction in the MW reactor, 2,4-D removal by the OBC-900C and OBC-900N was obviously increased  
32  
33 to  $81.6 \pm 0.8$  and  $57.4 \pm 4.1\%$ , respectively, *i.e.*,  $\sim 2.3$  times the removal efficiency under room temperature.  
34  
35 No 2,4-D removal was observed under MW irradiation only in the absence of biochar due to the low volatility  
36  
37 of 2,4-D. However, gas emission could be a potential problem of the MW system for semi-volatile and volatile  
38  
39 contaminants. MW treatment outperformed conventional heating in an oil bath at the same reaction  
40  
41 temperature ( $90 \text{ }^\circ\text{C}$ ) for 1–30 min (**Fig. 5** and **Fig. S1**). In particular, the OBC-900C, which achieved the  
42  
43 highest removal in MW, consumed less energy than the rest of the biochars during the temperature ramping  
44  
45 (1.39 *vs.* 1.68 kW) and holding (0.275 *vs.* 0.601 kW) stages, despite the same heating programme (**Fig. 6**).  
46  
47 This suggested a more efficient MW-to-thermal energy transformation over the MW-absorbing OBC-900C.  
48  
49 Furthermore, its temperature profile showed overshooting ( $\sim 1 \text{ }^\circ\text{C}$ ) after the ramping, which was absent from  
50  
51 the other biochars. The strong MW absorptivity of the OBC-900C might have induced localized overheating,  
52  
53 which promoted the removal of 2,4-D. Thus, the OBC-900C could absorb maximal electromagnetic energy  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65



1  
2  
3  
4 that ultimately penetrates into its carbon matrix and quickly dissipate as heat or other forms of energy [4].  
5

6  
7 There was only a slight improvement of 2,4-D removal in the presence of the ABC-900C under MW  
8  
9 irradiation ( $69.9 \pm 1.7\%$ ) compared to oil bath heating ( $62.4 \pm 0.6\%$ ), both of which were better than room-  
10  
11 temperature treatment ( $52.6 \pm 4.2\%$ ) (**Fig. 5**). In addition, the OBC-750C (pyrolyzed at a lower temperature  
12  
13 of  $750\text{ }^\circ\text{C}$ ) exhibited a significantly inferior performance for 2,4-D removal under the three different reaction  
14  
15 conditions (**Fig. 5**). These results indicate that biochar prepared from various feedstocks, purging gases, and  
16  
17 pyrolysis temperatures exhibited a distinctive sensitivity to MW irradiation. Carbon materials have been  
18  
19 explored as MW adsorbents due to their high dielectric loss that is usually dependent on two critical factors,  
20  
21 the bonding state of carbon atoms (*i.e.*, degree of graphitization) and the microstructure of the carbon matrix  
22  
23 [16]. On one hand, the large surface area ( $S_{\text{BET}} = 510.5\text{ m}^2\text{ g}^{-1}$ ), high proportion of micropores ( $V_{\text{micro}}/V_{\text{total}} =$   
24  
25  $67.4\%$ ), appropriate pore size ( $D_p = 2.99\text{ nm}$ ), and abundant surface functionalities ( $17.5\%$  C–O and  $17.1\%$   
26  
27  $\pi$ - $\pi^*$  transition in aromatic rings) of the ABC-900C could guarantee sufficient adsorption of aquatic organic  
28  
29 pollutants (**Table 1** and **Fig. 4**). On the other hand, the higher degree of graphitization of the OBC-900C  
30  
31 ( $A_D/A_G = 1.94$  and  $68.7\%$  aromatic C–C/C=C, **Figs. 3-4**), together with its greater microwave absorbing  
32  
33 property and medium-developed microporous structure, would be beneficial to the capture and degradation  
34  
35 of 2,4-D under MW irradiation.  
36  
37  
38  
39  
40  
41  
42

43 The MW-enhanced organic removal may also be attributed to the formation of various ROSs catalyzed by  
44  
45 the carbon surface [21]. As shown in **Fig. 7**, TBA addition only slightly decreased the 2,4-D removal to  $34.2$   
46  
47  $\pm 0.8\%$  by the ABC-900N while performances of the other biochars remained unaffected. In contrast, CF or  
48  
49 FFA noticeably inhibited the 2,4-D removal to the same extent in the MW systems containing the OBC-900C  
50  
51 and ABC-900C ( $44.5 \pm 5.6 - 52.8 \pm 0.7\%$  and  $20.4 \pm 0.4 - 22.3 \pm 4.2\%$ , respectively) compared with  $81.6 \pm 0.8$   
52  
53 and  $61.9 \pm 1.7\%$  removal with no scavengers (**Fig. 7**), indicating the equal contribution of  $\text{O}_2^{\cdot-}$  and  $^1\text{O}_2$  to 2,4-  
54  
55 D removal. However, in the case of  $\text{N}_2$  pyrolyzed biochars, FFA led to a more significant decrease in 2,4-D  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

removal compared with CF, *i.e.*, 49.1 ±4.9 vs. 36.6 ±0.3% and 10.5 ±2.6 vs. 3.1 ±0.8% for the OBC-900N and ABC-900N, respectively (**Fig. 7**), suggesting that <sup>1</sup>O<sub>2</sub> played a superior role than the other ROSs. In particular, the additional organic scavengers did not exhibit noticeable effect on 2,4-D removal under room temperature or oil bath conditions. This observation excluded the potential interference of these organic scavengers on 2,4-D adsorption, and reaffirmed that radicals were only generated in the MW system. The production of radical species is summarized in reactions **R1–R3** according to previous studies [23]. Upon MW irradiation, water (H<sub>2</sub>O) molecules surrounding biochar surface “hot spots” could be activated into <sup>•</sup>OH and hydrogen radicals (<sup>•</sup>H) (**R1**). Oxygen (O<sub>2</sub>) in the water medium would react with <sup>•</sup>H to form O<sub>2</sub><sup>•-</sup> and <sup>1</sup>O<sub>2</sub> (**R2**), which could further yield <sup>•</sup>OH *via* **R3**. These radicals (O<sub>2</sub><sup>•-</sup> and <sup>1</sup>O<sub>2</sub>) with powerful oxidization capacity could decompose the adsorbed or soluble 2,4-D into intermediates with lower molecular weight, and finally mineralize into CO<sub>2</sub> and H<sub>2</sub>O.



### 3.3. Desorption and reusability of the biochars

To further distinguish adsorption and degradation of 2,4-D under the three reaction conditions (MW irradiation, oil bath, and room temperature), the adsorbed 2,4-D on the spent biochars were extracted by different organic solvents (methanol, ethanol, hexane, acetonitrile, and DMSO respectively) *via* desorption at room temperature and under MW conditions, respectively. However, neither desorption procedures with any organic solvent could recover more than 10% 2,4-D from the reacted samples. These results might be due to strong binding between 2,4-D and biochar *via* diffusion into the inner porous structure and intensive chemisorption by the surface functionalities of biochar [40]. In addition, the 1-min TOC removal (59.2 ±2.5,

1  
2  
3  
4 43.3 ±0.9, 83.0 ±3.4, and 71.9 ±3.2%, respectively) by the OBC-900N, ABC-900N, OBC-900C, and ABC-  
5  
6  
7 900N, respectively, was slightly greater than the 2,4-D removal (57.4 ±4.1, 41.2 ±2.2, 81.6 ±0.8, and 69.9  
8  
9 ±1.7%, respectively) under MW conditions (**Fig. S2**). These results indicated that 2,4-D could be completely  
10  
11 mineralized into CO<sub>2</sub> and H<sub>2</sub>O by the MW-assisted removal in presence of biochar. Moreover, no obvious  
12  
13 peaks of any degradation intermediates were observed by HPLC analysis of the solutions after reaction or the  
14  
15 extraction solutions of the spent biochars, probably because of a strong entrapment of possible by-products  
16  
17 by the biochars. Thus, no direct evidence of 2,4-D decomposition (within the accuracies of the experimental  
18  
19 methods) could be provided in the current stage of our study. According to the latest findings [56], the  
20  
21 dechlorination rate of 2,4-D (*i.e.*, change of the Cl<sup>-</sup> concentration) was correlated to its degradation efficiency  
22  
23 when 2,4-D was completely mineralized into CO<sub>2</sub> and H<sub>2</sub>O. More comprehensive experimental design (*e.g.*,  
24  
25 extraction of reacted biochars by other means, full identification of 2,4-D intermediates, and detection of  
26  
27 released Cl<sup>-</sup>) would help to further prove and quantify the 2,4-D degradation in the MW/biochar system.  
28  
29  
30  
31  
32

33  
34 Reusability of the OBC-900N and OBC-900C biochars was tested in three consecutive cycles of 2,4-D  
35  
36 removal under MW irradiation. A progressive loss of biochar activity in each cycle is depicted in **Fig. 8**.  
37  
38 Without any treatment of regeneration, the performance of the OBC-900C (or OBC-900N) noticeably  
39  
40 dropped from 81.7 ±2.1% (or 61.2 ±0.9%) to 24.2 ±1.3% (or 21.2 ±1.1%) 2,4-D removal. This observation  
41  
42 could be ascribed to the high BET surface area and internal microporous structure of biochar. The degradation  
43  
44 by-products might accumulate and occupy the active sites on biochar surface for 2,4-D adsorption. It is also  
45  
46 possible that the carbon materials eventually crumble when “hot spots” formed inside micropores generate  
47  
48 sufficient confined vapour with increased pressure [6]. This so-called “popcorn effect” could impede biochar  
49  
50 stability with susceptible deactivation and fouling by intermediates [6]. Future studies should focus on biochar  
51  
52 regeneration *via* facile and low-cost treatment, for example, low-temperature heating in N<sub>2</sub> environment or  
53  
54 desorption by various types of green solvents.  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1  
2  
3  
4 For future design of more sustainable water/wastewater treatment processes, MW technology can be  
5  
6 effectively incorporated with membrane bioreactors and electro-/photo-catalysis process [3,4]. However,  
7  
8 most current studies on MW system for water/wastewater treatment are conducted in laboratory scale,  
9  
10 because (i) volume and power output of the available MW reactors are insufficient for widespread commercial  
11  
12 promotion, and (ii) low-cost, highly efficient, and recyclable catalysts are critical for industrial applications  
13  
14 [3,4]. With further development of equipment optimization and catalysts exploitation, MW technology is  
15  
16 expected to deliver good benefits for practical water and wastewater treatment.  
17  
18  
19  
20  
21  
22

## 23 **Conclusions**

24  
25  
26 This study has demonstrated that biochar derived from waste biomass of oak tree, with high lignin content  
27  
28 under 900 °C pyrolysis and CO<sub>2</sub> purging, can act as a ‘green’, highly efficient MW absorber. The CO<sub>2</sub> purging  
29  
30 can promote decomposition of lignin carbon at high pyrolysis temperature *via* fragmentation and  
31  
32 repolymerization, producing biochar with a developed hierarchical porous structure, enhanced graphitization  
33  
34 level, and improved surface chemistry. Under mild MW irradiation, 2,4-D was simultaneously adsorbed (*via*  
35  
36 electrostatic interaction, electron conjugation, and chemisorption) and degraded due to a MW-induced  
37  
38 thermal effect on the biochar surface that generated hydroxyl (<sup>•</sup>OH), anionic superoxide (O<sub>2</sub><sup>•-</sup>), and singlet  
39  
40 oxygen (<sup>1</sup>O<sub>2</sub>) radicals. This study has demonstrated the potential application of an economical, sustainable,  
41  
42 metal-free biochar in energy-saving, chemical-free water/wastewater treatment using MW, which could make  
43  
44 an important contribution to a clean water environment. Future studies are suggested to optimize the rational  
45  
46 design of MW-active biochar catalysts and investigate the applicability of the MW/biochar system to a  
47  
48 broader range of organic pollutants with diverse physicochemical properties in water/wastewater matrices.  
49  
50  
51  
52  
53  
54  
55  
56  
57

## 58 **Acknowledgement**

59  
60  
61  
62  
63  
64  
65

1  
2  
3  
4 The authors appreciate the financial support from the Hong Kong Research Grants Council (PolyU 15217818)  
5  
6 and Hong Kong Environment and Conversation Fund (ECF 87/2017) for this study.  
7  
8  
9

## 10 11 **References**

- 12  
13  
14 [1] Sun, J., Pan, L., Tsang, D.C.W., Zhan, Y., Zhu, L., Li, X.D., Organic contamination and remediation in the  
15  
16 agricultural soils of China: A critical review, *Science of the Total Environment*, 615 (2018), 724-740.  
17  
18 [2] Kümmerer, K., Dionysiou, D.D., Olsson, O., Fatta-Kassinos, D., A path to clean water. *Science*, 361  
19  
20 (2018), 222-224.  
21  
22 [3] Wei, R., Wang, P., Zhang, G., Wang, N., Zheng, T., Microwave-responsive catalysts for wastewater  
23  
24 treatment: A review, *Chemical Engineering Journal*, (2020), 122781.  
25  
26 [4] Xue, C., Mao, Y., Wang, W., Song, Z., Zhao, X., Sun, J., Wang, Y., Current status of applying microwave-  
27  
28 associated catalysis for the degradation of organics in aqueous phase-A review, *Journal of Environmental*  
29  
30 *Sciences*, 81 (2019), 119-135.  
31  
32 [5] Varisli, D., Korkusuz, C., Dogu, T., Microwave-assisted ammonia decomposition reaction over iron  
33  
34 incorporated mesoporous carbon catalysts., *Applied catalysis B: Environmental*, 201 (2017), 370-380.  
35  
36 [6] Garcia-Costa, A.L., Zazo, J.A., Rodriguez, J.J., Casas, J.A., Intensification of catalytic wet peroxide  
37  
38 oxidation with microwave radiation: activity and stability of carbon materials, *Separation and Purification*  
39  
40 *Technology*, 209 (2019), 301-306.  
41  
42 [7] Hu, L., Wang, P., Shen, T., Wang, Q., Wang, X., Xu, P., Zheng, Q., Zhang, G., The application of  
43  
44 microwaves in sulfate radical-based advanced oxidation processes for environmental remediation: A  
45  
46 review, *Science of The Total Environment*, (2020), 137831.  
47  
48 [8] Garcia-Costa, A.L., Zazo, J.A., Rodriguez, J.J., Casas, J.A., Microwave-assisted catalytic wet peroxide  
49  
50 oxidation. Comparison of Fe catalysts supported on activated carbon and  $\gamma$ -alumina, *Applied Catalysis B:*  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

- 1  
2  
3  
4 Environmental, 218 (2017), 637-642.  
5  
6  
7 [9] Chen, J., Pan, H., Hou, H., Li, H., Yang, J., Wang, L., High efficient catalytic degradation of PNP over  
8  
9 Cu-bearing catalysts with microwave irradiation, Chemical Engineering Journal, 323 (2017), 444-454.  
10  
11 [10] Wang, X., Mei, L., Xing, X., Liao, L., Lv, G., Li, Z., Wu, L., Mechanism and process of methylene blue  
12  
13 degradation by manganese oxides under microwave irradiation, Applied Catalysis B: Environmental,  
14  
15 160 (2014), 211-216.  
16  
17  
18 [11] Ahmed, A. B., Jibril, B., Danwittayakul, S., Dutta, J., Microwave-enhanced degradation of phenol over  
19  
20 Ni-loaded ZnO nanorods catalyst, Applied Catalysis B: Environmental, 156 (2014), 456-465.  
21  
22  
23 [12] Ling, L., Feng, Y., Li, H., Chen, Y., Wen, J., Zhu, J., Bian, Z., Microwave induced surface enhanced  
24  
25 pollutant adsorption and photocatalytic degradation on Ag/TiO<sub>2</sub>, Applied Surface Science, 483 (2019),  
26  
27 772-778.  
28  
29  
30 [13] Qi, Y., Mei, Y., Li, J., Yao, T., Yang, Y., Jia, W., Tong, X., Wu, J., Xin, B., Highly efficient microwave-  
31  
32 assisted Fenton degradation of metacycline using pine-needle-like CuCo<sub>2</sub>O<sub>4</sub> nanocatalyst, Chemical  
33  
34 Engineering Journal, 373 (2019), 1158-1167.  
35  
36  
37 [14] Qiu, Y. and Zhou, J., Highly effective and green microwave catalytic oxidation degradation of  
38  
39 nitrophenols over Bi<sub>2</sub>O<sub>2</sub>CO<sub>3</sub> based composites without extra chemical additives, Chemosphere, 214  
40  
41 (2019), 319-329.  
42  
43  
44 [15] Yao, X., Lin, Q., Zeng, L., Xiang, J., Yin, G., & Liu, Q. (2017). Degradation of humic acid using  
45  
46 hydrogen peroxide activated by CuO-Co<sub>3</sub>O<sub>4</sub>@ AC under microwave irradiation. Chemical Engineering  
47  
48 Journal, 330, 783-791.  
49  
50  
51 [16] Cai, B., Feng, J. F., Peng, Q. Y., Zhao, H. F., Miao, Y. C., Pan, H., Super-fast degradation of high  
52  
53 concentration methyl orange over bifunctional catalyst Fe/Fe<sub>3</sub>C@C with microwave irradiation, Journal  
54  
55 of Hazardous Materials, 392 (2020), 122279.  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

- 1  
2  
3  
4 [17] Yao, T., Qi, Y., Mei, Y., Yang, Y., Aleisa, R., Tong, X., Wu, J., One-step preparation of reduced graphene  
5  
6 oxide aerogel loaded with mesoporous copper ferrite nanocubes: A highly efficient catalyst in  
7  
8 microwave-assisted Fenton reaction, *Journal of Hazardous mMaterials*, 378 (2019), 120712.  
9  
10  
11 [18] Shen, M., Fu, L., Tang, J., Liu, M., Song, Y., Tian, F., Zhao, Z., Zhang, Z., Dionysiou, D.D., Microwave  
12  
13 hydrothermal-assisted preparation of novel spinel-NiFe<sub>2</sub>O<sub>4</sub>/natural mineral composites as microwave  
14  
15 catalysts for degradation of aquatic organic pollutants, *Journal of Hazardous Materials*, 350 (2018), 1-9.  
16  
17  
18 [20] Zhang, Z., Shan, Y., Wang, J., Ling, H., Zang, S., Gao, W., Zhao, Z., Zhang, H., Investigation on the  
19  
20 rapid degradation of congo red catalyzed by activated carbon powder under microwave irradiation,  
21  
22 *Journal of Hazardous Materials*, 147 (2007), 325-333.  
23  
24  
25 [21] Veksha, A., Pandya, P., Hill, J.M., The removal of methyl orange from aqueous solution by biochar and  
26  
27 activated carbon under microwave irradiation and in the presence of hydrogen peroxide, *Journal of*  
28  
29 *Environmental Chemical Engineering*, 3 (2015), 1452-1458.  
30  
31  
32 [22] Chen, J., Xue, S., Song, Y., Shen, M., Zhang, Z., Yuan, T., Tian, F., Dionysiou, D.D., Microwave-induced  
33  
34 carbon nanotubes catalytic degradation of organic pollutants in aqueous solution, *Journal of Hazardous*  
35  
36 *Materials*, 310 (2016), 226-234.  
37  
38  
39 [23] Rangabhashiyam, S. and Balasubramanian, P., The potential of lignocellulosic biomass precursors for  
40  
41 biochar production: performance, mechanism and wastewater application-A review, *Industrial Crops*  
42  
43 *and Products*, 128 (2019), 405-423.  
44  
45  
46 [24] Kumar, M., Xiong, X., Sun, Y., Iris, K.M., Tsang, D.C.W., Hou, D., Gupta, J., Bhaskard, T., Pandey, A.,  
47  
48 Critical review on biochar-supported catalysts for pollutant degradation and sustainable biorefinery.  
49  
50 *Advanced Sustainable Systems*, (2020), 1900149.  
51  
52  
53 [25] Shaheen, S.M., Niazi, N.K., Hassan, N.E., Bibi, I., Wang, H., Tsang, D.C.W., Ok., Y.S., Bolan, N.,  
54  
55 Rinklebe, J., Wood-based biochar for the removal of potentially toxic elements in water and wastewater:  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

- 1  
2  
3  
4 a critical review, *International Materials Reviews*, 64 (2019), 216-247.  
5  
6  
7 [26] El-Naggar, A., Lee, S.S., Awad, Y.M., Yang, X., Ryu, C., Rizwan, M., Rinklebe, J., Tsang, D.C.W., Ok,  
8  
9 Y.S., Influence of soil properties and feedstocks on biochar potential for carbon mineralization and  
10  
11 improvement of infertile soils, *Geoderma*, 332 (2018), 100-108.  
12  
13  
14 [27] Igalavithana, A.D., Lee, S.E., Lee, Y.H., Tsang, D.C.W., Rinklebe, J., Kwon, E.E., Ok, Y.S., Heavy metal  
15  
16 immobilization and microbial community abundance by vegetable waste and pine cone biochar of  
17  
18 agricultural soils, *Chemosphere*, 174 (2017), 593-603.  
19  
20  
21 [28] Dissanayake, P.D., Choi, S.W., Igalavithana, A.D., Yang, X., Tsang, D.C.W., Wang, C.H., Kua, H.W.,  
22  
23 Lee, K.B., Ok, Y.S., Sustainable gasification biochar as a high efficiency adsorbent for CO<sub>2</sub> capture: A  
24  
25 facile method to designer biochar fabrication, *Renewable and Sustainable Energy Reviews*, 124 (2020),  
26  
27 109785.  
28  
29  
30  
31 [29] Xu, X., Xu, Z., Gao, B., Zhao, L., Zheng, Y., Huang, J., Tsang, D.C.W., Ok, Y.S., Cao, X., New insights  
32  
33 into CO<sub>2</sub> sorption on biochar/Fe oxyhydroxide composites: Kinetics, mechanisms, and in situ  
34  
35 characterization, *Chemical Engineering Journal*, 384 (2020), 123289.  
36  
37  
38 [30] Sun, Y., Chen, S.S., Lau, A.Y.T., Tsang, D.C.W., Mohanty, S.K., Bhatnagar, A., Rinklebe, J., Lin, A.K.Y.,  
39  
40 Ok, Y.S. Waste-derived compost and biochar amendments for stormwater treatment in bioretention  
41  
42 column: Co-transport of heavy metals and colloid, *Journal of Hazardous Materials*, 383 (2020), 121243.  
43  
44  
45 [31] Rajapaksha, A.U., Alam, M.S., Chen, N., Alessi, D.S., Igalavithana, A.D., Tsang, D.C.W., Ok, Y.S.,  
46  
47 Removal of hexavalent chromium in aqueous solutions using biochars: Chemical and spectroscopic  
48  
49 investigations. *Science of the Total Environment*, 625 (2018), 1567-1573.  
50  
51  
52  
53 [32] Ruan, X., Sun, Y., Du, W., Tang, Y., Liu, Q., Zhang, Z., William, D., Ray L.F., Qian, R., Tsang, D.C.W.,  
54  
55 Formation, characteristics, and application of environmentally persistent free radicals (EPFRs) in  
56  
57 biochars and environmental matrices: A Review, *Bioresource Technology*, 281 (2019), 457-468.  
58  
59  
60  
61  
62  
63  
64  
65



- 1  
2  
3  
4 [33] Li, Z., Sun, Y., Yang, Y., Han, Y., Wang, T., Chen, J., Tsang, D.C.W., Biochar-supported nanoscale zero-  
5  
6 valent iron as an efficient catalyst for organic degradation in groundwater, *Journal of Hazardous*  
7  
8 *Materials*, 383 (2020), 121240.  
9  
10  
11 [34] Yu, I.K.M., Xiong, X., Tsang, D.C.W., Wang, L., Hunt, A.J., Song, H., Shang, J., Ok, Y.S., Poon, C.S.,  
12  
13 Aluminium-biochar composite as a sustainable heterogeneous catalyst for glucose isomerization in  
14  
15 biorefinery, *Green Chemistry*, 21 (2019), 1267-1281.  
16  
17  
18 [35] Xiong, X., Yu, I.K.M., Cao, L., Tsang, D.C.W., Zhang, S., Ok, Y.S., A review of biochar-based catalysts  
19  
20 for chemical synthesis, biofuel production, and pollution control. *Bioresource Technology*, 246 (2017),  
21  
22 254-270.  
23  
24  
25 [36] Mian, M.M., Liu, G., Fu, B., Conversion of sewage sludge into environmental catalyst and microbial  
26  
27 fuel cell electrode material: A review, *Science of The Total Environment*, 666 (2019), 525-539.  
28  
29  
30 [37] Sun, C., Chen, T., Huang, Q., Zhan, M., Li, X., Yan, J., Activation of persulfate by CO<sub>2</sub>-activated biochar  
31  
32 for improved phenolic pollutant degradation: Performance and mechanism, *Chemical Engineering*  
33  
34 *Journal*, 380 (2020), 122519.  
35  
36  
37 [38] Sun, Y., Yu, I.K.M., Tsang, D.C.W., Cao, X.D, Lin, D.H, Wang, L.L, Graham, N.J.D., Daniel, S.A.,  
38  
39 Michael, K., Ok, Y.S., Feng, Y.J., Li, X.D. Multifunctional iron-biochar composites for the removal of  
40  
41 potentially toxic elements, inherent cations, and hetero-chloride from hydraulic fracturing wastewater,  
42  
43 *Environment International*, 124 (2019), 521-532.  
44  
45  
46 [39] Wan, Z., Sun, Y., Tsang, D.C.W., Yu, I.K.M., Fan, J., Clark, J.H., Zhou, Y., Cao, X., Gao, B., Ok, Y.S.,  
47  
48 Sustainable biochar catalyst synergized with copper heteroatoms and CO<sub>2</sub> for singlet oxygenation and  
49  
50 electron transfer routes, *Green Chemistry*, 21 (2019), 4800.  
51  
52  
53 [40] Mandal, S., Sarkar, B., Igalavithana, A.D., Ok, Y.S., Yang, X., Lombi, E., Bolan, N., Mechanistic insights  
54  
55 of 2, 4-D sorption onto biochar: Influence of feedstock materials and biochar properties, *Bioresource*  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

- 1  
2  
3  
4 Technology, 246 (2017), 160-167.  
5  
6  
7 [41] Tiwari, B., Sellamuthu, B., Ouarda, Y., Drogui, P., Tyagi, R.D., Buelna, G., Review on fate and  
8  
9 mechanism of removal of pharmaceutical pollutants from wastewater using biological approach,  
10  
11 Bioresource Technology, 224 (2017), 1-12.  
12  
13  
14 [42] Shi, X., Leong, K.Y., Ng, H.Y., Anaerobic treatment of pharmaceutical wastewater: a critical review.  
15  
16 Bioresource Technology, 245 (2017), 1238-1244.  
17  
18  
19 [43] Wang, D., Sun, Y., Tsang, D.C.W., Khan, E., Cho, D.W., Zhou, Y., Qi, F., Gong, J., Wang, L., Synergistic  
20  
21 utilization of inherent halides and alcohols in hydraulic fracturing wastewater for radical-based treatment:  
22  
23 A case study of di-(2-ethylhexyl) phthalate removal, Journal of Hazardous Materials, 384 (2020),  
24  
25 121321.  
26  
27  
28 [44] Cho, D.W., Yoon, K., Ahn, Y., Sun, Y., Tsang, D.C.W., Hou, D., Ok, Y.S., Song, H., Fabrication and  
29  
30 environmental applications of multifunctional mixed metal-biochar composites (MMBC) from red mud  
31  
32 and lignin wastes, Journal of Hazardous Materials, 374 (2019), 412-419.  
33  
34  
35 [45] Lee, J., Yang, X., Cho, S.H., Kim, J.K., Lee, S.S., Tsang, D.C.W., Ok, Y.S., Kwon, E.E., Pyrolysis  
36  
37 process of agricultural waste using CO<sub>2</sub> for waste management, energy recovery, and biochar fabrication.  
38  
39 Applied Energy, 185 (2017), 214-222.  
40  
41  
42 [46] Qian, F., Zhu, X., Liu, Y., Hao, S., Ren, Z.J., Gao, B., Zong, R., Zhang, S., Chen, J., Synthesis,  
43  
44 characterization and adsorption capacity of magnetic carbon composites activated by CO<sub>2</sub>: implication  
45  
46 for the catalytic mechanisms of iron salts, Journal of Materials Chemistry A, 4 (2016), 18942-18951.  
47  
48  
49 [47] Yang, X., Yu, I.K.M., Cho, D.W., Chen, S.S., Tsang, D.C.W., Shang, J., Yip, A.C.K., Wang, L., Ok, Y.S.,  
50  
51 Tin-functionalized wood biochar as a sustainable solid catalyst for glucose isomerization in biorefinery,  
52  
53 ACS Sustainable Chemistry & Engineering, 7 (2019), 4851-4860.  
54  
55  
56 [48] Liu, Y., Zhu, X., Wei, X., Zhang, S., Chen, J., Ren, Z. J., CO<sub>2</sub> activation promotes available carbonate  
57  
58  
59  
60  
61  
62  
63  
64  
65

- 1  
2  
3  
4 and phosphorus of antibiotic mycelial fermentation residue-derived biochar support for increased lead  
5  
6 immobilization, *Chemical Engineering Journal*, 334 (2018), 1101-1107.  
7  
8
- [49] Igalavithana, A.D., Yang, X., Zahra, H.R., Tack, F.M., Tsang, D.C.W., Kwon, E.E., Ok, Y.S., Metal (loid)  
9 immobilization in soils with biochars pyrolyzed in N<sub>2</sub> and CO<sub>2</sub> environments, *Science of the total*  
10 *environment*, 630 (2018), 1103-1114.  
11  
12  
13  
14  
15
- [50] Kim, Y., Oh, J.I., Vithanage, M., Park, Y.K., Lee, J., Kwon, E.E., Modification of biochar properties  
16 using CO<sub>2</sub>, *Chemical Engineering Journal*, 372 (2019), 383-389.  
17  
18  
19  
20
- [51] Peng, Y., Sun, Y., Sun, R., Zhou, Y., Tsang, D.C.W., Chen, Q., Optimizing synthesis of Fe/Al  
21 (hydr)oxides-biochars to maximize phosphorus removal via response surface model, *Journal of Cleaner*  
22 *Production*, 237 (2019), 117770.  
23  
24  
25  
26  
27
- [52] Yang, F., Zhang, S., Sun, Y., Cheng, K., Li, J., Tsang, D.C.W., Fabrication and characterization of  
28 hydrophilic corn stalk biochar-supported nanoscale zero-valent iron composites for efficient metal  
29 removal, *Bioresource Technology*, 265 (2018), 490-497.  
30  
31  
32  
33  
34  
35
- [53] Yang, F., Zhang, S., Sun, Y., Tsang, D.C.W., Cheng, K., Ok, Y.S., Assembling biochar with various  
36 layered double hydroxides for enhancement of phosphorus recovery, *Journal of Hazardous Materials*,  
37 365 (2019), 665-673.  
38  
39  
40  
41  
42
- [54] Yang, F., Zhang, S., Sun, Y., Du, Q., Song J.P., Tsang, D.C.W., A novel electrochemical modification  
43 combined with one-step pyrolysis for preparation of sustainable thorn-like iron-based biochar  
44 composites, *Bioresource Technology*, 274 (2019), 379-385.  
45  
46  
47  
48  
49
- [55] Zhu, L., Zhao, N., Tong, L., Lv, Y., Li, G., Characterization and evaluation of surface modified materials  
50 based on porous biochar and its adsorption properties for 2, 4-dichlorophenoxyacetic acid, *Chemosphere*,  
51 210 (2018), 734-744.  
52  
53  
54  
55  
56
- [56] Li, W., Li, Y., Zhang, D., Lan, Y., Guo, J., CuO-Co<sub>3</sub>O<sub>4</sub>@CeO<sub>2</sub> as a heterogeneous catalyst for efficient  
57  
58  
59  
60  
61  
62  
63  
64  
65

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

degradation of 2, 4-dichlorophenoxyacetic acid by peroxymonosulfate, Journal of Hazardous Materials,  
381 (2020), 121209.

# Tailored design of graphitic biochar for high-efficiency and chemical-free microwave-assisted removal of refractory organic contaminants

Yuqing Sun<sup>a</sup>, Iris K.M. Yu<sup>b,c</sup>, Daniel C.W. Tsang<sup>a,\*</sup>, Jiajun Fan<sup>b</sup>, James H. Clark<sup>b,d</sup>, Gang Luo<sup>d</sup>, Shicheng Zhang<sup>d</sup>, Eakalak Khan<sup>e</sup>, Nigel J.D. Graham<sup>f</sup>

<sup>a</sup> Department of Civil and Environmental Engineering, The Hong Kong Polytechnic University, Hung Hom, Kowloon, Hong Kong, China.

<sup>b</sup> Green Chemistry Centre of Excellence, Department of Chemistry, University of York, York, YO10 5DD, UK.

<sup>c</sup> Department of Chemistry and Catalysis Research Center, Technische Universität München, Lichtenbergstrasse 4, Garching, 85748, Germany.

<sup>d</sup> Shanghai Key Laboratory of Atmospheric Particle Pollution and Prevention (LAP3), Department of Environmental Science and Engineering, Fudan University, Shanghai 200438, China.

<sup>e</sup> Department of Civil and Environmental Engineering and Construction, University of Nevada, Las Vegas, NV 89154, USA.

<sup>f</sup> Department of Civil and Environmental Engineering, Imperial College London, South Kensington Campus, London SW7 2AZ, UK.

\* Corresponding author email: [dan.tsang@polyu.edu.hk](mailto:dan.tsang@polyu.edu.hk)

## Abstract

Energy-saving, chemical-free, and high-efficiency microwave (MW)-assisted water treatment can be greatly facilitated *via* tailored design of an economical, sustainable, and ‘green’ carbonaceous catalyst. In this study, various biochars (BC) were pyrolyzed from two lignocellulosic waste biomasses, oak (O) and apple tree (A), at high temperature (900 °C) and under different gases (N<sub>2</sub> and CO<sub>2</sub>). The holistic characterization by advanced spectroscopic techniques demonstrated that CO<sub>2</sub> pyrolysis of feedstock with more lignin (*i.e.*, oak), produced biochar with increased aromaticity and degree of carbonization. CO<sub>2</sub> modification created a hierarchical porous structure, improved surface hydrophilicity, polarity, and acidity, and provided **higher**

**densities of** near-surface functionalities of the biochar. Without MW irradiation, ABC-900C (1 g L<sup>-1</sup>) provided the highest adsorption (52.6%, 1 min) of 2,4-dichlorophenoxy acetic acid (2,4-D) ascribed to large specific surface area, high micropore content, appropriate pore size, and abundant active groups. OBC-900C (1 g L<sup>-1</sup>) enabled significantly increased 2,4-D removal (81.6%, 1 min) under MW irradiation (90 °C) in contrast with an oil bath (55.7%, 90 °C, 1 min) and room temperature (33.9%, 1 min) conditions, due to its highest graphitization degree and medium-developed microporous structure. The MW-induced thermal effect formed “hot spots” on the biochar surface as evidenced by elevated temperature of the bulk solution and lowered energy consumption of the MW reactor in the presence of OBC-900C, compared to those of the other biochars. The scavenging tests suggested that the generation of highly oxidative hydroxyl (<sup>•</sup>OH), anionic superoxide (O<sub>2</sub><sup>•-</sup>), and singlet oxygen (<sup>1</sup>O<sub>2</sub>) radicals contributed to the removal of 2,4-D. This study has demonstrated that biochar with customized structure and high organic adsorption capacity can act as an effective MW absorber suitable for rapid and improved removal of toxic organics.

**Keywords:** Microwave irradiation; Engineered biochar; Graphitic carbon; Sustainable waste management; Advanced wastewater treatment.

## 1. Introduction

With the rapid economic development, continuous industrialization, and increasing expectations of quality of life, large volumes of diverse chemicals have been discharging into aquatic ecosystems and causing severe water pollution [1]. Conventional wastewater treatment has become less efficient, and even advanced oxidation processes (AOPs) exhibit limitations including high demand of energy and need for additional chemicals, incomplete removal of refractory organic pollutants, and generation of more toxic intermediates derived from their parent compounds [2]. In recent years, microwave (MW)-assisted water treatment has emerged as a promising technology [3,4]. MW irradiation, which has a wide range of frequency (0.3–300

GHz) and wavelength (1–0.001 m) [3], provides selective, volumetric, uniform, and non-contact heating for MW-absorbing materials (*i.e.*, MW catalysts) [4,5], and induces rapid and non-gradient temperature ramping. The thermal effect of MW irradiation may produce “hot spots” or micro-plasmas that ionize the surrounding atmosphere [6], which can accelerate organic decomposition and generate highly oxidative hydroxyl radicals ( $\cdot\text{OH}$ ) [4,6]. MW irradiation treatment presents advantages compared to other heating techniques of easy operation, improved processing efficiency, reduced energy and chemical consumption, shortened reaction time, and complete mineralization of organic contaminants [3,7].

MW catalysts usually consist of a single (or binary/ternary) metallic phase (*e.g.*, Fe [8], Cu [9], Mn [10], Ni [11], Ti [12], Co [13], and Bi [14]), supported on porous, conductive materials (*e.g.*, activated carbon (AC) [15], mesoporous carbon [16], reduced graphene oxide (rGO) [17], and minerals [18]), which favour dispersion of metals/metal oxides and accelerate recycling of metal redox pairs [17]. Nonetheless, these catalysts are prone to deactivation *via* metal leaching/detachment creating a new environmental problem [6]. In contrast, metal-free carbon materials display strong thermal stability and robust anti-oxidation abilities that maintain good catalytic performance upon repeated use [4]. Carbonaceous materials with high dielectric loss tangent values ( $\tan \delta$ ) are powerful MW absorbers [16], but seldom explored so far as MW catalysts for organics removal. Zhang et al. reported a MW-induced complete (97.9%) degradation of congo red (50 mg L<sup>-1</sup>, 25 mL) catalyzed by commercial granular AC powder (2.0 g L<sup>-1</sup>) in 2.5 min; however, no direct evidence was provided for the generation of reactive oxidative species (ROSs) and “hot spots” [20]. Veksha et al. claimed that MW irradiation on woodchip-derived AC (600 °C pyrolysis for 30 min followed by 10-min CO<sub>2</sub> activation at 780 °C) could not initiate the formation of “hot spots” or radicals for methyl orange (MO) decomposition [21]. Chen et al. reported MW-enhanced removal (100% within 7 min) of MO (25 mg L<sup>-1</sup>, 25 mL) due to the formation of  $\cdot\text{OH}$  over commercial multi-walled carbon nanotubes (CNTs) [22], yet did not discuss the existence of “hot spots” and differentiate organic adsorption from degradation [22]. In addition to

a lack of conclusive findings or solid evidence of MW-directed organic removal, the reported materials (AC and CNTs) were produced or purchased without science-informed design for high-performance functionalities under MW irradiation. Thus, there is a need for tailoring economical, sustainable, and ‘green’ carbon catalysts with favourable physicochemical characteristics, to achieve efficient MW absorption and fast removal of refractory organic pollutants.

Biochar is a carbon-rich solid material with aromatic surfaces produced *via* cost-effective thermal decomposition of various biomasses [23,24], including lignocellulosic wastes or residues from agricultural and forestry activities as the renewable feedstocks, under inert conditions [23,25]. Biochar finds wide applications in soil remediation [26,27], carbon dioxide (CO<sub>2</sub>) sequestration [28,29], decontamination of heavy metals [30,31], degradation of organic pollutants [32,33], biorefinery [34,35], and energy storage [36]. Its outstanding performance is attributed to the hierarchical porous structure and abundant surface functionalities, which are primarily dependent on the synthesis conditions including biomass composition (*e.g.*, cellulose, hemicellulose, and lignin), pyrolysis temperature, and atmosphere (*e.g.*, N<sub>2</sub> and CO<sub>2</sub>) [37]. Our recent studies revealed that high-temperature pyrolysis and CO<sub>2</sub> modification induced carbon reforming to improve the porous structure, increase carbonization level, and facilitate interface chemical interaction of biochar [38,39]. Herein, we hypothesize that: (i) MW-assisted organic compound removal is a combined process of simultaneous adsorption and degradation by biochar; (ii) highly porous and graphitic biochar with high MW absorption and organic adsorption capacities could act as effective MW-catalysts; and (iii) enhanced organic sequestration under MW irradiation catalyzed by biochar is attributed to the MW-induced thermal effect on the biochar surface.

In this study, two common lignocellulosic biomasses, oak tree (22 *wt.%* cellulose, 23 *wt.%* hemicellulose, and 55 *wt.%* lignin) and apple tree (43 *wt.%* cellulose, 22 *wt.%* hemicellulose, and 35 *wt.%* lignin) [23], with trace amounts of transition metals were selected as biochar feedstocks. Various biochars were prepared under



a high temperature (900 °C) and different purging gases (N<sub>2</sub> and CO<sub>2</sub>). The easily mobilized 2,4-dichlorophenoxy acetic acid (2,4-D) was selected as a target refractory organic contaminant, as it has a high water solubility (900 mg L<sup>-1</sup>), anionic nature ( $pK_a = 2.7$ ), recalcitrant chemical structure, and low biodegradability, and is one of the most widely used herbicides and possible human carcinogens with moderate toxicity [40]. The objectives of this study were to: (i) articulate the interactions of several pyrolysis parameters (*i.e.*, feedstock type and gaseous medium) for tailoring the biochar physicochemical properties, surface structure, and interfacial chemical behaviour; and (ii) capitalize on the evolution of MW-induced thermal effect for biochar-catalyzed organic removal *via* generation of “hot spots” and various ROSs. The results of this study are conducive to improving the future design of high-efficiency, sustainable, and ‘green’ engineered carbon catalysts for application of MW irradiation in wastewater treatment.

## 2. Materials and methods

### 2.1. Biomass and chemicals

Waste wood biomasses of oak tree and apple tree were collected from Wuxi city (Jiangsu province, China) and Guiyang city (Guizhou province, China), respectively, and were applied as biochar feedstocks without further treatment. All chemicals used in this study (*viz.* 2,4-dichlorophenoxyacetic acid (C<sub>8</sub>H<sub>6</sub>Cl<sub>2</sub>O<sub>3</sub>, 2,4-D), *tert*-butanol (C<sub>4</sub>H<sub>10</sub>O, TBA), chloroform (CHCl<sub>3</sub>, CF), furfuryl alcohol (C<sub>5</sub>H<sub>6</sub>O<sub>2</sub>, FFA), methanol (CH<sub>3</sub>OH), ethanol (C<sub>2</sub>H<sub>5</sub>OH), hexane (C<sub>6</sub>H<sub>14</sub>), acetonitrile (CH<sub>3</sub>CN), **dimethylsulfoxide ((CH<sub>3</sub>)<sub>2</sub>SO, DMSO)**, and acetic acid (CH<sub>3</sub>COOH)) were of analytical reagent grade and solvents were of high-performance liquid chromatography (HPLC) grade from Sigma-Aldrich Co. Lit. (St. Louis, USA). Ultrapure water (UW, 18.2 MΩ cm), obtained from a Millipore Milli-Q Water Purification System (Milford, USA), was employed for all experimental aqueous solutions.

### 2.2. Preparation of the biochars

Wood waste (oak tree and apple tree) were cut into small pieces (< 1 cm), crushed and sieved through a 120-mesh (particle size < 0.125 mm), and then pyrolyzed in a tube furnace that was heated to 900 °C at a heating rate of 10 °C min<sup>-1</sup>, and lasted for 2 h after reaching the target temperature with continuous N<sub>2</sub> or CO<sub>2</sub> purging at a flow rate of 200 mL min<sup>-1</sup>. After being cooled down to room temperature (23 ± 2 °C) inside the furnace, the samples were taken out, ground and passed through a 200-mesh sieve (particle size < 0.075 mm), and stored in airtight containers before use. The obtained oak and apple tree biochars were denoted as OBC-900N, OBC-900C, ABC-900N, and ABC-900C, respectively, where N/C corresponded to N<sub>2</sub>/CO<sub>2</sub> purging.

### 2.3. Characterization of the biochars

The ultimate elemental analysis (EA, Vario EL cube, Germany) was used to estimate the CHONS elemental ratio in the biochar samples. The surface morphology and approximate surface elemental analysis of the obtained biochar samples were observed using scanning electron microscopy coupled with energy-dispersive X-ray spectroscopy (SEM-EDS, JSM-IT300, JXA-8230, Hitachi, Japan). The textural characteristics were determined using N<sub>2</sub> adsorption-desorption isotherms obtained from a surface area analyzer (Quantachrome Autosorb, USA) at 77 K for Brunauer-Emmett-Teller (BET) surface area and Barrett-Joyner-Halenda (BJH) porosity analyses. The Fourier transform infrared (FTIR, Nicolet 6700 spectrometer, USA) spectroscopy was used to observe the near-surface functionalities on biochars with the wavelength range at 400–4000 cm<sup>-1</sup>. The micro-Raman spectrometer (Raman spectra, Renishwa Invia Fellex, UK) equipped with a Diode-Pumped Solid State (DPSS) at 532 nm excitation was used to record the defective level and graphitization degree of the biochars. The X-ray photoelectron spectroscopy (XPS, Thermo Fisher Scientific, USA) with Al K $\alpha$  radiation was used to investigate the composition and chemical state of the elements on the sample surfaces. The binding energy of all characteristic peaks were calibrated with carbon C1s core level at 284.8 eV. Devolution of XPS data was conducted using Shirley background associated with Gaussian-Lorentzian model in XPSPEAK41, and the component peaks were identified by comparison of

their binding energies (BEs) with the reported values in the literature.

#### 2.4. MW-assisted removal of 2,4-D by the biochars

The 2,4-D solution was prepared at an initial concentration of  $100 \text{ mg L}^{-1}$  (in accordance with the average concentration reported in 2,4-D manufacturing wastewaters [41,42]) by dissolving a certain amount of  $\text{C}_8\text{H}_6\text{Cl}_2\text{O}_3$  in 1 L UW under magnetic stirring at 200 rpm for 6 h. To initiate the reaction, 20 mL of the 2,4-D solution and 20 mg of the biochars (OBC-900N, OBC-900C, ABC-900N, and ABC-900C, respectively) were added in 100 mL Teflon reaction vessels without pH adjustment and heated in the Ethos UP MW Reactor (Milestone, 2450 MHz, maximum power of 1900 W) under continuous magnetic stirring. **The biochar loading (i.e.,  $1 \text{ g L}^{-1}$ ) was determined according to preliminary experiments (data not shown) for obtaining relatively high 2,4-D removal by the four biochars with distinguishable differences.** The MW temperature was ramped from room temperature to  $90 \text{ }^\circ\text{C}$  within 2 min, held for 1 min, and gradually cooled down to below  $60 \text{ }^\circ\text{C}$  by continuous mechanical ventilation in the MW reactor. The adopted reaction temperature and duration were comparable to previous studies on MW-assisted organic removal [20-22]. After reaction, an aliquot of 1 mL solution was withdrawn from the vessels, filtered into HPLC sample vials through  $0.45 \text{ }\mu\text{m}$  pore-size mixed cellulose ester membrane filters (MCE, Millipore), and tested for 2,4-D concentration **by HPLC.** The spent biochars were recovered by vacuum filtration, rinsed with UW, and oven dried at  $60 \text{ }^\circ\text{C}$  overnight. The reusability of biochars was investigated by reacting spent samples ( $1 \text{ g L}^{-1}$ ) with 20 mL solution of 2,4-D ( $100 \text{ mg L}^{-1}$ ) in the MW reactor. A control experiment with only MW and no biochar was conducted. A comparative experiment using oil bath as the heating source was also performed under the same reaction conditions. The adsorption of 2,4-D by biochars was investigated at room temperature. **No leaching of metals, organics, or nutrients was detected from the four biochars under the studied experimental conditions.**

To verify the *in-situ* formation of radicals, such as  $\cdot\text{OH}$ , anionic superoxide radical ( $\text{O}_2^{\cdot-}$ ), and singlet oxygen ( $^1\text{O}_2$ ), during MW-assisted removal of 2,4-D, certain quantities of different organic scavengers (TBA

( $k_{\text{OH}} = (3.2\text{--}7.6) \times 10^8 \text{ M}^{-1} \text{ s}^{-1}$ ), CF ( $k_{\text{O}_2^-} = (1.1\text{--}3.2) \times 10^9 \text{ M}^{-1} \text{ s}^{-1}$ ), and FFA ( $k'_{\text{O}_2} = 1.2 \times 10^8 \text{ M}^{-1} \text{ s}^{-1}$ ), respectively) were doped into the MW vessels to reach the target concentration of 45.2 mmol (at molar ratio to 2,4-D of 100:1) [39,43], respectively. The radical quenching experiment was conducted under the same MW/oil bath/room temperature conditions.

To extract adsorbed 2,4-D and possible degradation intermediates, after 1-min reaction in the three systems, the spent samples were: (i) transferred into 20 mL solution of organic solvent (methanol, ethanol, hexane, acetonitrile, and DMSO, respectively) under 8-h end-over-end shaking at 30 rpm [40]; or (ii) added into 20 mL mixed solution of water and different organic solvents (50%, v/v) under 1-min reaction in MW reactors at 90 °C [21]. The above solutions were then analyzed for the extracted 2,4-D.

### 2.5. Analytical methods

The samples were analyzed for 2,4-D by a HPLC (Hitachi Chromaster 5420, Japan, limit of detection (LOD) of 0.1 mg L<sup>-1</sup>) equipped with an ODS-2 chromatography column (150 mm × 4.6 mm, 5 μm) and an ultraviolet and visible spectrophotometry (UV-VIS) detector with UV wavelength set at 280 nm [44]. A mixture of 60% (v/v %) acetonitrile, 38% (v/v %) UW, and 2% (v/v %) acetic acid was used as the mobile phase at a flow rate of 0.5 mL min<sup>-1</sup> [44]. The peak for 2,4-D was detected at a retention time of 5.6 min [44]. The total organic carbon (TOC) concentration was measured by a TOC analyzer (Shimadzu, SSM-5000A, Japan, LOD of 0.1 mg L<sup>-1</sup>). The 2,4-D or TOC removal efficiency was calculated using Eq. 1 as follows.

$$\text{Removal efficiency} = (C_{\text{initial}} - C_{\text{final}}) / C_{\text{initial}} \times 100\% \quad (\text{Eq.1})$$

Standard calibration was carried out prior to each analysis. Standards were analyzed every 10 samples for quality assurance and quality control. All experiments were performed in at least triplicate, and the results are presented as mean ± standard deviations. One-way analysis of variance (ANOVA) by the Duncan test was applied to analyze the significance of differences between data (SPSS version 22.0). The lower-case letters in the figures represent data grouping based on the significance level of 0.05 ( $p < 0.05$ ).

### 3. Results and discussion

#### 3.1. Characterization of the biochars

The distinctive physicochemical properties of the various biochars prepared from different feedstocks under N<sub>2</sub>/CO<sub>2</sub> purging are summarized in **Table 1**. Pyrolysis of the lignin-rich biomass (*i.e.*, oak wood) produced biochars (OBC-900N and OBC-900C) with higher yield (20.8 and 19.8%) and carbon content (92.1 and 88.6 wt.%). Switching the purging gas from N<sub>2</sub> to CO<sub>2</sub> noticeably lowered the yield (from 19.8 to 17.0%) and carbon content (from 88.8 to 78.9 wt.%) of the resultant ABC-900s. These indicated that thermal decomposition of biomass in a CO<sub>2</sub> environment is more significant than that in a N<sub>2</sub> atmosphere, probably due to accelerated consumption of carbon matrix by CO<sub>2</sub> and other active gases produced during pyrolysis [45,46]. The elemental analysis revealed that the OBC-900s exhibited much lower molar ratios of H/C (0.010 of the OBC-900C and 0.011 of the OBC-900N) than the ABC-900s (0.025 of the ABC-900C and 0.079 of the ABC-900N), suggesting an increased biochar aromaticity with higher lignin content in the feedstocks and using CO<sub>2</sub> pyrolysis. The higher molar ratio of (O+N)/C of the ABC-900C (0.200) compared to ABC-900N (0.096) indicated an improved hydrophilicity and polarity in CO<sub>2</sub>. In particular, the ABC-900C contained a much higher oxygen content (20.3 wt.%) than the other three biochars, probably because of CO<sub>2</sub> induced carbon oxidation during cooling inside the tube furnace after pyrolysis [47]. The zeta potential of the OBC-900s was negative (-18.8 – -12.6 mV) in contrast to the positively charged surfaces of the ABC-900s (2.64 – 6.73 mV), which can be ascribed to the higher metal (*i.e.*, Ca, K, Mg, Na, Fe, and Al) content in the former (**Table 1**). The pH values of the CO<sub>2</sub> pyrolyzed biochars (10.8–10.9) were lower than those of the N<sub>2</sub> pyrolyzed biochars (11.2–12.4), despite their similar ash contents (**Table 1**). CO<sub>2</sub> may have acidified the biochars *via* the creation of more near-surface oxygen-containing functionalities [45,48], which could be verified by the XPS analysis in the subsequent discussion.

The SEM images clearly depict the morphological and structural differences in the biochars dependent on different feedstocks and purging gases (**Fig. 1**). The OBC-900s presented rougher surfaces because of their higher ash content (**Table 1**), while the ABC-900s exhibited more porous structures due to the hierarchical spatial structure of softwood (*e.g.*, apple tree) [23]. As shown in **Fig. 1**, micro- and meso-pores were highly developed inside the carbon matrix of the CO<sub>2</sub> biochars (*i.e.*, OBC-900C and ABC-900C). These were also evidenced by the surface area and pore size distribution of the biochars in **Table 1**. The BET surface area ( $S_{\text{BET}}$ , 479.9 or 510.5 m<sup>2</sup> g<sup>-1</sup>) and total pore volume ( $V_{\text{total}}$ , 0.325 or 0.349 cm<sup>3</sup> g<sup>-1</sup>) of biochars fabricated in a CO<sub>2</sub> environment (OBC-900C or ABC-900C) were significantly higher than those generated in a N<sub>2</sub> environment. The CO<sub>2</sub> medium promoted the formation of micropores (377.5 or 384.4 m<sup>2</sup> g<sup>-1</sup>) of the OBC-900C (or ABC-900C). The micropore volume also increased from 0.164 (ABC-900N, 46.8% of  $V_{\text{total}}$ ) to 0.235 (ABC-900C, 67.4% of  $V_{\text{total}}$ ) cm<sup>3</sup> g<sup>-1</sup>. The average pore diameter ( $D_p$ ) increased from 2.53 nm for the OBC-900N to 2.90 nm for the OBC-900C, indicating that CO<sub>2</sub> acted as a pore-enlarging agent. Tar and volatile organics generated from an incomplete thermal degradation of lignin could block the pores in biochars [49]. Such pore blocking was suppressed in CO<sub>2</sub>, which could expedite tar cracking/reforming *via* the thermodynamically favourable Boudouard reaction between the CO<sub>2</sub> and lignin-C (*viz.* C + CO<sub>2</sub> → CO) at ≥ 720 °C [50], resulting in highly porous biochars [45].

The near-surface chemical functionalities of the biochars were characterized by FTIR analysis, as shown in **Fig. 2**. The small peak at ~3760 cm<sup>-1</sup> ascribed to the –OH group was present in the spectra of all the biochars except the ABC-900N [51]. The peaks between 1360 and 1450 cm<sup>-1</sup> are due to the aromatic C=C rings [52,53], whereas the aromatic C–C rings appeared at ~760 cm<sup>-1</sup> [54]. The high-temperature (900 °C) pyrolysis eliminated the O-containing functional groups from the biochar surface and increased the content of condensed aromatic rings [38,39] as a result of intensive decomposition of the aliphatic and phenolic organic compounds *via* dehydration of cellulosic and ligneous components [39]. Biomass with higher lignin

content in a CO<sub>2</sub> atmosphere can provide biochars with a higher level of carbonization, as evidenced by the increasing intensity of aromatic peaks in the order of ABC-900N < ABC-900C < OBC-900N < OBC-900C (**Fig. 2**), in accordance with the elemental analysis (**Table 1**).

The graphitization degree of the biochars was further investigated by Raman analysis (**Fig. 3**). The Raman spectra of the biochar samples were deconvoluted into five characteristics peaks that were assigned to *sp*<sup>2</sup> C–H of aromatic rings (S<sup>1</sup>) at 1060 cm<sup>-1</sup>, defect bands and small ordered fused benzene rings (D) at 1310 cm<sup>-1</sup>, methyl group and amorphous carbon (V<sup>1</sup>) at 1380 cm<sup>-1</sup>, aromatics with 3–5 rings (G<sup>1</sup>) at 1540 cm<sup>-1</sup>, and highly ordered *sp*<sup>2</sup> graphitic carbon (G) at 1590 cm<sup>-1</sup>, respectively [39]. The area ratio of the D peak to the G peak ( $A_D/A_G$ ) of the CO<sub>2</sub> pyrolyzed composites (1.94–2.56) was smaller than that produced in N<sub>2</sub> (2.26–3.52), suggesting that a CO<sub>2</sub> medium induced higher aromaticity and graphitization within the carbon matrix during pyrolysis [45,50]. Higher proportions of the G (11.5–13.0%) and G<sup>1</sup> (2.58–6.72%) bands were formed in the OBC-900s. The ratio of  $A_D/A_G$  decreased when there was a larger lignin content in the feedstocks. The cellulose and hemicellulose with branched polymer structure and short side chains form volatile products during pyrolysis of wood biomass, whereas the lignin with complex crosslinking phenolic polymer structure contributes mainly to the biochar production [23]. At pyrolysis temperatures higher than 700 °C, the fragmentation and repolymerization of lignin monomers favour the biochar formation, which could be accelerated in the presence of CO<sub>2</sub> [23]. Thus, the CO<sub>2</sub> enhanced aromaticity could be attributed to accelerated conversion of lignin monomers [44].

XPS analysis was conducted to investigate the transformation of near-surface functional groups in various biochars (**Fig. 4**). For all the samples, the C 1s spectra consisted of three distinctive peaks that were attributed to the presence of aromatic C–C/C=C at 284.8 eV, C–O at 285.8 eV, and  $\pi$ – $\pi^*$  transition in aromatic rings at 288.3 eV, respectively [38]. As shown in **Fig. 4**, the ratio of aromatic C–C/C=C increased from 65.4–66.9%, for ABC-900s to 68.4–68.7% for OBC-900s. This observation reaffirmed the idea of an enhanced conversion

of the crosslinking C structure to condensed aromatic nature of biochars derived from lignin-rich feedstocks [23,39], agreeing with the elemental composition (**Table 1**), FTIR spectra (**Fig. 2**), and Raman spectra (**Fig. 3**). Moreover, by means of XPS analysis, oxygen-containing functional groups (C–O) were identifiable on the biochar surface, the ratio of which increased from 16.1% (ABC-900N) to 17.5% (ABC-900C) after CO<sub>2</sub> activation. This contradictory observation compared with FTIR analysis (**Fig. 2**) might be due to the effect of solution pH and pK<sub>a</sub> of biochar on the sensitivity of FTIR, which is a bulk technique that reflects the average bonding environment. The C–O might result from the interaction of CO<sub>2</sub> with organic/inorganic compounds in the biochar [49]. Moreover, the density of  $\pi$ – $\pi^*$  transition in aromatic rings increased from 14.7–15.1% in the OBC-900s to 17.0–17.1% in the ABC-900s (**Fig. 4**). According to a previous study [55], these functionalities (C–O and  $\pi$ – $\pi^*$  transition) on biochar could contribute to effective adsorption of 2,4-D. However, it should be acknowledged that the above discussion was mainly based on the peak fitting of XPS spectra, which might be complicated by the small differences between different biochars. More accurate analysis using advanced and computational techniques should also be pursued in future studies.

### 3.2. MW-assisted removal of 2,4-D by the biochars

Removal efficiencies of 2,4-D by various biochars under three reaction conditions (*i.e.*, room temperature, oil bath, and MW irradiation) are presented and compared in **Fig. 5**. CO<sub>2</sub> activated biochars (ABC-900C and OBC-900C) with increased  $S_{\text{BET}}$  (479.9 and 510.5 m<sup>2</sup> g<sup>-1</sup>) and  $D_p$  (2.90 and 2.99 nm) gave better 2,4-D adsorption performance than the N<sub>2</sub>-produced biochars. CO<sub>2</sub> modification significantly promoted 2,4-D adsorption on OBC-900 and ABC-900, with the equilibrium removal efficiency improved from 40.9 ± 0.7 to 49.4 ± 7.3% and from 41.8 ± 1.5 to 69.8 ± 7.0% (**Fig. S1 (Supporting Information)**) after 30-min reaction, respectively, at room temperature without heating. A previous study also discovered a positive correlation between the specific surface area of biochar (400–600 m<sup>2</sup> g<sup>-1</sup>) and its 2,4-D adsorption capacity [40],



indicating that the progressive widening of micropores into mesopores accommodated more 2,4-D molecules with polar surface area of  $47 \text{ \AA}^2$  [40]. Apart from a porous structure, other physicochemical properties of biochar also determined its capacity for 2,4-D adsorption. Our study suggested ABC-900C as the best-performing adsorbent of 2,4-D at room temperature. It had a zeta potential of 2.64 mV (**Table 1**) and thus a positively charged surface that favoured electrostatic interaction with the anionic form of 2,4-D at solution  $\text{pH} > 2.7$  [55]. In addition, biochars with higher content of the  $\pi$ - $\pi^*$  transition (17.1% of the ABC-900C, **Fig. 4**) as electron acceptor could strengthen attraction with the electron-rich benzene ring of 2,4-D as electron donor *via*  $\pi$ - $\pi$  interaction [55]. Moreover, the abundant oxygen-containing functional groups (17.5% C-O, **Fig. 4**) in the ABC-900C could contribute more active sites for 2,4-D adsorption [55]. Thus, adsorption of 2,4-D by biochar was **likely** a result of electrostatic interaction, electron conjugation, and chemisorption [55].

The significantly promoted removal of 2,4-D under MW irradiation is clearly illustrated in **Fig. 5**. After 1-min reaction in the MW reactor, 2,4-D removal by the OBC-900C and OBC-900N was obviously increased to  $81.6 \pm 0.8$  and  $57.4 \pm 4.1\%$ , respectively, *i.e.*,  $\sim 2.3$  times the removal efficiency under room temperature. No 2,4-D removal was observed under MW irradiation only in the absence of biochar due to the low volatility of 2,4-D. However, gas emission could be a potential problem of the MW system for semi-volatile and volatile contaminants. MW treatment outperformed conventional heating in an oil bath at the same reaction temperature ( $90 \text{ }^\circ\text{C}$ ) for 1–30 min (**Fig. 5** and **Fig. S1**). In particular, the OBC-900C, which achieved the highest removal in MW, consumed less energy than the rest of the biochars during the temperature ramping (1.39 *vs.* 1.68 kW) and holding (0.275 *vs.* 0.601 kW) stages, despite the same heating programme (**Fig. 6**). This suggested a more efficient MW-to-thermal energy transformation over the MW-absorbing OBC-900C. Furthermore, its temperature profile showed overshooting ( $\sim 1 \text{ }^\circ\text{C}$ ) after the ramping, which was absent from the other biochars. The strong MW absorptivity of the OBC-900C might have induced localized overheating, which promoted the removal of 2,4-D. Thus, the OBC-900C could absorb maximal electromagnetic energy

that ultimately penetrates into its carbon matrix and quickly dissipate as heat or other forms of energy [4].

There was only a slight improvement of 2,4-D removal in the presence of the ABC-900C under MW irradiation ( $69.9 \pm 1.7\%$ ) compared to oil bath heating ( $62.4 \pm 0.6\%$ ), both of which were better than room-temperature treatment ( $52.6 \pm 4.2\%$ ) (**Fig. 5**). In addition, the OBC-750C (pyrolyzed at a lower temperature of  $750\text{ }^\circ\text{C}$ ) exhibited a significantly inferior performance for 2,4-D removal under the three different reaction conditions (**Fig. 5**). These results indicate that biochar prepared from various feedstocks, purging gases, and pyrolysis temperatures exhibited a distinctive sensitivity to MW irradiation. Carbon materials have been explored as MW adsorbents due to their high dielectric loss that is usually dependent on two critical factors, the bonding state of carbon atoms (*i.e.*, degree of graphitization) and the microstructure of the carbon matrix [16]. On one hand, the large surface area ( $S_{\text{BET}} = 510.5\text{ m}^2\text{ g}^{-1}$ ), high proportion of micropores ( $V_{\text{micro}}/V_{\text{total}} = 67.4\%$ ), appropriate pore size ( $D_p = 2.99\text{ nm}$ ), and abundant surface functionalities (17.5% C–O and 17.1%  $\pi$ – $\pi^*$  transition in aromatic rings) of the ABC-900C could guarantee sufficient adsorption of aquatic organic pollutants (**Table 1** and **Fig. 4**). On the other hand, the higher degree of graphitization of the OBC-900C ( $A_D/A_G = 1.94$  and 68.7% aromatic C–C/C=C, **Figs. 3-4**), together with its greater microwave absorbing property and medium-developed microporous structure, would be beneficial to the capture and degradation of 2,4-D under MW irradiation.

The MW-enhanced organic removal may also be attributed to the formation of various ROSs catalyzed by the carbon surface [21]. As shown in **Fig. 7**, TBA addition only slightly decreased the 2,4-D removal to  $34.2 \pm 0.8\%$  by the ABC-900N while performances of the other biochars remained unaffected. In contrast, CF or FFA noticeably inhibited the 2,4-D removal to the same extent in the MW systems containing the OBC-900C and ABC-900C ( $44.5 \pm 5.6 - 52.8 \pm 0.7\%$  and  $20.4 \pm 0.4 - 22.3 \pm 4.2\%$ , respectively) compared with  $81.6 \pm 0.8$  and  $61.9 \pm 1.7\%$  removal with no scavengers (**Fig. 7**), indicating the equal contribution of  $\text{O}_2^{\cdot-}$  and  $^1\text{O}_2$  to 2,4-D removal. However, in the case of  $\text{N}_2$  pyrolyzed biochars, FFA led to a more significant decrease in 2,4-D

removal compared with CF, *i.e.*, 49.1 ±4.9 vs. 36.6 ±0.3% and 10.5 ±2.6 vs. 3.1 ±0.8% for the OBC-900N and ABC-900N, respectively (**Fig. 7**), suggesting that <sup>1</sup>O<sub>2</sub> played a superior role than the other ROSs. **In particular, the additional organic scavengers did not exhibit noticeable effect on 2,4-D removal under room temperature or oil bath conditions. This observation excluded the potential interference of these organic scavengers on 2,4-D adsorption, and reaffirmed that radicals were only generated in the MW system.** The production of radical species is summarized in reactions **R1–R3** according to previous studies [23]. Upon MW irradiation, water (H<sub>2</sub>O) molecules surrounding biochar surface “hot spots” could be activated into <sup>•</sup>OH and hydrogen radicals (<sup>•</sup>H) (**R1**). Oxygen (O<sub>2</sub>) in the water medium would react with <sup>•</sup>H to form O<sub>2</sub><sup>•-</sup> and <sup>1</sup>O<sub>2</sub> (**R2**), which could further yield <sup>•</sup>OH *via* **R3**. These radicals (O<sub>2</sub><sup>•-</sup> and <sup>1</sup>O<sub>2</sub>) with powerful oxidization capacity could decompose the adsorbed or soluble 2,4-D into intermediates with lower molecular weight, and finally mineralize into CO<sub>2</sub> and H<sub>2</sub>O.



### 3.3. Desorption and reusability of the biochars

To further distinguish adsorption and degradation of 2,4-D under the three reaction conditions (MW irradiation, oil bath, and room temperature), the adsorbed 2,4-D on the spent biochars were extracted by different organic solvents (methanol, ethanol, hexane, acetonitrile, **and DMSO** respectively) *via* desorption at room temperature and under MW conditions, respectively. However, neither desorption procedures with any organic solvent could recover more than 10% 2,4-D from the reacted samples. These results might be due to strong binding between 2,4-D and biochar *via* diffusion into the inner porous structure and intensive chemisorption by the surface functionalities of biochar [40]. In addition, the 1-min TOC removal (59.2 ±2.5,

43.3 ±0.9, 83.0 ±3.4, and 71.9 ±3.2%, respectively) by the OBC-900N, ABC-900N, OBC-900C, and ABC-900N, respectively, was slightly greater than the 2,4-D removal (57.4 ±4.1, 41.2 ±2.2, 81.6 ±0.8, and 69.9 ±1.7%, respectively) under MW conditions (**Fig. S2**). These results indicated that 2,4-D could be completely mineralized into CO<sub>2</sub> and H<sub>2</sub>O by the MW-assisted removal in presence of biochar. Moreover, no obvious peaks of any degradation intermediates were observed by HPLC analysis of the solutions after reaction or the extraction solutions of the spent biochars, probably because of a strong entrapment of possible by-products by the biochars. Thus, no direct evidence of 2,4-D decomposition (within the accuracies of the experimental methods) could be provided in the current stage of our study. According to the latest findings [56], the dechlorination rate of 2,4-D (*i.e.*, change of the Cl<sup>-</sup> concentration) was correlated to its degradation efficiency when 2,4-D was completely mineralized into CO<sub>2</sub> and H<sub>2</sub>O. More comprehensive experimental design (*e.g.*, extraction of reacted biochars by other means, full identification of 2,4-D intermediates, and detection of released Cl<sup>-</sup>) would help to further prove and quantify the 2,4-D degradation in the MW/biochar system.

Reusability of the OBC-900N and OBC-900C biochars was tested in three consecutive cycles of 2,4-D removal under MW irradiation. A progressive loss of biochar activity in each cycle is depicted in **Fig. 8**. Without any treatment of regeneration, the performance of the OBC-900C (or OBC-900N) noticeably dropped from 81.7 ±2.1% (or 61.2 ±0.9%) to 24.2 ±1.3% (or 21.2 ±1.1%) 2,4-D removal. This observation could be ascribed to the high BET surface area and internal microporous structure of biochar. The degradation by-products might accumulate and occupy the active sites on biochar surface for 2,4-D adsorption. It is also possible that the carbon materials eventually crumble when “hot spots” formed inside micropores generate sufficient confined vapour with increased pressure [6]. This so-called “popcorn effect” could impede biochar stability with susceptible deactivation and fouling by intermediates [6]. Future studies should focus on biochar regeneration *via* facile and low-cost treatment, for example, low-temperature heating in N<sub>2</sub> environment or desorption by various types of green solvents.

For future design of more sustainable water/wastewater treatment processes, MW technology can be effectively incorporated with membrane bioreactors and electro-/photo-catalysis process [3,4]. However, most current studies on MW system for water/wastewater treatment are conducted in laboratory scale, because (i) volume and power output of the available MW reactors are insufficient for widespread commercial promotion, and (ii) low-cost, highly efficient, and recyclable catalysts are critical for industrial applications [3,4]. With further development of equipment optimization and catalysts exploitation, MW technology is expected to deliver good benefits for practical water and wastewater treatment.

## Conclusions

This study has demonstrated that biochar derived from waste biomass of oak tree, with high lignin content under 900 °C pyrolysis and CO<sub>2</sub> purging, can act as a 'green', highly efficient MW absorber. The CO<sub>2</sub> purging can promote decomposition of lignin carbon at high pyrolysis temperature *via* fragmentation and repolymerization, producing biochar with a developed hierarchical porous structure, enhanced graphitization level, and improved surface chemistry. Under mild MW irradiation, 2,4-D was simultaneously adsorbed (*via* electrostatic interaction, electron conjugation, and chemisorption) and degraded due to a MW-induced thermal effect on the biochar surface that generated hydroxyl (<sup>•</sup>OH), anionic superoxide (O<sub>2</sub><sup>•-</sup>), and singlet oxygen (<sup>1</sup>O<sub>2</sub>) radicals. This study has demonstrated the potential application of an economical, sustainable, metal-free biochar in energy-saving, chemical-free water/wastewater treatment using MW, which could make an important contribution to a clean water environment. Future studies **are suggested to optimize the rational design of MW-active biochar catalysts and investigate the applicability of the MW/biochar system to a broader range of organic pollutants** with diverse physicochemical properties in water/wastewater matrices.

## Acknowledgement

The authors appreciate the financial support from the Hong Kong Research Grants Council (PolyU 15217818) and Hong Kong Environment and Conversation Fund (ECF 87/2017) for this study.

## References

- [1] Sun, J., Pan, L., Tsang, D.C.W., Zhan, Y., Zhu, L., Li, X.D., Organic contamination and remediation in the agricultural soils of China: A critical review, *Science of the Total Environment*, 615 (2018), 724-740.
- [2] Kümmerer, K., Dionysiou, D.D., Olsson, O., Fatta-Kassinos, D., A path to clean water. *Science*, 361 (2018), 222-224.
- [3] Wei, R., Wang, P., Zhang, G., Wang, N., Zheng, T., Microwave-responsive catalysts for wastewater treatment: A review, *Chemical Engineering Journal*, (2020), 122781.
- [4] Xue, C., Mao, Y., Wang, W., Song, Z., Zhao, X., Sun, J., Wang, Y., Current status of applying microwave-associated catalysis for the degradation of organics in aqueous phase-A review, *Journal of Environmental Sciences*, 81 (2019), 119-135.
- [5] Varisli, D., Korkusuz, C., Dogu, T., Microwave-assisted ammonia decomposition reaction over iron incorporated mesoporous carbon catalysts., *Applied catalysis B: Environmental*, 201 (2017), 370-380.
- [6] Garcia-Costa, A.L., Zazo, J.A., Rodriguez, J.J., Casas, J.A., Intensification of catalytic wet peroxide oxidation with microwave radiation: activity and stability of carbon materials, *Separation and Purification Technology*, 209 (2019), 301-306.
- [7] Hu, L., Wang, P., Shen, T., Wang, Q., Wang, X., Xu, P., Zheng, Q., Zhang, G., The application of microwaves in sulfate radical-based advanced oxidation processes for environmental remediation: A review, *Science of The Total Environment*, (2020), 137831.
- [8] Garcia-Costa, A.L., Zazo, J.A., Rodriguez, J.J., Casas, J.A., Microwave-assisted catalytic wet peroxide oxidation. Comparison of Fe catalysts supported on activated carbon and  $\gamma$ -alumina, *Applied Catalysis B:*

- Environmental, 218 (2017), 637-642.
- [9] Chen, J., Pan, H., Hou, H., Li, H., Yang, J., Wang, L., High efficient catalytic degradation of PNP over Cu-bearing catalysts with microwave irradiation, *Chemical Engineering Journal*, 323 (2017), 444-454.
- [10] Wang, X., Mei, L., Xing, X., Liao, L., Lv, G., Li, Z., Wu, L., Mechanism and process of methylene blue degradation by manganese oxides under microwave irradiation, *Applied Catalysis B: Environmental*, 160 (2014), 211-216.
- [11] Ahmed, A. B., Jibril, B., Danwittayakul, S., Dutta, J., Microwave-enhanced degradation of phenol over Ni-loaded ZnO nanorods catalyst, *Applied Catalysis B: Environmental*, 156 (2014), 456-465.
- [12] Ling, L., Feng, Y., Li, H., Chen, Y., Wen, J., Zhu, J., Bian, Z., Microwave induced surface enhanced pollutant adsorption and photocatalytic degradation on Ag/TiO<sub>2</sub>, *Applied Surface Science*, 483 (2019), 772-778.
- [13] Qi, Y., Mei, Y., Li, J., Yao, T., Yang, Y., Jia, W., Tong, X., Wu, J., Xin, B., Highly efficient microwave-assisted Fenton degradation of metacycline using pine-needle-like CuCo<sub>2</sub>O<sub>4</sub> nanocatalyst, *Chemical Engineering Journal*, 373 (2019), 1158-1167.
- [14] Qiu, Y. and Zhou, J., Highly effective and green microwave catalytic oxidation degradation of nitrophenols over Bi<sub>2</sub>O<sub>2</sub>CO<sub>3</sub> based composites without extra chemical additives, *Chemosphere*, 214 (2019), 319-329.
- [15] Yao, X., Lin, Q., Zeng, L., Xiang, J., Yin, G., & Liu, Q. (2017). Degradation of humic acid using hydrogen peroxide activated by CuO-Co<sub>3</sub>O<sub>4</sub>@ AC under microwave irradiation. *Chemical Engineering Journal*, 330, 783-791.
- [16] Cai, B., Feng, J. F., Peng, Q. Y., Zhao, H. F., Miao, Y. C., Pan, H., Super-fast degradation of high concentration methyl orange over bifunctional catalyst Fe/Fe<sub>3</sub>C@C with microwave irradiation, *Journal of Hazardous Materials*, 392 (2020), 122279.

- [17] Yao, T., Qi, Y., Mei, Y., Yang, Y., Aleisa, R., Tong, X., Wu, J., One-step preparation of reduced graphene oxide aerogel loaded with mesoporous copper ferrite nanocubes: A highly efficient catalyst in microwave-assisted Fenton reaction, *Journal of Hazardous Materials*, 378 (2019), 120712.
- [18] Shen, M., Fu, L., Tang, J., Liu, M., Song, Y., Tian, F., Zhao, Z., Zhang, Z., Dionysiou, D.D., Microwave hydrothermal-assisted preparation of novel spinel-NiFe<sub>2</sub>O<sub>4</sub>/natural mineral composites as microwave catalysts for degradation of aquatic organic pollutants, *Journal of Hazardous Materials*, 350 (2018), 1-9.
- [20] Zhang, Z., Shan, Y., Wang, J., Ling, H., Zang, S., Gao, W., Zhao, Z., Zhang, H., Investigation on the rapid degradation of congo red catalyzed by activated carbon powder under microwave irradiation, *Journal of Hazardous Materials*, 147 (2007), 325-333.
- [21] Veksha, A., Pandya, P., Hill, J.M., The removal of methyl orange from aqueous solution by biochar and activated carbon under microwave irradiation and in the presence of hydrogen peroxide, *Journal of Environmental Chemical Engineering*, 3 (2015), 1452-1458.
- [22] Chen, J., Xue, S., Song, Y., Shen, M., Zhang, Z., Yuan, T., Tian, F., Dionysiou, D.D., Microwave-induced carbon nanotubes catalytic degradation of organic pollutants in aqueous solution, *Journal of Hazardous Materials*, 310 (2016), 226-234.
- [23] Rangabhashiyam, S. and Balasubramanian, P., The potential of lignocellulosic biomass precursors for biochar production: performance, mechanism and wastewater application-A review, *Industrial Crops and Products*, 128 (2019), 405-423.
- [24] Kumar, M., Xiong, X., Sun, Y., Iris, K.M., Tsang, D.C.W., Hou, D., Gupta, J., Bhaskard, T., Pandey, A., Critical review on biochar-supported catalysts for pollutant degradation and sustainable biorefinery. *Advanced Sustainable Systems*, (2020), 1900149.
- [25] Shaheen, S.M., Niazi, N.K., Hassan, N.E., Bibi, I., Wang, H., Tsang, D.C.W., Ok, Y.S., Bolan, N., Rinklebe, J., Wood-based biochar for the removal of potentially toxic elements in water and wastewater:



- a critical review, *International Materials Reviews*, 64 (2019), 216-247.
- [26] El-Naggar, A., Lee, S.S., Awad, Y.M., Yang, X., Ryu, C., Rizwan, M., Rinklebe, J., Tsang, D.C.W., Ok, Y.S., Influence of soil properties and feedstocks on biochar potential for carbon mineralization and improvement of infertile soils, *Geoderma*, 332 (2018), 100-108.
- [27] Igalavithana, A.D., Lee, S.E., Lee, Y.H., Tsang, D.C.W., Rinklebe, J., Kwon, E.E., Ok, Y.S., Heavy metal immobilization and microbial community abundance by vegetable waste and pine cone biochar of agricultural soils, *Chemosphere*, 174 (2017), 593-603.
- [28] Dissanayake, P.D., Choi, S.W., Igalavithana, A.D., Yang, X., Tsang, D.C.W., Wang, C.H., Kua, H.W., Lee, K.B., Ok, Y.S., Sustainable gasification biochar as a high efficiency adsorbent for CO<sub>2</sub> capture: A facile method to designer biochar fabrication, *Renewable and Sustainable Energy Reviews*, 124 (2020), 109785.
- [29] Xu, X., Xu, Z., Gao, B., Zhao, L., Zheng, Y., Huang, J., Tsang, D.C.W., Ok, Y.S., Cao, X., New insights into CO<sub>2</sub> sorption on biochar/Fe oxyhydroxide composites: Kinetics, mechanisms, and in situ characterization, *Chemical Engineering Journal*, 384 (2020), 123289.
- [30] Sun, Y., Chen, S.S., Lau, A.Y.T., Tsang, D.C.W., Mohanty, S.K., Bhatnagar, A., Rinklebe, J., Lin, A.K.Y., Ok, Y.S. Waste-derived compost and biochar amendments for stormwater treatment in bioretention column: Co-transport of heavy metals and colloid, *Journal of Hazardous Materials*, 383 (2020), 121243.
- [31] Rajapaksha, A.U., Alam, M.S., Chen, N., Alessi, D.S., Igalavithana, A.D., Tsang, D.C.W., Ok, Y.S., Removal of hexavalent chromium in aqueous solutions using biochars: Chemical and spectroscopic investigations. *Science of the Total Environment*, 625 (2018), 1567-1573.
- [32] Ruan, X., Sun, Y., Du, W., Tang, Y., Liu, Q., Zhang, Z., William, D., Ray L.F., Qian, R., Tsang, D.C.W., Formation, characteristics, and application of environmentally persistent free radicals (EPFRs) in biochars and environmental matrices: A Review, *Bioresource Technology*, 281 (2019), 457-468.

- [33] Li, Z., Sun, Y., Yang, Y., Han, Y., Wang, T., Chen, J., Tsang, D.C.W., Biochar-supported nanoscale zero-valent iron as an efficient catalyst for organic degradation in groundwater, *Journal of Hazardous Materials*, 383 (2020), 121240.
- [34] Yu, I.K.M., Xiong, X., Tsang, D.C.W., Wang, L., Hunt, A.J., Song, H., Shang, J., Ok, Y.S., Poon, C.S., Aluminium-biochar composite as a sustainable heterogeneous catalyst for glucose isomerization in biorefinery, *Green Chemistry*, 21 (2019), 1267-1281.
- [35] Xiong, X., Yu, I.K.M., Cao, L., Tsang, D.C.W., Zhang, S., Ok, Y.S., A review of biochar-based catalysts for chemical synthesis, biofuel production, and pollution control. *Bioresource Technology*, 246 (2017), 254-270.
- [36] Mian, M.M., Liu, G., Fu, B., Conversion of sewage sludge into environmental catalyst and microbial fuel cell electrode material: A review, *Science of The Total Environment*, 666 (2019), 525-539.
- [37] Sun, C., Chen, T., Huang, Q., Zhan, M., Li, X., Yan, J., Activation of persulfate by CO<sub>2</sub>-activated biochar for improved phenolic pollutant degradation: Performance and mechanism, *Chemical Engineering Journal*, 380 (2020), 122519.
- [38] Sun, Y., Yu, I.K.M., Tsang, D.C.W., Cao, X.D, Lin, D.H, Wang, L.L, Graham, N.J.D., Daniel, S.A., Michael, K., Ok, Y.S., Feng, Y.J., Li, X.D. Multifunctional iron-biochar composites for the removal of potentially toxic elements, inherent cations, and hetero-chloride from hydraulic fracturing wastewater, *Environment International*, 124 (2019), 521-532.
- [39] Wan, Z., Sun, Y., Tsang, D.C.W., Yu, I.K.M., Fan, J., Clark, J.H., Zhou, Y., Cao, X., Gao, B., Ok, Y.S., Sustainable biochar catalyst synergized with copper heteroatoms and CO<sub>2</sub> for singlet oxygenation and electron transfer routes, *Green Chemistry*, 21 (2019), 4800.
- [40] Mandal, S., Sarkar, B., Igalavithana, A.D., Ok, Y.S., Yang, X., Lombi, E., Bolan, N., Mechanistic insights of 2, 4-D sorption onto biochar: Influence of feedstock materials and biochar properties, *Bioresource*

- Technology, 246 (2017), 160-167.
- [41] Tiwari, B., Sellamuthu, B., Ouarda, Y., Drogui, P., Tyagi, R.D., Buelna, G., Review on fate and mechanism of removal of pharmaceutical pollutants from wastewater using biological approach, *Bioresource Technology*, 224 (2017), 1-12.
- [42] Shi, X., Leong, K.Y., Ng, H.Y., Anaerobic treatment of pharmaceutical wastewater: a critical review. *Bioresource Technology*, 245 (2017), 1238-1244.
- [43] Wang, D., Sun, Y., Tsang, D.C.W., Khan, E., Cho, D.W., Zhou, Y., Qi, F., Gong, J., Wang, L., Synergistic utilization of inherent halides and alcohols in hydraulic fracturing wastewater for radical-based treatment: A case study of di-(2-ethylhexyl) phthalate removal, *Journal of Hazardous Materials*, 384 (2020), 121321.
- [44] Cho, D.W., Yoon, K., Ahn, Y., Sun, Y., Tsang, D.C.W., Hou, D., Ok, Y.S., Song, H., Fabrication and environmental applications of multifunctional mixed metal-biochar composites (MMBC) from red mud and lignin wastes, *Journal of Hazardous Materials*, 374 (2019), 412-419.
- [45] Lee, J., Yang, X., Cho, S.H., Kim, J.K., Lee, S.S., Tsang, D.C.W., Ok, Y.S., Kwon, E.E., Pyrolysis process of agricultural waste using CO<sub>2</sub> for waste management, energy recovery, and biochar fabrication. *Applied Energy*, 185 (2017), 214-222.
- [46] Qian, F., Zhu, X., Liu, Y., Hao, S., Ren, Z.J., Gao, B., Zong, R., Zhang, S., Chen, J., Synthesis, characterization and adsorption capacity of magnetic carbon composites activated by CO<sub>2</sub>: implication for the catalytic mechanisms of iron salts, *Journal of Materials Chemistry A*, 4 (2016), 18942-18951.
- [47] Yang, X., Yu, I.K.M., Cho, D.W., Chen, S.S., Tsang, D.C.W., Shang, J., Yip, A.C.K., Wang, L., Ok, Y.S., Tin-functionalized wood biochar as a sustainable solid catalyst for glucose isomerization in biorefinery, *ACS Sustainable Chemistry & Engineering*, 7 (2019), 4851-4860.
- [48] Liu, Y., Zhu, X., Wei, X., Zhang, S., Chen, J., Ren, Z. J., CO<sub>2</sub> activation promotes available carbonate

and phosphorus of antibiotic mycelial fermentation residue-derived biochar support for increased lead immobilization, *Chemical Engineering Journal*, 334 (2018), 1101-1107.

- [49] Igalavithana, A.D., Yang, X., Zahra, H.R., Tack, F.M., Tsang, D.C.W., Kwon, E.E., Ok, Y.S., Metal (loid) immobilization in soils with biochars pyrolyzed in N<sub>2</sub> and CO<sub>2</sub> environments, *Science of the total environment*, 630 (2018), 1103-1114.
- [50] Kim, Y., Oh, J.I., Vithanage, M., Park, Y.K., Lee, J., Kwon, E.E., Modification of biochar properties using CO<sub>2</sub>, *Chemical Engineering Journal*, 372 (2019), 383-389.
- [51] Peng, Y., Sun, Y., Sun, R., Zhou, Y., Tsang, D.C.W., Chen, Q., Optimizing synthesis of Fe/Al (hydr)oxides-biochars to maximize phosphorus removal via response surface model, *Journal of Cleaner Production*, 237 (2019), 117770.
- [52] Yang, F., Zhang, S., Sun, Y., Cheng, K., Li, J., Tsang, D.C.W., Fabrication and characterization of hydrophilic corn stalk biochar-supported nanoscale zero-valent iron composites for efficient metal removal, *Bioresource Technology*, 265 (2018), 490-497.
- [53] Yang, F., Zhang, S., Sun, Y., Tsang, D.C.W., Cheng, K., Ok, Y.S., Assembling biochar with various layered double hydroxides for enhancement of phosphorus recovery, *Journal of Hazardous Materials*, 365 (2019), 665-673.
- [54] Yang, F., Zhang, S., Sun, Y., Du, Q., Song J.P., Tsang, D.C.W., A novel electrochemical modification combined with one-step pyrolysis for preparation of sustainable thorn-like iron-based biochar composites, *Bioresource Technology*, 274 (2019), 379-385.
- [55] Zhu, L., Zhao, N., Tong, L., Lv, Y., Li, G., Characterization and evaluation of surface modified materials based on porous biochar and its adsorption properties for 2, 4-dichlorophenoxyacetic acid, *Chemosphere*, 210 (2018), 734-744.
- [56] Li, W., Li, Y., Zhang, D., Lan, Y., Guo, J., CuO-Co<sub>3</sub>O<sub>4</sub>@CeO<sub>2</sub> as a heterogeneous catalyst for efficient

degradation of 2, 4-dichlorophenoxyacetic acid by peroxymonosulfate, *Journal of Hazardous Materials*,  
381 (2020), 121209.

## **List of Table**

**Table 1.** Physicochemical characteristics of various biochars.

**Table 1.** Physicochemical characteristics of various biochars.

<b>Elemental Compositions</b>	<b>OBC-900N</b>	<b>ABC-900N</b>	<b>OBC-900C</b>	<b>ABC-900C</b>
<sup>a</sup> C (%)	92.1	88.8	88.6	78.9
<sup>a</sup> H (%)	0.082	0.585	0.077	0.164
<sup>a</sup> O (%)	7.67	10.8	11.1	20.3
<sup>a</sup> N (%)	0.165	N.D.	0.203	0.642
<sup>a</sup> S (%)	N.D.	N.D.	N.D.	N.D.
H/C	0.011	0.079	0.010	0.025
(O+N)/C	0.064	0.091	0.096	0.200
<sup>b</sup> Ca (%)	0.06	0.49	0.04	0.50
<sup>b</sup> K (%)	0.06	0.14	0.05	0.14
<sup>b</sup> Mg (%)	0.01	0.05	0.01	0.05
<sup>b</sup> Na (%)	0.01	0.02	N.D.	0.02
<sup>b</sup> Fe (%)	0.01	0.02	0.01	0.01
<sup>b</sup> Al (%)	N.D.	0.04	0.01	0.02
<b>Chemical Properties</b>	<b>OBC-900N</b>	<b>ABC-900N</b>	<b>OBC-900C</b>	<b>ABC-900C</b>
<sup>c</sup> pH	11.2	12.4	10.8	10.9
<sup>d</sup> Zeta potential (mV)	-12.6	6.73	-18.8	2.64
<b>Physical Properties</b>	<b>OBC-900N</b>	<b>ABC-900N</b>	<b>OBC-900C</b>	<b>ABC-900C</b>
Yield	20.8	19.8	19.8	17.0
BET surface area, $S_{\text{BET}}$ ( $\text{m}^2 \text{g}^{-1}$ )	432.0	435.2	479.9	510.5
Micropore surface area, $S_{\text{micro}}$ ( $\text{m}^2 \text{g}^{-1}$ )	259.4	276.1	377.5	384.4
External surface area, $S_{\text{ext}}$ ( $\text{m}^2 \text{g}^{-1}$ )	172.6	159.1	102.4	122.1
Total pore volume, $V_{\text{total}}$ ( $\text{cm}^3 \text{g}^{-1}$ )	0.304	0.313	0.325	0.349
Micropore volume, $V_{\text{micro}}$ ( $\text{cm}^3 \text{g}^{-1}$ )	0.132	0.164	0.194	0.235
$V_{\text{micro}}/V_{\text{total}}$ (%)	43.3	46.8	59.6	67.4
Average pore diameter, $D_p$ (nm)	2.53	2.73	2.90	2.99

<sup>a</sup> Determined by elemental analysis (O wt.% = 100% - C wt.% - H wt.% - N wt.% - ash wt.%).

<sup>b</sup> Determined by total digestion ( $\text{HNO}_3 + \text{HClO}_4$ ) and inductively coupled plasma atomic emission spectroscopy (ICP-AES, Thermo Scientific, LOD of  $0.1 \mu\text{g L}^{-1}$ ) analysis.

<sup>c</sup> 1 g solid + 20 mL DIW, 4-h end-over-end rotation (30 rpm), centrifugation (4000 rpm, 10 min).

<sup>d</sup> 0.25 g solid + 25 mL DIW, 30-min sonication, determined by DLS Zetasizer.

N.D.: Non detectable.

## **List of Figures**

**Fig.1.** SEM images of various biochars.

**Fig.2.** FTIR spectra of various biochars.

**Fig.3.** Deconvoluted Raman analysis of various biochars.

**Fig.4.** Deconvoluted XPS analysis of C1s binding states of various biochars.


**Fig.5.** 2,4-D removal efficiency of various biochars after 1-min reaction in the three systems.

**Fig.6.** Temperature and power of the microwave reactor containing the OBC-900 or the other three biochars.


**Fig.7.** Effect of different radical scavengers on the 2,4-D removal efficiency of various biochars after 1-min reaction in the microwave system.

**Fig.8.** Reusability of the OBC-900N and OBC-900C for 2,4-D removal after 1-min reaction in microwave system.




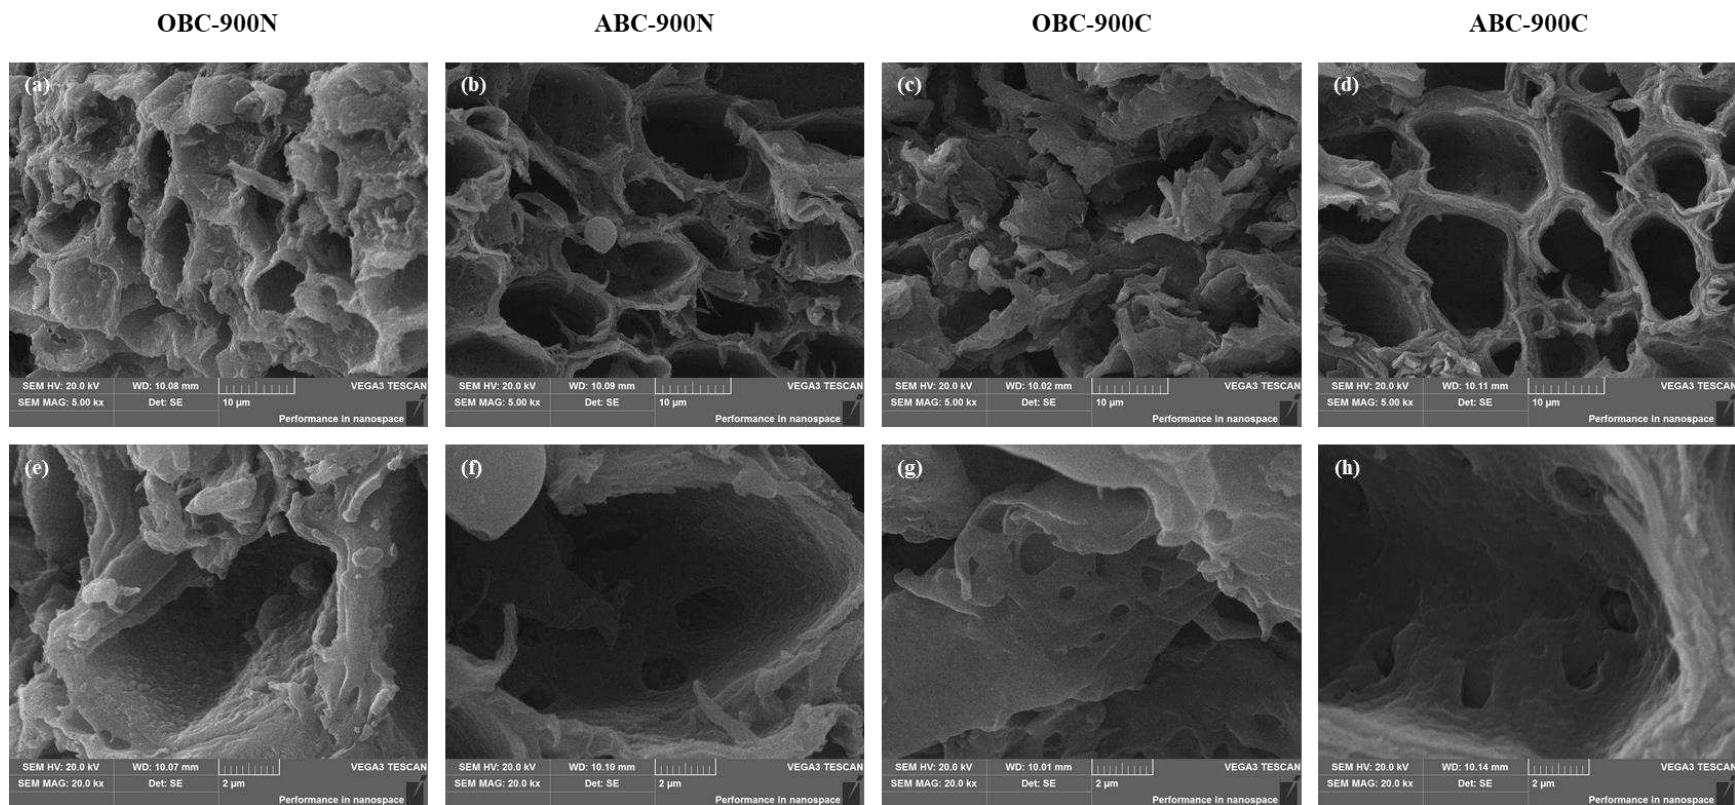


**Fig. 1.** SEM images of various biochars (a-d: 5,000× magnification; e-h: 20,000× magnification).

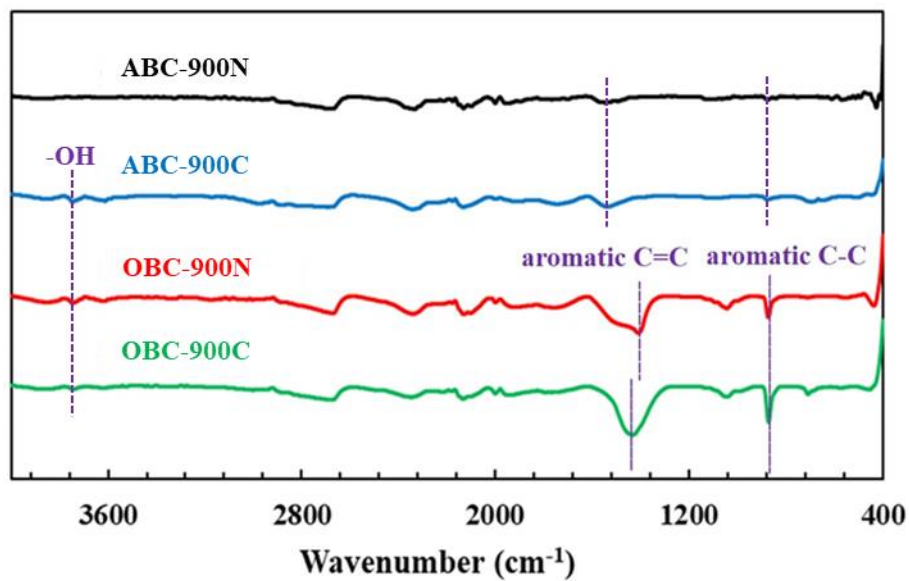


**Fig. 2.** FTIR spectra of various biochars (3760, 1360–1450, and 760  $\text{cm}^{-1}$  assigned to the  $\text{-OH}$  group, aromatic  $\text{C}=\text{C}$  rings, and aromatic  $\text{C}-\text{C}$  rings, respectively).

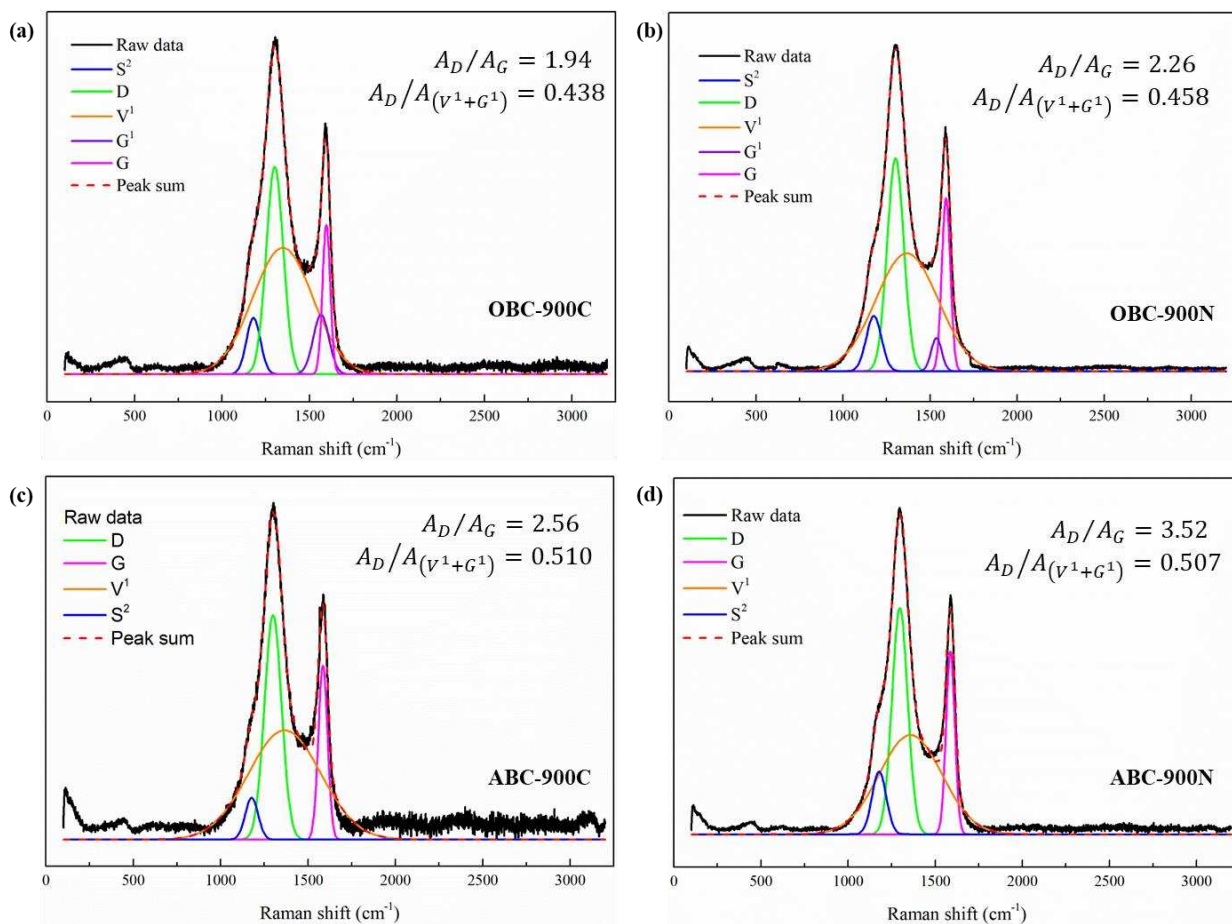


**Fig. 3.** Deconvoluted Raman analysis of various biochars (1230, 1310, 1380, 1540, and 1590  $\text{cm}^{-1}$  assigned to arylalkyl ether ( $S^2$ ), defect bands and small ordered fused benzene rings (D), methyl group and small amorphous carbon ( $V^1$ ), aromatics with 3–5 rings ( $G^1$ ), and highly ordered  $sp^2$  graphitic carbon (G), respectively).

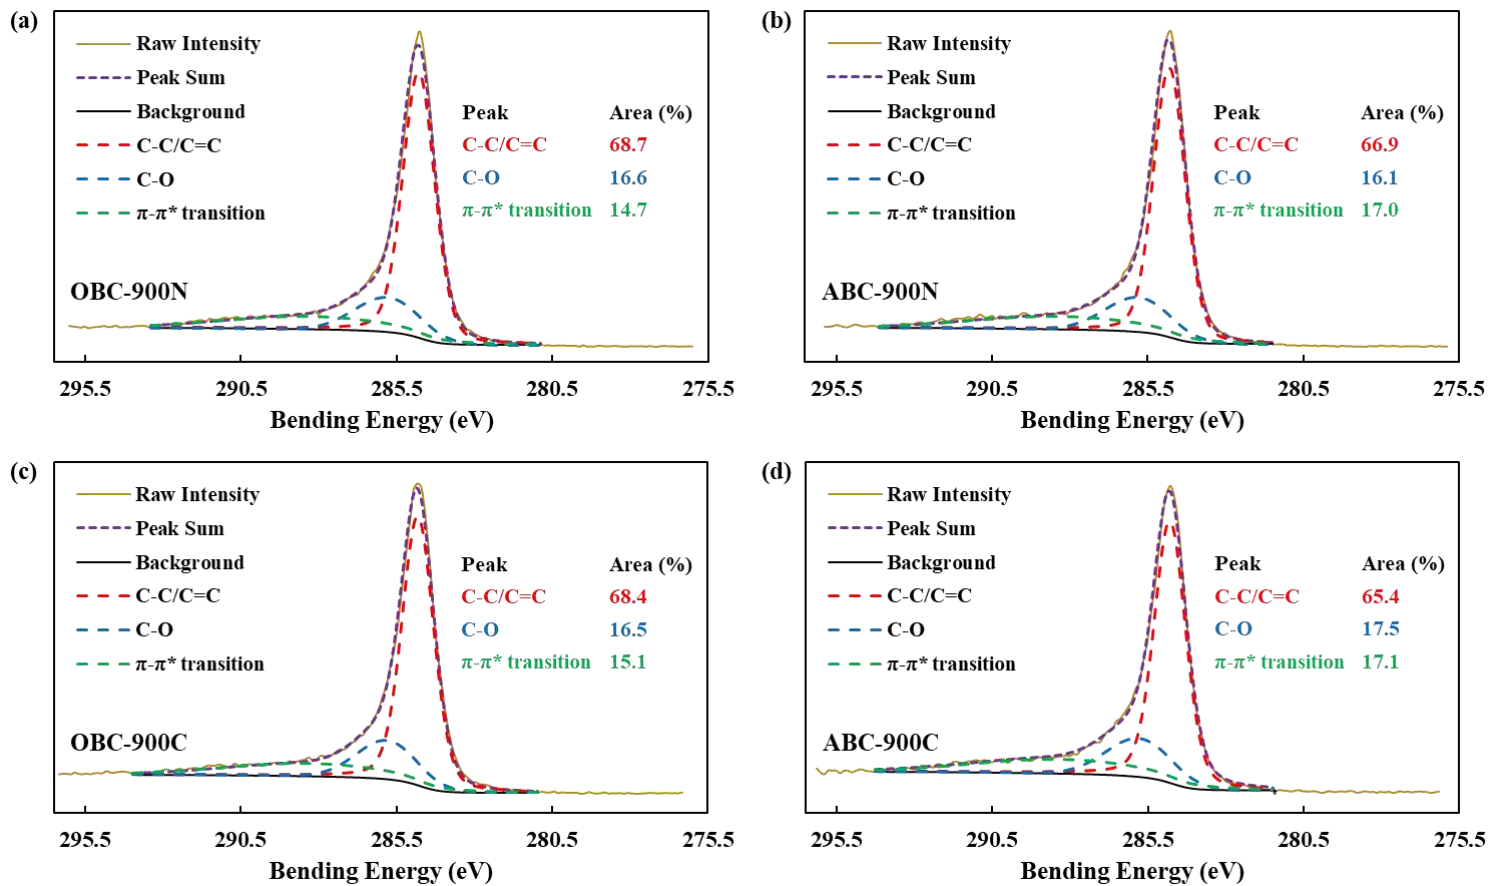


**Fig. 4.** Deconvoluted XPS analysis of C1s binding states of various biochars (284.8, 285.8, and 288.3 eV assigned to C-C/C=C, C-O, and  $\pi$ - $\pi^*$  transition in aromatic rings, respectively).

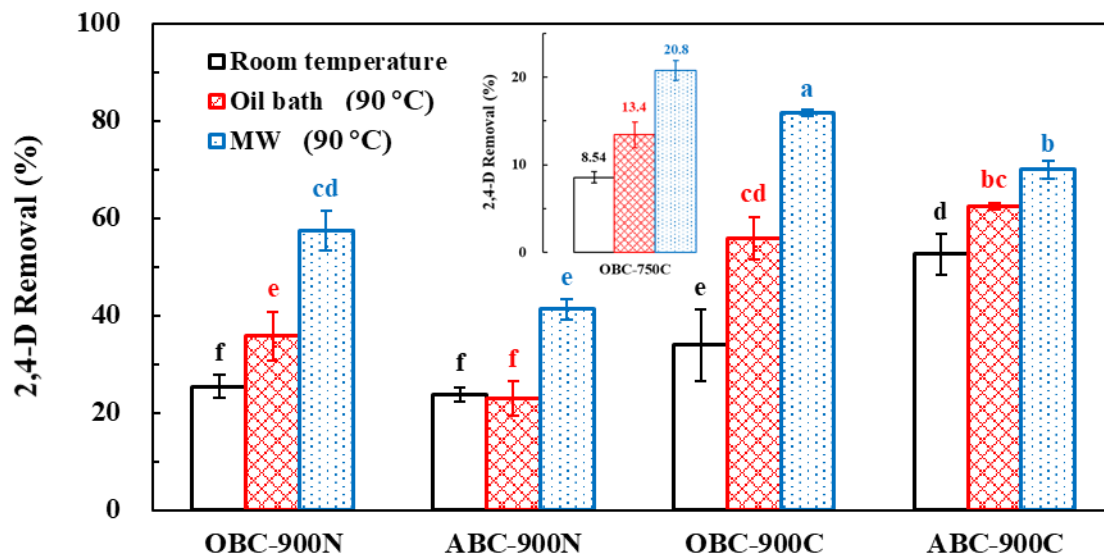


**Fig. 5.** 2,4-D removal efficiency of various biochars after 1-min reaction in the three systems (Reaction conditions: 2,4-D = 100 mg L<sup>-1</sup>, biochar = 1 g L<sup>-1</sup>, V<sub>solution</sub> = 20 mL, and n = 3; room temperature: 23 ± 2 °C; oil bath: temperature increased from 23 ± 2 °C to 90 °C in 20 min and hold for 1 min; microwave (MW): temperature increased from 23 ± 2 °C to 90 °C in 2 min and hold for 1 min, MW<sub>max</sub> = 1500W) (lower-case letters indicate the significance levels ( $p < 0.05$ ) of differences in the results of the four biochars).

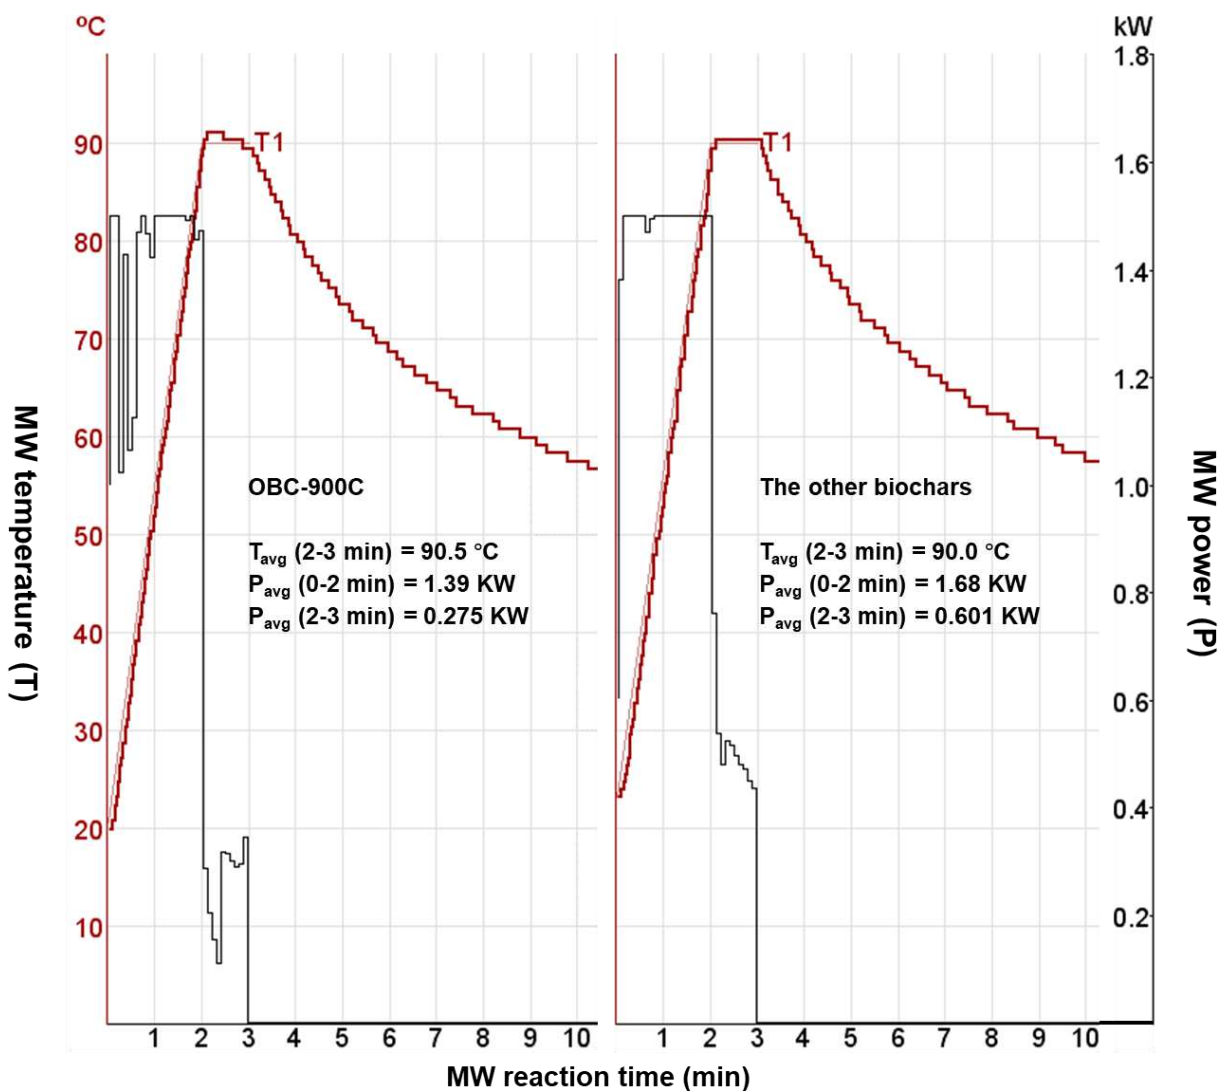

**Fig. 6.** Temperature and power of the microwave (MW) reactor containing the OBC-900 or the other three biochars (Reaction conditions: 2,4-D = 100 mg L<sup>-1</sup>, biochar = 1 g L<sup>-1</sup>, and V<sub>solution</sub> = 20 mL; MW: temperature increased from 23 ± 2 °C to 90 °C in 2 min and hold for 1 min, MW<sub>max</sub> = 1500W).

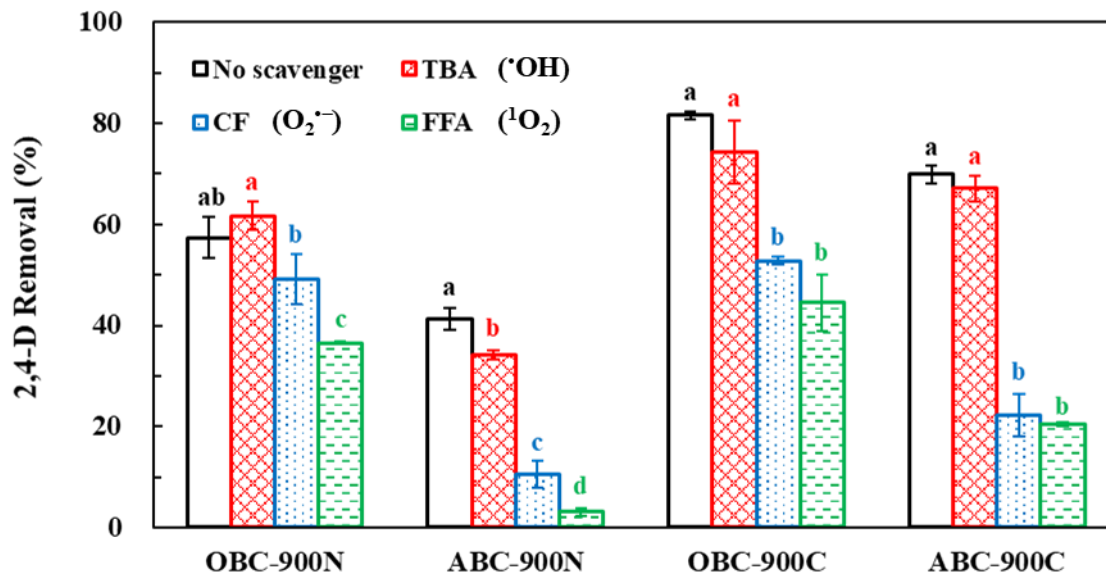


**Fig.7.** Effect of different radical scavengers on the 2,4-D removal efficiency of various biochars after 1-min reaction in the microwave (MW) system (Reaction conditions: 2,4-D = 100 mg L<sup>-1</sup> (0.452 mmol), biochar = 1 g L<sup>-1</sup>, TBA = CF = FFA = 45.2 mmol, V<sub>solution</sub> = 20 mL, and n = 3; MW: temperature increased from 23 ± 2 °C to 90 °C in 2 min and hold for 1 min, MW<sub>max</sub> = 1500W) (lower-case letters indicate the significance levels ( $p < 0.05$ ) of differences in the results of the same biochar).

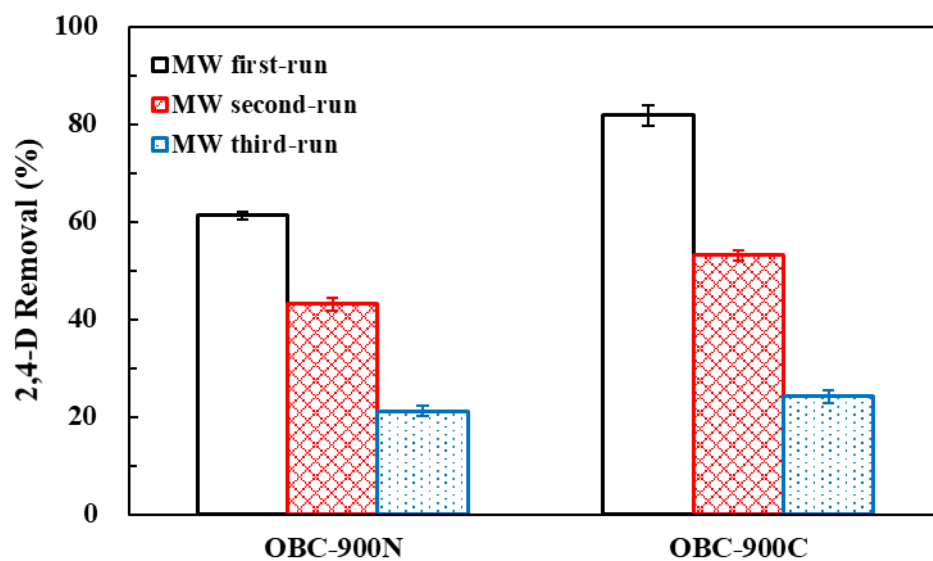


**Fig. 8.** Reusability of the OBC-900N and OBC-900C for 2,4-D removal after 1-min reaction in microwave (MW) system (Reaction conditions: 2,4-D = 100 mg L<sup>-1</sup>, biochar = 1 g L<sup>-1</sup>, V<sub>solution</sub> = 20 mL, and n=3; MW: temperature increased from 23 ± 2 °C to 90 °C in 2 min and hold for 1 min, MW<sub>max</sub> = 1500W).



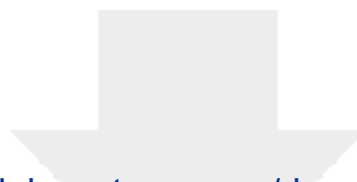

Click here to access/download  
**Supplementary Material**  
CEJ\_MW-Biochar\_2,4-D\_SI.docx



**Declaration of interests**

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

The authors declare the following financial interests/personal relationships which may be considered as potential competing interests: