



Deposited via The University of York.

White Rose Research Online URL for this paper:

<https://eprints.whiterose.ac.uk/id/eprint/164745/>

Version: Accepted Version

Article:

Jenkins, Sarah, Chantrell, Roy W. and Evans, Richard F.L. (2020) Spin wave excitations in exchange biased IrMn/CoFe bilayers. *Journal of Applied Physics*. 033903. ISSN: 1089-7550

<https://doi.org/10.1063/5.0006232>

Reuse

Items deposited in White Rose Research Online are protected by copyright, with all rights reserved unless indicated otherwise. They may be downloaded and/or printed for private study, or other acts as permitted by national copyright laws. The publisher or other rights holders may allow further reproduction and re-use of the full text version. This is indicated by the licence information on the White Rose Research Online record for the item.

Takedown

If you consider content in White Rose Research Online to be in breach of UK law, please notify us by emailing eprints@whiterose.ac.uk including the URL of the record and the reason for the withdrawal request.

Spin wave excitations in exchange biased IrMn/CoFe bilayers

Sarah Jenkins,^{1,*} Roy. W. Chantrell,¹ and Richard F. L. Evans^{1,†}¹Department of Physics, University of York, York, YO10 5DD, UK

Using an atomistic spin model we have simulated spin wave injection and propagation into antiferromagnetic IrMn from an exchange coupled CoFe layer. The spectral characteristics of the excited spin waves have a complex beating behaviour arising from the non-collinear nature of the antiferromagnetic order. We find that the frequency response of the system depends strongly on the strength and frequency of oscillating field excitations. We also find that the strength of excited spin waves strongly decays away from the interfacial layer with a frequency dependent attenuation. Our findings suggest that spin waves generated by coupled ferromagnets are too weak to reverse IrMn in their entirety even with resonant excitation of a coupled ferromagnet. However, efficient spin wave injection into the antiferromagnet is possible due to the non-collinear nature of the IrMn spin ordering.

INTRODUCTION

Spin wave propagation could potentially be used in the next generation of spintronic devices to transport and process information [1]. These new technologies could massively outperform current devices using electric currents as spin wave propagation occurs at very high frequencies and has a very low energy dissipation. One of the most important issues stopping the development of such devices is tuning the ferromagnetic resonance (FMR) frequency [2].

Ferromagnetic resonance was first predicted by Kittel in 1947[3]. The resonance frequency is experimentally measured by placing the magnetic material in a constant field with strength (B_0) and then applying an oscillating field with strength $B_{dr} \exp(i\omega t)$ with an angle of 90° between the fields. When the driving frequency equals the natural precession frequency of the magnetic material the magnetic material will absorb a large amount of energy from the applied oscillating field giving a large precession and a much higher measurable magnetisation. The resonance frequency ω_0 for a bulk-like sample is given analytically by

$$\omega_0 = \frac{\gamma}{2\pi} \sqrt{B_0(B_0 + B_{ani})}, \quad (1)$$

where B_{ani} is the anisotropy field of the material and $\gamma = 1.76 \text{ T}^{-1}\text{s}^{-1}$ is the gyro-magnetic ratio of the electron. In the thin film geometry or elongated nanoparticles this expression is modified to include the shape anisotropy arising from the long range dipole-dipole fields.

The FMR frequencies necessary in magnonic devices are beyond 5GHz, meaning that the FMR has to be increased from the natural resonance state of a material. The FMR frequency can naturally be increased by increasing the uniaxial anisotropy of the material. It has also been shown experimentally that coupling a FM to an AFM increases the anisotropy via the exchange bias effect causing the FMR frequency to increase by up to 10GHz [4]. Although this shift in resonance frequency has been well known for a number of years, the underlying physical causes and effect on the FM are still poorly understood [5]. Exchange bias occurs when a FM is coupled to an AFM, causing a shift in the magnetic hysteresis loop. The shift is proportional to the interface exchange field of the

AFM and caused by a statistical imbalance in the number of spins in each magnetic sublattice[6]. This natural bias field plays the same physical role as anisotropy, while its strength can be manipulated by electrical means [7, 8].

Another aspect of exchange biased systems is the possibility to excite antiferromagnetic spin-wave modes using external magnetic fields. For sufficiently strong coupling the oscillation of the ferromagnet should excite a dynamic response in the antiferromagnet, possibly inducing higher frequency modes of oscillation. Antiferromagnetic materials have a naturally high resonance frequency, typically in the THz range, and so the FM is not resonating at the natural resonance frequency of the AFM. The nature of the resonant coupling and ability to excite spin wave propagation into an antiferromagnet is poorly studied, and of significant practical interest.

In the following paper, atomistic simulations of IrMn/CoFe bilayers is used to study the dynamic response of an exchange biased system to an oscillating magnetic field. The exchange bias is found to increase the magnetic resonance frequency of CoFe by about 8GHz. From this the change in the magnetisation dynamics of CoFe can be observed and the underlying physical mechanisms understood.

METHODOLOGY

We simulate the system dynamics using an atomistic spin model where the energy of the system is defined using the spin Hamiltonian:

$$\mathcal{H} = - \sum_{i<j} J_{ij} \mathbf{S}_i \cdot \mathbf{S}_j - \frac{k_N}{2} \sum_{i \neq j}^z (\mathbf{S}_i \cdot \mathbf{e}_{ij})^2 - \mu_s \sum_i \mathbf{B}(t) \cdot \mathbf{S}_i \quad (2)$$

where \mathbf{S}_i is a unit vector describing the spin direction on CoFe/Mn sites i , k_N is the Néel pair anisotropy constant and \mathbf{e}_{ij} is a unit vector from site i to site j , z is the number of nearest neighbours and J_{ij} is the exchange interaction. The effective exchange interactions (J_{ij}) were limited to nearest and next nearest neighbours for the antiferromagnet [9, 10], and nearest neighbours for the ferromagnet. The interfacial exchange is set to a quarter of the bulk exchange in the antiferromagnet guided by first principles calculations [11, 12].

This is the author's peer reviewed, accepted manuscript. However, the online version of record will be different from this version once it has been copyedited and typeset.

PLEASE CITE THIS ARTICLE AS DOI: 10.1063/5.0006232

Quantity	Material	Symbol	Value	Units
NN Exchange	IrMn	J_{ij}^{nn}	-6.4×10^{-21}	J
NNN Exchange	IrMn	J_{ij}^{nnn}	5.1×10^{-21}	J
Interlayer Exchange	-	J_{ij}	1.5×10^{-21}	J
NN Exchange	CoFe	J_{ij}	4.6×10^{-21}	J
Neel pair anisotropy	IrMn	k_N	-4.2×10^{-22}	J
Anisotropy constant	CoFe	k_u	0	J
Magnetic Moment	IrMn	μ_S	2.6	μ_B
Magnetic Moment	CoFe	μ_S	2.5	μ_B
Gilbert damping	Both	λ	0.05	-

TABLE I. Parameters used in the atomistic spin model. where NN is short for nearest neighbour and NNN is short of next nearest neighbour.

These parameters are outlined in Table 1. We note that we omitted the dipole contribution to the Hamiltonian in our simulations for reasons of computational efficiency. In addition, given the small size and cubic shape of our system the dipole field contribution to the spin wave excitations would be negligible.

We simulate the dynamic behaviour using the stochastic Landau–Lifshitz–Gilbert (sLLG) equation applied at the atomistic level [13, 14] and given by

$$\frac{\partial \mathbf{S}_i}{\partial t} = -\frac{\gamma}{1 + \lambda^2} [\mathbf{S}_i \times \mathbf{B}_{\text{eff}} + \lambda \mathbf{S}_i \times (\mathbf{S}_i \times \mathbf{B}_{\text{eff}})], \quad (3)$$

where λ is the Gilbert damping constant and $|\gamma|$ is the gyromagnetic ratio. The effective field \mathbf{B}_{eff} is calculated from the derivative of the spin Hamiltonian with respect to the local spin moment ($\mathbf{B}_{\text{eff}} = -\mu_S^{-1} \partial \mathcal{H} / \partial \mathbf{S}_i + \mathbf{B}_{\text{th}}^i$) where $\mathbf{B}_{\text{th}}^i = \Gamma(t) \sqrt{\frac{2\lambda k_B T}{\gamma \mu_S \Delta t}}$ and Γ is a 3D random Gaussian distribution. The sLLG equation is integrated using a second order predictor corrector Heun scheme [13]. All simulations were conducted at $T = 0$ K to eliminate thermal noise. The calculations have been carried out using the VAMPIRE software package [13, 15].

The system is oriented with the (111) crystal direction perpendicular to the plane as is common in exchange biased devices, shown schematically in Fig. 1(a). Each of the different coloured spheres represents a different atomic site of the four total in the FCC base crystal unit cell. For the disordered γ -IrMn₃ phase the Ir atoms are randomly allocated to each of the sites (not shown). Periodic boundary conditions are applied along the x, y directions of the system to avoid missing exchange and Néel pair anisotropy bonds at the edges. To set the exchange bias we use an algorithmic setting procedure to determine the orientations of each magnetic sublattice for a given bias direction and pick the configuration with the lowest energy. To verify that the exchange bias is set correctly we perform a slow hysteresis loop with critical damping ($\lambda = 1$) and find a shift of -0.15 T at $T = 0$ K with unconditional stability at zero external applied field, as shown in Fig. 1(b). The exchange bias in our model comes from a statistical imbalance

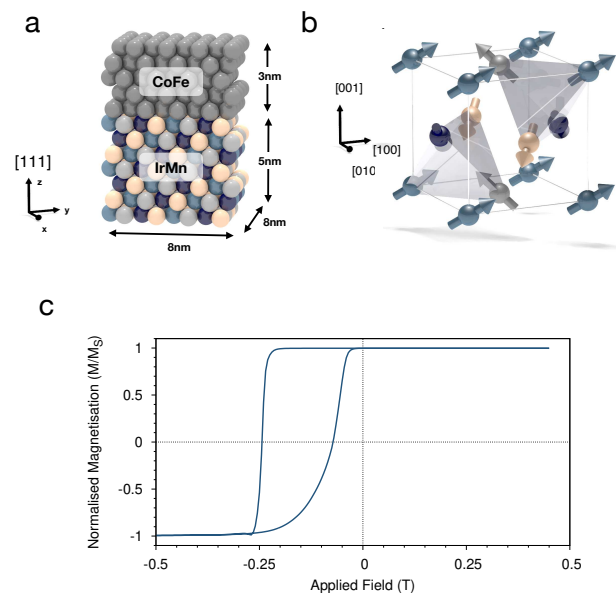


FIG. 1. (Color Online) (a) Schematic diagram of (111) oriented CoFe/ γ IrMn₃ bilayer. (b) Simulated ground state magnetic structure of γ -IrMn₃ (c) Simulated hysteresis loop showing exchange bias field arising from an imbalance of sublattice spins at the interface.[16]

in the number of spins in each magnetic sublattice leading to a small and realistic exchange bias field in comparison with experiments [17, 18]. Our model also correctly reproduces the tetrahedral (3Q) and triangular (T1) ground states for the disordered and ordered IrMn₃ phases respectively [9], shown schematically in Fig. 1(b).

To explore the dynamics of a coupled ferromagnet and antiferromagnet we model a single grain of γ IrMn₃ coupled to an effective ferromagnet with magnetic properties similar to Co₄₀Fe₆₀ with zero magnetocrystalline anisotropy similar to bulk CoFe alloy [19]. At this composition the CoFe alloy has an isotropic point which is useful for magnetic sensors using an exchange biased system to avoid an anisotropic bias in the magnetic orientation of the film. To determine the response of the IrMn/CoFe system to spin wave excitations we simulated a ferromagnetic-resonance type experiment by applying an oscillating magnetic field \mathbf{B}_t along the y -direction perpendicular to the exchange bias direction [20] set along x . Note that here we mostly consider a zero static-field resonance where the external field is set to zero. The time-dependent applied magnetic field is given by

$$\mathbf{B}(t) = \mathbf{B}_0 + \mathbf{B}_{\text{fmr}} \sin(2\pi\omega t) \quad (4)$$

where ω is the driving frequency varied in the range $\omega = 0.1 - 100$ GHz.

In our simulations, we consider only a small sample of a large continuous film, and also include periodic boundary conditions. While we naturally include the exchange bias effect at the single grain level, the small system size means that

This is the author's peer reviewed, accepted manuscript. However, the online version of record will be different from this version once it has been copyedited and typeset.

PLEASE CITE THIS ARTICLE AS DOI: 10.1063/5.0006232

spin waves are naturally limited to an 8 nm wavelength, therefore excluding long wavelength excitations. In general such excitations are important and are driven by inhomogeneities in the magnetic properties in the film, leading to incoherent spin wave excitations. In a polygranular exchange biased system we would expect that the distribution of exchange bias in the film will lead to the appearance of lower energy long-wavelength modes, which are neglected in our present simulations. Such simulations are computationally expensive due to the atomistic nature of our model, and so here we focus on the intrinsic coherent mode excitations in an exchange biased system.

FERROMAGNETIC RESONANCE IN EXCHANGE BIASED SYSTEMS

Initially, we consider the frequency response of CoFe without coupling it to an AFM. We approximate the exchange bias field as a 0.1 T static field along y , $\mathbf{B}_0 = \mu_0 H_{ex}$. We chose this value because it matches the exchange bias calculate in our IrMn/CoFe bilayer. We consider the response of only a single FM spin of CoFe, where the exchange interactions and dipole fields are not included. An oscillating field was applied along the x direction with strength 0.01T and a driving frequency of 10 GHz. We can predict the resonance frequency for our FM using equation 1 giving $\omega_0 = 2.8$ GHz. The response of the ferromagnet is shown in Fig. 2(a). The response shows a sinusoidal oscillation with a single frequency. Unlike in the non-zero field FMR experiment, the resonance monotonically decreases with driving frequency, since low frequencies give sufficient time for the ferromagnetic magnetization to completely align with the field direction. At a 10 GHz driving frequency the ferromagnetic layer shows a relatively weak response perpendicular to the driving field.

The simulated resonance peak is shown in Fig. 2(b), with a large peak at 2.8GHz as expected. The spectrum can be exactly fitted by a Lorentzian curve

$$L(\omega) = \frac{A}{\pi} \frac{0.5f}{(\omega - \omega_0)^2 + (0.5f)^2} \quad (5)$$

where f represents the width of the curve and A its amplitude [20]. Our results for an isolated CoFe layer agree with known analytical results demonstrating the basic correctness of our numerical model. This result would also be representative of a simple micromagnetic calculation, with no simulated degrees of freedom from the antiferromagnet and a simple fixed magnetic field.

We next consider a more realistic situation coupling the CoFe layer to an antiferromagnet with a resulting exchange bias field. Here the simulation is slightly modified, removing the 0.1 T external field (representing the exchange bias) but the oscillating field remained the same with a fixed driving frequency of $\omega = 10$ GHz. The time dependent response of the x -component of the magnetization of the ferromagnetic layer as a function of different oscillating field strengths is shown

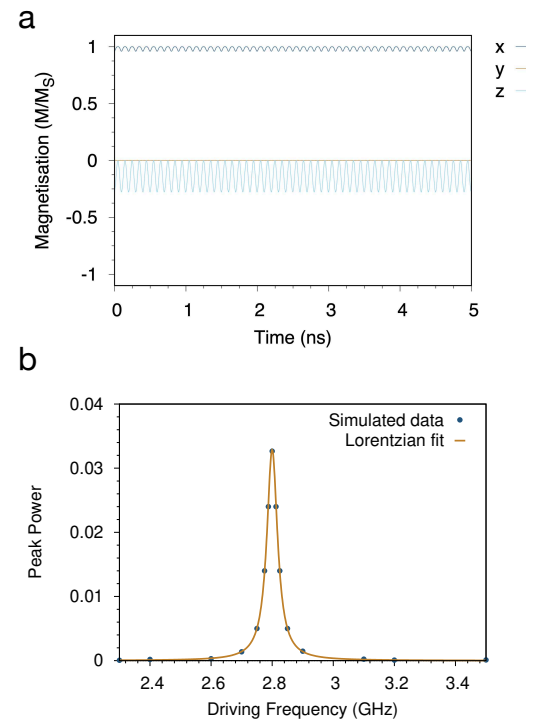


FIG. 2. Ferromagnetic resonance for an isolated layer of CoFe (a) showing a sinusoidal variation of the magnetization components in time. (b) The frequency dependent resonance curve gives a peak with a driving frequency of 2.8GHz as predicted from equation 1, and a fit to a Lorentzian curve given by Eq. 5.

in Fig 3 (left) and the associated Fourier transform (right). The coupling of the ferromagnetic layer to the γ -IrMn₃ film leads to a much richer time dependent behaviour in the case of strong excitations, and large excursions of the magnetization. The Fourier transforms clearly show the evolution of a single main frequency component in Fig 3(a) to a larger 10GHz frequency response with a superimposed high frequency component in Fig 3(b) to a complex multi-frequency response in Fig 3(c). The complex response of the system to different excitation field strengths suggests that the response of an exchange biased system is not at all trivial. Indeed, for the strongest excitation field of $B_{fmr} = 0.1$ T shown in Fig 3(c), a beating-like behaviour of the magnetization is observed.

At this point it is useful to consider the atomic origin of the exchange bias effect in CoFe/IrMn systems, caused by a natural imbalance in the number of interface spins in one of the four magnetic sublattices. When these interface spins are coupled to a neighbouring ferromagnet by the exchange interaction the ferromagnet develops a strong preference for aligning with the net interface magnetization, which is also strongly exchange coupled to the bulk of the antiferromagnet. While the exchange bias effect on the ferromagnet is well understood, the reciprocal effect on the antiferromagnet is often neglected. However, the static evolution of the reversible and irreversible components of the interfacial spins is known to

This is the author's peer reviewed, accepted manuscript. However, the online version of record will be different from this version once it has been copyedited and typeset.

PLEASE CITE THIS ARTICLE AS DOI: 10.1063/5.0006232

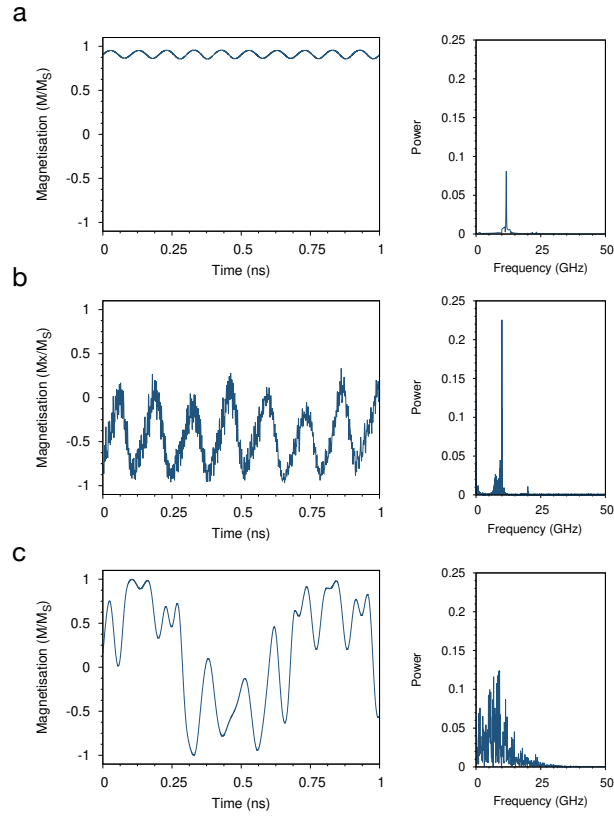


FIG. 3. Response of the ferromagnetic layer to a 10 GHz driving field frequency with an applied field strength of (a) $B_{\text{fmr}} = 0.01$ T, (b) $B_{\text{fmr}} = 0.05$ T (c) and $B_{\text{fmr}} = 0.1$ T. The time data is offset by $t = 50$ ns after the simulation is started to remove transient effects.

follow the orientation of the ferromagnet [17]. Given the different atomic environment of the interfacial spins, it is reasonable to assume that the natural resonance frequency of those spins is quite different from the bulk of the ferromagnetic layer, and also from the bulk antiferromagnet. We can then consider our exchange bias system as a system of coupled oscillators with different natural frequencies. This naturally explains the appearance of complex beating and also its semi-chaotic behaviour in time. The natural frequency of optical excitations of antiferromagnets is in the THz range, and so here we only excite coherent (acoustic) modes in the antiferromagnet, where the 3Q ground state is rotated coherently in space, equivalent to rotation of a ferromagnet in an anisotropy field. Of course, the differing properties of the interface and bulk of the antiferromagnetic layer mean that the response of the antiferromagnet is not entirely coherent, contributing to the broad frequency response in the strongly excited case. There may also be contributions to the beating behaviour due to the finite size of the simulated grain, leading to standing spin waves in the system. However, this would be peculiar to non-collinear antiferromagnets as no such effects are seen in ferromagnets where strong exchange interactions

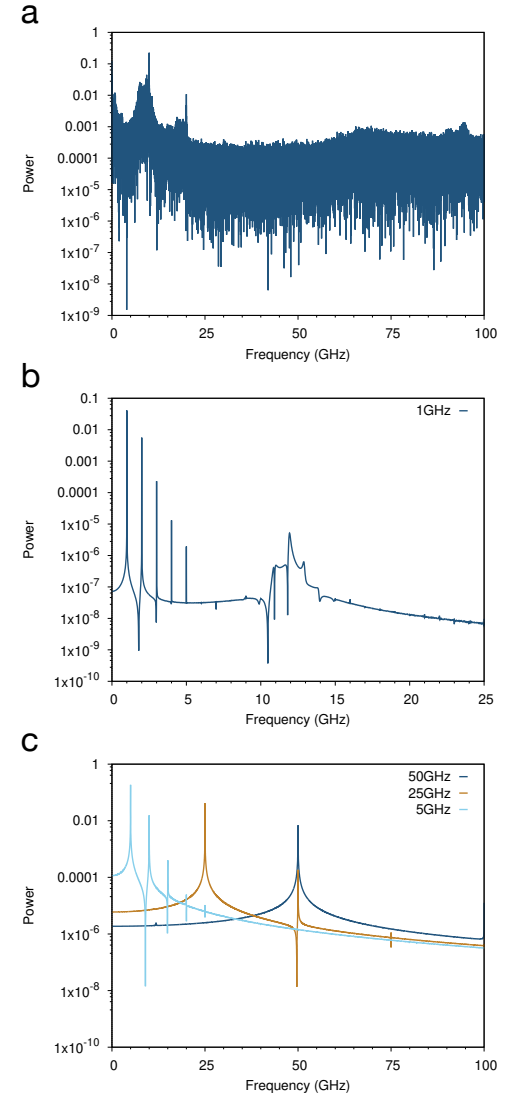


FIG. 4. Response of the ferromagnetic layer to a 0.05T oscillating field with a driving frequencies of (a) 10GHz, (b) 1GHz and (c) 5,25 and 50GHz. The power is calculated from a Fourier transform of the time dependent magnetization after 50 ns, plotted on a logarithmic scale to accentuate the different excited frequencies.

give a uniform response. Further optical FMR measurements may yield observations of more complex frequency responses in the case of high frequency excitations [21]. **We note that chaotic-like dynamic behaviour has also been observed before in purely ferromagnetic systems [22] under certain excitation conditions. Under the excitation conditions simulated here this never appears for the purely ferromagnetic case, and so the complex dynamics are a clear result of the coupling to the antiferromagnet.**

We now consider the frequency dependence of the response of the ferromagnet for a fixed driving field strength of $|\mathbf{B}_{\text{fmr}}| = 0.05$ T, shown in Fig. 4. As with the field strength dependent response, there is a complex frequency dependence of

This is the author's peer reviewed, accepted manuscript. However, the online version of record will be different from this version once it has been copyedited and typeset.

PLEASE CITE THIS ARTICLE AS DOI: 10.1063/5.0006232

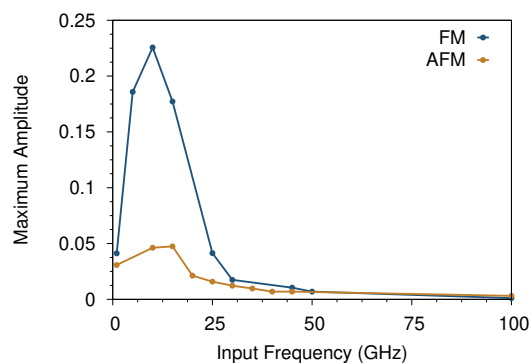


FIG. 5. Comparative plot of the peak power spectral density for the FM and for the AFM interface (0nm from the interface) as a function of different input driving frequencies for CoFe/ γ -IrMn₃ with 0.05 T driving field.

the power. For a driving frequency $\omega = 10$ GHz close to resonance, the frequency response is extremely broad, with moderate excitations at all frequencies, and a broad peak around 10 GHz. In contrast, an off-resonant excitation at $\omega = 1$ GHz shows a clearer spectral character, with a principle peak at the driving frequency, and an exponential decrease in the power at harmonic frequencies at 2, 3, 4 and 5 GHz. The presence of harmonics gives a square-wave character to the time series, but the logarithmic decay of the power of the higher harmonics makes this a weak effect giving a small asymmetry to the single frequency sine wave. There is an additional weak frequency component in the 10-14 GHz range close to the natural resonance which is not visually apparent but shows weak excitation of the antiferromagnet at the 1 GHz driving frequency. For higher frequency driving fields at 5-50 GHz, the harmonic components persist at integer multiples of the driving frequency, with the same logarithmic drop-off of the power with increasing harmonics, characteristic of a near-undetectable asymmetry in the $m_x(t)$ response. Overall our data suggests that the complex frequency response and beating effects only occur when the driving frequency is only close to the resonance frequency of around 10 GHz.

The frequency dependence of the peak power (principal peak) as a function of the driving frequency is shown in Fig. 5 for both the FM and AFM at the interface, showing the strength of the principal excitation as well as the transmission of power into the interfacial layer of the AFM. The power in the FM shows a broad peak in the vicinity of the resonance frequency around 10 GHz, but with a much larger linewidth than seen for the isolated layer in Fig. 2. The increase in line width is indicative of an increase in damping, as previously seen in exchange biased systems [23]. The excitation peak power in the interfacial AFM layer follows a similar trend to the FM, though with a much broader peak, indicating the propagation of spin waves into the AFM across the sub-20 GHz range of excitation frequencies.

In exchange-biased systems the exchange bias field is de-

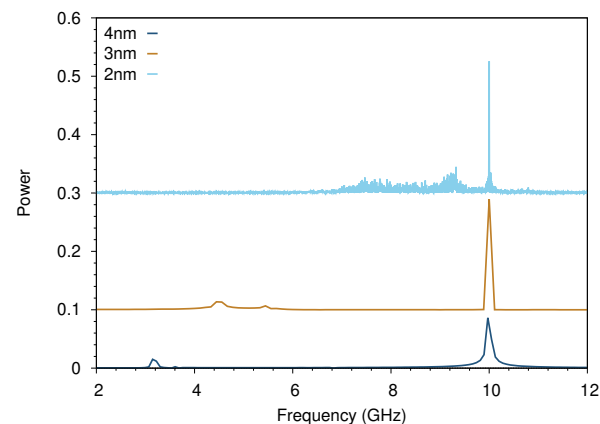


FIG. 6. Thickness dependence of the excited spin wave spectrum for a 0.05T oscillating field at a driving frequency of 10 GHz. With increasing film thickness the spin wave spectrum develops a pure spectral character to to the decreased strength of the coupling.

pendent on the thickness of the FM layer, as the effect is purely interfacial origin, at least for thin films where exchange coupling dominates and the FM behaves coherently. In Fig. 6 we present the calculated power spectrum for a 0.05T oscillating field at a driving frequency of 10 GHz for different ferromagnet thicknesses. As expected, there is a strong peak at the driving frequency of $\omega = 10$ GHz. However, the complex character of the frequency response of the FM for the 2 nm thick film is strongly suppressed. As the exchange bias field is reduced with increasing FM thickness, this leads to weaker coupled excitations. The principal peak at 10 GHz systematically decreases in height and increases in breadth with increasing film thickness, and becomes spectrally cleaner at intermediate off-resonant frequencies, showing an absence of significant beating. In addition a weak secondary peak appears at 3.3 GHz and 4.5 GHz for 3 nm and 4 nm thicknesses respectively that is clearly thickness dependent, which could indicate a shift of the natural resonance of the system. Overall this suggests that with increasing thickness the coupling between the FM and AFM reduces the strength of excitations and with it a less complex coupled excitation.

EXCITATION OF SPIN WAVES IN THE ANTI-FERROMAGNET

The coupling of the ferromagnet to the antiferromagnet naturally leads to the propagation of spin waves into the IrMn layer, known as evanescent AFM spin wave modes [24]. The interfacial nature of exchange bias coupling naturally leads to a stronger excitation at the interfacial layer, while the strong magnetic anisotropy in IrMn reduces the strength of excitations away from the interface. The time-dependent response of the dominant magnetic sublattice at the interface (responsible for the exchange bias) and bottom of the IrMn layer is shown in Fig. 7. The data show a similar characteristic beating

This is the author's peer reviewed, accepted manuscript. However, the online version of record will be different from this version once it has been copyedited and typeset.

PLEASE CITE THIS ARTICLE AS DOI: 10.1063/5.0006232

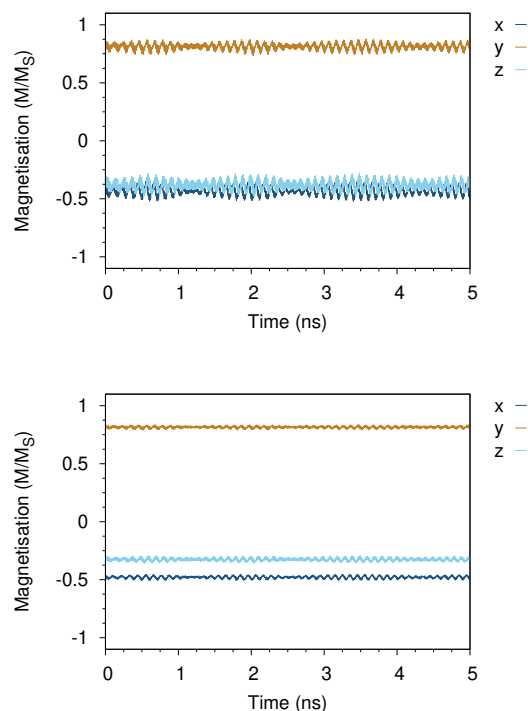


FIG. 7. Time dependent sublattice magnetizations of the dominant antiferromagnetic sublattice (responsible for the exchange bias) at the interface (top) and bottom of the IrMn layer (bottom) for a driving frequency of 10 GHz. The time data is offset by $t = 50$ ns after the simulation is started to remove transient effects. Color Online.

behaviour but much weaker than observed for the ferromagnet, even at the interfacial layer in direct contact with it. This suggests that the coupling between the antiferromagnet and ferromagnet is far from rigid despite the strong exchange bias field and unidirectional coupling, and it seems that high frequency excitations allow for large excursions of the ferromagnet from the biasing antiferromagnet. Naturally the IrMn moments are highly stable due to their high magnetic anisotropy.

To further explore the spectral characteristics of the response of the antiferromagnet we computed a Fourier transform of the equilibrated signal taken over a period of 100 ns and shown in Fig. 8 for the dominant IrMn magnetic sublattice at (0 nm) and far away (3.6 nm) from the interface. The spectral characteristics of the antiferromagnetic sublattice at the different locations are very similar, exhibiting a principal peak at the 10 GHz driving frequency, but also with significant peaks with significant bandwidth. In particular there are strong oscillations in the 100 GHz range characteristic of the naturally fast dynamics of antiferromagnetic materials. In the vicinity of the driving frequency at 10 GHz, the spectral power density is approximately half as strong for the bottom IrMn layer compared to the interface, while in the 100 GHz region this is reduced to approximately 1/3. This suggests a natural frequency dependence of the attenuation of spin waves propagating in the antiferromagnet, with higher frequency modes

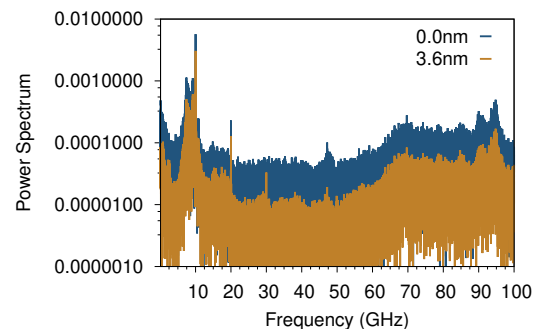


FIG. 8. The frequency spectra for the AFM at the interface (0.0 nm from the interface) and at the edge (3.6 nm from the interface) obtained from the Fourier transform of the FMR data. Color Online.

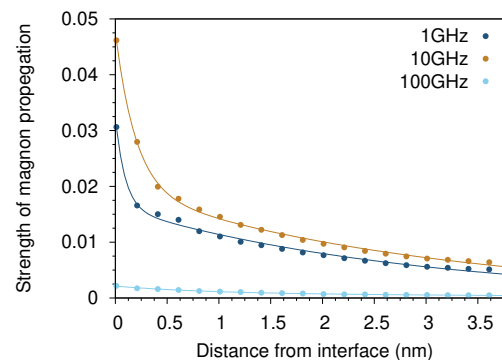


FIG. 9. Layerwise response of IrMn. The maximum response of a sublattice for each layer of the AFM. The highest amplitude frequency response occurs at zero distance from the interface. As the distance from the interface increases the amplitude decreases. This happens for all input frequencies. Color Online.

being dissipated more strongly. Interestingly the data show a significant coupling of spin waves between the ferromagnet and antiferromagnet, and similar behaviour has been observed in recent experiments for the FeMn/Py system [25] with broad implications for tuning the dynamic response of materials in the 5-200 GHz frequency range.

Although the excited spin waves in the antiferromagnet have an intrinsic frequency dependent transmission coefficient, the coupled system itself also has a natural resonance at around 10 GHz. Thus, at the couple resonance frequency the interfacial spins are strongly excited, leading to larger excitations in the antiferromagnet. To investigate the propagation of spin waves into the antiferromagnet, we have computed the strength of excitation as a function of different driving frequencies. The decay of the spin wave magnitude as a function of distance from the interface and driving frequency is shown in Fig. 9. The magnitude of the excitations shows an exponential-like decay away from the interface but with a slow tail suggesting that spin waves excited in the antiferromagnet will propagate a significant distance before decaying to an un-

Frequency (GHz)	Decay length (nm)	
	b_1	b_2
1	0.356 ± 0.016	10.673 ± 1.812
10	0.333 ± 0.013	5.115 ± 0.263
100	0.179 ± 0.094	1.089 ± 0.237

TABLE II. Fitted frequency decay lengths in the antiferromagnet from Eq. 6 for different excitation frequencies.

detectable level, perhaps up to tens of nanometres. To characterise the frequency dependence of the decay of spin waves in the antiferromagnet we fit a general two-term exponential function of the form

$$f(x) = A_1 \exp(-b_1 x) + A_2 \exp(-b_2 x) \quad (6)$$

where A_1, A_2, b_1 and b_2 are fitting parameters. The fitted characteristic decay lengths are shown in Tab. II. The decays are poorly fitted with a single exponential, indicating two important length scales associated with the decay of the spin waves. The strongest excitation is clearly in the 10 frequency GHz region, while 1 GHz and 100 GHz are both weaker being off-resonant. From the fitted values it is clear the near interface decay is extremely rapid in all three cases, with a characteristic length scale of around 3 Å, or approximately one atom. In contrast the long-distance decay is more strongly dependent on the the driving frequency, showing a systematic reduction of the propagation distance with increasing driving frequency. These two characteristic lengthscales can then be associated with two different physical phenomena. The short-range decay is due to the interfacial atomic layer where there is a large reduction of magnetic anisotropy in the IrMn due to the missing exchange and pair-anisotropy bonds. This allows for relatively large excursions of the coupled interfacial spins under ferromagnetic resonance, as well as spins in the IrMn sublayer that are directly exchange coupled to the interface spins. The second characteristic decay is then due to the propagation of excitations into the bulk of the antiferromagnet, where the exchange coupling and magnetic anisotropy are both large. Here, the excitations are coherent in nature, exciting collective (acoustic) oscillations of the antiferromagnetic ground state structure. Here lower frequency excitations are preferred since the response of the antiferromagnet becomes quasi-static, while at higher driving frequencies the antiferromagnet is less able to respond to the higher frequency oscillations. This explains the much longer decay length for the off-resonant excitation at 1 GHz, even though the response of the the ferromagnet is weaker. This supports the idea that the frequency overlap of the ferromagnet and antiferromagnet response is essential in correctly propagating spin waves into a coupled antiferromagnet [25]. The resonance in the 10 GHz range is close to reported experimental values for a similar material system [26].

CONCLUSIONS

In conclusion, we have performed atomistic modelling of spin wave injection and propagation into IrMn from an exchange biased CoFe-bilayer. We have found that the spectral characteristics of the excited spin waves have a complex behaviour and systematic beating arising from the non-collinear nature of the antiferromagnetic order, behaving as coupled oscillators when strongly excited. The strength of excited evanescent spin waves decays strongly away from the interfacial layer but with a slow tail, and high frequency waves in the 100 GHz range are more strongly attenuated. Our results suggest that efficient spin wave injection into IrMn is possible and that the combined resonance frequency is significantly higher than for the isolated ferromagnetic layer. Furthermore, the non-collinear nature of the antiferromagnetic order enables the efficient excitation of antiferromagnetic spin waves in the 1-20 GHz frequency range which may enable new applications and devices with a tunable frequency response. Here we neglect the role of long-range dipole-dipole interactions on the computed spin wave spectra, instead focusing on the fundamental small-scale interactions in an exchange biased system. For extended systems the dipole-dipole interactions are expected to make an important contribution and will be necessary for a detailed comparison with experimental data. Future work will consider the effects of temperature, long-distance decay of the generated spin waves and additional composition and ordering effects.

AUTHOR CONTRIBUTIONS

SJ performed the atomistic simulations, analysed and plotted the data. SJ and RE drafted the paper. All authors contributed to the writing of the manuscript and interpretation of results.

DATA AVAILABILITY

The data that support the findings of this study are available from the corresponding author upon reasonable request.

ACKNOWLEDGMENTS

We gratefully acknowledge the provision of computer time made available on the VIKING cluster, a high performance compute facility provided by the University of York. The authors are grateful to Vincent Baltz for insightful discussions.




* sarah.jenkins@york.ac.uk



† richard.evans@york.ac.uk

This is the author's peer reviewed, accepted manuscript. However, the online version of record will be different from this version once it has been copyedited and typeset.


PLEASE CITE THIS ARTICLE AS DOI: 10.1063/1.50006232

- [1] A. V. Chumak, V. I. Vasyuchka, A. A. Serga, and B. Hillebrands, Magnon spintronics 10.1038/NPHYS3347 (2015).
- [2] J. B. Mohammadi, J. M. Jones, S. Paul, B. Khodadadi, C. K. A. Mewes, T. Mewes, and C. Kaiser, Broadband ferromagnetic resonance characterization of anisotropies and relaxation in exchange-biased IrMn/CoFe bilayers, *PHYSICAL REVIEW B* **95**, 64414 (2017).
- [3] C. Herring, C. Kittel, B. Telephorie, M. Hili, and E. Jersey, *On the Theory of Spin Waves in Ferromagnetic Media*, Tech. Rep.
- [4] N. N. Phuoc, L. T. Hung, and C. K. Ong, Ultra-high ferromagnetic resonance frequency in exchange-biased system, *Journal of Alloys and Compounds* 10.1016/j.jallcom.2010.07.064 (2010).
- [5] J.-G. Hu, G.-J. Jin, and Y.-Q. Ma, Ferromagnetic resonance and exchange anisotropy in ferromagnetic/antiferromagnetic bilayers, *Journal of Applied Physics* **91**, 2180 (2002).
- [6] S. Jenkins, R. W. Chantrell, T. J. Klemmer, and R. F. Evans, Magnetic anisotropy of the noncollinear antiferromagnet IrMn₃, *Physical Review B* **100**, 10.1103/PhysRevB.100.220405 (2019).
- [7] S. Fukami, C. Zhang, S. DuttaGupta, A. Kurenkov, and H. Ohno, Magnetization switching by spin-orbit torque in an antiferromagnet-ferromagnet bilayer system, *Nature Materials* **15**, 535 (2016).
- [8] P.-H. Lin, B.-Y. Yang, M.-H. Tsai, P.-C. Chen, K.-F. Huang, H.-H. Lin, and C.-H. Lai, Manipulating exchange bias by spin-orbit torque, *Nature Materials* **18**, 335 (2019).
- [9] S. Jenkins and R. F. L. Evans, Enhanced finite size and interface mixing effects in iridium manganese ultra thin films, *Journal of Applied Physics* **124**, 152105 (2018).
- [10] S. Jenkins, R. W. Chantrell, T. J. Klemmer, and R. F. L. Evans, Magnetic anisotropy of the noncollinear antiferromagnet irmn₃, *Phys. Rev. B* **100**, 220405 (2019).
- [11] L. Szunyogh, L. Udvardi, J. Jackson, U. Nowak, and R. Chantrell, Atomistic spin model based on a spin-cluster expansion technique: Application to the IrMn₃/Co interface, *Physical Review B* **83**, 024401 (2011).
- [12] L. Szunyogh, B. Lazarovits, L. Udvardi, J. Jackson, and U. Nowak, Giant magnetic anisotropy of the bulk antiferromagnets IrMn and IrMn₃ from first principles, *Physical Review B - Condensed Matter and Materials Physics* **79**, 1 (2009).
- [13] R. F. Evans, W. J. Fan, P. Chureemart, T. A. Ostler, M. O. Ellis, and R. W. Chantrell, Atomistic spin model simulations of magnetic nanomaterials, *Journal of Physics Condensed Matter* **26**, 10.1088/0953-8984/26/10/103202 (2014).
- [14] M. O. A. Ellis, R. F. L. Evans, T. A. Ostler, J. Barker, U. Atxitia, O. Chubykalo-Fesenko, and R. W. Chantrell, The Landau-Lifshitz equation in atomistic models, *Low Temperature Physics* **41**, 705 (2015), <https://doi.org/10.1063/1.4930971>.
- [15] VAMPIRE software package v5 available from <https://vampire.york.ac.uk/>, (2020).
- [16] S. Jenkins, A. Meo, L. E. Elliott, S. K. Piotrowski, M. Bapna, R. W. Chantrell, S. A. Majetich, and R. F. L. Evans, Magnetic stray fields in nanoscale magnetic tunnel junctions, *Journal of Physics D: Applied Physics* **53**, 044001 (2019).
- [17] H. Ohldag, A. Scholl, F. Nolting, E. Arenholz, S. Maat, A. T. Young, M. Carey, and J. Stöhr, Correlation between Exchange Bias and Pinned Interfacial Spins, *Physical Review Letters* **91**, 017203 (2003).
- [18] K. O'Grady, L. E. Fernandez-Outon, and G. Vallejo-Fernandez, A new paradigm for exchange bias in polycrystalline thin films, *Journal of Magnetism and Magnetic Materials* **322**, 883 (2010).
- [19] R. S. Sundar and S. C. Deevi, Soft magnetic fcco alloys: alloy development, processing, and properties, *International Materials Reviews* **50**, 157 (2005), <https://doi.org/10.1179/174328005X14339>.
- [20] J. R. Massey, K. Matsumoto, M. Strungaru, R. C. Temple, T. Higo, K. Kondou, R. F. L. Evans, G. Burnell, R. W. Chantrell, Y. Otani, and C. H. Marrows, Phase boundary exchange coupling in the mixed magnetic phase regime of a pd-doped ferri epilayer, *Phys. Rev. Materials* **4**, 024403 (2020).
- [21] R. J. Hicken, A. Barman, V. V. Kruglyak, and S. Ladak, Optical ferromagnetic resonance studies of thin film magnetic structures, *Journal of Physics D: Applied Physics* **36**, 2183 (2003).
- [22] A. Borisov, B. Filippov, V. Zverev, and B. Rubinstein, On the magnetization chaotic dynamics in the ferromagnetic resonance region, *Journal of Magnetism and Magnetic Materials* **110**, 202 (1992).
- [23] B. K. Kuanr, R. E. Camley, and Z. Celinski, Exchange bias of nio/nife: Linewidth broadening and anomalous spin-wave damping, *Journal of Applied Physics* **93**, 7723 (2003), <https://doi.org/10.1063/1.1557964>.
- [24] R. Khymyn, I. Lisenkov, V. S. Tiberkevich, A. N. Slavin, and B. A. Ivanov, Transformation of spin current by antiferromagnetic insulators, *Phys. Rev. B* **93**, 224421 (2016).
- [25] D. M. Polishchuk, T. I. Polek, V. Y. Borynskyi, A. F. Kravets, A. I. Tovstolytkin, and V. Korenivski, Coupled ferromagnetic-resonance modes and frequency enhancement in py/femn bilayers under magnetic proximity effect (2019), arXiv:1906.11688.
- [26] J. Beik Mohammadi, J. M. Jones, S. Paul, B. Khodadadi, C. K. A. Mewes, T. Mewes, and C. Kaiser, Broadband ferromagnetic resonance characterization of anisotropies and relaxation in exchange-biased irmn/cofe bilayers, *Phys. Rev. B* **95**, 064414 (2017).

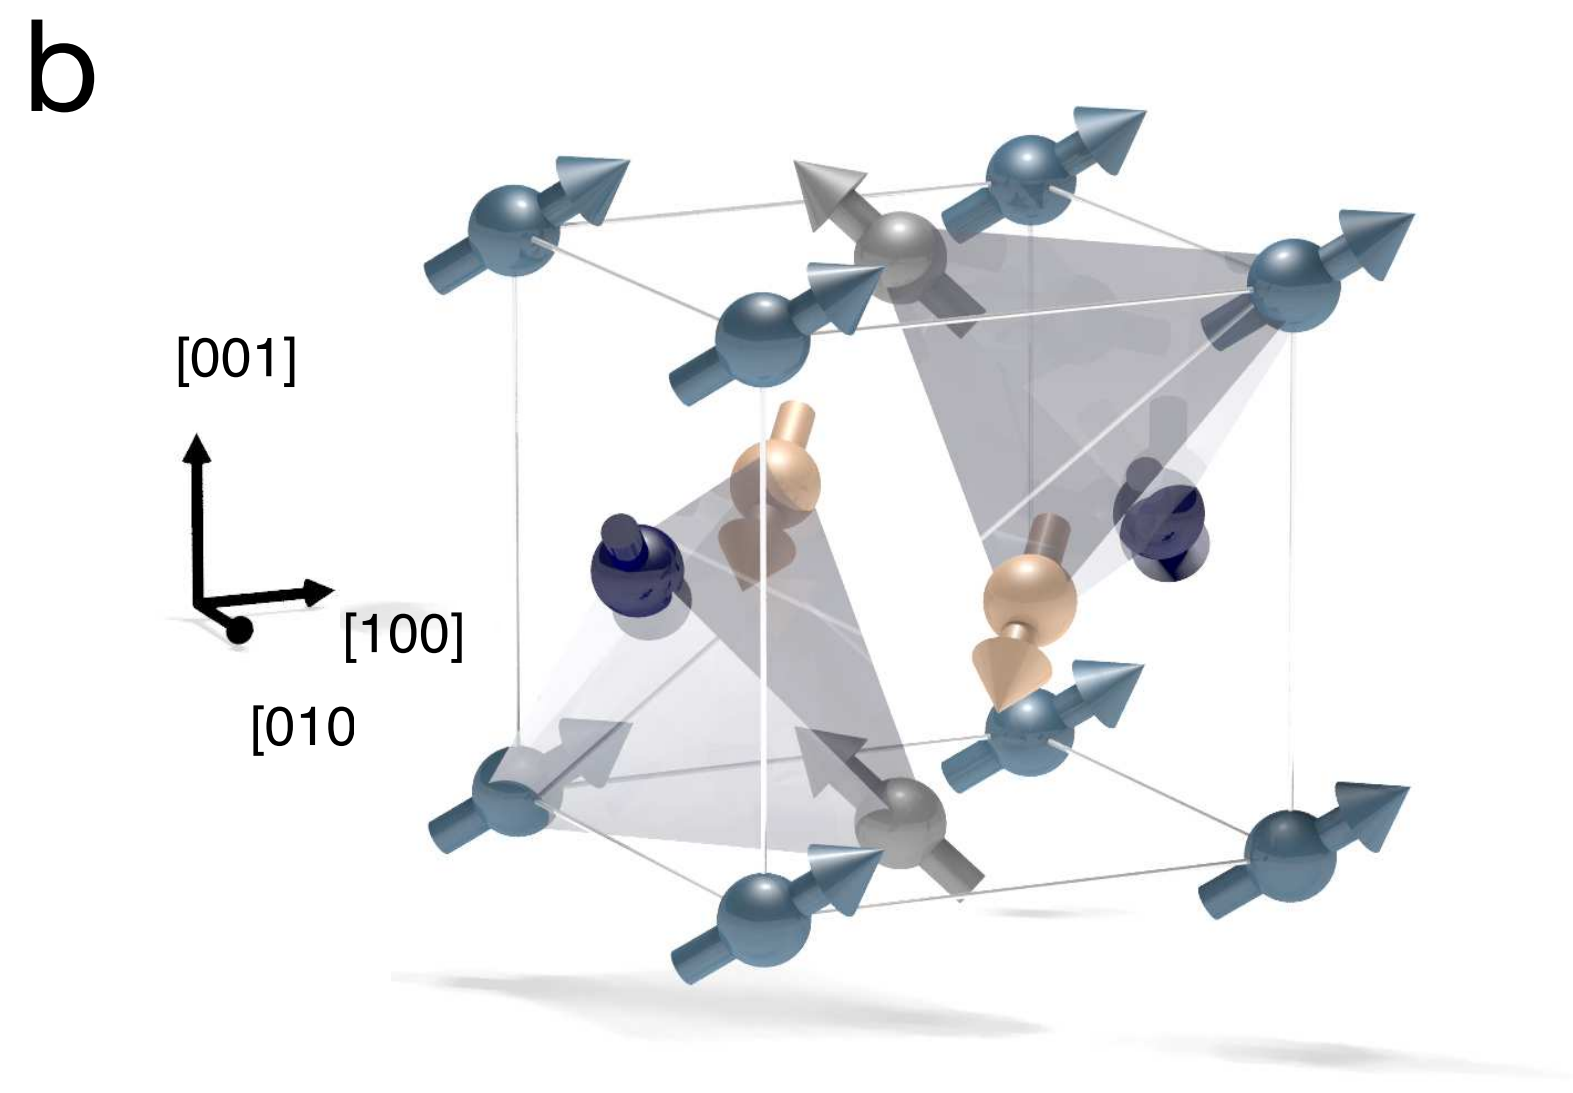
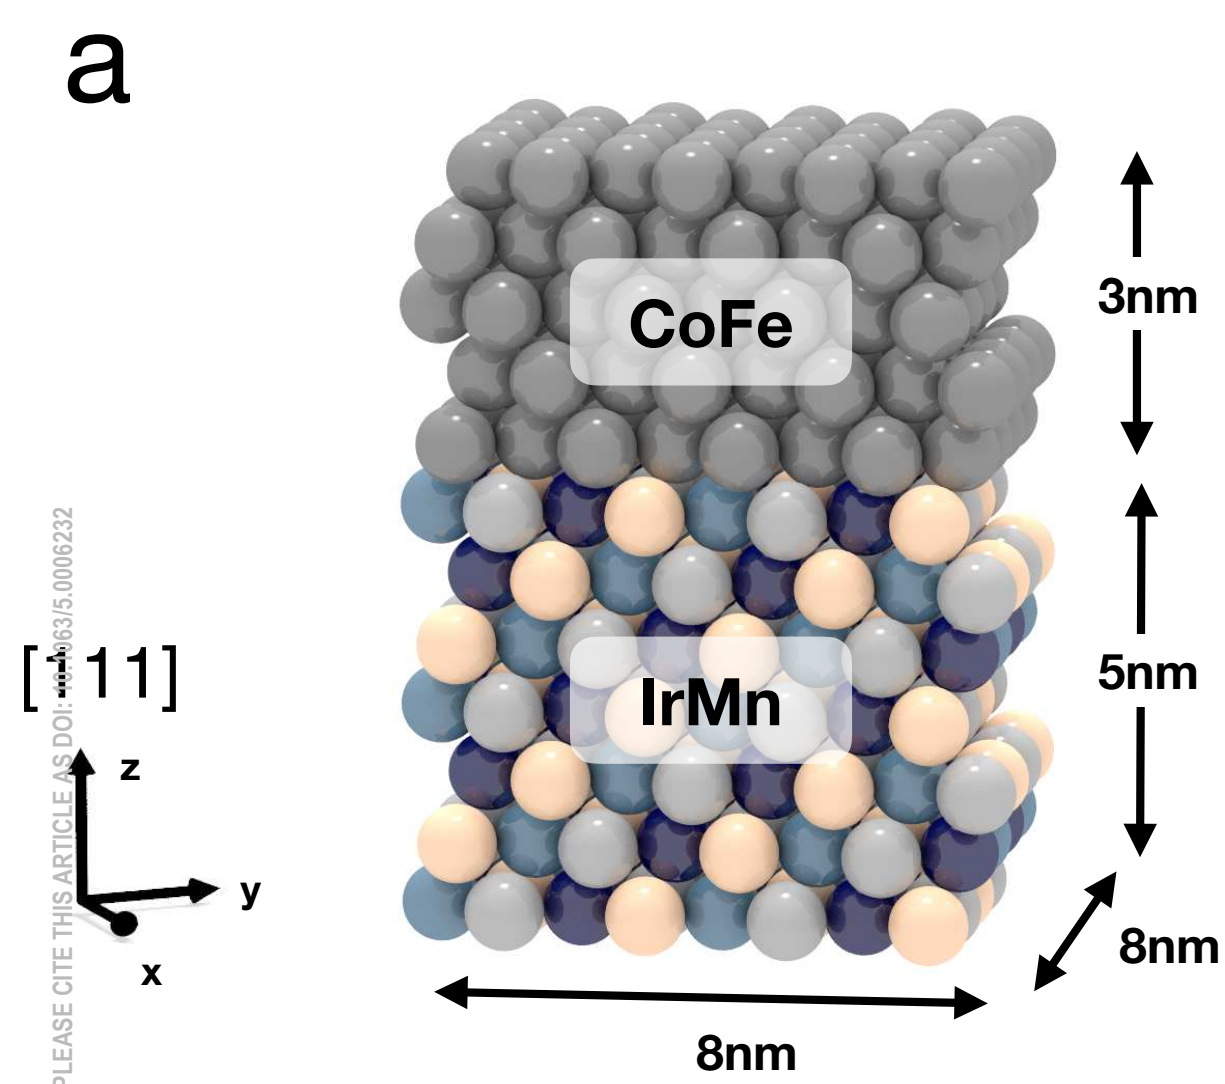
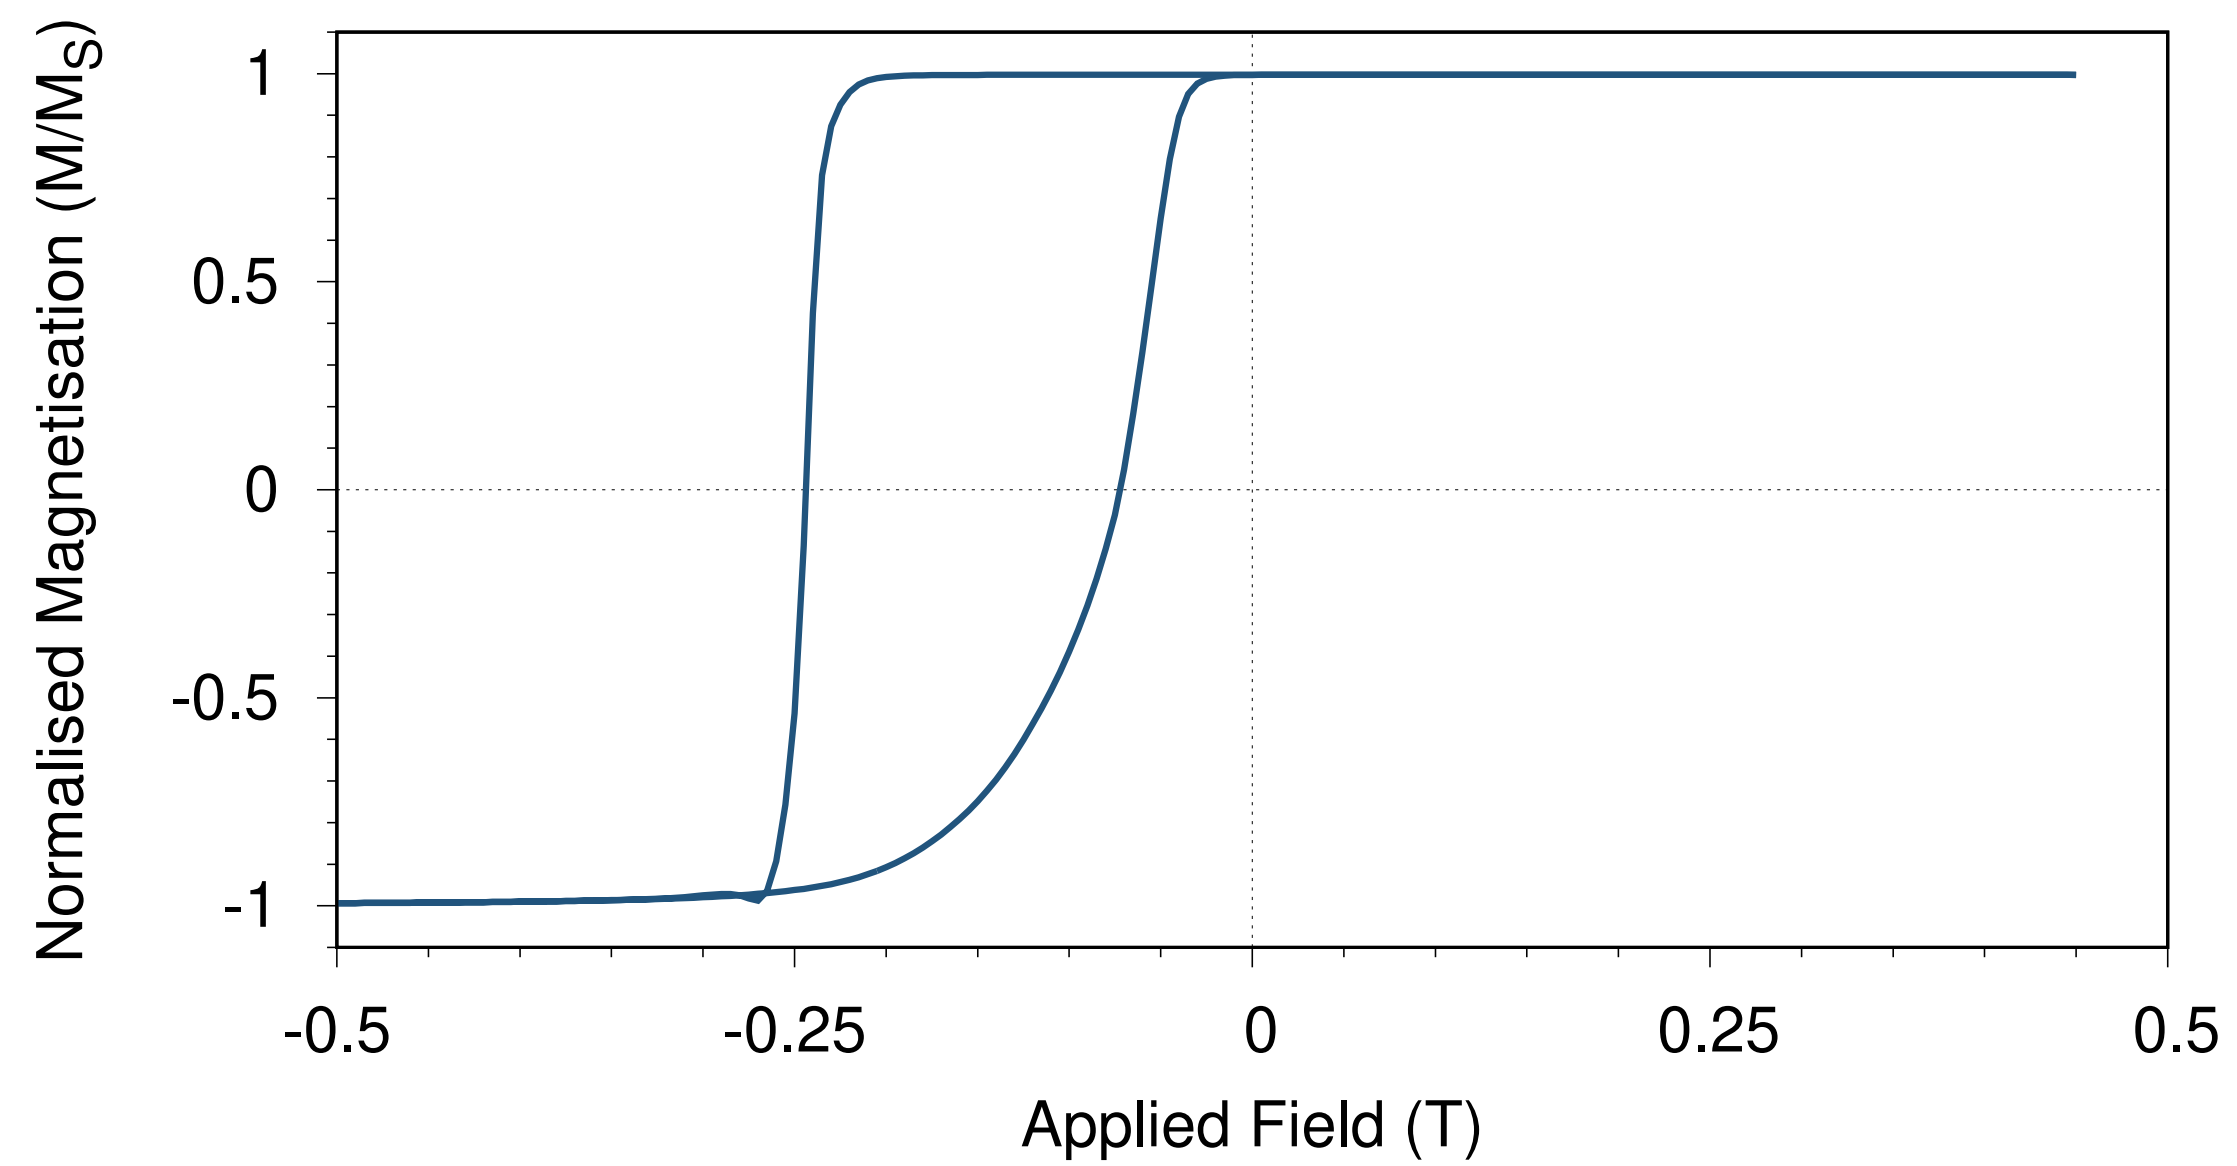
**c**

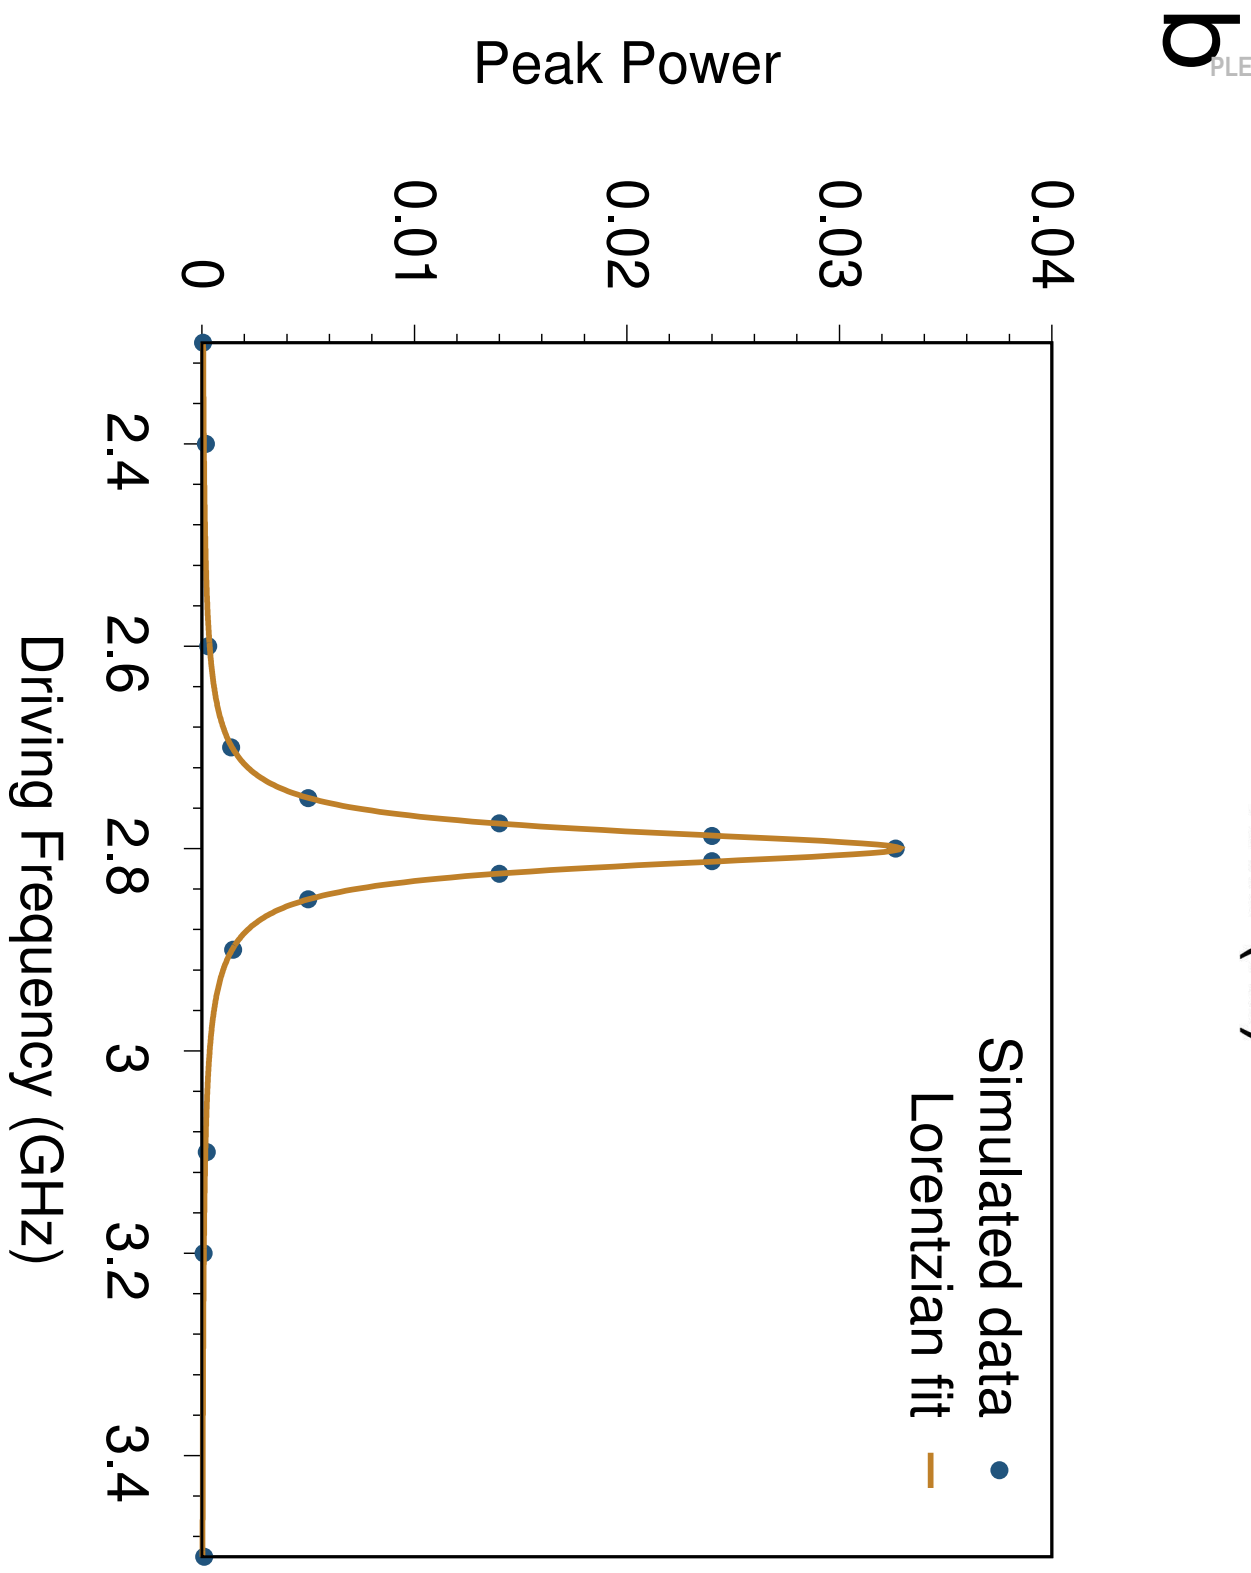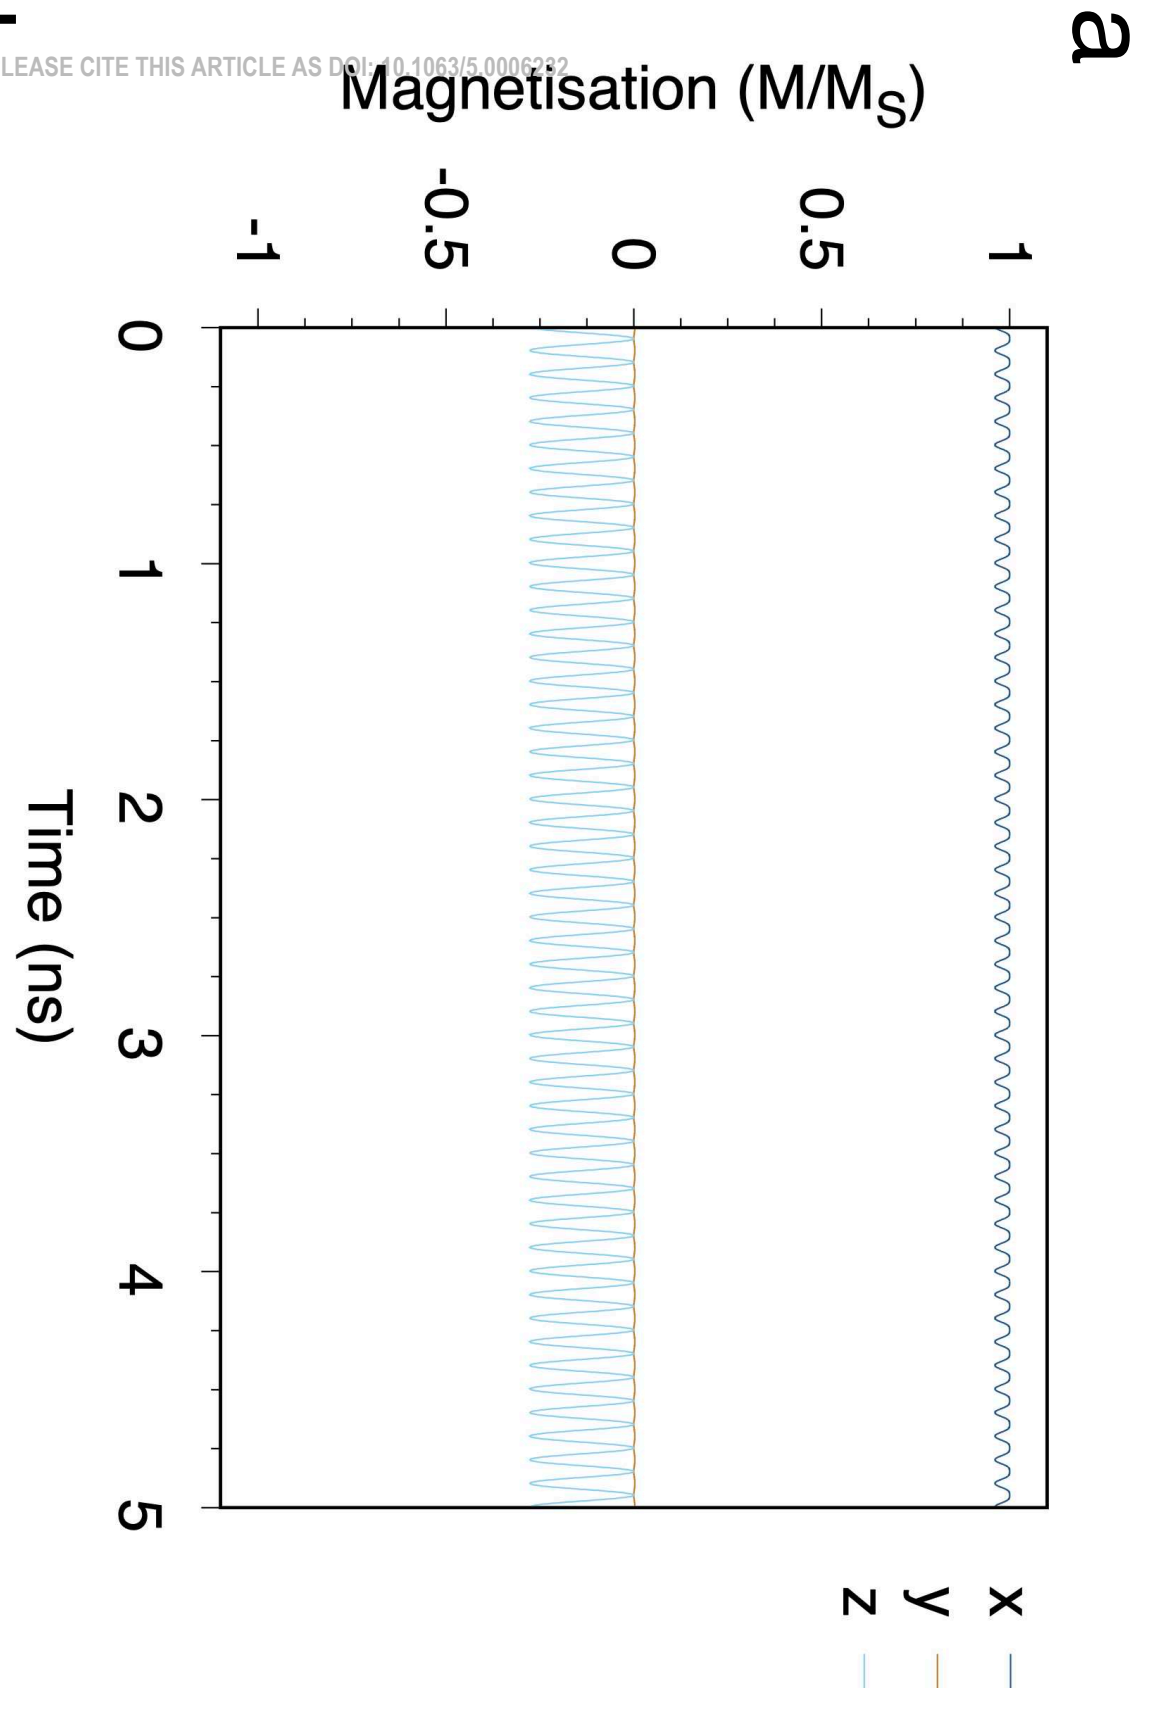

PLEASE CITE THIS ARTICLE AS DOI: 10.1063/5.0006232

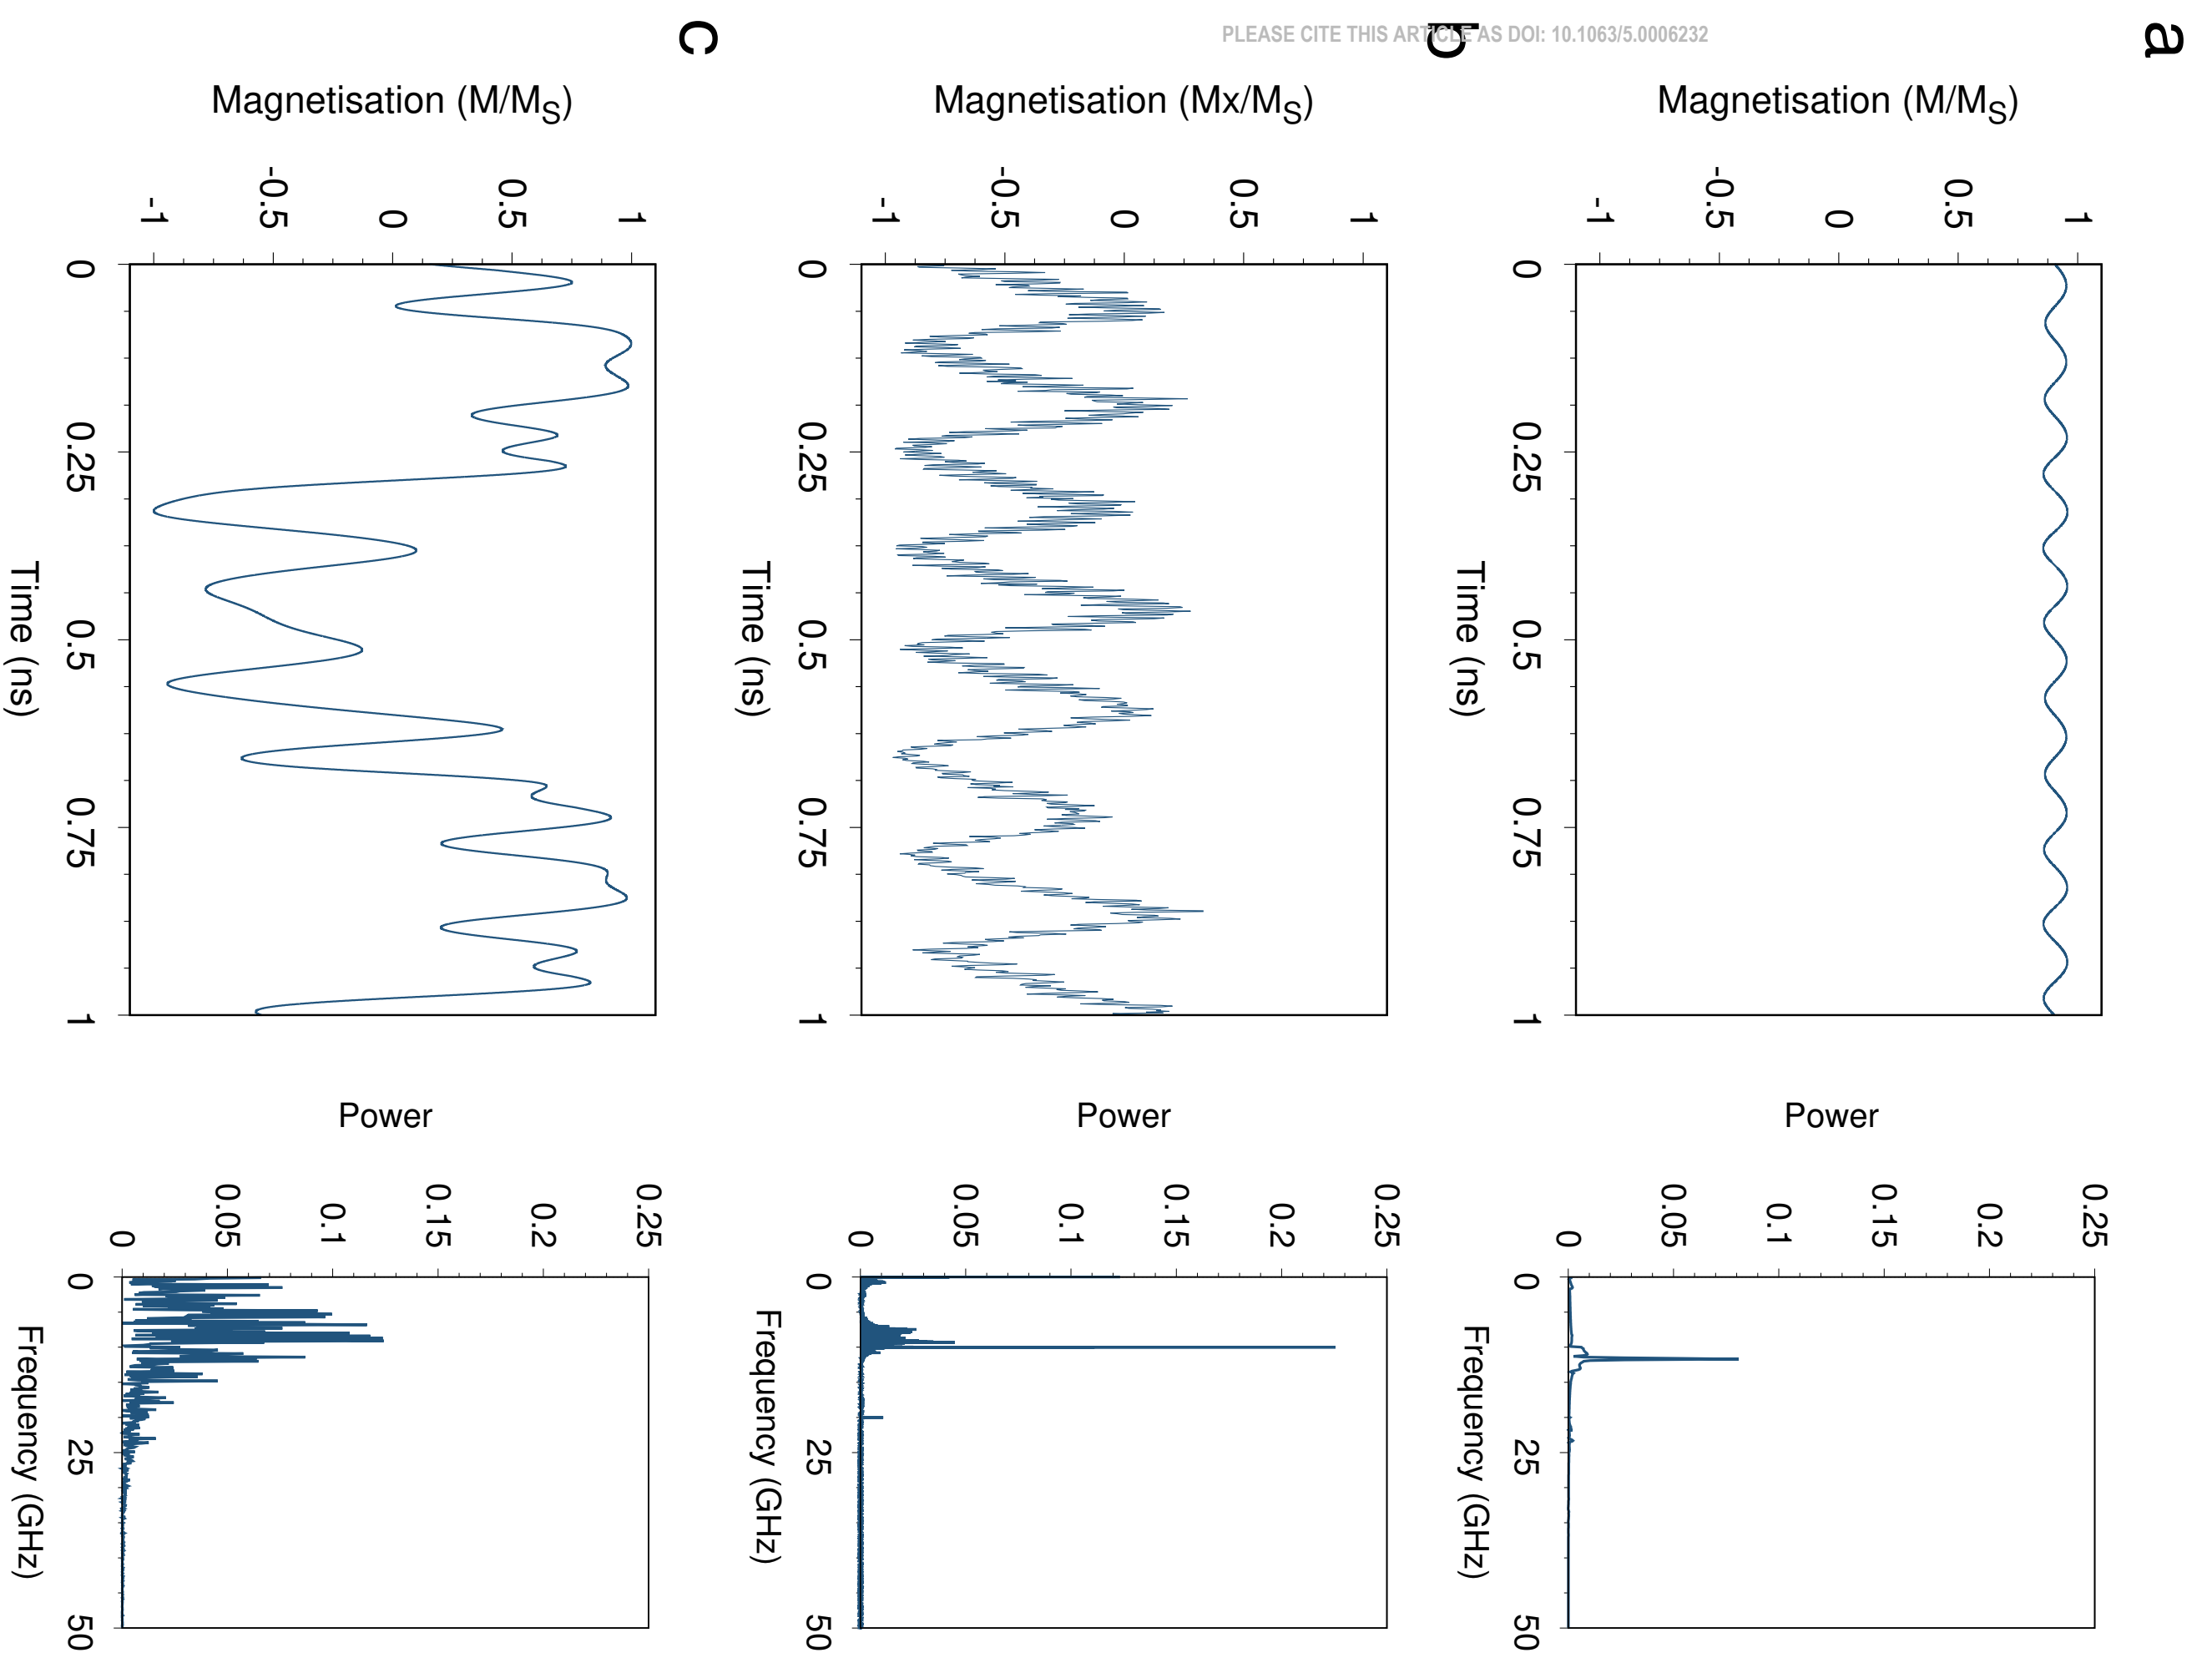


PLEASE CITE THIS ARTICLE AS DOI: 10.1063/5.0006232

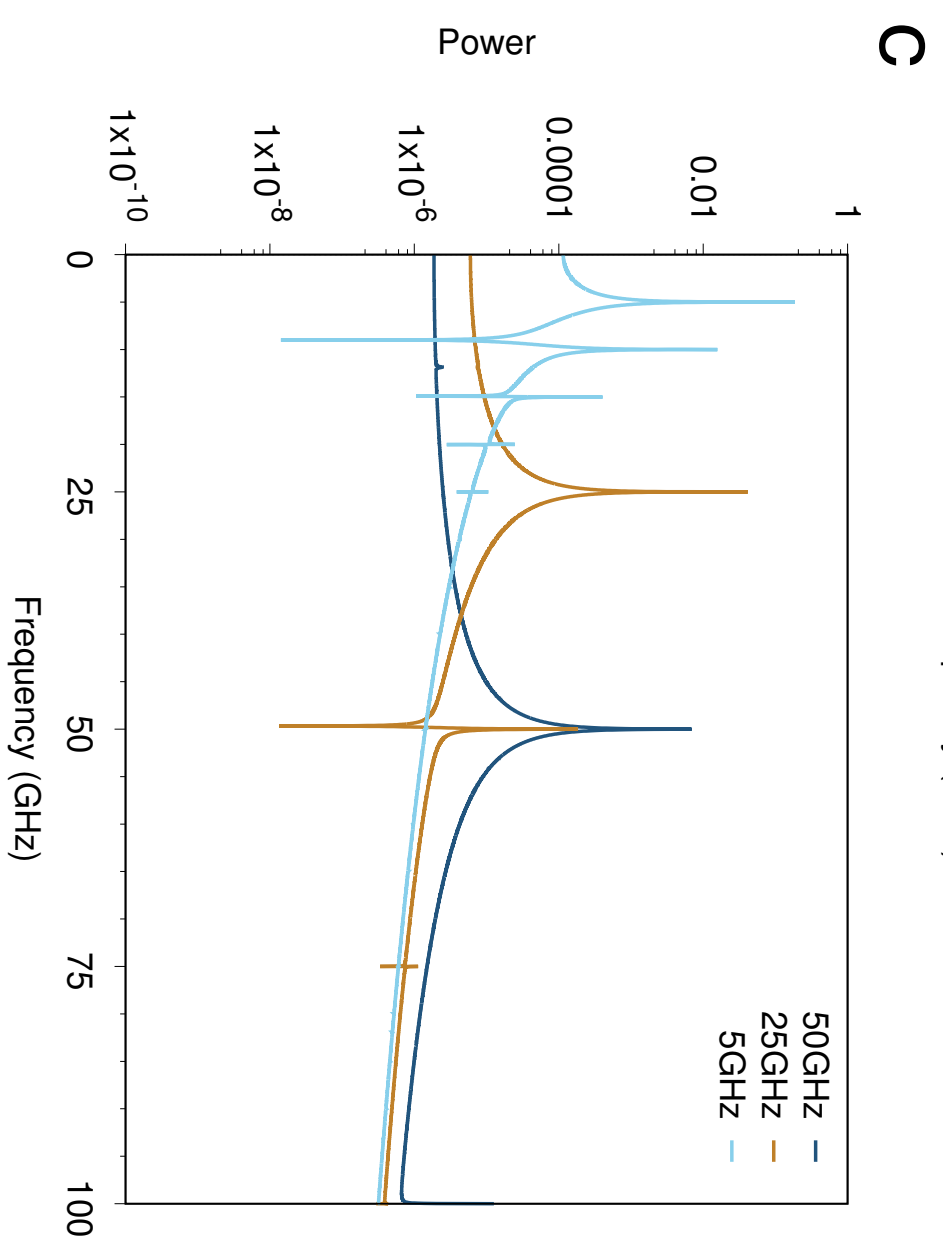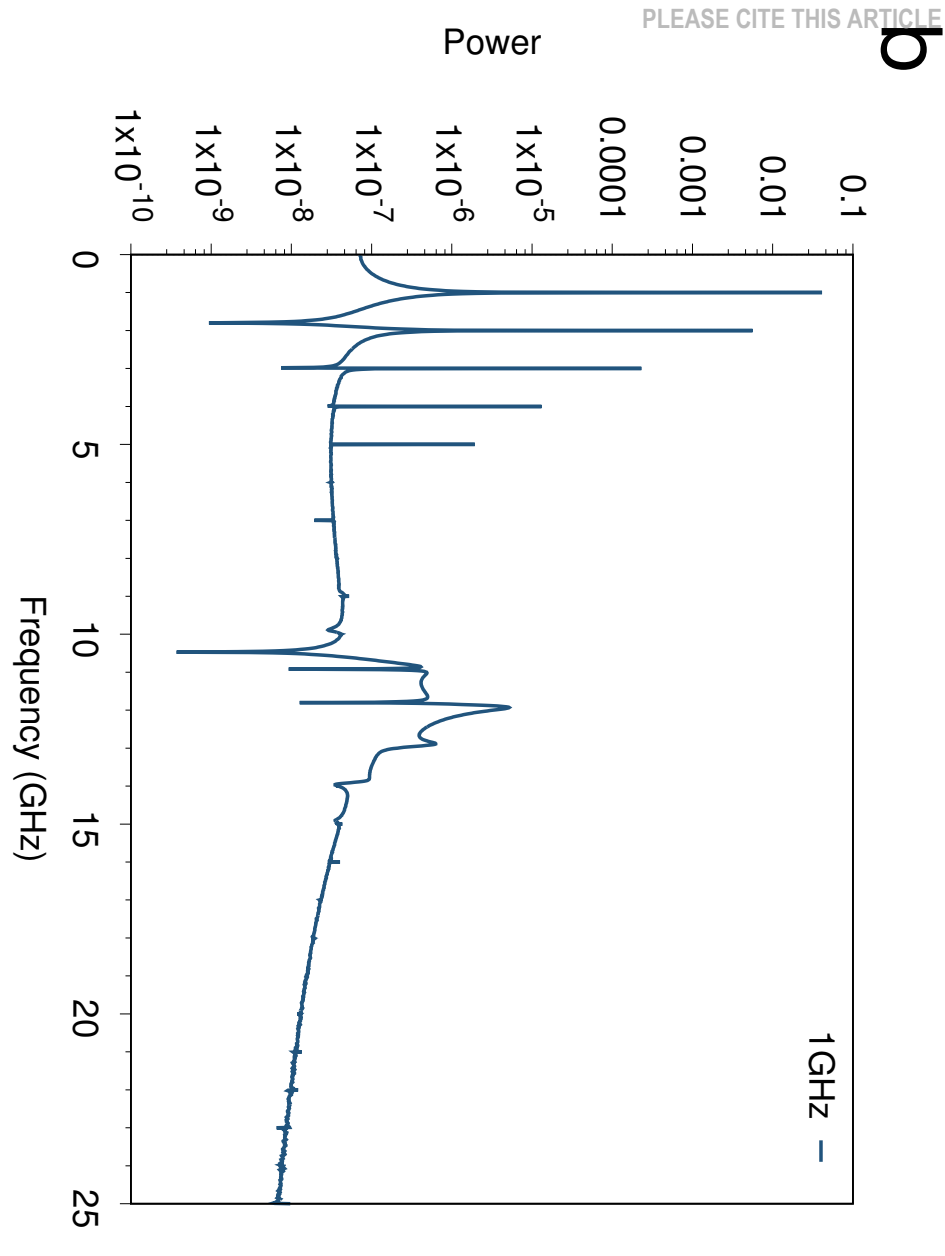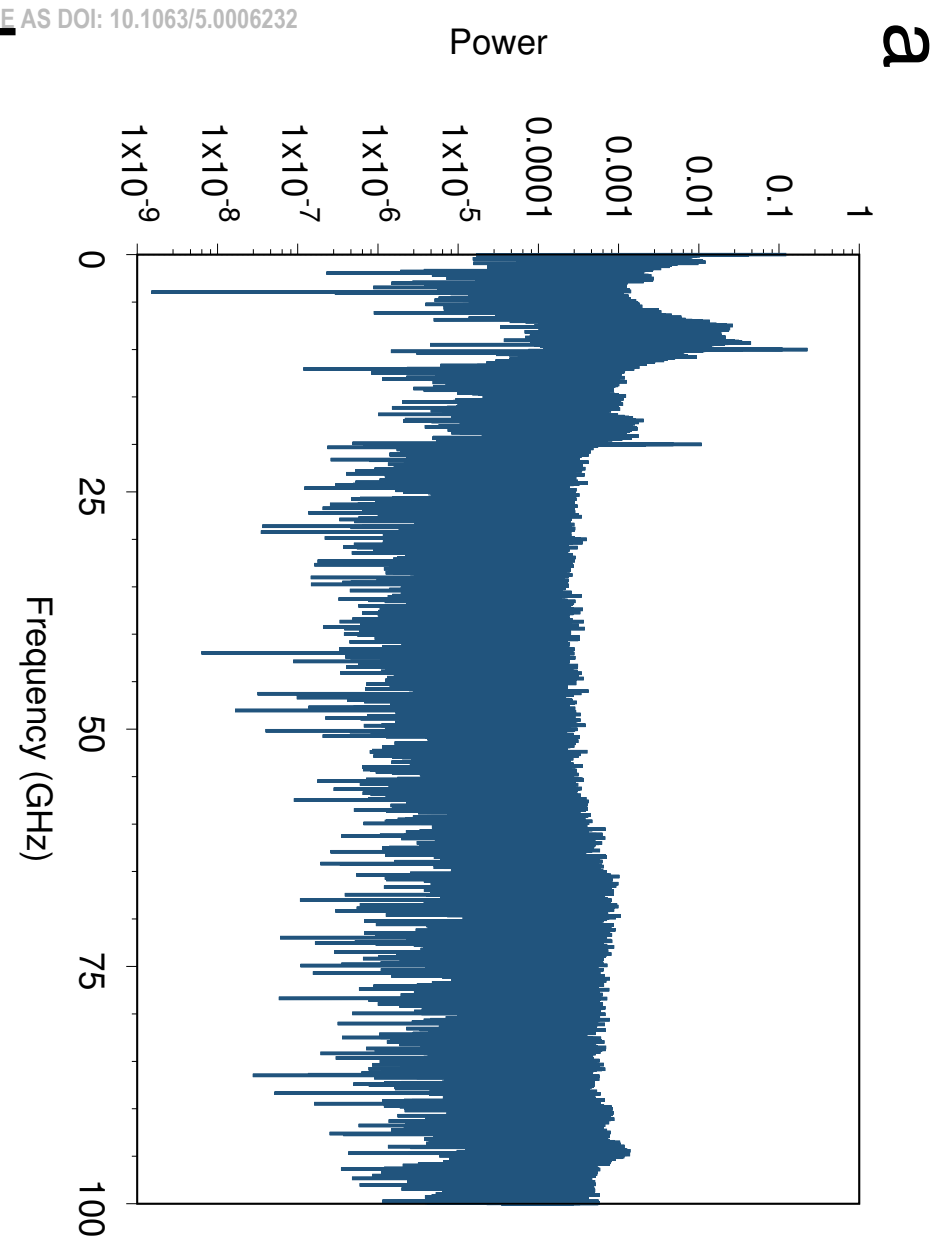


This is the author's peer reviewed, accepted manuscript. However, the online version of record will be different from this version once it has been copyedited and typeset.

PLEASE CITE THIS ARTICLE AS DOI: 10.1063/5.0006232

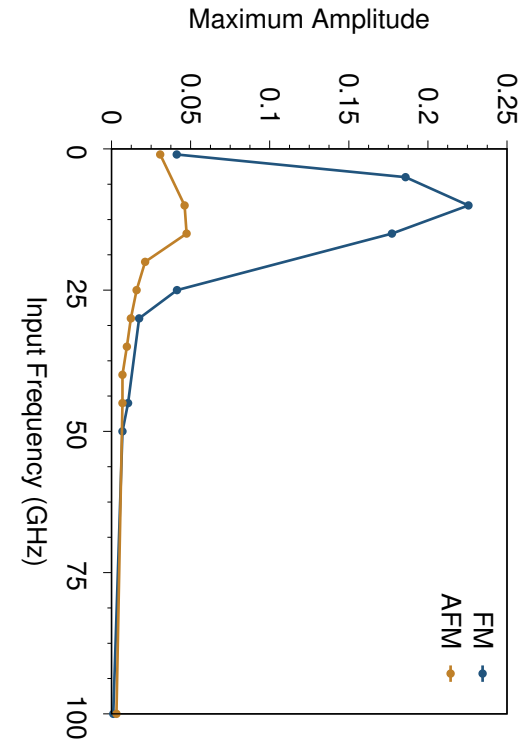


This is the author's peer reviewed, accepted manuscript. However, the online version of record will be different from this version once it has been copyedited and typeset.

PLEASE CITE THIS ARTICLE AS DOI: 10.1063/5.0006232

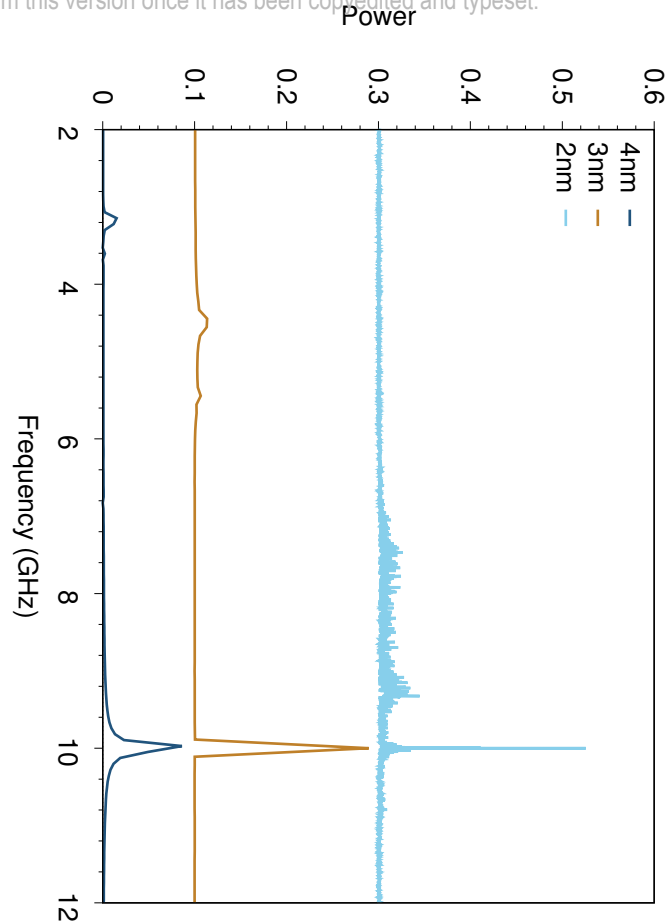


This is the author's peer reviewed, accepted manuscript. However, the online version of record will be different from this version once it has been copyedited and typeset.

PLEASE CITE THIS ARTICLE AS DOI: 10.1063/5.0006232

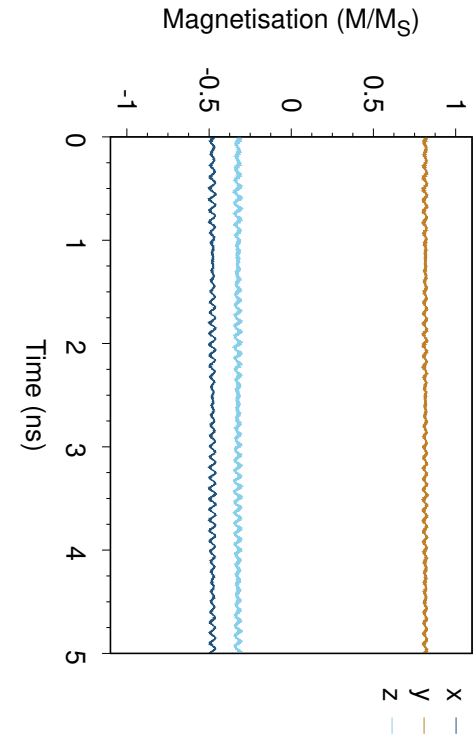


This is the author's peer reviewed, accepted manuscript. However, the online version of record will be different from this version once it has been copyedited and typeset.

PLEASE CITE THIS ARTICLE AS DOI: 10.1063/5.0006232

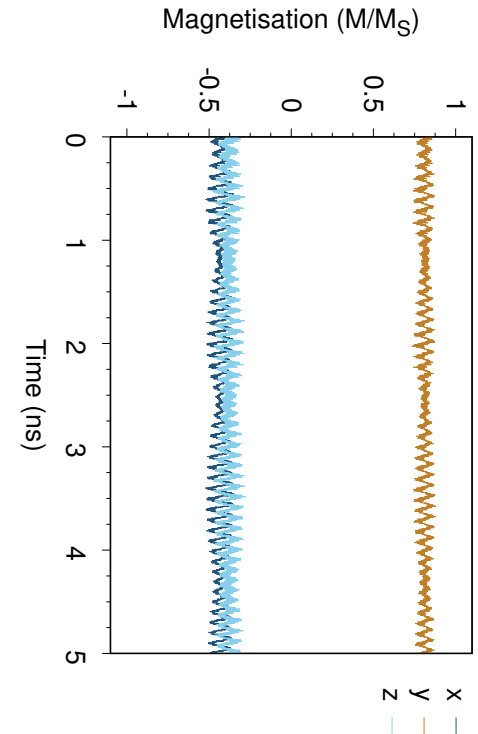

This is the author's peer reviewed, accepted manuscript. However, the online version of record will be different from this version once it has been copyedited and typeset.

PLEASE CITE THIS ARTICLE AS DOI: 10.1063/5.0006232

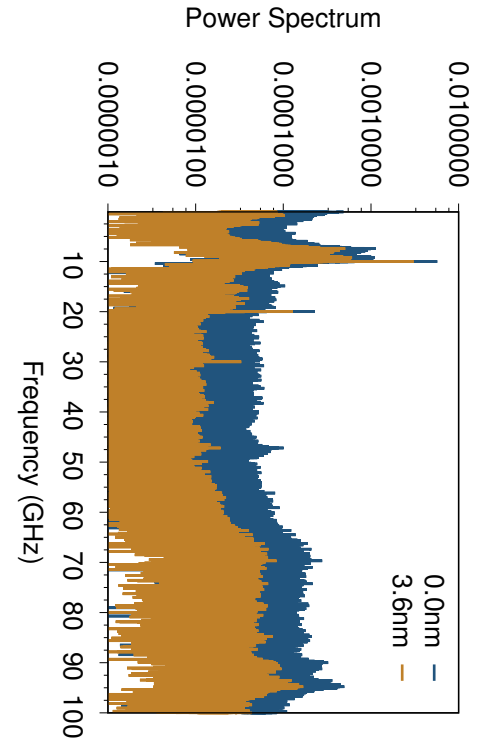

This is the author's peer reviewed, accepted manuscript. However, the online version of record will be different from this version once it has been copyedited and typeset.

PLEASE CITE THIS ARTICLE AS DOI: 10.1063/5.0006232

