

This is a repository copy of *Enzyme-catalyzed synthesis of malonate polyesters and their use as metal chelating materials*.

White Rose Research Online URL for this paper:

<https://eprints.whiterose.ac.uk/id/eprint/175968/>

Version: Accepted Version

---

**Article:**

Byrne, Fergal, Assemat, Jamie, Stanford, Amy et al. (3 more authors) (2021) Enzyme-catalyzed synthesis of malonate polyesters and their use as metal chelating materials. Green Chemistry. ISSN: 1463-9270

<https://doi.org/10.1039/D1GC01783G>

---

**Reuse**

Items deposited in White Rose Research Online are protected by copyright, with all rights reserved unless indicated otherwise. They may be downloaded and/or printed for private study, or other acts as permitted by national copyright laws. The publisher or other rights holders may allow further reproduction and re-use of the full text version. This is indicated by the licence information on the White Rose Research Online record for the item.

**Takedown**

If you consider content in White Rose Research Online to be in breach of UK law, please notify us by emailing [eprints@whiterose.ac.uk](mailto:eprints@whiterose.ac.uk) including the URL of the record and the reason for the withdrawal request.


# Green Chemistry

Cutting-edge research for a greener sustainable future

Accepted Manuscript

View Article Online  
View Journal

This article can be cited before page numbers have been issued, to do this please use: F. Byrne, J. Assemat, A. Stanford, T. J. Farmer, J. Comerford and A. Pellis, *Green Chem.*, 2021, DOI: 10.1039/D1GC01783G.

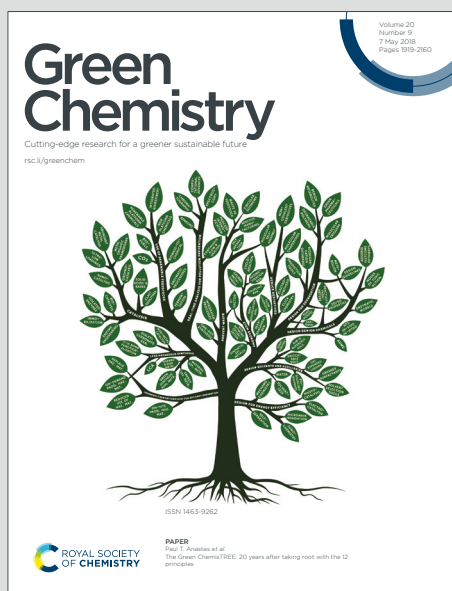

This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

# Enzyme-catalyzed synthesis of malonate polyesters and their use as metal chelating materials


Fergal P. Byrne<sup>1,\*</sup>, Jamie M. Z. Assemat<sup>1</sup>, Amy E. Stanford<sup>1</sup>, Thomas J. Farmer<sup>1</sup>,  
James W. Comerford<sup>1, 2</sup>, Alessandro Pellis<sup>1, 3, \*</sup>

<sup>1</sup> Green Chemistry Centre of Excellence, Department of Chemistry, University of York,  
Heslington, York YO10 5DD, United Kingdom

<sup>2</sup> SINTEF, Forskningsveien 1A, 0373, Oslo, Norway

<sup>3</sup> University of Natural Resources and Life Sciences, Vienna, Department of  
Agrobiotechnology, Institute of Environmental Biotechnology, Konrad Lorenz Strasse  
20, 3430, Tulln an der Donau, Austria

\* Correspondence to: Dr. Alessandro Pellis, [alessandro.pellis@boku.ac.at](mailto:alessandro.pellis@boku.ac.at) and Dr.  
Fergal Byrne, [fergal.byrne@york.ac.uk](mailto:fergal.byrne@york.ac.uk)

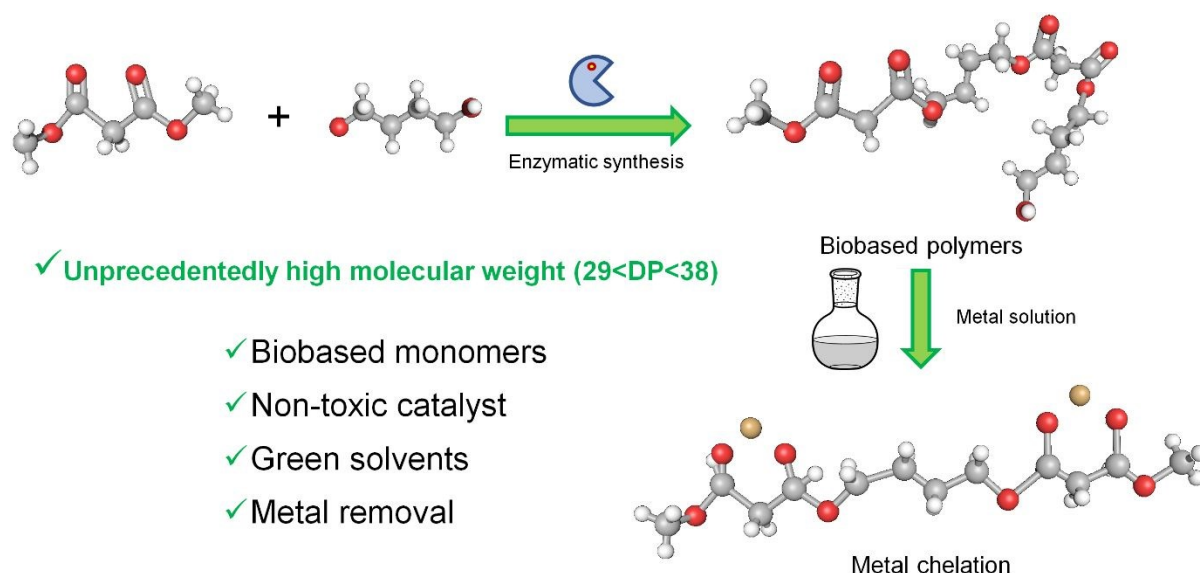

Graphical abstract



## Abstract

View Article Online  
DOI: 10.1039/D1GC01783G

Following the environmental problems caused by non-degradable plastics there is a need to synthesise greener and more sustainable polymers. In this work we describe, for the first time, the facile enzyme-catalysed synthesis of linear polyesters using dimethyl malonate as the diester. These polymers, containing a different aliphatic diol component ( $C_4$ ,  $C_6$  or  $C_8$ ), were synthesised in solventless conditions using immobilized *Candida antarctica* lipase B as the biocatalyst. The potential of enzymes for catalysing this reaction is compared with the unsuccessful antimony- and titanium-catalysed synthesis ( $T > 150^\circ\text{C}$ ). The application of the synthesized polymers as effective metal chelators in biphasic, green solvent systems was also described, together with the characterisation of the synthesised materials.

**Keywords:** biobased polyesters, enzymatic synthesis, sustainable solvents, metal chelation, water detoxification

## Introduction

Due to the functionality limitations and the pollution caused by fossil-derived polymers,<sup>1</sup> the chemical industry urges the development of greener routes to produce novel bio-based, degradable (or compostable) materials. Several steps in this direction were recently made, especially in the polyesters field, with the development of poly(ethylene 2,5-furandicarboxylate) (PEF) as a poly(ethylene terephthalate) (PET) substitute due to its similar mechanical and barrier properties<sup>2,3</sup> and better biodegradability.<sup>4,5</sup> Other furan- and pyridine-based polymers potentially useful for packaging and film applications were developed, but their synthesis remains limited to laboratory-scale.<sup>6</sup>



44 Recently, the potential of enzymes as green and selective biocatalysts has  
45 been demonstrated on several aromatic and aliphatic monomers, which is of great  
46 interest when the polycondensation of monomers carrying lateral functionalities is  
47 desired, as highlighted in several review articles.<sup>7, 8</sup> Such functionalities - the vinyl  
48 group of itaconic acid, the secondary hydroxy group of glycerol, sorbitol or mucic acid,  
49 etc. - are prone to a wide array of side reactions (such as Ordeli saturation, radical  
50 crosslinking, etc.) when traditional metal- or acid-catalyzed polymerization reactions  
51 are carried out.<sup>9, 10</sup> In fact, previously synthesized metal-chelating polymers based on  
52 a diethylenetriaminepentaacetic acid pendant group required a Michael addition of a  
53 thiol to be carried out in a second reaction step, and the double bond of the itaconate  
54 moiety was preserved only thanks to the use of very toxic chemicals such as 2-  
55 furanmethanethiol and a phosphazene base as the initiator.<sup>11</sup>

56 In this work, attention was focused on malonate-derived aliphatic polyesters. Malonic  
57 acid is a source of bio-based 1,3-diketone functionality, and it is produced  
58 commercially by Lygos using engineered yeast strains.<sup>12</sup> To the best of our knowledge,  
59 malonate-derived polyesters were reported before in the literature only in the form of  
60 short oligomers having a maximum DP of around 5<sup>13</sup>. In fact, the reports dealing with  
61 malonate polymers describe mainly the synthesis of aliphatic hyperbranched  
62 polyesters (HBPE) from various monomers derived in one step from commercial  
63 diethyl malonate.<sup>14</sup> The acid- and metal- catalyzed polycondensation of malonate  
64 derivatives bearing aliphatic residues<sup>15</sup> was also reported together with the sequential  
65 anionic polymerization of ethylene oxide and methyldiene malonate to obtain  
66 poly(ethylene oxide)-block-poly(methyldiene malonate 2.1.2) block copolymers  
67 bearing a primary amino group at the PEO chain end.<sup>16</sup> The only work where the  
68 malonate unit was changed from a malonic acid or dialkyl ester to being part of the







main chain, is the work of Doğan and Küsefoğlu, published in 2008, that reported the 1,4-diazabicyclo[2.2.2]octane-catalyzed synthesis of a biodegradable polymeric foam from epoxidized soybean oil and malonic acid.<sup>17</sup>


There has been increased interest in elemental sustainability in recent years. Commonly used metals such as cobalt, nickel, copper and zinc have reserves expected to last only 50-100 years. Recovery of these metals from waste streams is vital to maintain supplies of these dwindling resources.<sup>18</sup> One method of recovering metals from aqueous waste streams is solvent-based hydrometallurgy.<sup>19, 20</sup> This involved contacting an organic solution containing metal chelators with an aqueous metal solution. A biphasic system emerges, in which metal ions can pass from the aqueous phase to the metal chelators in the organic phase. The metals can be recovered from the organic phase by re-extraction by an acidic solution, allowing the free chelators in the organic phase to be reused.<sup>20</sup> However, issues of toxicity, bioaccumulation and persistence in the environment of chelators are common.<sup>21</sup> In addition, most currently available chelators are petroleum-derived with few examples of bio-based products (Nouryon Dissolvine range being a rare example).<sup>22</sup> As such, bio-based, safe, water-insoluble metal chelators are sought after.

Many functional groups can be used as chelators, such as oximes, carboxylates, phosphorous acids, and 1,3-diketones. 1,3-Diketones such as LIX54 (Figure 1) are commercially available for this purpose,<sup>19, 23</sup> but naturally occurring other 1,3-diketones such as 14,16-hentriacontanedione are present in plant waxes.<sup>24, 25</sup> Indeed, biphasic extraction systems have been proposed in the past using bio-derived lipophilic chelators sourced from wheat straw wax,<sup>25</sup> as well as modified wax products to produce super-chelators.<sup>24</sup>

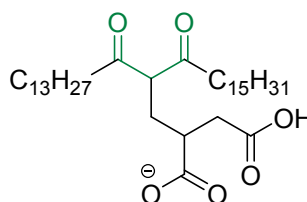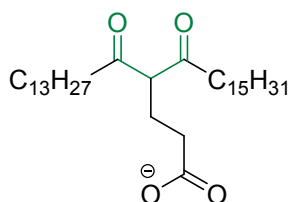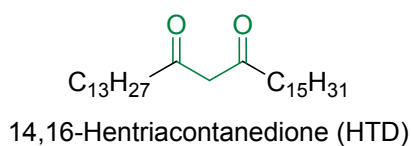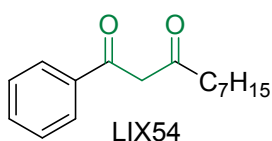


**Previous work**

Modified HTD chelators using methyl acrylate (left) and itaconic acid (right)

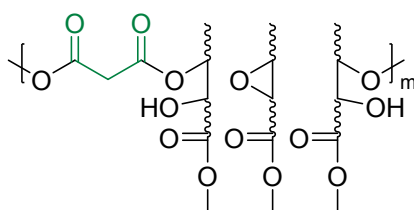

Epoxidised soybean oil/malonic acid polymers

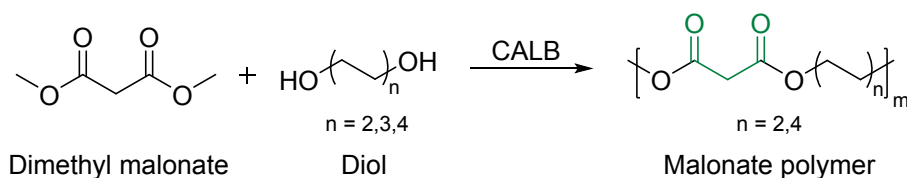**This work**

**Figure 1.** Structures of the previously described 1,3-diketone chelators LIX54, 14,16-hentriacontanedione and the malonate-based polymers described in this work.

Herein we present the facile enzyme-catalyzed synthesis of dimethyl malonate-based linear polyesters having a different aliphatic diol component ( $C_4$ ,  $C_6$  or  $C_8$ ). The reaction was conducted in solventless conditions using immobilized *Candida antarctica* lipase B as the biocatalyst. The potential of enzymes for catalysing this reaction is compared with the largely unsuccessful chemo-catalytic metal-catalyzed



103 synthesis. The application of the synthesized polymers as effective metal chelators in  
104 biphasic, solvent-based hydrometallurgy is also described together with a detail  
105 characterization of the synthesized materials. Moreover, these aliphatic polyesters are  
106 known to be easily degraded to their constituent monomers (diacids and polyols) using  
107 a variety of hydrolytic enzymes (eg. lipases, cutinases),<sup>26, 27</sup> therefore allowing the  
108 recovery of such building blocks and the re-synthesis of the polymer in a closed-loop  
109 circular economy concept.

### 111 Synthesis of malonate-based aliphatic polymers

112 Quite surprisingly, very few reports describing the use of malonic acid (or its esters)  
113 as the diacid component of polyesters were found in the literature<sup>28, 29</sup> and none of  
114 them focuses on the chelating properties of these polymers. We therefore initially  
115 attempted to synthesize malonate polyesters using the most commonly known metal  
116 catalysts for polycondensation reactions: antimony oxide and titanium butoxide,  
117 catalysts widely known for the synthesis of PET,<sup>30</sup> PEF<sup>31</sup> and a wide range of other  
118 aliphatic and aromatic polyesters.<sup>32</sup> Unfortunately, when using dimethyl malonate  
119 (DMM) as the diester in combination with various aliphatic polyols, the metal-catalyzed  
120 synthesis was unsuccessful, with obtained  $M_n$ s between 1000 and 2600 Da (DP of 6  
121 and 16 respectively, Table 1).

122 The rather low molecular weights obtained in this work using metal catalysts  
123 can be explained with the fact that  $\beta$ -diketones, such as malonates, are known  
124 chelating agents and can therefore competitively chelate the catalyst metal ions,  
125 reducing their capacity to promote the transesterification reaction. This idea is  
126 supported by the fact that titanium forms complexes with dimethyl malonate<sup>33</sup> creating  
127 a useful catalyst for the polymerization of polypropylene.<sup>34</sup> One of the few available





reports on malonate polyesters is the  $P_2O_5$ -catalyzed synthesis of poly(1,3-propyl malonate), but also in this case the obtained molecular weights were really limited since the maximum achieved DP was approximately 5.<sup>13</sup>

**Table 1.** Metal-catalyzed synthesis of malonate polyesters.

Diol	Catalyst	$M_n$ [Da]*	$M_w$ [Da]*	$\bar{D}^*$
1,4-BDO	$Sb_2O_3$	2100	4000	1.90
	$Ti(O^iBu)_4$	2600	4600	1.79
1,8-ODO	$Sb_2O_3$	1000	2400	2.28
		1600	2800	1.68


\* Calculated via GPC

Taking inspiration from recent papers on environmentally friendly synthesis of polymers, and due to the impossibility to obtain polymers using traditionally-used methods, an enzymatic approach was used in order to synthesize a series of malonate-containing aliphatic polyesters using diols having a chain length from 4 to 8 carbon atoms. For the synthesis performed in this work, an immobilized preparation of *Candida antarctica* lipase B (iCaLB) was used as the biocatalyst since this enzyme was reported to be an excellent candidate for such synthesis reactions<sup>7, 35</sup>. The polycondensation reaction progressed at very mild (85 °C, 1000/20 mbar, 6+18 h) solventless conditions. The application of such environmentally-friendly synthesis protocol was possible since DMM is a liquid at the used operational temperature while the corresponding diacid, malonic acid, has a melting temperature reported to be between 135 °C and 137 °C.

The enzymatic synthesis experiments show similar  $M_n$  values of around 6000 Da for all the used diols while the  $M_w$  values increase from 9000 Da to 12-14K Da with the increase of the diol's chain length (Figure 1). The reported values are in line with previous reports of solvent-free enzymatic polycondensations where the used



diester was dimethyl adipate that also showed similar  $M_n$  (~7000 Da) and increasing  $M_w$  (from 11 to 14K Da) when the same three aliphatic diols having increasing carbon chain length were used<sup>35</sup>. The decrease of the DP as the diol increases, as seen for both the malonate and the adipate polyesters, is also a common trait (Figure 2).<sup>7, 35</sup>

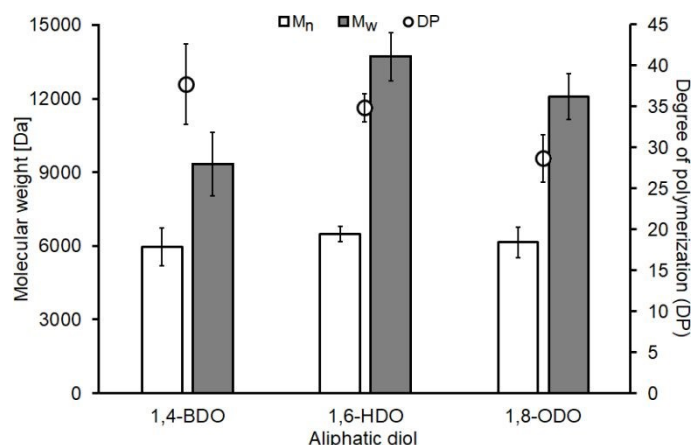

**Figure 2.** Enzymatic synthesis of linear malonate-based polyesters. Number average molecular weights ( $M_n$ , white bars) and weight average molecular weights ( $M_w$ , grey bars) were determined via gel permeation chromatography using polystyrene standards. The degree of polymerization (DP, white circles) was determined dividing the  $M_n$  by the  $M_0$  (weight of the repetitive unit of the polymer). All experiments were performed in duplicates and shown  $\pm$  the standard deviation.

All synthesized malonate-based polyesters have  $29 < DP < 38$ , therefore presenting molecular masses significantly higher in comparison of the short oligomers previously synthesized using  $P_2O_5$  and our own chemocatalytic synthesis approach (Table 1). The polymers were recovered using a simple vacuum filtration that allowed the removal of the immobilized enzyme and the work-up solvent was then removed *via* rotary evaporation. All isolated polyesters were colourless viscous liquids and subsequently used for the chelation experiments without further purification.

Polymer structures and relative monomer conversions were elucidated via  $^1H$ -NMR spectroscopy (Figures S1-S5 in ESI). Upon reaction, the  $-CH_2-\underline{CH_2}-OH$  signal from the




diol has a characteristic change of chemical shift from 3.65 ppm to 4.14 ppm, proving the formation of an ester bond. Additionally, the  $-\text{OCH}_3$  signal from the malonate, observable at 3.75 ppm disappears due to the release of MeOH with the progression of the reaction. The signals at 3.38 ppm ( $\text{C}-\text{CH}_2-\text{C}$  of the malonate) and in the 1.3–1.8 ppm range ( $-\text{CH}_2-\text{CH}_2-\text{OH}$  of the diols) do not noticeably change chemical shift upon elongation of the polymer chain.  $^{13}\text{C}$ -NMR spectroscopy of the polymer reveals the typical signals for these aliphatic polyesters (Figure S6 in ESI).

### Metal chelation in biphasic systems based on green solvents.

The malonate polyesters were assessed for their ability to extract metal ions from aqueous streams in a biphasic system. The biphasic system involved dissolving the polyester in an organic solvent and mixing it with a metal-containing aqueous solution. Upon contact between the two phases, metal transfer occurs from the aqueous phase to the diketone chelating points on the polyester in the organic phase, purifying the aqueous phase. Separation of the two phases and re-extraction of the organic phase with an acidic stripping solution can recover the metal from the polyester for reuse, and also regenerate the diketone chelating point on the polyester.

Copper was chosen as the target metal for chelation using the polyesters due to it being a common pollutant in metallurgy waste streams<sup>36</sup>.  $\text{Cl}^-$  was selected as the counter ion as it has previously been shown to be effective in the chelation of copper using diketone species due to it being a strong inner-sphere ligand.<sup>24, 25</sup> The chelation tests were carried out across a pH range of 8.4–12.3.



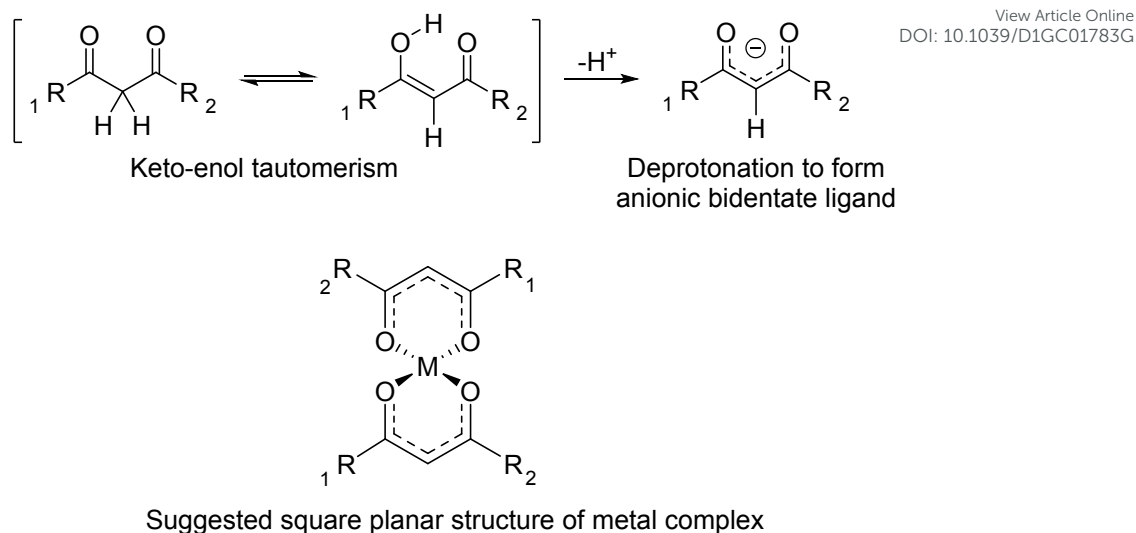

**Figure 3.** Keto-enol tautomerism of 1,3-diketones followed by deprotonation to form negatively charged bidentate ligand.

Several requirements exist for the choice of organic solvent for this purpose. It must partition well with water; the chelating agent must favour solubility in the organic solvent over water; it must facilitate enol formation; and it must not be reactive in the extraction conditions. As the solvent does not need to be evaporated at any stage of the extraction process, a low boiling point is not necessary. In fact, a higher boiling point will reduce losses to the atmosphere, improving the economics of such an extraction process. In addition, it will add to the green credentials of the process, as emissions, exposure to workers and solvent demand are reduced. The CHEM21 solvent selection guide recommends a boiling point of between 70-139 °C.<sup>37</sup>

Three candidate solvents were ultimately selected using the CHEM21 solvent guide<sup>37</sup>: *para*-cymene, ethyl levulinate and anisole. *para*-Cymene and anisole have boiling points within the ideal range (70-139 °C), while that of ethyl levulinate is 206 °C. However, as the solvent/polymer mixture can be used repeatedly, this higher than preferred boiling point is not a significant issue. All three candidates are aprotic,




meaning the enol form is more likely to be favoured<sup>25</sup> which is a prerequisite for chelation ability (keto form is stabilised by intermolecular hydrogen-bonding in protic solvents)<sup>38</sup>. Polymer insolubility in BDO MAL polymer prevented *para*-cymene from being tested, while ethyl levulinate likely chelated with metal ions during extraction, indicated by a green complex being formed when mixed with copper solutions. Anisole could dissolve all polymers, and also scores well in the CHEM21 solvent selection guide, being classified as “recommended”<sup>37</sup>. As such, anisole was chosen as the most appropriate solvent for this process.

The 1,3-diketones functionality can exist in keto and enol forms (Figure 3). In basic conditions, deprotonation of the acidic proton in the 2-position forms an anionic bidentate ligand which are weak chelators. A square planar complex is suggested, similar to that of bis(acetylacetonato)copper(II), as previously determined by single crystal X-ray diffraction<sup>39</sup>. As the polymers existed as a viscous liquid, possibly due to residual solvent that could not be removed *in vacuo*, powder XRD could not be carried out to confirm the square planar complex in the malonate polymers of this work.

The polymers with the highest (ODO MAL) and lowest (BDO MAL)  $M_0$  were chosen as model to perform chelation tests with  $\text{CuCl}_2$ . A pH range of 8.4–12.3 was used for the tests. Chelation tests were carried out in a biphasic system consisting of a  $\text{CuCl}_2$ -rich aqueous phase (0.05 M  $\text{CuCl}_2$ , 0.25 M  $\text{NH}_3$ ) and an organic solution of the chelating polymer (0.05 M). Interestingly, the density of the aqueous metal solutions at higher pH (10.4–12.3) changed such that the layers switched in the biphasic system when the BDO MAL was used. This is due to the proximity of the density of pure anisole (0.995 g mL<sup>-1</sup>) to that of water (1.000 g mL<sup>-1</sup>), which must be taken into consideration in an industrial process.



Figure 4 shows that optimal pH for extraction was similar in both cases, with ~pH 10 being optimal for ODO MAL and BDO MAL polymers (specific pH's and absorbances for chelation tests are shown in Table S2 and S3 in ESI). This is consistent with previous observations of 1,3-diketones being more effective in basic conditions<sup>17</sup>. Superior extraction was obtained with the ODO MAL, with mean Cu extraction of 22.7% compared to 15.7% for the BDO MAL polymer. Extraction with the malonate polymers is comparable with the commercial LIX54 (18% in a 50:50 mix of LIX54/kerosene, 40% using pure LIX54),<sup>23</sup> demonstrating the potential of such a chelating polymer for use in an industrial setting. Further work is required on optimising the conditions for extraction (polymer loading, further solvent investigation, more robust pH control), their stability over multiple uses and their affinities for other metals in mixed aqueous streams which will be the focus of a subsequent full article.

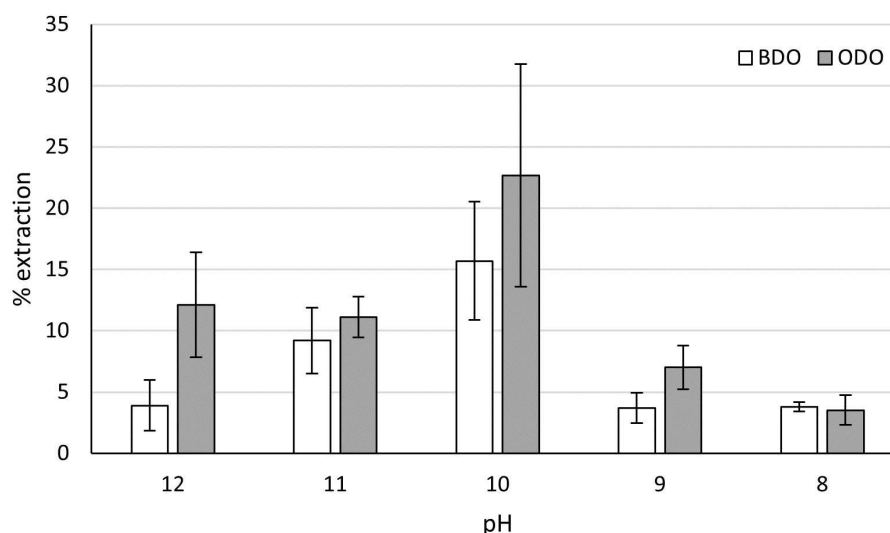

**Figure 4.** The % extraction of Cu(II) from ammoniacal solutions using “BDO” MAL and “ODO” MAL at different pHs and 1:1 by weight loading of chelator:Cu(II). The pH shown in the graph has been rounded to the nearest whole number for visual clarity. Exact pH values are shown in the electronic supplementary information.

## Conclusions

A series of malonate polymers were successfully synthesized using environmentally-friendly conditions (enzymatic catalyst,  $T < 90\text{ }^{\circ}\text{C}$ , solvent for the workup: MeTHF) and used to achieve the efficient chelation of copper, a common pollutant in metallurgy waste streams. A superior extraction efficiency of 23% was obtained with the ODO MAL polymer that is comparable with commercially-available LIX54 (18% in a 50:50 mix of LIX54/kerosene, 40% using pure LIX54), demonstrating the potential of this new class of polyesters for use in an industrial setting. Enzymatic catalysis, showing high selectivity, low operational temperatures and benign reaction conditions, is emerging as a useful tool to complement chemo-catalytic routes for the synthesis of multifunctional polymers having structures that are otherwise not possible to obtain using traditional metal- and acid based-methods.

## Acknowledgements

A. P. thanks the FWF Erwin Schrödinger fellowship (grant agreement J 4014-N34) for financial support. A. E. S. thanks the Department of Chemistry of the University of York for funding her summer vacation placement to undertake this research.

## Author contributions

A. P., J. M. Z. A. and A. E. S. performed the enzymatic polymer synthesis and material's characterization. F. P. B., J. M. Z. A. and A. E. S. performed the chelation experiments. A. P. and J.W.C. performed the chemo-catalytic synthesis. A.P. and F. P. B. planned the experiments and wrote the manuscript. F. P. B., A. P. and T. J. F. supervised the work. All authors corrected the manuscript and discussed the data prior to submission.



## Notes

The authors declare no conflict of interests.

## References

- (1) Lechner, A.; Keckeis, H.; Lumesberger-Loisl, F.; Zens, B.; Krusch, R.; Tritthart, M.; Glas, M.; Schludermann, E. The Danube so Colourful: A Potpourri of Plastic Litter Outnumbers Fish Larvae in Europe's Second Largest River. *Environmental Pollution* **2014**, *188*, 177–181. <https://doi.org/10.1016/j.envpol.2014.02.006>.
- (2) Papageorgiou, G. Z.; Tsanaktsis, V.; Bikiaris, D. N. Synthesis of Poly(Ethylene Furandicarboxylate) Polyester Using Monomers Derived from Renewable Resources: Thermal Behavior Comparison with PET and PEN. *Physical Chemistry Chemical Physics* **2014**, *16* (17), 7946–7958. <https://doi.org/10.1039/c4cp00518j>.
- (3) Papageorgiou, G. Z.; Papageorgiou, D. G.; Terzopoulou, Z.; Bikiaris, D. N. Production of Bio-Based 2,5-Furan Dicarboxylate Polyesters: Recent Progress and Critical Aspects in Their Synthesis and Thermal Properties. *European Polymer Journal*. Elsevier Ltd October 1, 2016, pp 202–229. <https://doi.org/10.1016/j.eurpolymj.2016.08.004>.
- (4) Weinberger, S.; Haernvall, K.; Scaini, D.; Ghazaryan, G.; Zumstein, M. T.; Sander, M.; Pellis, A.; Guebitz, G. M. Enzymatic Surface Hydrolysis of Poly(Ethylene Furanoate) Thin Films of Various Crystallinities. *Green Chemistry* **2017**, *19* (22), 5381–5384. <https://doi.org/10.1039/c7gc02905e>.
- (5) Weinberger, S.; Canadell, J.; Quartinello, F.; Yeniad, B.; Arias, A.; Pellis, A.; Guebitz, G. Enzymatic Degradation of Poly(Ethylene 2,5-Furanoate) Powders





- and Amorphous Films. *Catalysts* **2017**, *7* (11), 318.  
<https://doi.org/10.3390/catal7110318>.
- (6) Pellis, A.; Comerford, J. W.; Weinberger, S.; Guebitz, G. M.; Clark, J. H.; Farmer, T. J. Enzymatic Synthesis of Lignin Derivable Pyridine Based Polyesters for the Substitution of Petroleum Derived Plastics. *Nature Communications* **2019**, *10* (1), 1–9. DOI: 10.1038/s41467-019-09817-3.
- (7) Kobayashi, S. Lipase-catalyzed polyester synthesis--a green polymer chemistry. *Review Proc Jpn Acad Ser B Phys Biol Sci* **2010**, *86* (4), 338-65. <https://doi.org/10.2183/pjab.86.338>.
- (8) Gross, R. A.; Kumar, A.; Kalra, B. Polymer Synthesis by In Vitro Enzyme Catalysis. *Chem. Rev.* **2001**, *101*, 2097–2124.
- (9) Pellis, A.; Hanson, P. A.; Comerford, J. W.; Clark, J. H.; Farmer, T. J. Enzymatic Synthesis of Unsaturated Polyesters: Functionalization and Reversibility of the Aza-Michael Addition of Pendants. *Polymer Chemistry* **2019**, *10* (7), 843–851. <https://doi.org/10.1039/c8py01655k>.
- (10) Farmer, T.; Castle, R.; Clark, J.; Macquarrie, D. Synthesis of Unsaturated Polyester Resins from Various Bio-Derived Platform Molecules. *International Journal of Molecular Sciences* **2015**, *16* (12), 14912–14932. <https://doi.org/10.3390/ijms160714912>.
- (11) Illy, N.; Majonis, D.; Herrera, I.; Ornatsky, O.; Winnik, M. A. Metal-Chelating Polymers by Anionic Ring-Opening Polymerization and Their Use in Quantitative Mass Cytometry. **2012**, *13*, 41. <https://doi.org/10.1021/bm300613x>.
- (12) Malonic acid <https://lygos.com/products/> (accessed June 15, 2021).
- (13) Ravve, A.; Pasternack, G.; Brown, K. H.; Radlove, S. B. Synthesis of Photocrosslinkable Polyesters by the Knoevenagel Reaction. *Journal of*



- 330 *Polymer Science: Polymer Chemistry Edition* **1973**, 11 (7), 1733–1752. View Article Online  
DOI: 10.1039/D1GC01783G
- 331 <https://doi.org/10.1002/pol.1973.170110720>.
- 332 (14) Santra, S.; Kumar, A. Facile Synthesis of Aliphatic Hyperbranched Polyesters  
333 Based on Diethyl Malonate and Their Irreversible Molecular Encapsulation.  
334 *Chemical Communications* **2004**, No. 18, 2126–2127.  
335 <https://doi.org/10.1039/b404447a>.
- 336 (15) Kolb, N.; Meier, M. A. R. Monomers and Their Polymers Derived from  
337 Saturated Fatty Acid Methyl Esters and Dimethyl Carbonate. *Green Chemistry*  
338 **2012**, 14 (9), 2429–2435. <https://doi.org/10.1039/c2gc35793c>.
- 339 (16) Studer, P.; Larras, V.; Riess, G. Amino End-Functionalized Poly(Ethylene  
340 Oxide)-Block-Poly(Methylidene Malonate 2.1.2) Block Copolymers: Synthesis,  
341 Characterization, and Chemical Modification for Targeting Purposes. *European*  
342 *Polymer Journal* **2008**, 44 (6), 1714–1721.  
343 <https://doi.org/10.1016/j.eurpolymj.2008.04.003>.
- 344 (17) Doğan, E.; Küsefoğlu, S. Synthesis and *in Situ* Foaming of Biodegradable  
345 Malonic Acid ESO Polymers. *Journal of Applied Polymer Science* **2008**, 110  
346 (2), 1129–1135. <https://doi.org/10.1002/app.28708>.
- 347 (18) Dodson, J. R.; Hunt, A. J.; Parker, H. L.; Yang, Y.; Clark, J. H. Elemental  
348 Sustainability: Towards the Total Recovery of Scarce Metals. *Chemical*  
349 *Engineering and Processing: Process Intensification* **2012**, 51, 69–78.  
350 <https://doi.org/10.1016/j.cep.2011.09.008>.
- 351 (19) Alguacil, F. J.; Alonso, M. Effect of Ammonium Sulphate and Ammonia on the  
352 Liquid-Liquid Extraction of Zinc Using LIX 54. *Hydrometallurgy* **1999**, 53 (2),  
353 203–209. [https://doi.org/10.1016/S0304-386X\(99\)00045-6](https://doi.org/10.1016/S0304-386X(99)00045-6).

- (20) Wilson, A. M.; Bailey, P. J.; Tasker, P. A.; Turkington, J. R.; Grant, R. A.; Love, J. B. Solvent Extraction: The Coordination Chemistry behind Extractive Metallurgy. *Chemical Society Reviews*. Royal Society of Chemistry January 7, 2014, pp 123–134. <https://doi.org/10.1039/c3cs60275c>.
- (21) Nowack, B.; VanBriesen, J. M. Chelating Agents in the Environment; UTC, 2005; Vol. 14, pp 1–18. <https://doi.org/10.1021/bk-2005-0910.ch001>.
- (22) Discover our Dissolvine® product range <https://www.nouryon.com/products/chelates/dissolvine/> (accessed Apr 7, 2021).
- (23) Kyuchoukov, G.; Bogacki, M. B.; Szymanowski, J. Copper Extraction from Ammoniacal Solutions with LIX 84 and LIX 54. *Industrial and Engineering Chemistry Research* **1998**, 37 (10), 4084–4089. <https://doi.org/10.1021/ie980192v>.
- (24) Asemave, K.; Byrne, F. P.; Clark, J. H.; Farmer, T. J.; Hunt, A. J. Modification of Bio-Based  $\beta$ -Diketone from Wheat Straw Wax: Synthesis of Polydentate Lipophilic Super-Chelators for Enhanced Metal Recovery. *RSC Advances* **2019**, 9 (7), 3542–3549. DOI: 10.1039/c8ra09426h.
- (25) Asemave, K.; Byrne, F.; Farmer, T. J.; Clark, J. H.; Hunt, A. J. Rapid and Efficient Biphasic Liquid Extraction of Metals with Bio-Derived Lipophilic  $\beta$ -Diketone. *RSC Advances* **2016**, 6 (98), 95789–95792. DOI: 10.1039/c6ra24104b.
- (26) Gamerith, C.; Vastano, M.; Ghorbanpour, S. M.; Zitzenbacher, S. et al. Enzymatic Degradation of Aromatic and Aliphatic Polyesters by *P. pastoris* Expressed Cutinase 1 from *Thermobifida cellulositica*. *Front Microbiol.* **2017**, 8, 938. DOI: 10.3389/fmicb.2017.00938
- (27) Shi, K.; Jing, J.; Song, L.; Su, T.; Wang, Z. Enzymatic hydrolysis of polyester: Degradation of poly( $\epsilon$ -caprolactone) by *Candida antarctica* lipase and *Fusarium solani*



- cutinase. *Int. J. Biol. Macromol.* **2020**, *144*, 183–189. DOI: 10.1016/j.ijbiomac.2019.12.105
- (28) Tomke, P. D.; Zhao, X.; Chiplunkar, P. P.; Xu, B.; Wang, H.; Silva, C.; Rathod, V. K.; Cavaco-Paulo, A. Lipase-Ultrasound Assisted Synthesis of Polyesters. *Ultrasonics Sonochemistry* **2017**, *38*, 496–502. <https://doi.org/10.1016/j.ultsonch.2017.03.051>.
- (29) *Diester-Based Polymer Electrolytes for High Voltage Lithium Ion Batteries*; 2017.
- (30) Finelli, L.; Lorenzetti, C.; Messori, M.; Sisti, L.; Vannini, M. Comparison between Titanium Tetrabutoxide and a New Commercial Titanium Dioxide Based Catalyst Used for the Synthesis of Poly(Ethylene Terephthalate). *Journal of Applied Polymer Science* **2004**, *92* (3), 1887–1892. <https://doi.org/10.1002/app.20171>.
- (31) Loos, K.; Zhang, R.; Pereira, I.; Agostinho, B.; Hu, H.; Maniar, D.; Sbirrazzuoli, N.; Silvestre, A. J. D.; Guigo, N.; Sousa, A. F. A Perspective on PEF Synthesis, Properties, and End-Life. *Frontiers in Chemistry*. Frontiers Media S.A. July 31, 2020, p 585. <https://doi.org/10.3389/fchem.2020.00585>.
- (32) Guidotti, G.; Gigli, M.; Soccio, M.; Lotti, N.; Gazzano, M.; Siracusa, V.; Munari, A. Poly(Butylene 2,5-Thiophenedicarboxylate): An Added Value to the Class of High Gas Barrier Biopolyesters. *Polymers* **2018**, *10* (2). DOI: 10.3390/polym10020167.
- (33) Marrone, A.; Renzetti, A.; De Maria, P.; Gérard, S.; Sapi, J.; Fontana, A.; Re, N. Condensation of  $\beta$ -Diester Titanium Enolates with Carbonyl Substrates: A Combined DFT and Experimental Investigation. *Chemistry - A European Journal* **2009**, *15* (43), 11537–11550. DOI: 10.1002/chem.200901595.
- (34) Gueta-Neyroud, T.; Tumanskii, B.; Botoshansky, M.; Eisen, M. S. Synthesis, Characterization and Catalytic Activity of the Complex Titanium



- Bis(Dimethylmalonate)-Bis(Diethylamido) in the Polymerization of Propylene  
*Journal of Organometallic Chemistry* **2007**, 692 (5), 927–939. DOI:  
 10.1016/j.jorganchem.2006.10.031.
- (35) Pellis, A.; Comerford, J. W.; Maneffa, A. J.; Sipponen, M. H.; Clark, J. H.;  
 Farmer, T. J. Elucidating Enzymatic Polymerisations: Chain-Length Selectivity  
 of *Candida Antarctica* Lipase B towards Various Aliphatic Diols and Dicarboxylic  
 Acid Diesters. *European Polymer Journal* **2018**, 106, 79–84. DOI:  
 10.1016/j.eurpolymj.2018.07.009.
- (36) Matinde, E.; Simate, G. S.; Ndlovu, S. Mining and Metallurgical Wastes: A  
 Review of Recycling and Re-Use Practices. *Journal of the Southern African  
 Institute of Mining and Metallurgy*. South African Institute of Mining and  
 Metallurgy August 1, 2018, 825–844. DOI: 10.17159/2411-  
 9717/2018/v118n8a5.
- (37) Prat, D.; Wells, A.; Hayler, J.; Sneddon, H.; McElroy, C. R.; Abou-Shehada, S.;  
 Dunn, P. J. CHEM21 Selection Guide of Classical- and Less Classical-  
 Solvents. *Green Chem.* **2015**, 18 (1), 288–296. DOI: 10.1039/c5gc01008j.
- (38) Sandusky, P. O. Expansion of the Classic Acetylacetone Physical Chemistry  
 Laboratory NMR Experiment: Correlation of the Enol-Keto Equilibrium Position  
 with the Solvent Dipole Moment. *Journal of Chemical Education* **2014**, 91, 739–  
 742. DOI: 10.1021/ed400583q.
- (39) Lebrun, P. C.; Lyon, W. D.; Kuska, H. A. Crystal Structure of Bis(2,4-  
 Pentanedionato)Copper(II). *Journal of Crystallographic and Spectroscopic  
 Research* **1986**, 16 (6), 889–893. <https://doi.org/10.1007/BF01188194>.




429

430

431

[View Article Online](#)  
DOI: 10.1039/D1GC01783G

Open Access Article. Published on 29 June 2021. Downloaded on 7/6/2021 7:15:27 PM.



This article is licensed under a Creative Commons Attribution 3.0 Unported Licence.