



Deposited via The University of Sheffield.

White Rose Research Online URL for this paper:

<https://eprints.whiterose.ac.uk/id/eprint/188433/>

Version: Published Version

---

**Article:**

Simoni, M., Hanein, T., Woo, C.L. et al. (2022) Decarbonisation of calcium carbonate in sodium hydroxide solutions under ambient conditions: effect of residence time and mixing rates. *Physical Chemistry Chemical Physics*, 26. pp. 16125-16138. ISSN: 1463-9076

<https://doi.org/10.1039/d2cp01412b>

---

**Reuse**

This article is distributed under the terms of the Creative Commons Attribution (CC BY) licence. This licence allows you to distribute, remix, tweak, and build upon the work, even commercially, as long as you credit the authors for the original work. More information and the full terms of the licence here:

<https://creativecommons.org/licenses/>

**Takedown**

If you consider content in White Rose Research Online to be in breach of UK law, please notify us by emailing [eprints@whiterose.ac.uk](mailto:eprints@whiterose.ac.uk) including the URL of the record and the reason for the withdrawal request.



Cite this: DOI: 10.1039/d2cp01412b

# Decarbonisation of calcium carbonate in sodium hydroxide solutions under ambient conditions: effect of residence time and mixing rates†

 Marco Simoni,<sup>ib</sup>\*<sup>a</sup> Theodore Hanein,<sup>ib</sup>\*<sup>a</sup> Chun Long Woo,<sup>a</sup> Mark Tyrer,<sup>ib</sup><sup>b</sup> Magnus Nyberg,<sup>c</sup> Juan-Carlos Martinez,<sup>c</sup> Nestor I. Quintero-Mora,<sup>d</sup> John L. Provis<sup>ib</sup><sup>a</sup> and Hajime Kinoshita\*<sup>a</sup>

The decarbonisation of CaCO<sub>3</sub> is essential for the production of lime (Ca(OH)<sub>2</sub> and CaO), which is a commodity required in several large industries and the main precursor for cement production. CaCO<sub>3</sub> is usually decarbonised at high temperatures, generating gaseous CO<sub>2</sub> which will require post-process capture to minimise its release into the environment. We have developed a new process that can decarbonise CaCO<sub>3</sub> under ambient conditions, while sequestering the CO<sub>2</sub> as Na<sub>2</sub>CO<sub>3</sub>·H<sub>2</sub>O or Na<sub>2</sub>CO<sub>3</sub> in the same stage. Here, the effects of increasing stirring rates and residence times on reaction efficiency of the key reaction occurring between CaCO<sub>3</sub> and NaOH solution are studied. It is shown that the reaction is enhanced at lower stirring rates and longer residence times up to 300 seconds of contact between the reactants. The mass balance performed for Ca and CO<sub>2</sub> revealed that up to the 95% of the process CO<sub>2</sub> embodied in CaCO<sub>3</sub> was sequestered, with maximum capture rate assessed at *nn* moles CO<sub>2</sub> captured per second of reaction progress. A deeper insight into the precipitation of Na<sub>2</sub>CO<sub>3</sub>·H<sub>2</sub>O or Na<sub>2</sub>CO<sub>3</sub> under different reaction conditions was gained, and SEM-EDX analysis enabled the observation of the reaction front by detection of Na migrating towards inner regions of partially-reacted limestone chalk particles.

 Received 25th March 2022,  
 Accepted 4th May 2022

DOI: 10.1039/d2cp01412b

[rsc.li/pccp](http://rsc.li/pccp)

## 1. Introduction

Lime (CaO) and slaked lime (Ca(OH)<sub>2</sub>) are essential components for a wide range of industries and applications worldwide,<sup>1</sup> such as steel manufacturing, construction, water treatment, mineral processing, and others. Given its very low toxicity and mild basic properties,<sup>2,3</sup> Ca(OH)<sub>2</sub> is also widely used in the food industry.<sup>4</sup> The production of Ca(OH)<sub>2</sub> is currently performed through a two-step process, involving (1) the calcination of limestone to give lime, CaO (eqn (1) and (2))<sup>5</sup> its subsequent hydration “slaking” (eqn (2)).<sup>1,6</sup>



<sup>a</sup> Department of Materials Science & Engineering, University of Sheffield, S1 3JD, Sheffield, UK. E-mail: [t.hanein@sheffield.ac.uk](mailto:t.hanein@sheffield.ac.uk), [h.kinoshita@sheffield.ac.uk](mailto:h.kinoshita@sheffield.ac.uk), [marco.simoni.w@gmail.com](mailto:marco.simoni.w@gmail.com)

<sup>b</sup> Collegium Basilea, Institute of Advanced Study, Hochstrasse 51, 4053 Basel, Switzerland

<sup>c</sup> CEMEX Asia Research AG, Römerstrasse 13, 2555 Brügg, Switzerland

<sup>d</sup> CEMEX Operaciones Mexico, Constitution 444 pte. Monterrey, Mexico

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d2cp01412b>


In the slaked lime manufacturing process, the calcination of limestone represents the most energy-demanding and CO<sub>2</sub> emitting step; it is conducted in several types of firing kilns,<sup>1</sup> and it leads to the release of the process CO<sub>2</sub> from the decarbonisation stoichiometry (eqn (1)), and fuel-derived CO<sub>2</sub> by combustion of fossil fuels used to heat the kiln to provide the firing temperature required (between 800 and 1200 °C).<sup>7,8</sup> The following step 2 (eqn (2)) mainly requires electrical energy input, to handle and mix the reactants and products of this exothermic hydration process.<sup>1</sup> Therefore, the efficiency linked to the energy usage within a given kiln plays a crucial role in defining the overall sustainability of the process; multiple factors may influence the energy input and the resulting efficiency for a given kiln type, such as the quality and the particle size of the limestone feed, the degree of conversion desired, and the moisture.<sup>9</sup> About 1.0–1.8 kg of CO<sub>2</sub> are emitted per kg of lime produced,<sup>1</sup> and given the worldwide annual production (over 70 Mt in 2020<sup>10</sup>), the lime industry is a significant emitter of greenhouse gases (GHG) which are the main contributors to global warming.

Intense efforts and significant investment from this industry are needed to mitigate the emissions of CO<sub>2</sub> to the atmosphere.



Considering the calcination of limestone in a broader sense, such a process is also the basis of the Portland cement production industry; over 6 Gt of limestone are annually processed to satisfy the cement market (over 4 Gt in 2018<sup>11</sup>), resulting in about 3–4 Gt of CO<sub>2</sub> emitted from chemical and fuel contributions combined ( $\approx 4\%$  of the total anthropogenic emissions<sup>12,13</sup>). Given the size of both the lime and cement market worldwide, the validation of a more sustainable limestone decarbonisation route would be a significant contribution to meet the goal (overall 86% CO<sub>2</sub> emissions cut by 2050) set and agreed by the United Nations.<sup>8,14,15</sup>

Our previous work demonstrated the technical feasibility of an alternative route to decarbonisation of limestone, achieved at ambient conditions without heating.<sup>16</sup> The process is based on the reaction between CaCO<sub>3</sub> particles and highly concentrated NaOH solutions to produce Ca(OH)<sub>2</sub> and Na<sub>2</sub>CO<sub>3</sub>·H<sub>2</sub>O or Na<sub>2</sub>CO<sub>3</sub>, allowing for the decarbonisation directly from the solid limestone and simultaneous sequestration of CO<sub>2</sub> into stable mineral forms (eqn (3)).



This process is particularly beneficial because it does not require the combustion of fuels and avoids the associated CO<sub>2</sub> emissions, while the process CO<sub>2</sub> embodied in CaCO<sub>3</sub> is sequestered as Na<sub>2</sub>CO<sub>3</sub>·H<sub>2</sub>O or Na<sub>2</sub>CO<sub>3</sub>. Our previous study also highlighted the feasibility of applying this process to impure industrial grade limestone with significant silica content.<sup>16</sup>

It is well known that the overall reaction rate in heterogeneous systems would depend on the reaction rate of the involved chemical reactions and the thickness of the product surface layer,<sup>17</sup> according to the un-reacted core model.<sup>18,19</sup> Both the residence time and the mixing rate might affect the reaction kinetic, since a longer contact between the reactants and a higher turbulence would generally enhance the efficacy of a reaction. It is also true that a greater centrifugal force on the solid particles compared with the liquid phase may also affect the overall reactivity of the components,<sup>20</sup> due to a separation of the phases resulting in a lower contact surface.<sup>21–23</sup> Given that, this work aims to clarify the dependence of the system studied on the stirring rate and residence time, in order to optimise the process with a view toward its industrialisation. It must be mentioned that such a study only represents a preliminary step towards the scale-up of the process, which needs to take into account evident technical difficulties before considering industrial applicability. These issues are mainly linked to the handling of highly-corrosive NaOH solutions, the management of chlorine gas deriving from the enhanced production of the required chemical NaOH, and the adjustment of the processing conditions in accordance with the scaling-up. Although, the liquid stream from the solid chlor-alkali process is a  $\approx 32$  wt% NaOH solution (approximately 12 M),<sup>24</sup> comparable with the concentrations used here. Moreover, the excess of chlorine gas may be water scrubbed, and the resulting solutions may be used for the production of Cl-containing cements<sup>25</sup> for non-reinforced concrete. Considering that over

the 60% of the concrete worldwide is unreinforced,<sup>26</sup> significant proportions of the toxic chlorine gas from the chlor-alkali process might be immobilised upon cementation. Despite the title study aims to investigate the effect of crucial processing conditions, the authors are fully aware that the presented outcomes might fail in representing the system behaviour at larger scale. Although, this preliminary investigation offers that fundamental basic starting point for a more detailed investigation targeting the proper scale-up of the process.

The present study also aims to clarify the equilibrium between the species Na<sub>2</sub>CO<sub>3</sub>·H<sub>2</sub>O and Na<sub>2</sub>CO<sub>3</sub> at the processing conditions considered, since the co-production of Ca(OH)<sub>2</sub> and Na<sub>2</sub>CO<sub>3</sub>·H<sub>2</sub>O implies the need for a following separation of the products, crucial for their individual sale or use, not discussed here. For instance, high Na contents (above 2 wt%) would prevent the use of Ca(OH)<sub>2</sub> for cement production,<sup>27,28</sup> limiting the applicability of this novel technology. Since the solubility of the different species here involved would likely play a key-role for their effective separation, the present study also assessed the precipitation of the by-product Na<sub>2</sub>CO<sub>3</sub>·H<sub>2</sub>O or Na<sub>2</sub>CO<sub>3</sub> ( $x = 0, 1$  in eqn (3), respectively) depending on the reaction conditions used. Finally, solid particles of an industrial grade chalk are reacted to quantify the reaction progress by visual tracking of the products surface layer *via* SEM-EDX analyses.

## 2. Materials and methods

### 2.1. Materials

The materials used in this work included commercial grade chemicals: Sigma-Aldrich CaCO<sub>3</sub> ( $\geq 99\%$ ) and Honeywell Fluka NaOH ( $\geq 97\%$ ). Additionally, the same industrial grade chalk used in a previous study were also considered as a source of CaCO<sub>3</sub>,<sup>16</sup> the oxide elemental composition is reported in Table 1 below. A dry-state Particle Size Distribution (PSD) analysis was chosen for targeted samples, in order to avoid the dissolution of the solids at any extent. About 10 g of material was used for the analysis, and the value reported for each sample is an average of 10 consecutive measurements.

### 2.2. Experimental procedure

Given the high conversion extent observed in a previous study<sup>15</sup> for the ternary system of 27.1 wt% CaCO<sub>3</sub>, 32.4 wt% NaOH, and 40.5 wt% H<sub>2</sub>O, this starting composition was considered in the following experiments to assess the effect of varying selected parameters on the reaction efficiency. First, NaOH was mixed with distilled water, resulting in a temperature increase of the system to  $\sim 80$  °C due to the exothermic dissolution reaction. The solutions were then heated to 90 °C in a PTFE beaker with a volume of 6.5 cm<sup>3</sup>, to achieve an identical initial temperature

**Table 1** Elemental oxide composition (wt%) of the solid chalk used in the present work, including Loss On Ignition (LOI%) value

	CaO	SiO <sub>2</sub>	Al <sub>2</sub> O <sub>3</sub>	Fe <sub>2</sub> O <sub>3</sub>	K <sub>2</sub> O	MgO	Others	LOI%
Wt%	44.0	21.0	3.0	1.1	0.6	0.3	<2.0%	29.5



for all experimental runs; following this, 10 g of  $\text{CaCO}_3$  were introduced and no further temperature control was applied as the reaction was allowed to progress under laboratory ambient conditions ( $T \approx 20^\circ\text{C}$ ). To ensure mixing, a PTFE centrifugal stirrer shaft (flat propeller, diameter 4 cm) was used with a Heidolph RZR 2020 overhead mixer, rotating in the bottom centre of the PTFE beaker. The use of PTFE was essential to avoid corrosion that may be caused by the hyper-alkaline NaOH solutions used. To study the effect of the mixing rate on the reaction efficiency, a series of experiments were carried out at each of 40, 300, 500, 800 and 2000 rpm for durations of 30, 300, 720, and 1200 s. The conditions used for each sample are reported in Appendix. After the desired duration of reaction, 50 mL of methanol was added and the whole paste was stirred for 300 s to wash by dissolving any unreacted NaOH (NaOH solubility in methanol =  $238\text{ g L}^{-1}$ <sup>29</sup>). The very low solubility of  $\text{Ca(OH)}_2$ ,<sup>3</sup>  $\text{CaCO}_3$ ,<sup>30</sup>  $\text{Na}_2\text{CO}_3\cdot\text{H}_2\text{O}$ ,<sup>31</sup> and  $\text{Na}_2\text{CO}_3$ <sup>31</sup> in methanol allows these solids to remain in the system without being lost during the washing.

The reagent grade chalk was reacted at slightly milder mixing regime, to better preserve the condition of the products. The reaction was performed in a plastic vessel with a magnetic stirring of 300 rpm for a total residence time of 300 s. 8.4 g of NaOH were added into 12.3 g of  $\text{H}_2\text{O}$  to form 17 M NaOH solution, and the solution was cooled down to room temperature before adding 2.5 g of chalk, making the initial system of  $\text{H}_2\text{O}$  (54.7 wt%), NaOH (37.2 wt%) and chalk (8.1 wt%). A significantly high water-to-solid ratio was chosen to ensure a satisfactory mixing of all the reactants, with the less energetic stirring; anyway, the chosen composition has been tested on reagent grade  $\text{CaCO}_3$  already, and it led to an almost total conversion to products.<sup>16</sup> After five minutes of reaction, 32 mL of methanol was added to the resulting paste and stirred for five minutes in order to remove any remaining NaOH.

Following their collection by vacuum filtration, all the solid products here discussed were dried in an  $80^\circ\text{C}$  oven for 2 hours; following, the samples selected for TG and XRD analyses were finely ground and sieved below  $63\ \mu\text{m}$ . For the SEM analysis, selected samples were ground or not, to observe the targeted parameters discussed below.

### 2.3. Characterisation techniques

**2.3.1. X-ray diffraction (XRD).** X-Ray diffraction (XRD) was used to qualitatively identify the reaction products of the reaction. The analysis was conducted by using a Bruker D2 PHASER desktop X-ray diffractometer in Bragg–Brentano geometry, with a  $\text{Cu-K}\alpha$  radiation source running at 30 kV and 10 mA, a one-dimensional LYNXEYE detector, and a 1 mm divergence slit. All the samples were powders, and they were loaded onto sample holders with a diameter and depth of 2.5 cm and 1 mm, respectively. All the analyses were conducted between  $5^\circ$  and  $80^\circ 2\theta$ , with a step size of  $0.02^\circ$  at 0.5 seconds per step; the stage was set to rotate at 15 rpm. Qualitative phase identification was carried out using the Highscore-Plus software and the PDF-4 2019 database.

**2.3.2. Thermogravimetry (TG/DTG).** Thermogravimetric analysis (TGA) was carried out by sampling about 40 mg of

products to be analysed on a PerkinElmer TGA 4000 from  $30^\circ\text{C}$  to  $800^\circ\text{C}$  at a heating rate of  $10^\circ\text{C min}^{-1}$  with a  $40\text{ mL min}^{-1}$   $\text{N}_2$  flow. The temperature was kept at  $800^\circ\text{C}$  for 1 hour to ensure complete loss of  $\text{CO}_2$  from  $\text{CaCO}_3$ . To identify evolving gases, a Hiden mass spectrometer (HPR-20 GIC EGA) was used to record the signals for  $\text{H}_2\text{O}$  and  $\text{CO}_2$ , the only gases involved here. The reaction efficiency  $\alpha$ , only reflecting the fraction of  $\text{CaCO}_3$  converted to  $\text{Ca(OH)}_2$ , was calculated from the weight loss in the temperature ranges for the thermal decomposition of  $\text{Ca(OH)}_2$  ( $310\text{--}470^\circ\text{C}$ <sup>32</sup>) and  $\text{CaCO}_3$  ( $560\text{--}800^\circ\text{C}$ <sup>33</sup>), as reported in Fig. 1 and eqn (4).

$$\alpha = \frac{w\%_{[\text{Ca(OH)}_2]}}{\text{MW}_{\text{Ca(OH)}_2} \left( \frac{w\%_{\text{Ca(OH)}_2}}{\text{MW}_{\text{Ca(OH)}_2}} + \frac{w\%_{[\text{CaCO}_3]}}{\text{MW}_{\text{CaCO}_3}} \right)} \quad (4)$$

The content of  $\text{Na}_2\text{CO}_3\cdot\text{H}_2\text{O}$  could similarly be estimated from mass loss in the temperature range  $50\text{--}130^\circ\text{C}$ <sup>34</sup> (Fig. 1). The measurement was repeated 6 times for each sample to estimate the measurement error ( $\pm 0.16\text{ wt\%}$ ,  $\pm 0.10\text{ wt\%}$  and  $\pm 0.16\text{ wt\%}$  for  $\text{Na}_2\text{CO}_3\cdot\text{H}_2\text{O}$ ,  $\text{Ca(OH)}_2$  and  $\text{CaCO}_3$ , respectively).

**2.3.3. Scanning electron microscopy (SEM).** A Hitachi TM3030 scanning electron microscope with energy-dispersive X-ray spectroscopy (SEM-EDX) was used to gain a deeper insight on the penetration of sodium upon reaction. The solids were mounted in epoxy resin without crushing and left to harden for 72 hours. The analysis surface was ground and polished with progressively finer abrasives, up to a  $1\ \mu\text{m}$  finish,<sup>35</sup> in addition, the samples were polished on cashmere polishing cloths by using diamond pastes of 6, 3, 2, 1 and  $0.25\ \mu\text{m}$  (MetPrep). The samples then underwent a three-step carbon coating and were back-loaded to a metallic holder. Electrically conductive silver paint (RS Components) was applied at the metallic base-epoxy-resin interface to ensure sufficient conductivity and good quality of the SEM images, collected at a working distance of

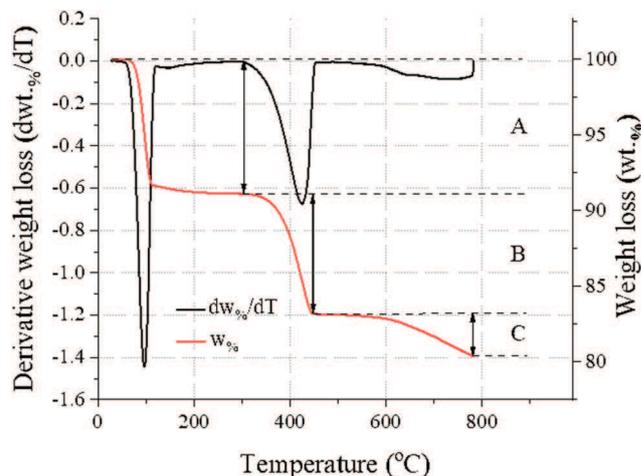


Fig. 1 Generic temperature-trend from the TG (wt%) and DTG data ( $dw\%/dT$ ), showing the weight loss events of the sample associated with:  $\text{Na}_2\text{CO}_3\cdot\text{H}_2\text{O}$  (A),  $\text{Ca(OH)}_2$  (B), and  $\text{CaCO}_3$  (C).



7.4 ± 0.1 mm. Separately, selected samples were crushed and sieved to targeted size ranges and attached to conductive carbon adhesive tapes (Agar Scientific).

### 3. Results and discussion

#### 3.1. Reaction products

The system under consideration shows a good capability to convert  $\text{CaCO}_3$  to  $\text{Ca(OH)}_2$ ,  $\text{Na}_2\text{CO}_3 \cdot \text{H}_2\text{O}$ , and  $\text{Na}_2\text{CO}_3$ ;<sup>16</sup> here, the series of samples mixed at 300 rpm for all the residence times considered was taken as a representative baseline. The XRD analysis (Fig. 2) showed the presence of only  $\text{CaCO}_3$ ,  $\text{Ca(OH)}_2$ ,  $\text{Na}_2\text{CO}_3 \cdot \text{H}_2\text{O}$  and  $\text{Na}_2\text{CO}_3$ , with respective main reflection angles  $2\theta$  of 29.5°, 18.1°, 17.1°, and 30.2°, within the solid products.

Specifically, the intensity of the peaks linked to  $\text{Ca(OH)}_2$  and  $\text{Na}_2\text{CO}_3 \cdot \text{H}_2\text{O}$  was increasing at longer residence times, while  $\text{CaCO}_3$  content appeared to decrease; in addition, the signals linked to  $\text{Na}_2\text{CO}_3$  could be detected at residence times of up to 300 seconds, while at longer ones those were not observable. The relative proportions of  $\text{Na}_2\text{CO}_3 \cdot \text{H}_2\text{O}$  and  $\text{Na}_2\text{CO}_3$  will be discussed in detail in Section 3.3.

In accordance with the XRD outcomes, the TG/dTG analysis of the same baseline samples (Fig. 3) showed increasing weight losses in the temperature intervals 50–130 °C and 310–470 °C, referring to  $\text{Na}_2\text{CO}_3 \cdot \text{H}_2\text{O}$ <sup>34</sup> and  $\text{Ca(OH)}_2$ ,<sup>32</sup> respectively, and a decreasing  $\text{CaCO}_3$  content (560–800 °C<sup>33</sup>) at longer residence times.

The quantification of phases from the TG analysis (Fig. 3) is reported in Fig. 4A. The amount of  $\text{Na}_2\text{CO}_3$  could not be directly quantified, since its thermal decomposition would occur above 851 °C<sup>36</sup> and the analysis was conducted up to 800 °C. However, the quantification of  $\text{Na}_2\text{CO}_3$  could be performed indirectly by taking into account the difference between the total (100%) and the sum of the other phases ( $\text{CaCO}_3$ ,  $\text{Ca(OH)}_2$ , and  $\text{Na}_2\text{CO}_3 \cdot \text{H}_2\text{O}$ ). This approach could be considered reliable, since the XRD analysis confirmed the presence of the only phases  $\text{CaCO}_3$ ,  $\text{Ca(OH)}_2$ ,  $\text{Na}_2\text{CO}_3 \cdot \text{H}_2\text{O}$ , and  $\text{Na}_2\text{CO}_3$  in the solid system (Fig. 2).

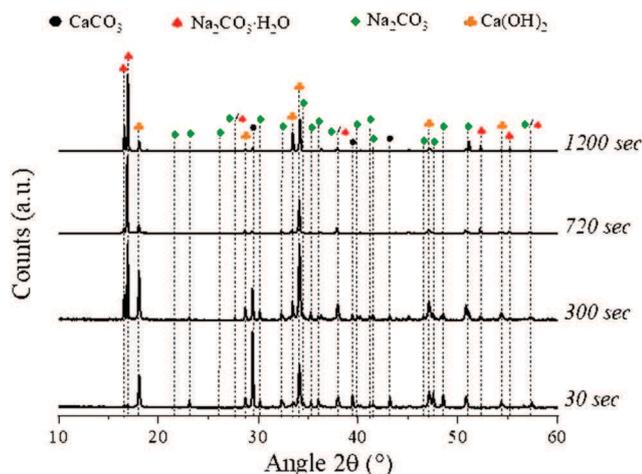


Fig. 2 XRD patterns of the samples obtained at 300 rpm for all the residence times investigated, highlighting the peaks of all the species detected.

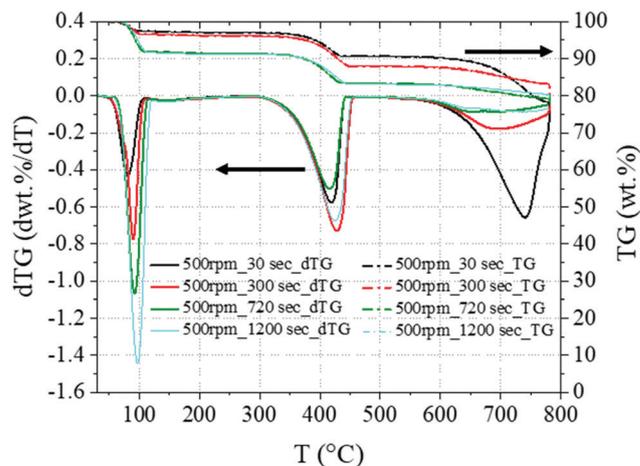


Fig. 3 TG and dTG analysis performed on the baseline series 500rpm\_30–1200 s, showing the weight losses in the regions 50–130 °C, 310–470° and 560–800 °C which are assigned to  $\text{Na}_2\text{CO}_3 \cdot \text{H}_2\text{O}$ ,  $\text{Ca(OH)}_2$  and  $\text{CaCO}_3$ , respectively. The black arrows clarify the axes referred to the data shown.

The XRD analysis also suggested the absence of any amorphous phase since no raised baseline was detected in any pattern (Fig. 2). In addition, the weight uptake resulting from the incorporation of  $\text{Na}^+$  and  $\text{OH}^-$  ions from the solution may be used as a further confirmation of the phases detected by XRD and their quantification by TG. This value was calculated for each system by considering the ratio between the final measured weight of the dried products and the initial weight of  $\text{CaCO}_3$ . The weight uptake can represent the extent of reaction, assuming that any residual  $\text{NaOH}$  is removed from the system after washing. Such an assumption appeared to be confirmed by the absence of the  $\text{NaOH}$  characteristic peak at  $2\theta = 16^\circ$ <sup>37</sup> in the XRD analysis reported in Fig. 2. Fig. 4B shows the experimental weights registered for the representative series of samples, together with the theoretical lines that would result from the quantitative precipitation of  $\text{Na}_2\text{CO}_3 \cdot \text{H}_2\text{O}$  or  $\text{Na}_2\text{CO}_3$ .

#### 3.2. Effect of stirring rate

The characterisation performed on all samples allowed for the determination of the effect on the reaction extent linked to the stirring rate. A Ca mass balance was performed for all the samples discussed here, in order to validate the results from TG analysis; the difference between the inbound ( $\text{CaCO}_3$ ) and outbound ( $\text{Ca(OH)}_2$  and  $\text{CaCO}_3$ ) calcareous species was considered to do that, revealing oscillations of ±0.2 g of Ca. The Ca mass balance supported the TG analysis, and the specific values for each sample discussed is reported as  $\text{ESI}^\dagger$  alongside an overview of the samples phase compositions gained by TG analysis. The XRD analysis was qualitatively reflecting the quantification performed, considering the decreasing intensity of the main peak related to  $\text{CaCO}_3$  at  $2\theta = 29.5^\circ$  at longer, whereas those related to the products  $\text{Ca(OH)}_2$ ,  $\text{Na}_2\text{CO}_3 \cdot \text{H}_2\text{O}$ , and  $\text{Na}_2\text{CO}_3$  were increasing in intensity (Fig. 5).

The TG quantification reported in Fig. 6 shows the highest conversion at a stirring rate of 40 rpm, while significant



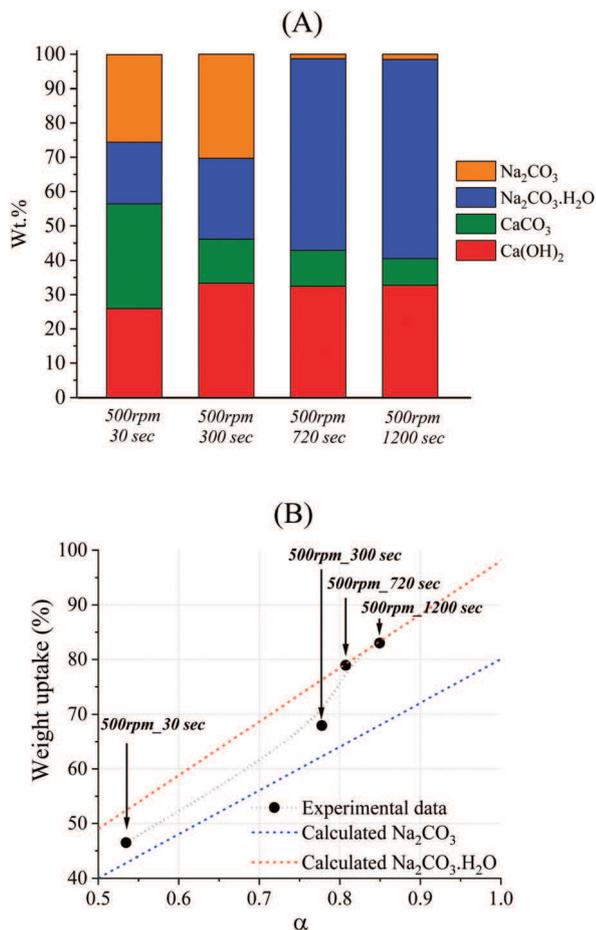


Fig. 4 Phase compositions of the samples reacted at 300 rpm at increasing residence times (A); trend of the weight uptake experimentally observed as a function of conversion (black labels), with lines indicating the relationships that would have been observed if the sodium carbonates were present solely as  $\text{Na}_2\text{CO}_3\cdot\text{H}_2\text{O}$  (red line), or solely as  $\text{Na}_2\text{CO}_3$  (blue line) (B).

efficiency drops were observed at 2000 rpm. The loss of efficiency at increased stirring rate was most notable in those samples reacted for 30 seconds, with an efficiency drop of 34.1% between 40 and 300 rpm observed for this residence time; the impact was reduced at increasing ones. Generally, the increase in reaction extent above 300 seconds was limited.

These outcomes might be justified by physical reasons, as mentioned in Section 1, linked to the significantly different density of a 45 wt% NaOH solution ( $1.42\text{--}1.48\text{ kg dm}^{-3}$ <sup>38</sup>) and the reagent grade  $\text{CaCO}_3$  ( $2.93\text{ kg dm}^{-3}$ <sup>39</sup>). That would be expected to cause a net separation of the liquid and solid phases within the paste at higher stirring rates due to centrifugation effects, leading to a lower contact between the reactants<sup>21–23</sup> and a resulting hindered conversion, as shown in Fig. 7.

Alternatively, the lower conversion registered at higher stirring rates may be linked to the main mechanism ruling the reaction progress; several models were considered, including diffusion, and contracting volume or surface, but a nucleation mechanism was strongly suggested. Fig. 8 shows the fitting

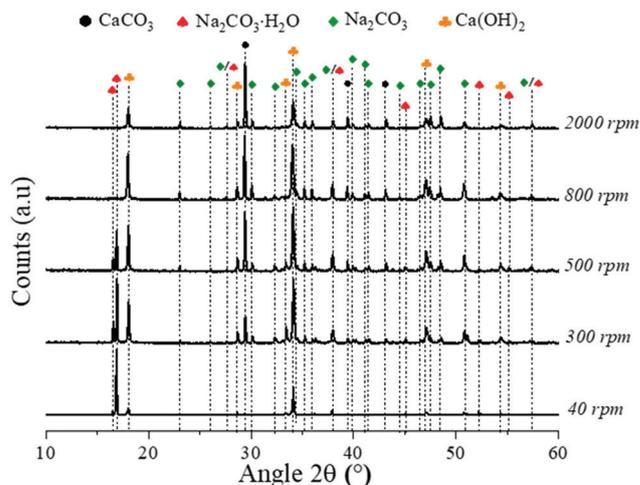


Fig. 5 XRD patterns for the samples reacted for 300 seconds as a function of stirring rate.

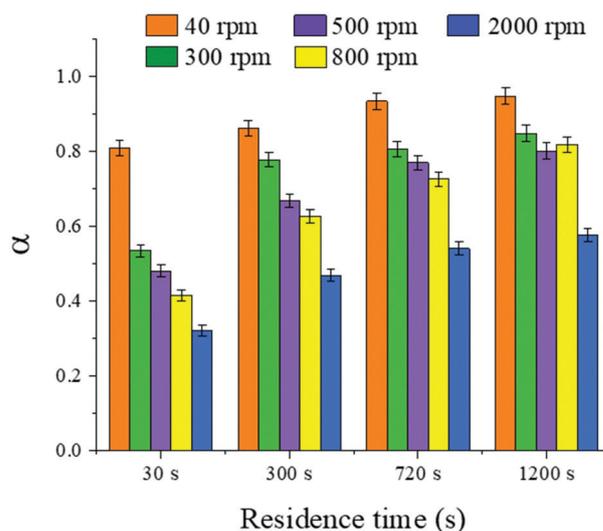


Fig. 6 Conversion extents obtained at each residence time and stirring rate investigated.

between the whole set of experimental data reported here and the nucleation model proposed by Avrami–Erofeyev;<sup>40</sup> it is reflected in eqn (5), where  $k$  and  $\alpha$  identify the kinetic constant and the conversion extent of the reaction, respectively and its integrated form (eqn (6)).

$$f(\alpha) = \left(\frac{1}{k}\right) \left(\frac{\delta\alpha}{\delta t}\right) = 3(1-\alpha)[- \ln(1-\alpha)]^2 \quad (5)$$

$$g(\alpha) = [- \ln(1-\alpha)]^3 = kt \quad (6)$$

While  $\alpha$  was calculated from eqn (4), the kinetic constant  $k$  was obtained by dividing  $\alpha$  for the residence time considered; doing this, the kinetic related to the conversion of  $\text{CaCO}_3$  to  $\text{Ca(OH)}_2$  could be outlined, whereas the formation of  $\text{Na}_2\text{CO}_3\cdot\text{H}_2\text{O}$  and  $\text{Na}_2\text{CO}_3$  was not taken into account here. The decarbonisation



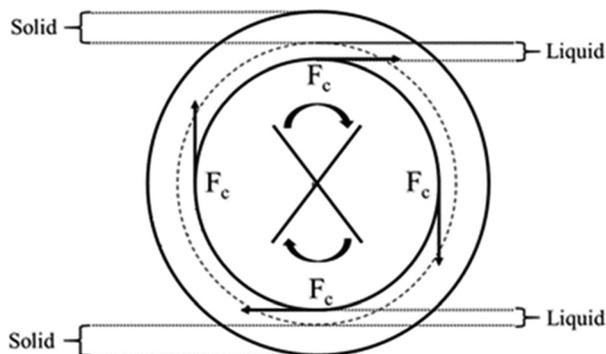


Fig. 7 Schematic representation of the partition occurring between the solid ( $\text{CaCO}_3$ ) and liquid ( $\text{NaOH sol.}$ ) phases at increasing centrifugal force ( $F_c$ ) or stirring rate.

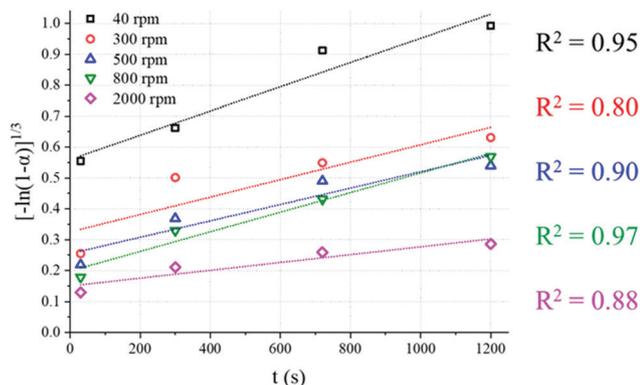


Fig. 8 Fitting between the experimental data for all the samples here discussed and the Avrami–Erofeyev nucleation model represented by eqn (6); the samples were grouped according to the stirring rate used, and  $R^2$  values are highlighted for each one.

rate was significantly decreasing after 30 seconds of reaction, when a maximum rate of  $2.7 \times 10^{-3}$  moles of  $\text{CaCO}_3$  converted

per second was achieved at 40 rpm, over the double than the kinetics observed at 2000 rpm ( $1.2 \text{ moles CaCO}_3 \text{ s}^{-1}$ ). The slower kinetics registered at different rates confirms the need for a precise optimisation aiming to an eventual scale-up.

Given the heterogeneous reaction taken into account here, a nucleation mechanism involves the primary formation of small crystals of the new product phase within large ones of the reactant; this process is thermodynamically unfavourable at first, given the higher free Gibbs energy  $\Delta G^{41}$  linked to the instability of the nuclei formed.<sup>42</sup> Upon achievement of a critical size, the nucleus assumes a more stable configuration, while expanding and incorporating other potential nuclei; nucleation continues until the progression front covers the whole surface of the solid. From here, the nucleation kinetic lowers because of the surface product layer which reduces the contact surface between the reactants.

The effect of stirring rate on the nucleation density and crystal morphology has been empirically accepted in chemical and cast metals industries,<sup>43</sup> and the role of convection in single crystals forming has been widely discussed already.<sup>44,45</sup> Generally, the studies report an enhanced nucleation density in dynamic conditions with respect to static ones,<sup>46</sup> leading to shorter residence times required.<sup>47</sup> Taking into account the high  $R^2$  values reported in Fig. 8 in correlation with the Avrami–Erofeyev model, the present study would introduce controversial outcomes at first sight. In fact, nucleation appears to be hindered at higher stirring rates, when the collisions between the reactants and the formation of surface irregularities and cracks should statistically be more frequent. Such a controversial observation might be likely explained by considering an enhanced partition of the solid and liquid bulks at higher stirring rates,<sup>22</sup> preventing further contact and reaction progression (Fig. 7). In other words, despite the higher turbulence, the entropy of the system would lower as a consequence of the hindered contact between solid and liquid reactants, reflecting a higher  $\Delta G$  at faster stirring rates. Such an effect could be further increased by the eventual distorted expansion of the

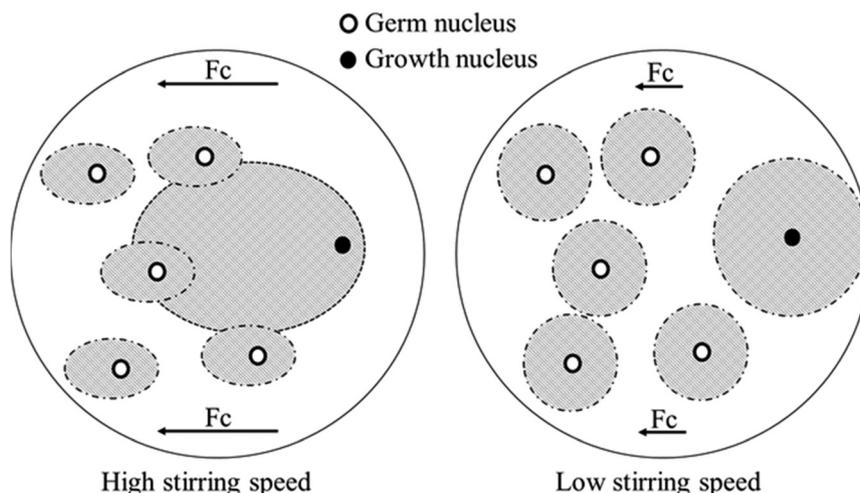




Fig. 9 Schematic representation of the nucleation front progression (grey pattern) occurring at high (left) and low (right) stirring rates.



nuclei undergoing axial centrifugal forces  $F_c$ ,<sup>48</sup> as also outlined in Fig. 9.

### 3.3. Equilibrium between $\text{Na}_2\text{CO}_3 \cdot \text{H}_2\text{O}$ and $\text{Na}_2\text{CO}_3$

As mentioned in Section 1, an effective separation of the products will be required upon reaction, and it may likely involve their dissolution in water or solvent. The separation would likely exploit the different solubility of  $\text{Ca}(\text{OH})_2$ ,  $\text{Na}_2\text{CO}_3 \cdot \text{H}_2\text{O}$ , and  $\text{Na}_2\text{CO}_3$ , and the understanding of the equilibrium between  $\text{Na}_2\text{CO}_3 \cdot \text{H}_2\text{O}$  and  $\text{Na}_2\text{CO}_3$  could dictate the optimal processing conditions. The proportioning of  $\text{Na}_2\text{CO}_3 \cdot \text{H}_2\text{O}$  and  $\text{Na}_2\text{CO}_3$  at different stirring rates and residence times has been here assessed, and useful information has been provided for an eventual scale-up of the process. Together with the phase quantification performed by TG, the XRD analysis confirmed the enhanced formation of  $\text{Na}_2\text{CO}_3 \cdot \text{H}_2\text{O}$  with respect to  $\text{Na}_2\text{CO}_3$  up to a stirring rate of 800 rpm (Fig. 5) and at increasing residence times (Fig. 2). To gain further insight, the behaviour of  $\text{Na}_2\text{CO}_3 \cdot \text{H}_2\text{O}$  and  $\text{Na}_2\text{CO}_3$  in the  $\text{Na}_2\text{CO}_3$ - $\text{NaOH}$ - $\text{H}_2\text{O}$  system was studied using PHREEQC – PH REDox EQUilibrium (in C language), a geochemical modelling software simulating a variety of reactions and processes at equilibrium,<sup>49</sup> in particular focusing on the activity of water. The simulation was performed at 20, 60 and 100 °C; both  $\text{Na}_2\text{CO}_3 \cdot \text{H}_2\text{O}$  (0.1 mol) and  $\text{Na}_2\text{CO}_3$  (0.1 mol) were initially introduced into 100 mL of pure water, and NaOH was added in successive steps up to 20 M; given the high NaOH concentrations taken into account, the Pitzer model was used here.<sup>50</sup> The  $\text{Na}_2\text{CO}_3 \cdot \text{H}_2\text{O}$  and  $\text{Na}_2\text{CO}_3$  phases were specified by the equilibria reported below in eqn (7) and (8), respectively, while the total 2 moles of NaOH additions were performed in 20 steps up to a molality of 20 (2 moles NaOH in 0.1 kg  $\text{H}_2\text{O}$ ).



Precipitate compositions were then determined as a function of water activity, Fig. 10B, where the highest concentrations of NaOH correspond to the lowest calculated water activities (Fig. 10A). The simulation revealed the favourable ranges of the activity of water ( $a_{\text{H}_2\text{O}}$ ) for the precipitation of  $\text{Na}_2\text{CO}_3 \cdot \text{H}_2\text{O}$  ( $0.6 < a_{\text{H}_2\text{O}} < 0.8$ ) and  $\text{Na}_2\text{CO}_3$  ( $a_{\text{H}_2\text{O}} < 0.6$ ), as shown in Fig. 10B. Increasing NaOH concentrations would lead to a higher viscosity<sup>51,52</sup> while the activity of water would be significantly reduced<sup>53–55</sup> (Fig. 10A).

Additionally, given the stoichiometry of the reaction (eqn (3)), and considering the concentration of dissolved  $\text{Ca}^{2+}$  to be negligible under these highly alkaline conditions due to the limited solubility of  $\text{Ca}(\text{OH})_2$ , the final  $\text{OH}^-$  concentration would depend on the consumption of NaOH to convert  $\text{CaCO}_3$  to products. In other words, a higher conversion would lead to lower final  $\text{OH}^-$  concentrations, as outlined by the experimental data reported in Fig. 11.

Following the quantification of the solid phase species within the system, the molar proportion of  $\text{Na}_2\text{CO}_3 \cdot \text{H}_2\text{O}$  formed

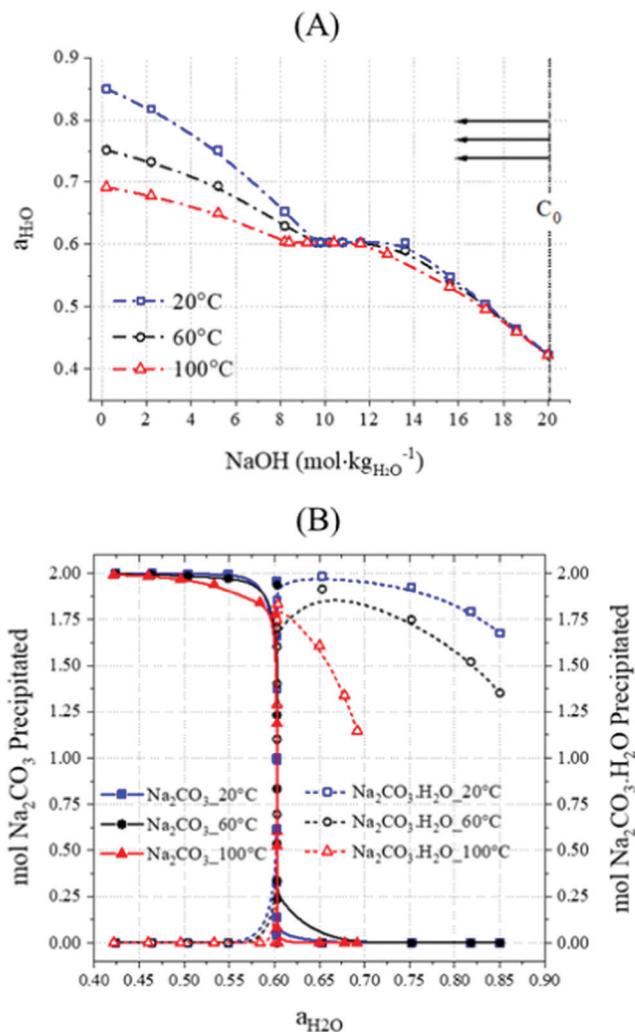


Fig. 10 PHREEQC simulation showing (A) the activity of water as a function of NaOH molalities at 20, 60 and 100 °C in a system with 100 g, 106 g, and 124 g of  $\text{H}_2\text{O}$ ,  $\text{Na}_2\text{CO}_3 \cdot \text{H}_2\text{O}$ , and  $\text{Na}_2\text{CO}_3$ , respectively, and (B) precipitated moles of  $\text{Na}_2\text{CO}_3 \cdot \text{H}_2\text{O}$  and  $\text{Na}_2\text{CO}_3$  at 20, 60 and 100 °C; the initial NaOH concentration of the solutions used for this set of samples is labelled as  $C_0$ .

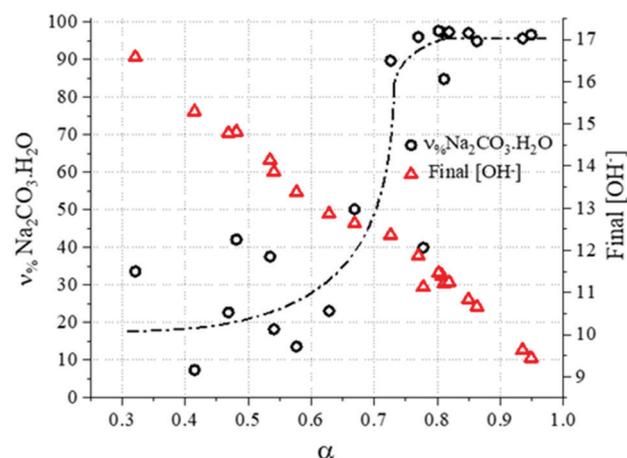


Fig. 11  $v_{\%} \text{Na}_2\text{CO}_3 \cdot \text{H}_2\text{O}$  values and final  $\text{OH}^-$  concentration, experimentally determined as a function of conversion.



in the binary system  $\text{Na}_2\text{CO}_3\cdot\text{H}_2\text{O}/\text{Na}_2\text{CO}_3$  can be calculated. Doing this, it was possible to observe that  $\text{Na}_2\text{CO}_3$  was dominantly forming at the early stage of the reaction (or when the progress of the reaction is limited) because of the low activity of water due to the high concentration of  $\text{NaOH}$  in the system (Fig. 11). However, as the reaction progresses, the formation of  $\text{Na}_2\text{CO}_3\cdot\text{H}_2\text{O}$  may have been enhanced by the rising  $\text{H}_2\text{O}$  activity due to the consumption of  $\text{NaOH}$ , as shown in eqn (3). This would explain the higher contents of  $\text{Na}_2\text{CO}_3$  in the systems with a limited progress of the reaction, corresponding to shorter residence times (Fig. 4A) or faster stirring rates (Fig. 5). These outcomes are in accordance with the thermodynamic trends reported in Fig. 10B.

### 3.4. $\text{CO}_2$ capture

The quantification of  $\text{Na}_2\text{CO}_3\cdot\text{H}_2\text{O}$  and  $\text{Na}_2\text{CO}_3$  also allowed to calculate the fraction of  $\text{CO}_2$  trapped out of the initial amount introduced as  $\text{CaCO}_3$ , and to outline the  $\text{CO}_2$  capture rate. Eqn (9) outlines the mass balance for  $\text{CO}_2$  upon reaction, taking into account the initial  $\text{CO}_2$  introduced with  $\text{CaCO}_3$  ( $g\text{CO}_{2,\text{Initial}}$ ), the fraction of  $\text{CO}_2$  captured through precipitation of  $\text{Na}_2\text{CO}_3\cdot\text{H}_2\text{O}$  and  $\text{Na}_2\text{CO}_3$  ( $g\text{CO}_{2,\text{Captured}}$ ), and the  $\text{CO}_2$  embodied into unreacted  $\text{CaCO}_3$  ( $g\text{CO}_{2,\text{Unreacted}}$ ). These parameters were calculated by taking into account  $\text{CO}_2$  fractions of 44.0 wt%, 35.5 wt% and 41.5 wt% for  $\text{CaCO}_3$ ,  $\text{Na}_2\text{CO}_3\cdot\text{H}_2\text{O}$ , and  $\text{Na}_2\text{CO}_3$ , respectively, apart from the sample-specific phase assemblage.

$$g\text{CO}_{2,\text{Initial}} - g\text{CO}_{2,\text{Captured}} = g\text{CO}_{2,\text{Unreacted}} \quad (9)$$

Approximately 4.4 g of  $\text{CO}_2$  are embodied into the initial 10 g of  $\text{CaCO}_3$  powders reacted, and for all the samples the mass balance depicted in eqn (9) was respected with uncertainties of  $\pm 0.1$  g. That may be observed in Fig. 12A, where  $g\text{CO}_{2,\text{Captured}}$  and  $g\text{CO}_{2,\text{Unreacted}}$  are plotted against the residence time for all the samples discussed. It is clear that the reaction between  $\text{CaCO}_3$  and  $\text{NaOH}$  leads to the prompt immobilisation of the

process  $\text{CO}_2$  upon precipitation of  $\text{Na}_2\text{CO}_3\cdot\text{H}_2\text{O}$  and  $\text{Na}_2\text{CO}_3$  (Fig. 12A). The rate of  $\text{CO}_2$  capture, expressed as  $\text{mol}_{\text{CO}_2}$  captured  $\text{s}^{-1}$ , was reflecting the cumulative precipitation rate of  $\text{Na}_2\text{CO}_3\cdot\text{H}_2\text{O}$  and  $\text{Na}_2\text{CO}_3$ ; it is formulated in eqn (10), where the subscripts for the variable  $t$  indicate the consecutive intervals considered.

$$k_{\text{CO}_2 \text{ Captured}} = \frac{[(g\text{CO}_{2,\text{Captured}})_{t_{n+1}} - (g\text{CO}_{2,\text{Captured}})_{t_n}]}{(t_{n+1} - t_n)} \quad (10)$$

The capture rate  $k$ , plotted as  $-\ln k$  in Fig. 12B, was decreasing for all the samples at longer residence times, in line with the limited reaction extent registered above 300 seconds (Fig. 6). The highest  $\text{CO}_2$  capture rate ( $2.7 \times 10^{-3} \text{ mol}_{\text{CO}_2} \text{ s}^{-1}$ ) was registered for the sample reacted at 40 rpm for 30 seconds, and a 94%  $\text{CO}_2$  capture was achieved after 720 seconds of reaction progress at the same stirring rate. The high resemblance with the trends reported in Fig. 6 suggest that the precipitation of  $\text{Ca}(\text{OH})_2$  does not affect the trapping of the process  $\text{CO}_2$  into  $\text{Na}_2\text{CO}_3\cdot\text{H}_2\text{O}$  nor  $\text{Na}_2\text{CO}_3$ , and also reflecting a high accordance to the stoichiometry depicted in eqn (3).

### 3.5. Decarbonisation of industrial grade chalk

Chalk with larger particle sizes were subjected to the same reaction, and the size of the reacting solids was chosen upon sieving. The dry PSD analysis revealed a much higher mean particle diameter ( $D_x(50)$  of 1.29 mm, Fig. 13B) respect with the reagent grade  $\text{CaCO}_3$  ( $D_x(50)$  of 26.6  $\mu\text{m}$ , Fig. 13A); during the analysis, weighted residual and laser obscuration of 3.25% and 2.97%, respectively, were registered. Additionally, both XRF (Table 1) and TG analyses were performed on the solids, upon fine grinding and sieving below 38  $\mu\text{m}$ .

Fig. 14 shows the outcomes of the XRD analysis performed on the ground products; the peaks related to the products  $\text{Ca}(\text{OH})_2$ ,  $\text{Na}_2\text{CO}_3\cdot\text{H}_2\text{O}$ , and  $\text{Na}_2\text{CO}_3$  could be observed in the

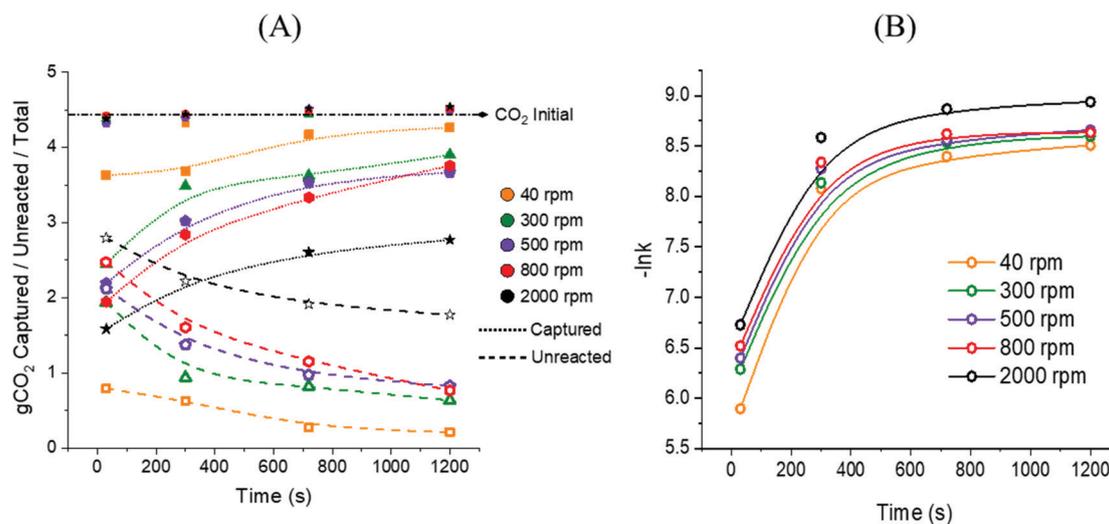


Fig. 12 Trends of  $g\text{CO}_{2,\text{Captured}}$  and  $g\text{CO}_{2,\text{Unreacted}}$  at increasing residence times registered for all the samples discussed here (A);  $\text{CO}_2$  capture rate ( $\text{mol}_{\text{CO}_2}$  Captured  $\text{s}^{-1}$ ) calculated for all the samples from eqn (10) (B).



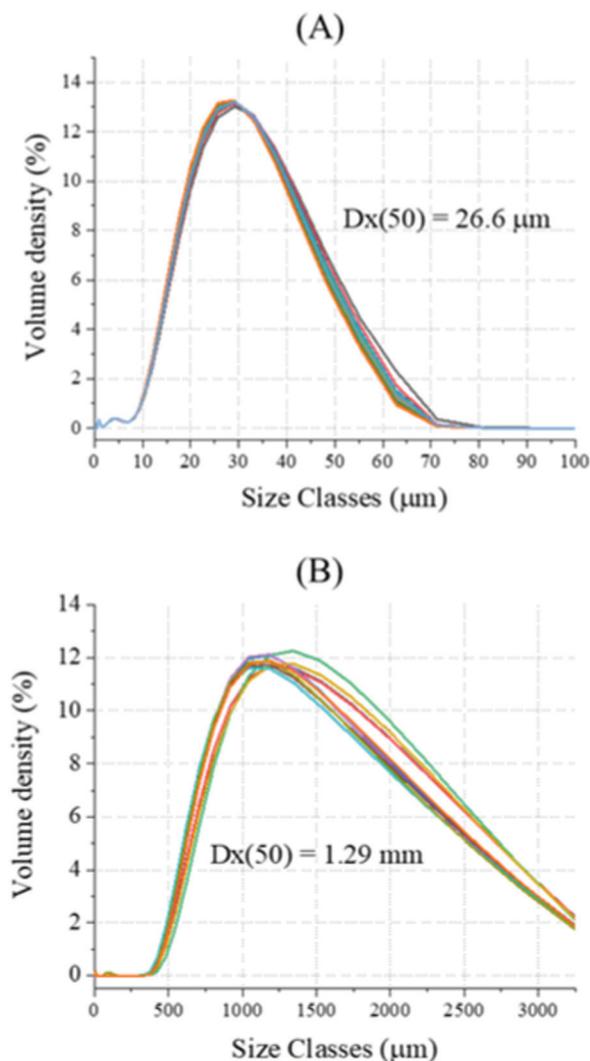


Fig. 13 Dry-state Particle Size Distribution (PSD) analysis was performed on reagent grade  $\text{CaCO}_3$  (A) and industrial grade chalk (B); ten measurements per sample were performed, and the average value was considered.

reacted solids, together with a slight reduction in intensity of  $\text{CaCO}_3$ .

The TG analysis (Fig. 15) reported a total 30.6 wt% loss for the sample, and the extent of reaction  $\alpha$  was estimated to be 0.3, given the contents of  $\text{CaCO}_3$  (53.8 wt%) and  $\text{Ca(OH)}_2$  (17.4 wt%). A 2.3 wt% loss observed in the temperature range of 50–130 °C, likely referring to the dehydration of  $\text{Na}_2\text{CO}_3 \cdot \text{H}_2\text{O}$ , whose content was estimated to be 16 wt%.

The XRD analysis could also reveal traces of  $\text{Na}_2\text{CO}_3$ , which could not be reliably quantified by TG (Section 3.1) because of the significant presence of impurities (Table 1); for the same reason, it was not possible to reliably assess the proportioning between  $\text{Na}_2\text{CO}_3 \cdot \text{H}_2\text{O}$  and  $\text{Na}_2\text{CO}_3$ . It must be mentioned that the large particle size here would significantly affect the yield of the reaction, by largely decreasing the contact surface between the liquid and solid reactants. The DTG curve also shows a small shoulder at 802.7 °C. Based on the XRD analysis (Fig. 14), this could be assigned to the decarbonisation of vaterite, a metastable

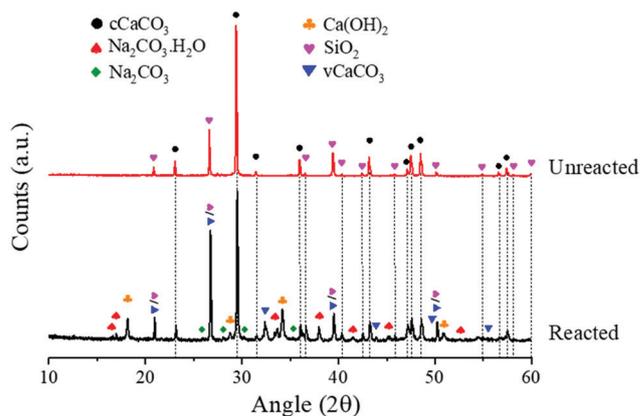


Fig. 14 XRD patterns of the reacted and unreacted industrial grade chalk, with labelled phases  $\text{cCaCO}_3$  (calcite),  $\text{Ca(OH)}_2$ ,  $\text{Na}_2\text{CO}_3 \cdot \text{H}_2\text{O}$ ,  $\text{Na}_2\text{CO}_3$  and  $\text{vCaCO}_3$  (vaterite).

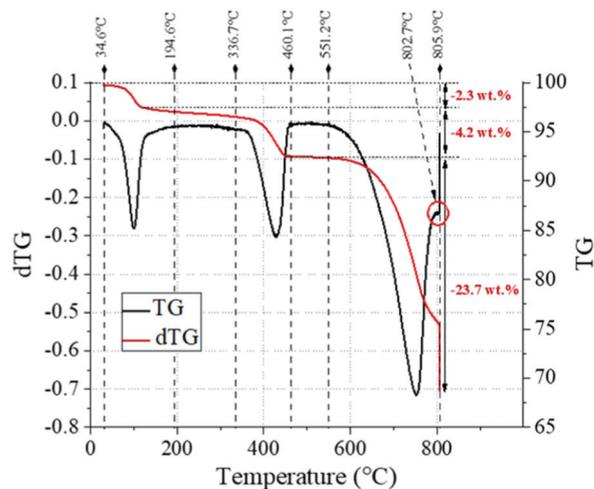


Fig. 15 TG (black line) and DTG (red line) trends for the industrial grade chalk reacted here, highlighting the key temperature ranges and the corresponding weight losses observed.

polymorph of calcite which is often observed during the synthesis of precipitated calcium carbonate,<sup>56–58</sup> and which is seen in the XRD results for the reacted sample in Fig. 14. Fig. 16A–F show the SEM analysis performed on two representative samples taken from the reacted and unreacted chalk solid particles. As expected, Na could only be detected in the reacted particles (Fig. 16B), in line with the formation of  $\text{Na}_2\text{CO}_3 \cdot \text{H}_2\text{O}$  or  $\text{Na}_2\text{CO}_3$ , and higher signals were detected towards the external sections of the solid bead; such a detail will be discussed below, where the EDX analysis of a large number of reacted solid particles is taken into account. Here, the EDX quantification of Na was performed with the software Quantax-70 by considering internal and external sections of the solid particles, chosen by taking into account the Na mapping in Fig. 16B, which highlights a sharp change in Na concentration at a depth of about 200  $\mu\text{m}$ .

Specifically, sodium contents of 18.92 wt% and 7.32 wt% were detected in the external and internal sections of the



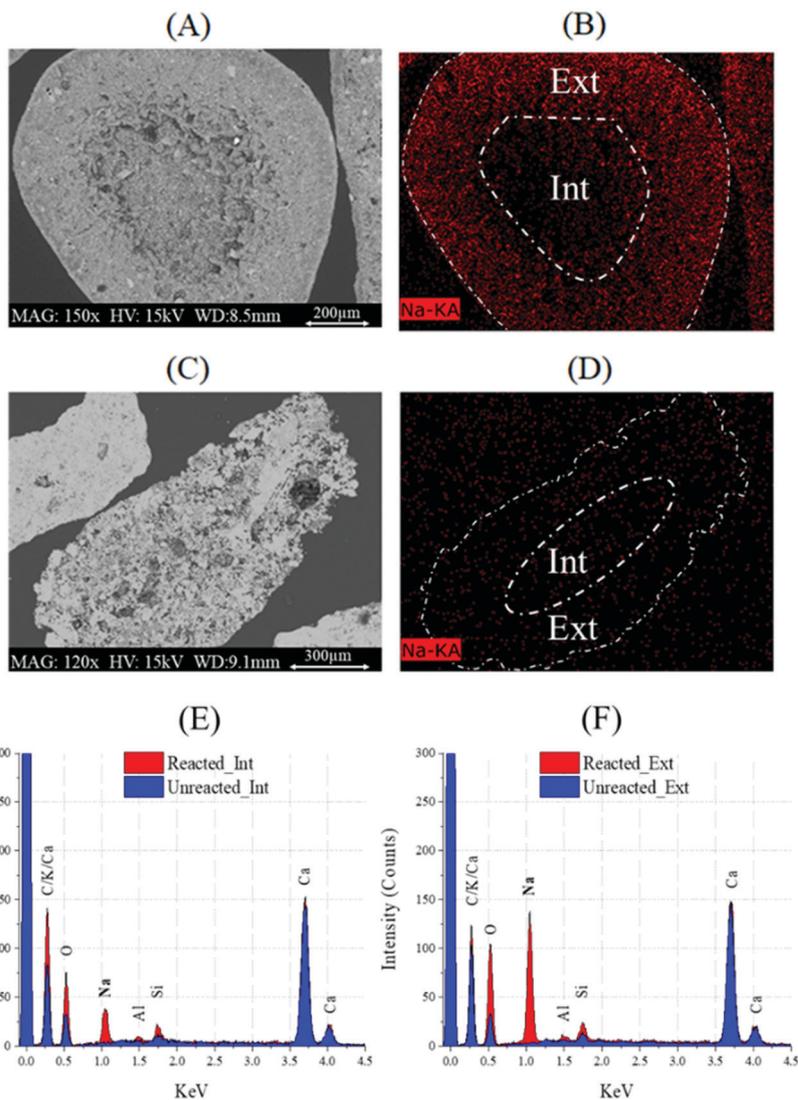


Fig. 16 SEM images of two representative reacted (A) and unreacted (C) solid chalk particles, with respective Na mapping (red highlighted) in (B) and (D), where the external (Ext) and internal (Int) areas discussed in the body text are displayed in white. Dispersive X-Ray (EDX) analysis performed on the (E) unreacted and (F) reacted chalk particles, with maps of the elements Na, Si and Ca.

reacted particle, respectively, whereas negligible sodium contents (0.01–0.06 wt%) could be observed in the unreacted chalk. In any case, the sodium peak seen in Fig. 16B and D is reflected in Fig. 16E and F, where the EDX analysis showed Na signals around 1 keV; as observed, no signals linked to Na could be detected for the unreacted particle, while a significant gap was observed between the external and internal sections of the reacted one. Moreover, rather homogeneous distribution of Ca (Fig. 17C, D and 18C, D) is observed, with slightly higher contents in the internal regions respect with the external ones. That is an expected result, since the stoichiometry of the reaction would lead to an overall weight increase given the reactant ( $\text{CaCO}_3$ ) and products ( $\text{Ca(OH)}_2$ ,  $\text{Na}_2\text{CO}_3 \cdot \text{H}_2\text{O}$ , and  $\text{Na}_2\text{CO}_3$ ) involved (Section 3.1 and Fig. 4B). Despite Ca should not be lost from the solid surface throughout the reaction, as outlined from the Ca mass balance in ESI,<sup>†</sup> the uptake of sodium would result in a final lower Ca proportion in those

local regions where the reaction occurred more extensively. As previously mentioned, the particles undergoing SEM analysis were grouped into two sets by their size:  $700 \leq D \leq 1000 \mu\text{m}$  and  $400 \mu\text{m} \leq (D) \leq 700 \mu\text{m}$ .

In both groups, higher contents of Na could be detected in the peripheral regions of each solid particle, at the solid/liquid interface during the reaction. A significant presence of Na was detected within the particles up to a depth of 150–200  $\mu\text{m}$  on average, as shown in Fig. 17B and 18B. A normalized radius DN was taken into account to display the results, and it was calculated by dividing the punctual length on the radius where the elemental quantification was performed by the total radius of the specific particle. As a DN of 0.5 identifies the centre of the particle, DN of 0 and 1 reflect its extremes; given that, the Na and Ca contents were detected at DN values of 0.0, 0.25, 0.50, 0.75 and 1.0 to better display the gradient observed at gradual depths from the surface. On average of five samples,



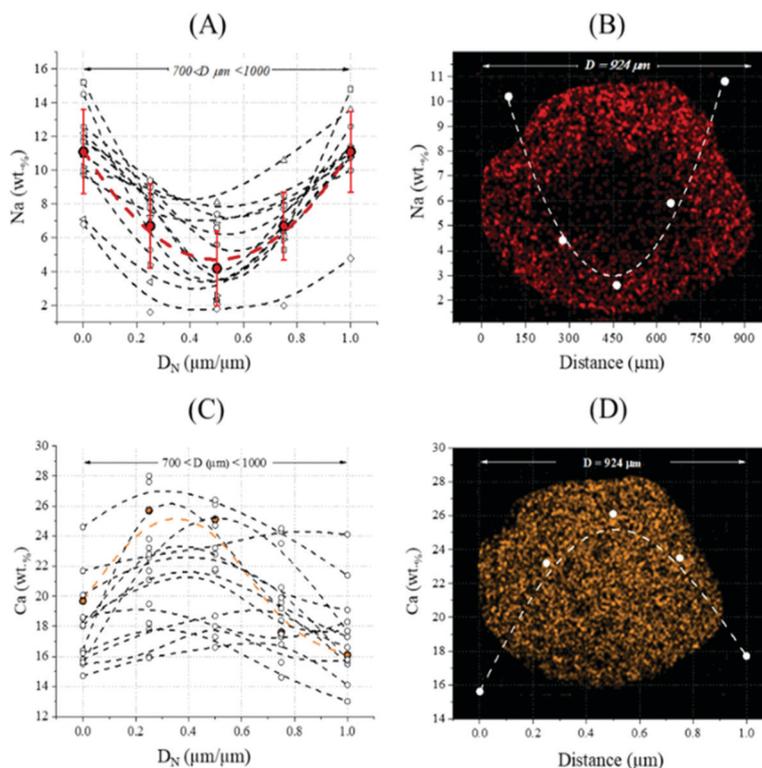


Fig. 17 Na wt% and Ca wt% contents plotted against the normalised particle size considered ( $D_N$ ) for the  $700 \mu\text{m} \leq (D) \leq 1000 \mu\text{m}$  group (A and C, respectively) and their distribution in a  $D = 924 \mu\text{m}$  sample (B and D, respectively).

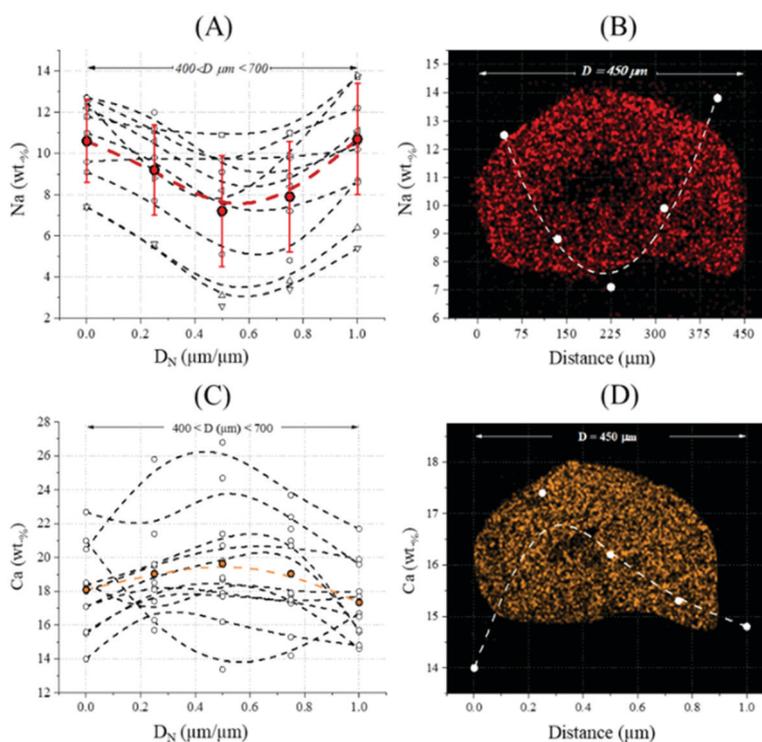


Fig. 18 Na wt% and Ca wt% contents plotted against the normalised length considered for the  $400 \mu\text{m} \leq (D) \leq 700 \mu\text{m}$  group (A and C, respectively); specific Na wt% and Ca wt% gradients registered for a targeted size ( $D = 450 \mu\text{m}$ ) sample (B and D, respectively).



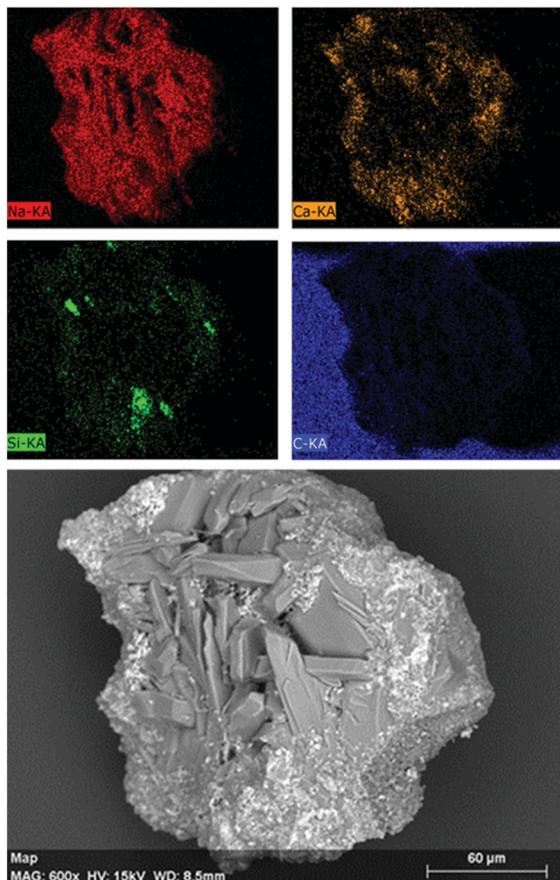


Fig. 19 SEM images of the reaction products from the chalk upon grinding and sieving between 150 and 250  $\mu\text{m}$ ; the samples were attached on conductive carbon adhesive tapes.

Na contents were (wt%) of  $11.1 \pm 2.5$  (DN = 0) and  $4.2 \pm 2.2$  (DN = 0.5) for the larger group of particles, while  $10.6 \pm 2.0$  (DN = 0) and  $7.2 \pm 2.7$  (DN = 0.5) were observed for the smaller particles. Regarding Ca (Fig. 17C, D and 18C, D), slightly higher contents in the inner regions of the solids were observed; the lower local Na content would suggest limited reaction progress into these regions, consistent with the low overall extent of reaction  $\alpha$  of 0.3.

Fig. 19 shows the SEM-EDX analysis performed on a single reacted chalk bead collected upon grinding and sieving between 150 and 250  $\mu\text{m}$ . Pseudo-hexagonal shaped crystals of  $\text{Na}_2\text{CO}_3 \cdot \text{H}_2\text{O}$  and  $\text{Na}_2\text{CO}_3$ <sup>59</sup> are surrounded by small-sized  $\text{Ca}(\text{OH})_2$  crystals, showing a faceted tetrakaidekahedral morphology.<sup>60</sup> As supported by the XRF and XRD analyses reported in Table 1 and Fig. 14, respectively, significant silica agglomerates could also be detected; in the reaction products, those were partially covered by  $\text{Ca}(\text{OH})_2$  layers.

## 4. Conclusions

The study of the reaction of  $\text{CaCO}_3$  in  $\text{NaOH}$  solution allowed for the optimisation of processing parameters such as the residence time and the mixing rate. Close to optimum

conversion could be obtained after 300 seconds of stirring, while further contact between the reactants did not lead to significant yield improvements. A low stirring rate resulted in enhancing the conversion extent. It is likely that the lower conversion achieved at high stirring rates may be linked to enhanced events of nuclei incorporation or the solid/liquid partition at higher centrifugal force. The proportioning of  $\text{Na}_2\text{CO}_3 \cdot \text{H}_2\text{O}$  and  $\text{Na}_2\text{CO}_3$  was found to be largely affected by the activity of water of the system considered; specifically,  $\text{Na}_2\text{CO}_3 \cdot \text{H}_2\text{O}$  and  $\text{Na}_2\text{CO}_3$  were the favoured species in the final systems at higher and lower water activity, respectively. However, the reaction was effectively capturing the process  $\text{CO}_2$  embodied in  $\text{CaCO}_3$ , up to the 95% of the total introduced into the system. The comparison between the SEM-EDX analysis of reacted and unreacted chalk samples suggested the possibility of assessing the reaction extent by detection of Na within the solid products. Assuming so, the reaction progression could be visually observed by detection of Na, whose gradient was defined for the solid reacted particles, and whose propagation was observed up to 150  $\mu\text{m}$  deep from the solid/liquid interface. The lower reaction extent obtained for larger  $\text{CaCO}_3$  solids ( $D \sim 1 \text{ mm}$ ) suggested that this alternative route would require additional grinding to achieve a satisfactory decarbonisation, if compared to the average size of the raw  $\text{CaCO}_3$  feed (2–200  $\mu\text{m}$ ) used in a conventional lime or cement plant.<sup>1</sup> Although, we believe that the additional emissions arising from the higher electrical consumption required for a finer  $\text{CaCO}_3$  would be negligible, if compared with the avoided combustion and process  $\text{CO}_2$ .

In conclusion, the chemical decarbonisation of  $\text{CaCO}_3$  allowed for the nearly total capture of the process  $\text{CO}_2$ , while converting  $\text{CaCO}_3$  to the essential lime. These positive outcomes may be obtained relatively simply, given the mild mixing conditions and heating required; despite that, the use of highly-corrosive  $\text{NaOH}$  solutions requires further investigation for an eventual scale-up.

## Author contributions

Theodore Hanein and Hajime Kinoshita discovered and conceptualized the technology. Theodore Hanein, Hajime Kinoshita, John L. Provis, and Marco Simoni developed the technology and designed the methodology and experiments. Theodore Hanein, Marco Simoni, and Chun Long Woo carried out experiments. Marco Simoni drafted the original manuscript. Theodore Hanein, Hajime Kinoshita, and John L. Provis acquired funding, and supervised Marco Simoni and Chun Long Woo about authorship. Theodore Hanein, Hajime Kinoshita, John Provis, Mark Tyrer, Juan-Carlos Martinez, Magnus Nyberg, Alan Maries, John Stennet and Nestor I. Quintero-Mora reviewed and edited the manuscript.

## Conflicts of interest

The authors declare that they have no competing interests as defined by Physical Chemistry Chemical Physics, or other



interests that might be perceived to influence the interpretation of the article.

## Acknowledgements

This work was funded by the Engineering and Physical Science Research Council (EPSRC) and CEMEX under grant ID EP/R025959/1. The group would also express gratitude to Dr John Stennet for the support and knowledge received.

## References

- 1 F. Schorcht, *et al.*, Best available techniques (BAT) reference document for the production of cement, lime and magnesium oxide. European Commission Joint Research Centre Institute for Prospective Technological Studies (Report EUR 26129 EN), Luxembourg: Publications Office of the European Union, 2013, [https://eippcb.jrc.ec.europa.eu/reference/BREF/CLM\\_Published\\_def.pdf](https://eippcb.jrc.ec.europa.eu/reference/BREF/CLM_Published_def.pdf), DOI: 10.2788/12850.
- 2 P. C. Foreman and I. E. Barnes, A review of calcium hydroxide, *Int. Endod. J.*, 1990, **23**(6), 283–297, DOI: [10.1111/j.1365-2591.1990.tb00108.x](https://doi.org/10.1111/j.1365-2591.1990.tb00108.x).
- 3 A. Farhad and Z. Mohammadi, Calcium hydroxide: a review, *Int. Dent. J.*, 2005, **55**(5), 293–301, DOI: [10.1111/j.1875-595X.2005.tb00326.x](https://doi.org/10.1111/j.1875-595X.2005.tb00326.x).
- 4 A. Dowling, J. O'Dwyer and C. C. Adley, Lime in the lime-light, *J. Cleaner Prod.*, 2015, **92**, 13–22, DOI: [10.1016/j.jclepro.2014.12.047](https://doi.org/10.1016/j.jclepro.2014.12.047).
- 5 G. Habert, *et al.*, Environmental impacts and decarbonization strategies in the cement and concrete industries, *Nat. Rev. Earth Environ.*, 2020, 1–15, DOI: [10.1038/s43017-020-0093-3](https://doi.org/10.1038/s43017-020-0093-3).
- 6 J. A. H. Oates, *Lime and limestone: chemistry and technology, production and uses*, John Wiley & Sons, 2008, ISBN 3-527-29527-5.
- 7 A. S. Gutiérrez, J. B. C. Martínez and C. Vandecasteele, Energy and exergy assessments of a lime shaft kiln., *Appl. Therm. Eng.*, 2013, **51**(1–2), 273–280, DOI: [10.1016/j.applthermaleng.2012.07.013](https://doi.org/10.1016/j.applthermaleng.2012.07.013).
- 8 L. Barcelo, *et al.*, Cement and carbon emissions, *Mater. Struct.*, 2014, **47**(6), 1055–1065, DOI: [10.1617/s11527-013-0114-5](https://doi.org/10.1617/s11527-013-0114-5).
- 9 A. A. Boateng, *Rotary kilns: transport phenomena and transport processes*, Butterworth–Heinemann, 2015, ISBN 978-0-12-803780-5.
- 10 ReportLinker, Global Calcium Hydroxide Industry, October, 2020, [https://www.reportlinker.com/p05956205/?utm\\_source=GNW](https://www.reportlinker.com/p05956205/?utm_source=GNW).
- 11 R. M. Andrew, Global CO<sub>2</sub> emissions from cement production, *Earth Syst. Sci. Data*, 2018, **10**(1), 195–217, DOI: [10.5281/zenodo.831455](https://doi.org/10.5281/zenodo.831455).
- 12 T. Stocker, *Climate change 2013: the physical science basis: Working Group I contribution to the Fifth assessment report of the Intergovernmental Panel on Climate Change*, Cambridge University Press, 2014.
- 13 P. Friedlingstein, *et al.*, Global carbon budget, *Earth Syst. Sci. Data*, 2019, **11**(4), 1783–1838, DOI: [10.5194/essd-11-1783-2019](https://doi.org/10.5194/essd-11-1783-2019).
- 14 J. Rogelj, *et al.*, Paris Agreement climate proposals need a boost to keep warming well below 2C, *Nature*, 2016, **534**(7609), 631, DOI: [10.1038/nature18307](https://doi.org/10.1038/nature18307).
- 15 J. Skea, P. Ekins and M. Winskel, *Energy 2050: Making the transition to a secure low carbon energy system*, Routledge, 2011, ISBN 978-1-84971-084-8.
- 16 T. Hanein, *et al.*, Decarbonisation of calcium carbonate at atmospheric temperatures and pressures, with simultaneous CO<sub>2</sub> capture, through production of sodium carbonate, *Energy Environ. Sci.*, 2021, **14**(12), 6595–6604, DOI: [10.1039/D1EE02637B17](https://doi.org/10.1039/D1EE02637B17).
- 17 P. W. M. Jacobs and F. C. Tompkins, Chemistry of the solid state, *Surfaces of Solids*, 1955, 91–122.
- 18 S. Homma, *et al.*, Gas–solid reaction model for a shrinking spherical particle with unreacted shrinking core, *Chem. Eng. Sci.*, 2005, **60**(18), 4971–4980, DOI: [10.1016/j.ces.2005.03.057](https://doi.org/10.1016/j.ces.2005.03.057).
- 19 M. Castellote and C. Andrade, Modelling the carbonation of cementitious matrixes by means of the unreacted-core model, UR-CORE, *Cem. Concr. Res.*, 2008, **38**(12), 1374–1384, DOI: [10.1016/j.cemconres.2008.07.004](https://doi.org/10.1016/j.cemconres.2008.07.004).
- 20 S. L. Soo, *Fluid dynamics of multiphase systems*, Blaisdell Publishing Co., Waltham, Mass, 1967, OCLC No. 1301193.
- 21 M. I. Yudine, Physical considerations on heavy-particle diffusion, *Advances in geophysics*, Elsevier, 1959, pp. 185–191, DOI: [10.1016/S0065-2687\(08\)60106-5](https://doi.org/10.1016/S0065-2687(08)60106-5).
- 22 M. Micheletti, *et al.*, Particle concentration and mixing characteristics of moderate-to-dense solid–liquid suspensions, *Ind. Eng. Chem. Res.*, 2003, **42**(24), 6236–6249, DOI: [10.1021/ie0303799](https://doi.org/10.1021/ie0303799).
- 23 A. Tamburini, *et al.*, Dense solid–liquid off-bottom suspension dynamics: simulation and experiment, *Chem. Eng. Res. Des.*, 2009, **87**(4), 587–597, DOI: [10.1016/j.cherd.2008.12.024](https://doi.org/10.1016/j.cherd.2008.12.024).
- 24 F. Du, *et al.*, Sodium Hydroxide Production from Seawater Desalination Brine: Process Design and Energy Efficiency, *Environ. Sci. Technol.*, 2018, **52**(10), 5949–5958, DOI: [10.1021/acs.est.8b01195](https://doi.org/10.1021/acs.est.8b01195).
- 25 J. Neubauer and H. Pöllmann, Alinite—Chemical composition, solid solution and hydration behaviour, *Cem. Concr. Res.*, 1994, **24**(8), 1413–1422, DOI: [10.1016/0008-8846\(94\)90154-6](https://doi.org/10.1016/0008-8846(94)90154-6).
- 26 K. L. Scrivener, V. M. John and E. M. Gartner, Eco-efficient cements: Potential economically viable solutions for a low-CO<sub>2</sub> cement-based materials industry, *Cem. Concr. Res.*, 2018, **114**, 2–26, DOI: [10.1016/j.cemconres.2018.03.015](https://doi.org/10.1016/j.cemconres.2018.03.015).
- 27 A. Leemann and B. Lothenbach, The influence of potassium–sodium ratio in cement on concrete expansion due to alkali–aggregate reaction., *Cem. Concr. Res.*, 2008, **38**(10), 1162–1168, DOI: [10.1016/j.cemconres.2008.05.004](https://doi.org/10.1016/j.cemconres.2008.05.004).
- 28 E. T. Bueno, *et al.*, A review of ground waste glass as a supplementary cementitious material: A focus on alkali–silica reaction, *J. Cleaner Prod.*, 2020, **257**, 120180, DOI: [10.1016/j.jclepro.2020.120180](https://doi.org/10.1016/j.jclepro.2020.120180).
- 29 A. Seidell, *Solubilities of inorganic and metal organic compounds*, 1940, ISBN: 0598437002, 9780598437006.



- 30 G. W. Morey, The action of water on calcite, magnesite and dolomite, *Am. Mineral.*, 1962, **47**(11–12), 1456–1460.
- 31 J. L. Ellingboe and J. H. Runnels, Solubilities of Sodium Carbonate and Sodium Bicarbonate in Acetone–Water and Methanol–Water Mixtures, *J. Chem. Eng. Data*, 1966, **11**(3), 323–324.
- 32 J. Zelić, D. Rušić and R. Krstulović, Kinetic analysis of thermal decomposition of Ca(OH)<sub>2</sub> formed during hydration of commercial Portland cement by DSC, *J. Therm. Anal. Calorim.*, 2002, **67**(3), 613–622, DOI: [10.1023/A:1014348603686](https://doi.org/10.1023/A:1014348603686).
- 33 P. K. Gallagher and D. W. Johnson Jr, The effects of sample size and heating rate on the kinetics of the thermal decomposition of CaCO<sub>3</sub>, *Thermochim. Acta*, 1973, **6**(1), 67–83, DOI: [10.1016/0040-6031\(73\)80007-3](https://doi.org/10.1016/0040-6031(73)80007-3).
- 34 M. Hartman, *et al.*, Thermal dehydration of the sodium carbonate hydrates, *Chem. Eng. Commun.*, 2001, **185**(1), 1–16, DOI: [10.1080/00986440108912851](https://doi.org/10.1080/00986440108912851).
- 35 K. O. Kjellsen, *et al.*, Preparation of flat-polished specimens for SEM-backscattered electron imaging and X-ray microanalysis—importance of epoxy impregnation, *Cem. Concr. Res.*, 2003, **33**(4), 611–616, DOI: [10.1016/S0008-8846\(02\)01029-3](https://doi.org/10.1016/S0008-8846(02)01029-3).
- 36 K. Motzfeldt, The thermal decomposition of sodium carbonate by the effusion method, *J. Phys. Chem.*, 1955, **59**(2), 139–147.
- 37 E. Raymundo-Pinero, *et al.*, KOH and NaOH activation mechanisms of multiwalled carbon nanotubes with different structural organisation, *Carbon*, 2005, **43**(4), 786–795, DOI: [10.1016/j.carbon.2004.11.005](https://doi.org/10.1016/j.carbon.2004.11.005).
- 38 D. W. Green and M. Z. Marylee, *Perry's chemical engineers' handbook*, McGraw-Hill Education, 2019.
- 39 P. Patnaik, *Handbook of inorganic chemicals*, McGraw-Hill, New York, 2003, vol. 529.
- 40 A. Khawam and D. R. Flanagan, Solid-state kinetic models: basics and mathematical fundamentals, *J. Phys. Chem. B*, 2006, **110**(35), 17315–17328, DOI: [10.1021/jp062746a](https://doi.org/10.1021/jp062746a).
- 41 P. G. Vekilov, Nucleation, *Cryst. Growth Des.*, 2010, **10**(12), 5007–5019, DOI: [10.1021/cg1011633](https://doi.org/10.1021/cg1011633).
- 42 J. J. De Yoreo and P. G. Vekilov, Principles of crystal nucleation and growth, *Rev. Mineral. Geochem.*, 2003, **54**(1), 57–93, DOI: [10.2113/0540057](https://doi.org/10.2113/0540057).
- 43 J. W. Mullin, *Crystallization*, Elsevier, 4th Edn, 2001, DOI: [10.1021/op0101005](https://doi.org/10.1021/op0101005).
- 44 J. C. Brice, Some thermodynamic aspects of the growth of strained crystals, *J. Cryst. Growth*, 1975, **28**(2), 249–253, DOI: [10.1016/0022-0248\(75\)90241-9](https://doi.org/10.1016/0022-0248(75)90241-9).
- 45 J. D. Weeks and G. H. Gilmer, Dynamics of crystal growth, *Adv. Chem. Phys.*, 1979, **40**(489), 157–227.
- 46 H. Hu, *et al.*, Nucleation and crystal growth control for scalable solution-processed organic–inorganic hybrid perovskite solar cells, *J. Mater. Chem. A*, 2020, **8**(4), 1578–1603, DOI: [10.1039/C9TA11245F](https://doi.org/10.1039/C9TA11245F).
- 47 A. Kouchi, A. Tsuchiyama and I. Sunagawa, Effect of stirring on crystallization kinetics of basalt: texture and element partitioning, *Contrib. Mineral. Petrol.*, 1986, **93**(4), 429–438, DOI: [10.1007/BF00371713](https://doi.org/10.1007/BF00371713).
- 48 J. Garside, A. Mersmann and J. Nývlt, *Measurement of crystal growth and nucleation rates*, IChemE, 2002.
- 49 D. L. Parkhurst and C. A. J. Appelo, *Description of input and examples for PHREEQC version 3: a computer program for speciation, batch-reaction, one-dimensional transport, and inverse geochemical calculations*, US Geological Survey, 2013, DOI: [10.3133/tm6A43](https://doi.org/10.3133/tm6A43).
- 50 K. S. Pitzer, Ion interaction approach: theory and data correlation, *Activity coefficients in electrolyte solutions*, CRC Press, 2018, pp. 75–153.
- 51 O. Miyawaki, *et al.*, Activity and activity coefficient of water in aqueous solutions and their relationships with solution structure parameters, *Biosci., Biotechnol., Biochem.*, 1997, **61**(3), 466–469, DOI: [10.1271/bbb.61.466](https://doi.org/10.1271/bbb.61.466).
- 52 J. Mazurkiewicz, P. Tomasik and J. Zaplotny, Relationships between water activity and viscosity of solutions, *Food hydrocolloids*, 2001, **15**(1), 43–46, DOI: [10.1016/S0268-005X\(00\)00048-5](https://doi.org/10.1016/S0268-005X(00)00048-5).
- 53 R. T. Pabalan and K. S. Pitzer, Thermodynamics of NaOH (aq) in hydrothermal solutions, *Geochim. Cosmochim. Acta*, 1987, **51**(4), 829–837, DOI: [10.1016/0016-7037\(87\)90295-X](https://doi.org/10.1016/0016-7037(87)90295-X).
- 54 J. Balej, Water vapour partial pressures and water activities in potassium and sodium hydroxide solutions over wide concentration and temperature ranges, *Int. J. Hydrogen Energy*, 1985, **10**(4), 233–243, DOI: [10.1016/0360-3199\(85\)90093-X](https://doi.org/10.1016/0360-3199(85)90093-X).
- 55 J. Jiang and S. I. Sandler, A new model for the viscosity of electrolyte solutions, *Ind. Eng. Chem. Res.*, 2003, **42**(25), 6267–6272, DOI: [10.1021/ie0210659](https://doi.org/10.1021/ie0210659).
- 56 S. R. Kamhi, On the structure of vaterite CaCO<sub>3</sub>, *Acta Crystallogr.*, 1963, **16**(8), 770–772, DOI: [10.1107/S0365110X63002000](https://doi.org/10.1107/S0365110X63002000).
- 57 J. D. Rodriguez-Blanco, S. Shaw and L. G. Benning, The kinetics and mechanisms of amorphous calcium carbonate (ACC) crystallization to calcite, via vaterite, *Nanoscale*, 2011, **3**(1), 265–271, DOI: [10.1039/C0NR00589D](https://doi.org/10.1039/C0NR00589D).
- 58 N. Spanos and P. G. Koutsoukos, The transformation of vaterite to calcite: effect of the conditions of the solutions in contact with the mineral phase, *J. Cryst. Growth*, 1998, **191**(4), 783–790, DOI: [10.1016/S0022-0248\(98\)00385-6](https://doi.org/10.1016/S0022-0248(98)00385-6).
- 59 S. Yu and C. T. Oguchi, Is sodium sulphate invariably effective in destroying any type of rock?, *Geol. Soc. London, Spec. Publ.*, 2010, **333**(1), 43–58, DOI: [10.1144/SP333.5](https://doi.org/10.1144/SP333.5).
- 60 X. Chen, *et al.*, Morphology prediction of portlandite: Atomistic simulations and experimental research, *Appl. Surf. Sci.*, 2020, **502**, 144296, DOI: [10.1016/j.apsusc.2019.144296](https://doi.org/10.1016/j.apsusc.2019.144296).

