



UNIVERSITY OF LEEDS

This is a repository copy of *Utilization of Granular Wastes in Transportation Infrastructure – A Circular Economy Perspective*.

White Rose Research Online URL for this paper:

<https://eprints.whiterose.ac.uk/202104/>

Version: Accepted Version

Article:

Indraratna, B., Arachchige, C.M.K., Rujikiatkamjorn, C. et al. (2 more authors) (2024) Utilization of Granular Wastes in Transportation Infrastructure – A Circular Economy Perspective. *Geotechnical Testing Journal*, 47 (1). ISSN 0149-6115

<https://doi.org/10.1520/GTJ20220233>

© 2023 This author accepted manuscript is provided for your own personal use only. It may not be used for resale, reprinting, systematic distribution, emailing, or for any other commercial purpose without the permission of the publisher.

Reuse

Items deposited in White Rose Research Online are protected by copyright, with all rights reserved unless indicated otherwise. They may be downloaded and/or printed for private study, or other acts as permitted by national copyright laws. The publisher or other rights holders may allow further reproduction and re-use of the full text version. This is indicated by the licence information on the White Rose Research Online record for the item.

Takedown

If you consider content in White Rose Research Online to be in breach of UK law, please notify us by emailing eprints@whiterose.ac.uk including the URL of the record and the reason for the withdrawal request.



eprints@whiterose.ac.uk
<https://eprints.whiterose.ac.uk/>

1 **Utilization of Granular Wastes in Transportation Infrastructure – A**
2 **Circular Economy Perspective**

3 **Buddhima Indraratna¹, Chathuri M. K. Arachchige², Cholachat Rujikiatkamjorn³, Ana**
4 **Heitor⁴, and Yujie Qi⁵**

5 ¹Distinguished Professor of Civil Engineering, Director of Transport Research Centre, School of
6 Civil and Environmental Engineering, University of Technology Sydney, NSW 2007, Australia.
7 (Corresponding author), e-mail: buddhima.indraratna@uts.edu.au, [https://orcid.org/0000-0002-](https://orcid.org/0000-0002-9057-1514)
8 [9057-1514](https://orcid.org/0000-0002-9057-1514)

9 ²Research Associate, Transport Research Centre, School of Civil and Environmental
10 Engineering, University of Technology Sydney, NSW 2007, Australia. e-mail:
11 chathuri.arachchige@uts.edu.au, <https://orcid.org/0000-0003-1554-6527>

12 ³Professor of Civil Engineering, School of Civil and Environmental Engineering, University of
13 Technology Sydney, NSW 2007, Australia. e-mail: cholachat.rujikiatkamjorn@uts.edu.au,
14 <https://orcid.org/0000-0001-8625-2839>

15 ⁴Lecturer of Geotechnical Engineering, School of Civil Engineering, University of Leeds, UK.
16 email: a.heitor@leeds.ac.uk, <https://orcid.org/0000-0002-2346-8250>

17 ⁵Lecturer of Civil Engineering, School of Civil and Environmental Engineering, University of
18 Technology Sydney, NSW 2007, Australia. e-mail: yujie.qi@uts.edu.au, [https://orcid.org/0000-](https://orcid.org/0000-0002-3486-2130)
19 [0002-3486-2130](https://orcid.org/0000-0002-3486-2130)

20

1 **ABSTRACT**

2 Attributed to environmental preservation in urban infrastructure development, recycling of waste
3 materials produced in the coal and steel industry as well as reusing off-the-road tires is a high
4 priority in Australia. In this paper, the practical applications of (i) coal wash and steel furnace
5 slag mixtures, (ii) coal wash and fly ash mixtures, and (iii) rubber crumbs from recycled tires
6 mixed with granular fills are discussed. In this regard, some examples of real-life applications in
7 port reclamation, road and rail environment in the state of New South Wales, Australia (e.g., Port
8 Kembla, Kangaroo Valley highway and Chullora Rail Precinct) are highlighted. The
9 performance of the materials is assessed and their mixed composition optimized using large-
10 scale laboratory testing, while confirming their suitability in transportation infrastructure. The
11 paper outlines various aspects of site investigation, construction techniques, and the installation
12 of instrumentation to evaluate the field performance of waste materials, in contrast to traditional
13 (natural) quarried materials. The results from case studies demonstrate that properly engineered
14 waste material mixtures can exhibit promising characteristics to efficiently meet the expected
15 technical standards, as proven by experimental results and field performance monitoring in real-
16 life projects. These research outcomes blatantly support a circular economy perspective to be
17 embraced in the future development of transportation infrastructure, with the aim of catering for
18 increased freight loading and track longevity with substantially reduced maintenance intensity.

19 **Keywords**

20 Circular Economy, Industry Waste Materials, Recycled Tires, Sustainability, Transport
21 Infrastructure.

1 **Introduction**

2 In view of Australian geographic and demographic trends combined with inevitable long-
3 distance supply chains associated with the mining and agriculture industries, the operational
4 efficiency of transportation infrastructure in terms of safety and reliability is vital for a
5 sustainable national economy. The use of coal mining wastes (e.g., coal wash, steel furnace slag,
6 and fly ash) offer significant monetary benefits over conventional (quarried) aggregates in
7 substructure construction and land reclamation projects (Indraratna et al. 1994). Despite its
8 favorable properties, such as adequate shear strength and permeability (drainage), Heitor et al.
9 (2015) have shown that the breakage of coal wash is significant during initial compaction and
10 subsequent shearing under live loading.

11 Through extensive laboratory studies, it is proven that combinations of granular wastes
12 including rubber tire segments, steel slag and coal wash can offer adequate load-bearing
13 properties to replace traditional (natural) road base, ballast, capping and structural fill, while
14 ensuring enhanced longevity of transportation corridors. The application of coal wash (e.g.,
15 Leventhal 1996; Rujikiatkamjorn et al. 2013; Heitor et al. 2015) and mixtures of coal wash, steel
16 furnace slag and rubber crumbs (Chiaro et al. 2014; Indraratna et al. 2018; Qi et al. 2018) have
17 demonstrated that marginal materials could be optimally engineered to attain acceptable
18 mechanical and geotechnical characteristics, in relation to the required specifications of port
19 reclamation fill (Indraratna et al. 2015), capping or sub-ballast layers in rail tracks (Indraratna et
20 al. 2018). Wang et al. (2019) have proven the performance of coal wash mixture as an
21 appropriate base or subbase material for pavements.

1 Several laboratory studies have demonstrated the potential use of rubber inclusions such
2 as rubber granules, rubber geogrids, and waste tires in strengthening track substructure (Sol-
3 Sánchez et al. 2015; Fernández et al. 2018; Koohmishi and Azarhoosh, A. 2020; Arachchige et
4 al. 2022*b*; Indrarathna et al. 2022*c*). Recently, Arachchige et al. (2022*a*) conducted large-scale
5 triaxial tests and demonstrated the favorable mechanical and compressibility characteristics of an
6 optimally blended mix of ballast aggregates (latite basalt) and rubber granules for heavy haul
7 railways, namely the Rubber Intermixed Ballast System (RIBS). Recycled rubber panels derived
8 from discarded rubber conveyor belts from minerals processing plants would offer a potential
9 energy-absorbing inclusion within the track substructure to provide increased reinforcement
10 against undue lateral movement of granular particles. Using waterjet cutting, Energy-Absorbing
11 Rubber Geogrids (EARS) made of used conveyor belts were prepared as grids with
12 predetermined aperture sizes and shapes. They were expected to serve in a similar capacity to
13 conventional high-density polyethylene geogrids, the difference being their energy-absorbing
14 capacity attributed to increased damping. In another study by Indraratna et al., (2022*c*), real-size
15 prototype tests were conducted using the National Facility for Cyclic Testing of High-speed Rail
16 to investigate the performance of Infilled Tire Cell Foundation (ITCF) where recycled tires
17 infilled with granular waste are assembled beneath the ballast layer to replace traditional capping
18 material. Test data indicated reduced lateral deformation within the ballast layer and reduced
19 acceleration of the concrete sleepers, compared to a traditional track structure. The tire assembly
20 infilled with used ballast aggregates could be placed as an energy-absorbing medium to replace a

1 traditional rockfill capping layer apart from providing adequate confinement to control lateral
2 movement.

3 This paper describes real-life trials that were conducted at (i) Chullora Rail Technology
4 Precinct (ii) Port Kembla Reclamation, and (iii) Kangaroo Valley Highway to assess the
5 potential benefits of granular waste materials when innovatively blended in optimal mix
6 compositions. The technical contents elucidate the salient aspects of material preparation,
7 construction procedures with field instrumentation, and loading processes. The ultimate goal is to
8 promote more economical and carbon-efficient infrastructure components by adopting granular
9 waste materials for sustainable transportation infrastructure within the framework of a circular
10 economy as strategically fostered by the State Government, c/o Transport for NSW.

11 **CHULLORA RAIL PRECINCT**

12 A fully instrumented track was constructed at Chullora (New South Wales, Australia) to
13 investigate real-life scale applications of laboratory-proven recycled rubber elements solutions.
14 This track was constructed in collaboration with industry stakeholders such as Transport for
15 NSW (formerly Sydney Trains), Bridgestone Corporation, and Ecoflex. Three different
16 innovative applications were tested, namely RIBS, EARS, and ITCF. In addition, an
17 instrumented standard track section was also built for comparison and benchmark purposes.

18 **Site Description**

19 The test track section constructed in Chullora Technology Precinct had a total length of 380 m,
20 and was situated between two turnouts from 17.61 to 17.99 km (Figure 1). For construction and
21 monitoring purposes, the track was divided into four sections, namely (i) Section F-G: ITCF

1 section (from 17.720 to 17.740 km), (ii) Section E-F: Control track section (from 17.800 to
2 17.840 km), (iii) Section D-E: EARS section (from 17.840 to 17.860 km) and (iv) Section B-C:
3 RIBS section (from 17.900 to 17.920 km). As shown in Fig. 1, three 20-m long sections were
4 constructed with intermediate standard sections to avoid the boundary effects.

5 The sub-surface profile comprises a layer of compacted fill followed by a thin sandy clayey silt,
6 residual silty clays with ironstone gravel, and stiff clay or shale bedrock. The stiff weathered
7 shale was encountered as an inclined layer at 1.2 m and 3.8 m deep at the RIBS and ITCF
8 sections, respectively. Although the water table was located below 5 m depth, the subgrade layer
9 was found to be saturated due to waterlogging under heavy to medium rainfall.

10 **Material preparation and track construction**

11 Fresh ballast complied with the nominal 60-graded specification (AS 2758.7:2015, T HR TR
12 00192 ST:2018-TfNSW) *Aggregates and Rock for Engineering Purposes - Railway Ballast*) was
13 selected for all test sections except for the RIBS section. In the RIBS section, a 150-mm thick
14 layer having fresh ballast mixed with 10% recycled rubber granules (by weight) was placed
15 above the capping layer (Fig 3). In this test section, the rubber particle size was in the range of 8
16 to 15 mm. While Arachchige et al. (2022a) suggested an optimum rubber particle size range of
17 9.5 to 19 mm, a slight deviation was considered because the optimum range recommended
18 according to the standard sieve sizes was not available commercially. As shown in Fig. 2a, a
19 large-scale calibrated volumetric mixer was employed to mix fresh ballast and rubber particles to
20 the desired mix proportion, and it ensured the particle size distribution of the mix still complied
21 with the ballast specifications. The particle size distributions of RIBS, fresh ballast, and capping

1 materials are shown in Fig. 2*b*. The capping material contained 15% fines (e.g. smaller than 75
2 μm), which slightly deviated from the standard of *Earthwork Materials* by Transport for New
3 South Wales, Australia (T HR CI 12111 SP:2018-TfNSW). Table 1 shows the grain size
4 characteristics of the fresh ballast, RIBS, and sub-ballast used for the field trial.

5 For the EARS section, rubber geogrids with square apertures were prepared by water jet
6 cutting method using end-of-life conveyor belts rubber panels. The aperture size and thickness of
7 the rubber panel (1 m \times 1 m) were 51 \times 51 mm², and 10 mm, respectively. The panels were laid at the
8 interface of the capping and ballast layers. For ballast-infilled tire assembly (ITCF), the
9 conventional capping (subballast) layer was replaced with 200 mm thick and 600 mm diameter
10 tires filled with compacted fresh ballast. The ITCF units were assembled in a triangular pattern.
11 A control track section having 250 mm ballast and 200 mm capping was constructed in
12 accordance with the standard for *Earthworks and Formation* by Transport for New South Wales,
13 Australia (T HR CI 12110 ST:2018-TfNSW).

14 In all sections, the other track components, including sleepers and rails adopted were the
15 same. Medium-duty concrete sleepers and AS60SC rails manufactured according to the
16 Australian standards for *Railway Track Material, Part 1: Steel Rails* (AS 1085.1:2019, were used
17 for the track. Figure 3 shows the vertical cross-sections of (a) standard track, (b) RIBS, (c)
18 EARS and (d) ITCF. After excavating the stiff clayey subgrade (500-mm below the original
19 ground level), 200 mm diameter cess drains were installed in the gravel layer to facilitate the
20 drainage. A layer of nonwoven geotextile was placed between the capping layer and the ballast
21 interface to ensure the ballast would not be contaminated with fines from the capping layer. The

1 maximum dry densities of ballast, capping, and RIBS layers are reported in Table 1. Figure 4
2 presents the placement of RIBS material, the placement of energy-absorbing rubber geogrids,
3 and the assembly of tire cells at the ITCF section.

4 **Instrumentation scheme**

5 In each section, pressure cells having 200 mm in diameter, were placed horizontally at three
6 interfaces (i.e., sleeper-ballast, ballast-capping, and capping-subgrade) to measure vertical stress.
7 In addition, pressure cells were placed vertically in each section below the sleeper edge at the
8 mid-level of the ballast layer to measure the lateral pressure within the ballast layer. The active
9 face of the pressure cell was against and perpendicular to the centreline of the track. Electrical
10 cables connected to the sensors were covered with flexible conduits to avoid damage during
11 track operation. The cables were connected to a high-speed data acquisition system (DAQ)
12 mounted on cabinets located at the side of the track. For greater autonomy, the data acquisition
13 system was powered by solar cells and batteries, automatically triggered, and the data were
14 recorded at 50 Hz sample frequency.

15 **Loading application**

16 A locomotive (81 Class: 21.5-ton axle load and 21.15 m long) was selected as the rolling stock
17 for all the test sections. Limited running at a speed of 10-13 km/h was due to the restriction at the
18 site. The typical vertical pressure variations under loading conditions are shown for the control
19 track section in Fig. 5. In this study, a loading cycle is defined by a pass of one axle, i.e., a set of
20 three wheels. A total number of 12 loading cycles (an initial loading test) was conducted. As no

1 considerable change was observed in the value of vertical pressure from the 1st to the 12th
2 loading cycle, the 5th loading cycle (N=5) was considered to analyse the pressure distribution.

3 **Pressure distributions**

4 Figure 5b shows the variations in vertical pressure distributions at different levels of the
5 substructure in the 5th loading cycle. As expected, the vertical stresses at the base of the ballast
6 layer were significantly reduced, e.g., by more than 30%, in RIBS and EARS sections compared
7 to the control section. Minor reductions of vertical pressure around 3% and 11% were observed
8 at the ballast-sleeper interface of the RIBS and ITCF sections, respectively. This may be
9 attributed to the effect of the decreased overall stiffness of the track substructure due to the
10 rubber inclusion within the depth of influence. Since the rubber geogrid is relatively thin
11 compared to the thickness of the entire substructure, the effect of the rubber geogrid is negligible
12 on the stress redistribution at the ballast-sleeper interface level in the EARS section.

13 Furthermore, considering the stresses at the subgrade-capping interface, for the RIBS and
14 EARS sections, there is a substantial reduction in the vertical stress transferred into the subgrade,
15 albeit more prominent in the EARS track section. In contrast, there is a 55% increase in vertical
16 stress at the capping-ballast interface for the ITCF track section compared to the control section
17 (Fig. 5b). While this might not correspond to the intuitive behavior first expected, no
18 considerable change was observed in the vertical stress at the subgrade-capping interface. It
19 implies that the ITCF layer acts as a relatively stiff capping layer, thus resulting in an increase in
20 stresses on the ballast layer.

1 Lateral pressure was measured using vertically installed pressure cells in the middle of
2 the ballast layer at a point below the sleeper edge. Figure 6 compares normalized lateral
3 pressures ($\tilde{\sigma}_L$) in all sections. The $\tilde{\sigma}_L$ is the ratio between the recorded maximum lateral pressure
4 in a particular section and the control section. Lateral pressures were measured at the middle of
5 the ballast layer vertically below the edge of the sleeper. Lateral pressure through lateral
6 confinement is essential to control ballast dilation and to reduce track instability. The normalized
7 lateral pressures in RIBS, EARS, and ITCF sections increase by 3.4, 1.4, and 10 times,
8 respectively. This is not surprising as the RIBS facilitates a well-interlocked particle assembly,
9 EARS provides an effective interlock between the ballast and its apertures at the interface, and
10 ITCF enhances capping layer confinement via the tire cell assembly.

11

12 **PORT KEMBLA OUTER HARBOUR RECLAMATION**

13 Port Kembla (100 kilometers south of Sydney) opened in the late 1890s to facilitate general
14 cargo loading and unloading and the export of steel and coal from the Illawarra region. In the
15 past decades, to keep pace with the growth of the local industries the Port has been expanding,
16 particularly the inner harbor. To alleviate congestion, enhance capacity and increase
17 productivity, the port authority planned the development of the Outer Harbor (Fig. 7). The Port
18 Kembla Outer Harbor created additional bulk cargo berths and terminal areas on 45 hectares of
19 reclaimed land.

20 **Site description**

21 A volcanic sandstone bedrock can be found at the bottom of the Outer Harbour area (RL -15 to

1 20 m) (Stroud et al. 1995). At the site, the thickness of the estuarine clay was relatively thin and
2 hence consolidation settlement is not a critical issue. Therefore, the type of fill selected for the
3 reclamation scheme was critical to ensure an acceptable level of long-term settlement and
4 sufficient load-bearing capacity. In addition, it is essential that a geotechnical characterization of
5 fill materials and associated stabilization techniques is conducted to avoid sudden subsidence of
6 granular media, large lateral displacements and differential movements that could, in turn, cause
7 damage to the main structures, as well as to adjacent facilities (pipelines, retaining walls, etc.).
8 At Port Kembla, an innovative blend of locally available granular waste by-products including
9 coal wash (CW) and Basic Oxygen Steel furnace slag (BOS) were considered in lieu of
10 conventional dredged fills (Rujikiatkamjorn et al. 2013; Tasalloti et al. 2015). While the blends
11 of these two wastes are attractive from an economical and environmental standpoint, their
12 individual adverse geotechnical properties, i.e., particle breakage for CW (Indraratna 1994,
13 Heitor et al., 2015) and swelling for BOS slag (Chiaro et al. 2015) poses some challenges. A
14 series of experimental investigations were conducted by Chiaro et al. (2015) and Tasalloti et al.
15 (2015) to assess CW-BOS mixtures suitability for port application in terms of: (i) compaction
16 effectiveness; (ii) permeability; (iii); shear strength and bearing capacity (iv) particle degradation
17 after compaction and shearing; and (v) swelling behavior. CW-BOS mixtures of 3:1, 1:1, and 1:3
18 (ratio by weight of dry CW:BOS) were prepared.

19 Figure 8 shows the performance of the CW-BOS blends in terms of swelling and particle
20 breakage. It can be observed that the free swelling behavior due to hydration of free lime (CaO)
21 and free magnesium (MgO) can be up to 8% for pure BOS and decreases with an increase in CW

1 content. Similarly, the Breakage Index (BI), used to quantify particle breakage, decreases with
2 increased BOS content. Interestingly, Figure 8 shows that the individual adverse characteristics
3 of CW and BOS slags can be minimized when the two waste materials are blended. To evaluate
4 shear strength properties of the mixtures, a series of drained triaxial compression tests with a
5 confining pressure of 120 kPa (mimicking port loading conditions) were conducted on fully
6 saturated specimens. The friction angles of mixtures are shown in Table 2. As expected, the
7 friction angle increases from 36.5 degrees to 38 degrees when the BOS content increases due to
8 better particle interlock. Similarly, the soaked CBR values increase from 8% to 31% as the
9 proportion of BOS increases. However, the permeability of the mixtures decreases from 5×10^{-7}
10 m/s (100% BOS) to 5.0×10^{-7} m/s (100% CW) as the result of the reduction in void ratio with an
11 increase in BOS content. When used as a fill, the content of BOS needs to be optimized to
12 prevent excessive settlement and swelling, which can damage the infrastructure in the Por (Fig
13 8). The following criteria were adopted to determine the appropriate mixtures to be used as an
14 engineering fill at the Port Kembla Reclamation Project.

15 (a) Friction angle greater than or equal to 30° and/or a CBR $> 10\%$ to provide sufficient
16 bearing capacity and curtail long-term deformation

17 (b) Permeability coefficient in the range of 1×10^{-8} m/sec and 1×10^{-6} m/sec (similar to
18 sandy soil) to ensure sufficient drainage and minimize accumulation of excess pore
19 pressure

20 (c) Swelling should be less than 3% to maintain the stability and serviceability of the
21 infrastructure

1 (d) Particle breakage should be less than 10% to maintain the original particle size
2 distribution affecting the shear strength of the mixtures

3 Two mixtures with BOS content of 57% and 73% were selected for the field trial and
4 verification in September 2012 at Port Kembla Reclamation Site before assessing swelling and
5 particle breakage (Indraratna et al. 2015). The field trial was an essential step to assess in-situ
6 swelling and performance of CW-BOS blends as compacted fill. The trial site (55 m long, 14 m
7 wide, and 1.4 m deep) was divided into two equal sub-sections where approximately 1200 tons
8 of CW and 1600 tons of BOS were used to prepare the mixtures using an excavator, grader and a
9 twin-shaft pugmill. A 13-ton vibration smooth steel drum roller was used to compact 300 mm
10 thick lifts. To evaluate compaction efficiency, both sand cone replacement and nuclear density
11 techniques were adopted. It was found that four roller passes could achieve a compacted dry
12 density over 90% standard Proctor compaction. After the compaction, a series of dynamic cone
13 penetration tests were conducted. The number of blows to penetrate 100 mm was greater than
14 10, which is on par with dense sandy soils.

15 After six months, free swelling for sections with BOS content of 57% and 73% were
16 found to be 4.5% and 6%, respectively. Based on the field trial and further laboratory
17 investigations, it was concluded that although the strength of mixtures with BOS content over
18 50% is higher than that of conventional fill (e.g., sandy soil), a relatively high level of swelling
19 (i.e., > 3%) should be controlled by reducing the BOS content when used as structural fill, unless
20 the overburden pressure of at least 100 kPa is applied through live load and surcharge weight of
21 pavement and built infrastructure.

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21

MOSS VALE ROAD, KANGAROO VALLEY

Coal mining wastes from the Illawarra region, NSW, Australia (e.g., coal wash) have significant monetary benefits over conventional (quarried) aggregates when utilized in construction and reclamation projects in the form of pavement and fill materials (Indraratna et al. 1994, Wang et al. 2019). Despite its favorable properties, such as adequate shear strength, Heitor et al. (2015) showed that the extent of coal wash breakage during compaction and shearing is significant, which in turn can hinder its application as base/subbase material in road pavements. To address this limitation, an innovative solution incorporating fly ash (FA) fines was investigated by Wang et al. 2019. The FA fines can increase the compatibility and, therefore, the mechanical interlock and the permeability of compacted CW. In addition, the Fly Ash (FA) fines serve as a void filler, reducing the potential breakage of coal wash particles and thus enhancing the properties of the mix. In Wang et al., 2019 study, a Class F Fly ash (FA) with no pozzolanic activity was procured from Eraring Power Station (New South Wales, Australia). Fig. 9a shows the particle size distribution (PSD) of CW, FA and different mixes having different FA content. It can be observed that PSD of CW does not satisfy the minimum fines content specified by Transport for NSW formerly Road and Maritime Services or RMS, for base/subbase material. However, with the addition of FA content ranging from 7 to 15% by weight, the particle size distribution curve of the mixes complies with the acceptable range for a base/subbase material. However, while the 7-15% FA mixes conform with the expectations in terms of PSD, it is crucial to assess their suitability as a base and/or sub-base material.

1 Wang et al. (2019) reported that maximum values using unconfined compressive test and
2 California Bearing Ratio (CBR) were obtained for mixes of CW having 7% FA. This is not
3 surprising as the minimum void ratio under modified Proctor compaction energy is also obtained
4 for this mix (Fig. 9b). Furthermore, the collapse potential was well below the allowable range
5 with a permeability of less than 5×10^{-7} m/sec.

6 To evaluate the real scale performance of the selected mix, a road pavement construction
7 trial was conducted at Moss Vale Road (Kangaroo Valley, NSW) with the support of Transport
8 for NSW. The site was located at the intersection of Moss Vale Road and Cavan Road, Kangaroo
9 Valley, NSW (Figure 10). For this site, a design ESAs (Equivalent Standard Axles) of 3×10^6 was
10 considered and hence the minimum required thickness adopted of the road base was 300 mm.
11 The area was divided into two sections (3.5 m width and 20 m long), (a) a control section using
12 conventional base material, i.e. densely graded base or DGB20 and (b) Coal wash Fly Ash
13 Mixture (7% FA prepared at 6% water content). The existing road surface and the base layer
14 (260 mm thick) were first milled. A volumetric mixer was employed to mix CW and FA. Then,
15 the selected CWFA mix and DGB20 were compacted using a smooth steel roller in the test and
16 control sections, respectively. The dry density of the CWFA mix recorded on site was 1.76 t/m^3 ,
17 whereas, for DGB20, the maximum dry density was 2.28 t/m^3 with a water content of 8%.
18 (RMS, 2013). During compaction, a number of instruments were installed to monitor the CWFA
19 mix performance under the same traffic conditions as the control section (e.g., moisture and
20 suction sensors). The road surface was then sealed and opened for traffic.

1 The photo illustration of the different construction phases is shown in Figure 11. Based
2 on the insignificant change in suction readings, the results show that the CWFA can prevent the
3 infiltration of moisture during rainfall. As shown in Fig. 12, the rutting profile of CWFA
4 indicates similar performance compared to the conventional section (DGB20). The long-term
5 performance is still being monitored at the site.

6

7 **Conclusion**

8 This paper describes the practical applications of various waste materials in transport
9 infrastructure (rail, road and port). The main types of waste considered range from those derived
10 from coal mining (coal wash), steel manufacturing (BOF steel furnace slag), coal-fired energy
11 plants (fly ash), and recycled rubber elements from used tires and conveyor belts. After detailed
12 laboratory characterisation, the successful blends of these wastes were considered in three real-
13 life projects, namely, the Port Kembla reclamation project, Kangaroo valley road construction,
14 and the rail test track at Chullora Technology Precinct. The results of real-time monitoring of the
15 real-life applications outlined in this paper showed that:

- 16 • The track sections having rubber intermixed ballast stratum (RIBS) and Energy
17 Absorbing Rubber Seam (EARS) exhibited a 30% reduction of the vertical pressures at
18 the base of the ballast layer, indicating less impact on ballast aggregates and hence
19 degradation.

- 1 • The application of recycled ballast infilled tire cell assembly (ITCF) as the capping layer
2 provides better lateral support by increasing the confining pressure of the ballast layer by
3 more than ten times.
- 4 • Reduced vertical stresses in the formation of RIBA and EARS track sections could
5 reduce the natural ballast particle degradation, and increased lateral pressures of ITCF
6 section could reduce ballast dilation. This indicates that the proposed recycled rubber
7 elements inclusions could have substantial long-term benefits, such as a reduction in
8 track maintenance interventions. However, to analyze the long-term behavior, tracks
9 should be tested for an increased number of loading cycles.
- 10 • The field tests carried out at the Port Kembla Reclamation confirmed that the compacted
11 mixtures of CW-BOS had similar performance to conventional sandy fills. However, the
12 mix having a higher BOF slag content showed considerable swelling and thus should be
13 avoided in practice.
- 14 • A field study at Kangaroo Valley using a mixture of coal wash and 7% fly ash performed
15 similarly to the conventional aggregate based on the rut depth evaluation.

16

17 **ACKNOWLEDGEMENTS**

18 Financial assistance provided by the Australian Research Council (ARC) ITTC-Rail, Linkage
19 and Discovery Projects (DP220102862, LP100200265, LP160100280, LP200200915,
20 IC170100006) and industry partners including Transport for NSW (formerly Sydney Trains and
21 Road and Maritime Service), Bridgestone Corporation, EcoFlex, Global Synthetics, Douglas

1 Partners, South32, Port Kembla Port Corporation, BHP Billiton-Illawarra Coal, Coffey
2 Geotechnics, Menard Bachy, and Australian Steel Mill Services is gratefully acknowledged.
3 Also, the assistance provided by Dr Chazath Kaliboullah, Dr SM Ali Tasalloti, Dr Dong Wang,
4 Dr Gabriele Chiaro, Dr Pankaj Baral, Dr Miriam Tawk, Dr Trung Ngo, Dr Rakesh Malisetty, Ms
5 Fatima Mehmood, Dr Mandeep Singh, Mr Anees Siddiqui, Mr Joseph Arivalagan, Mr Courage
6 Dzaklo, Mr Aaron Eagleton, Mr Babar Sajjad, Mr Shigeki Endo, Ms Robyn Lyster, Mr Jim
7 Grant, Mr Dipendra Badu, Mr Geoff McIntosh in executing field trial tests is gratefully
8 appreciated. The authors would also like to acknowledge the assistance provided by EngAnalysis
9 for the installation of instrumentation at the Chullora Technology Precinct. Some contents of the
10 paper have been published earlier in scholarly journals and reproduced herein with kind
11 permission from Ground Improvement, Transportation Geotechnics, among others.

12

1 **References**

- 2 Arachchige, C.M.K., B. Indraratna, Y. Qi, and C. Rujikiatkamjorn. 2022a. "Geotechnical
3 Characteristics of a Rubber Intermixed Ballast System," *Acta Geotechnica* 17, no. 5
4 (2022): 1847-1858. <https://doi.org/10.1007/s11440-021-01342-2>
- 5 Arachchige, C.M.K., B. Indraratna, Y. Qi, and C. Rujikiatkamjorn. 2022b. "Deformation and
6 Degradation Behaviour of Rubber Intermixed Ballast System under Cyclic Loading."
7 *Engineering Geology*, 307 (September 2022): p.106786.
8 <https://doi.org/10.1016/j.enggeo.2022.106786>
- 9 AS (Australian Standards). 2015. *Aggregates and Rock for Engineering Purposes. Part 7:*
10 *Railway Ballast*. AS 2758.7(2015). Standards Australia.
- 11 AS (Australian Standards). 2019. *Railway Track Material, Part 1: Steel Rails*. AS 1085.1(2019).
12 Standards Australia.
- 13 Chiaro, G., B. Indraratna, S.M. Tasalloti, and C. Rujikiatkamjorn. 2014. "Optimisation of Coal
14 Wash-Slag Blend as a Structural fill." *Ground Improvement* 168, Issue GI1: 33-34.
15 <http://dx.doi.org/10.1680/grim.13.00050>
- 16 Fernández, P. M., C.H. Signes, I.V. Sanchís, D.P. Mira, and R.I. Franco. 2018. "Real scale
17 evaluation of vibration mitigation of sub-ballast layers with added tyre-derived
18 aggregate." *Construction and Building Materials* 169: 335-346.
19 <https://doi.org/10.1016/j.conbuildmat.2018.03.027>
- 20 Google (2022) Kangaroo Valley. Available at, <https://perma.cc/8324-UHK6>
- 21 Google (2022) Port Kembla. Available at, <https://perma.cc/RCY6-7486>

- 1 Heitor, A., B. Indraratna, C.I. Kaliboullah, C. Rujikiatkamjorn, and G.W. McIntosh. 2015.
2 "Drained and Undrained Shear Behaviour of Compacted Coal Wash." *Journal of*
3 *Geotechnical and Geoenvironmental Engineering* 142, no. 5.
4 [https://doi.org/10.1061/\(ASCE\)GT.1943-5606.0001422](https://doi.org/10.1061/(ASCE)GT.1943-5606.0001422)
- 5 Indraratna, B. 1994. "Geotechnical Characterization of Blended Coal Tailings for Construction
6 and Rehabilitation Work." *Quarterly Journal of Engineering Geology and Hydrogeology*
7 27, no. 4: 353-361. <https://doi.org/10.1144/GSL.QJEGH.1994.027.P4.06>
- 8 Indraratna, B., F. Mehmood, S. Mishra, T. Ngo, and C. Rujikiatkamjorn. 2022c. "The Role of
9 Recycled Rubber Inclusions on Increased Confinement in Track Substructure."
10 *Transportation Geotechnics*, 36 (September 2022): 100829.
11 <https://doi.org/10.1016/j.trgeo.2022.100829>
- 12 Indraratna, B., I. Gasson, and R. Chowdhury. 1994. "Utilization of Compacted Coal tailings as
13 Structural Fill." *Canadian Geotechnical Journal* 31, no. 5: 614-623.
14 <https://doi.org/10.1139/t94-074>
- 15 Indraratna, B., A. Heitor, C. Rujikiatkamjorn. 2015. "Ground improvement methods for port
16 infrastructure expansion. " *Geotechnical Engineering* 46, no. 3: 125-130.
- 17 Indraratna, B., Qi, Y. and Heitor, A. (2018), "Evaluating the Properties of Mixtures of Steel
18 Furnace Slag, Coal Wash, and Rubber Crumbs Used as Subballast", *Journal of Materials*
19 *in Civil Engineering* 30, no 1: 04017251. [https://doi.org/10.1061/\(ASCE\)MT.1943-](https://doi.org/10.1061/(ASCE)MT.1943-5533.0002108)
20 [5533.0002108](https://doi.org/10.1061/(ASCE)MT.1943-5533.0002108)
- 21 Koohmishi, M. and Azarhoosh, A. 2020. "Hydraulic conductivity of fresh railway ballast mixed

1 with crumb rubber considering size and percentage of crumb rubber as well as aggregate
2 gradation." *Construction and Building Materials* 241: 118133.
3 <https://doi.org/10.1016/j.conbuildmat.2020.118133>

4 Leventhal, A. (1996), "Coal Washery Reject as an Engineered Material", in National Symposium
5 on the Use of Recycled Materials in Engineering Construction, 54-59.

6 Qi, Y., B. Indraratna, A. Heitor, and J.S. Vinod, J.S. 2018. "Effect of Rubber Crumbs on the
7 Cyclic Behavior of Steel Furnace Slag and Coal Wash Mixtures", *Journal of*
8 *Geotechnical and Geoenvironmental Engineering* 144, no 2: 04017107.
9 [https://doi.org/10.1061/\(ASCE\)GT.1943-5606.0001827](https://doi.org/10.1061/(ASCE)GT.1943-5606.0001827)

10 Rujikiatkamjorn, C., B. Indraratna, and G. Chiaro. 2013. "Compaction of Coal Wash to
11 Optimise its Utilisation as Water-front Reclamation Fill." *Geomechanics and*
12 *Geoengineering* 8, no. 1: 36-45. <https://doi.org/10.1080/17486025.2012.727475>

13 Sol-Sánchez, M., N. Thom, F. Moreno-Navarro, M. Rubio-Gamez, and G. Airey. 2015. "A study
14 into the use of crumb rubber in railway ballast." *Construction and Building Materials* 75:
15 19-24. <https://doi.org/10.1016/j.conbuildmat.2014.10.045>

16 Stabilco NSW, "Kangaroo valley pavement rehabilitation. Performance based product trial
17 report." RMS, 2013, <https://perma.cc/4LVQ-SN3G>

18 Stroud, W.J., L. Sherwin, H.N. Roy, and C.J. Baker. 1985. Wollongong - Port Hacking 1:100
19 000 Geological Sheet 9029-9129, 1st edition. Geological Survey of New South Wales,
20 Sydney. <https://perma.cc/32V8-EFJZ>

21 Tasalloti, S.M.A., B. Indraratna, C. Rujikiatkamjorn, A. Heitor, and G. Chiaro. 2015. "A

1 Laboratory Study on the Shear Behavior of Mixtures of Coal Wash and Steel Furnace
2 Slag as Potential Structural Fill," *Geotechnical Testing Journal* 38, no 4: 1-12.
3 [doi:10.1520/GTJ20140047](https://doi.org/10.1520/GTJ20140047)

4 The Asset Standards Authority. 2018. *Ballast*. T HR TR 00192 ST (2018). Transport for New
5 South Wales, Australia.

6 The Asset Standards Authority. 2018. *Earthworks and Formation*. T HR CI 12110 ST (2018).
7 Transport for New South Wales, Australia.

8 The Asset Standards Authority. 2018. *Earthwork Materials*. T HR CI 12111 SP (2018).
9 Transport for New South Wales, Australia.

10 Wang, D., M. Tawk, B. Indraratna, A. Heitor, and C. Rujikiatkamjorn. 2019. "A Mixture of
11 Coal Wash and Fly Ash as a Pavement Substructure Material." *Transportation*
12 *Geotechnics* 21: 100265. <https://doi.org/10.1016/j.trgeo.2019.100265>

13

1 **TABLE 1** Grain size characteristics of the fresh ballast, RIBS, and capping materials

Material	d_{max} (mm)	d_{min} (mm)	d_{50} (mm)	C_u	C_c	Maximum dry density (t/m ³)
Ballast	63	9.5	37.5	2.84	1.42	1.60
RIBS	63	9.5	37.5	2.84	1.42	1.45
Capping	19	0.044	2.36	75.4	1.20	2.14


2

3 **TABLE 2** Friction angle, California Bearing Ratio (CBR) and permeability coefficient for CW,
4 BOS and CW-BOS mixtures (Chiaro et al. 2015).

Material	Friction Angle (Degrees)	CBR (%) soaked	Permeability coefficient (m/s)	Swelling (%)
CW	36.5	8	5×10^{-9}	-0.6
CW-BOS 3:1	37.2	18	6×10^{-8}	0.3
CW-BOS 1:1	37.1	24	2×10^{-7}	4
CW-BOS 1:3	38.6	25	4×10^{-7}	-
BOS	38.3	31	5×10^{-7}	8

5
6
7
8

1 **FIG. 1** Plan view of the track.

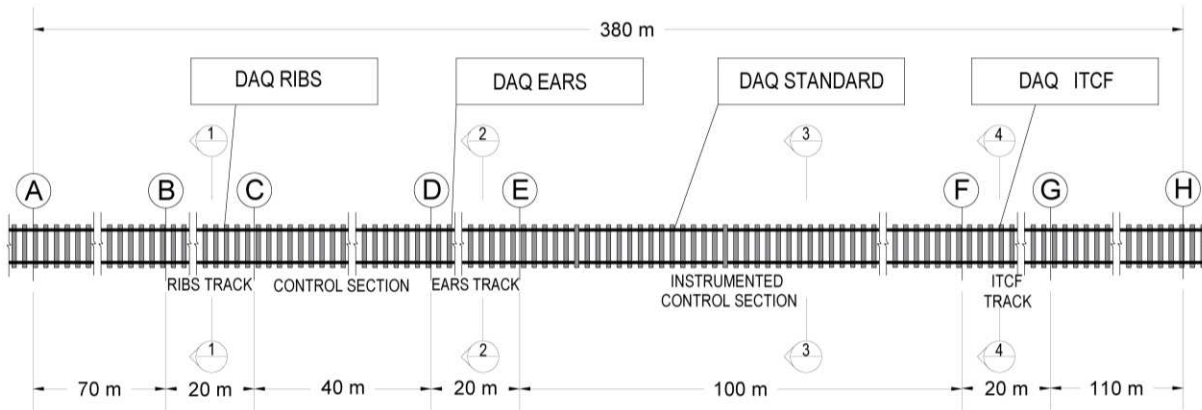

2

3

4


1

2 **FIG. 2** Preparation of RIBS: (a) Volumetric mixer for mixing of ballast and rubber particles (b)

3 PSD of fresh ballast, RIBS, and capping.



(a)

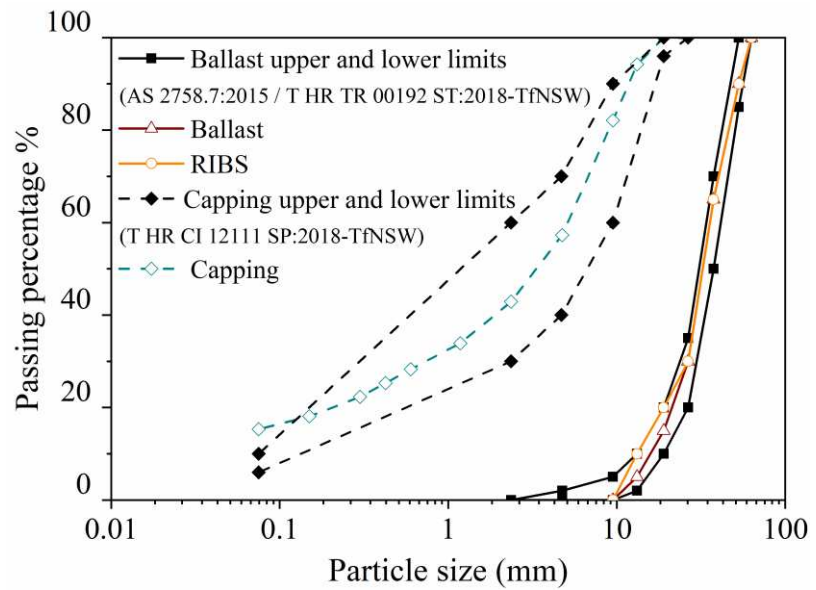


(b)

4
5

6
7


1 **FIG. 3** Typical cross sections (a) standard section (b) RIBS section (c) EARS section and (d)
 2 ITCF section.

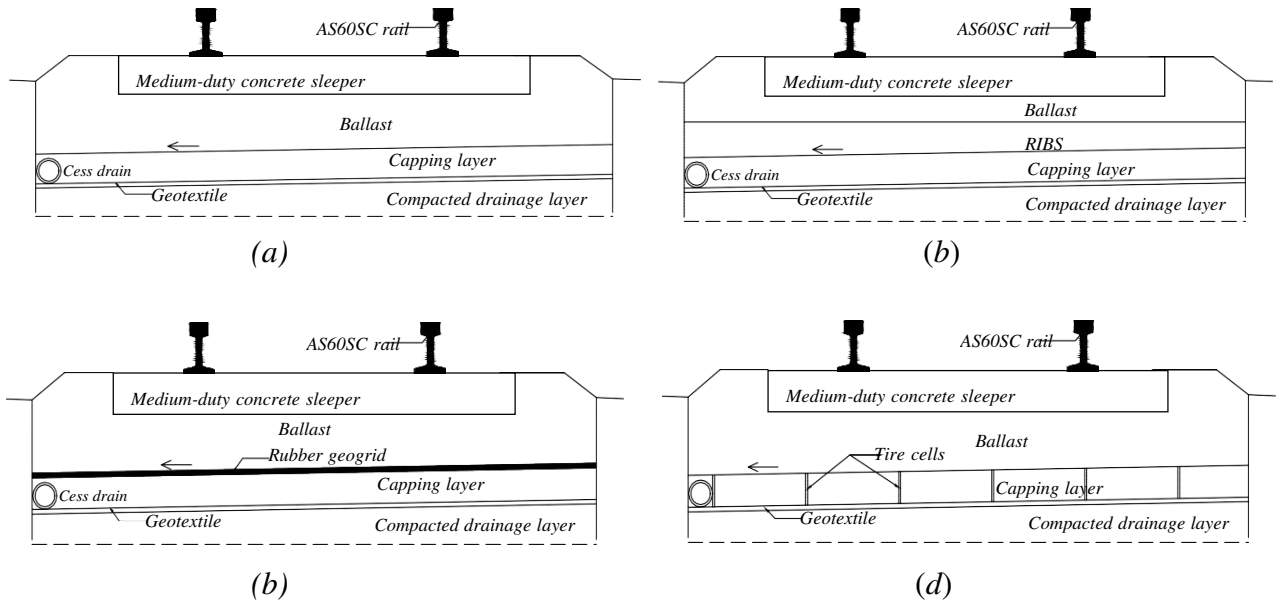

1 **FIG. 4** Track construction (a) Placing RIBS in the RIBS rack (b) Rubber geogrids in the EARS
2 section and (c) Tire cell assembly in the ITCF section.



(a)

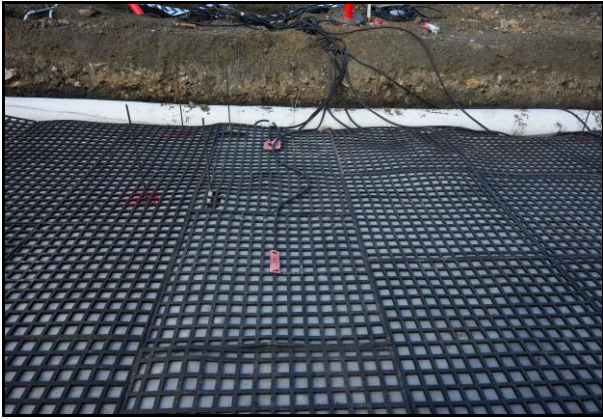

(b)




(c)

3
4

5
6
7


8
9

1
 2 **FIG. 5** (a) Vertical pressure distributions under dynamic loading (b) Vertical pressure
 3 distribution of standard track, RIBS track, EARS track and ITCF track.

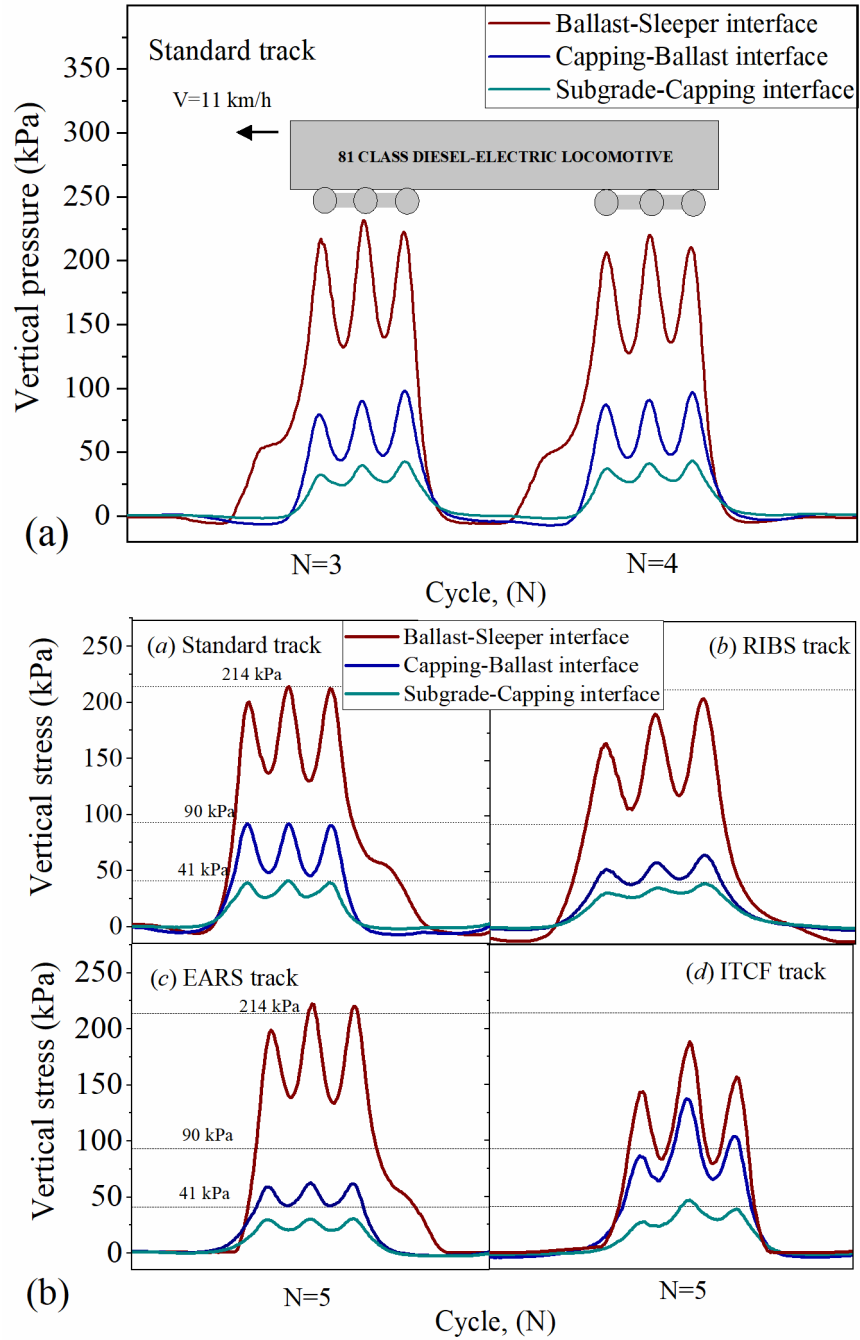

4

1 **FIG 6.** Normalized lateral pressures in track sections.

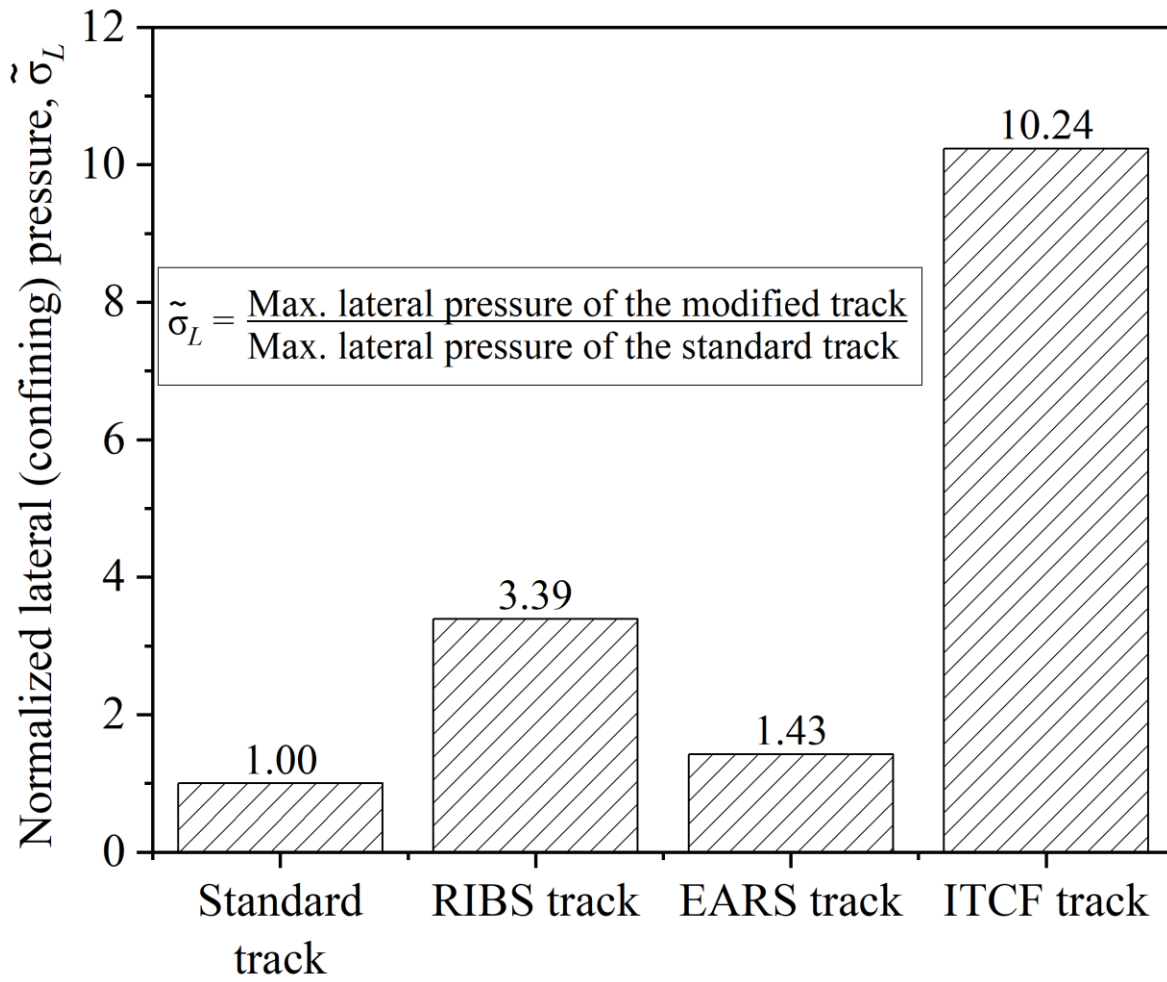

2
3
4
5
6
7
8
9

1

2 **FIG 7.** Location of Port Kembla reclamation project (a) before the reclamation in 2011 and (b)


3 after the reclamation in 2017 (Google (2022) Port Kembla).



4

5

(a)

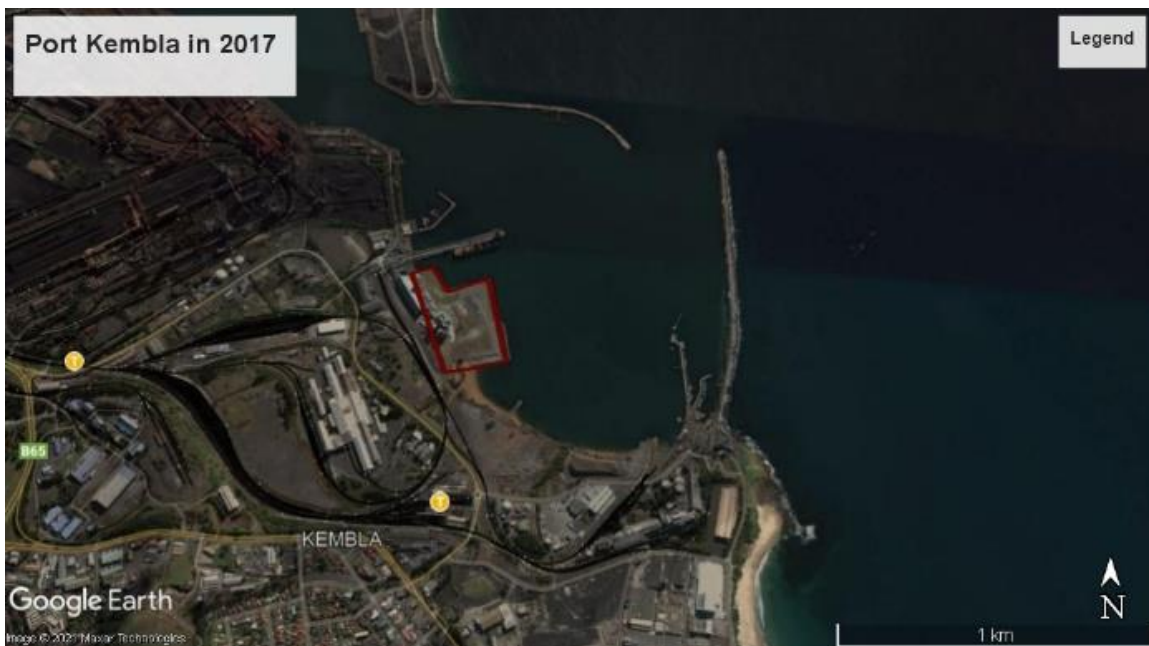


6

(b)

1
2 **FIG 8.** Optimisation of CW-BOS blend as structural fill for port reclamation (Chiaro et al.
3 2015).

4

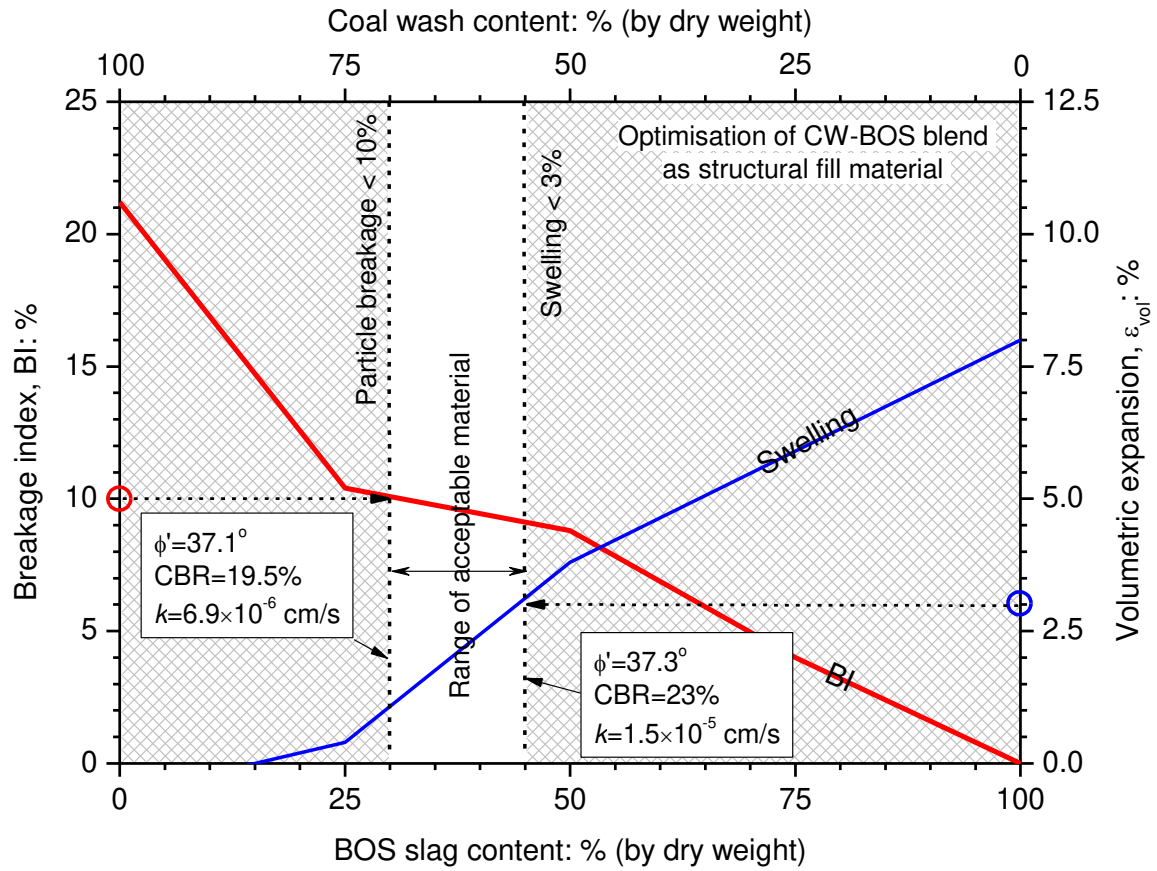

5

6


7

8


9

10

1 **FIG 9.** (a) PSD curves of CW, FA and CWFA mixtures and (b) Variations of California Bearing
 2 Ratio (CBR), Unconfined compressive Strength (UCS) and Void ratio under different FA
 3 contents (Wang et al. 2019).

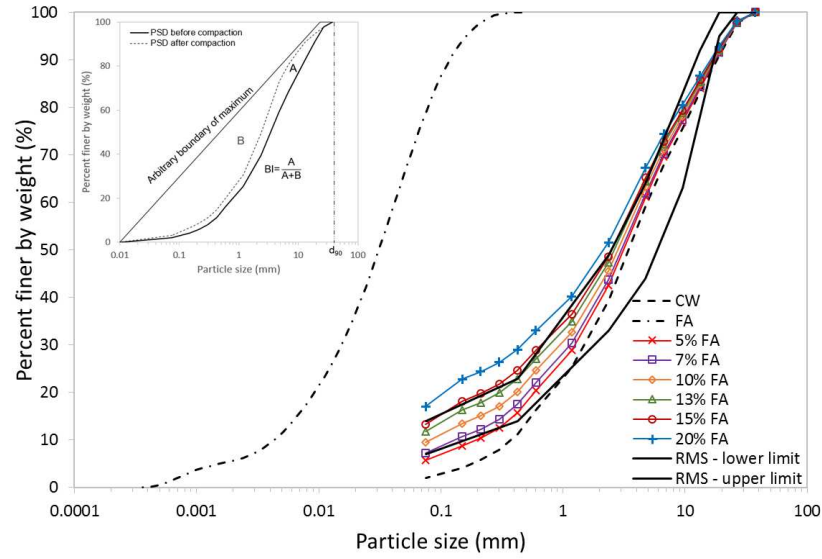

(a)

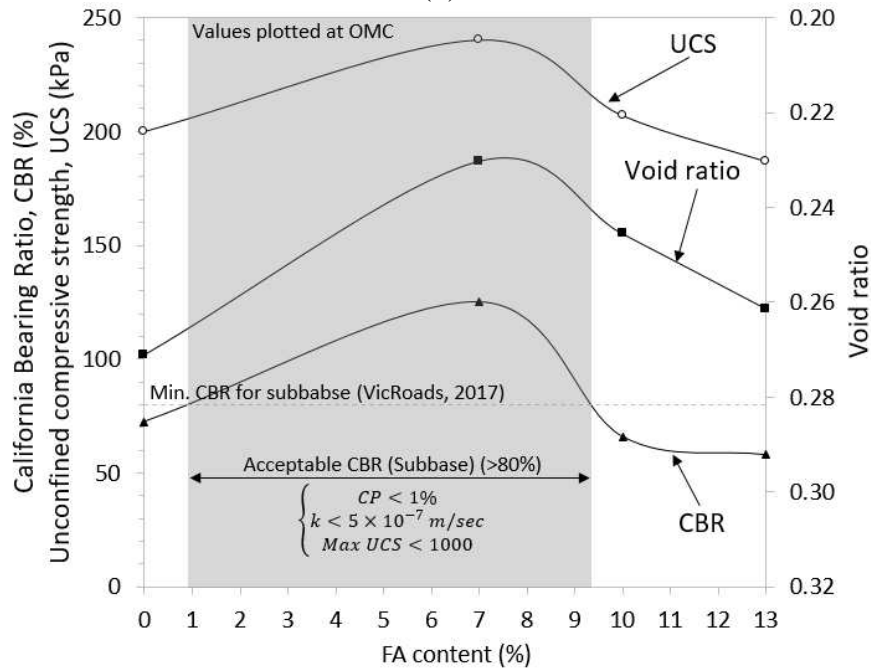

(b)

4
5

6
7

1
2
3

FIG 10. Field trial site (Google (2022) Kangaroo Valley).



4
5
6
7
8
9
10
11
12
13
14
15
16
17
18

1 **FIG 11.** Construction sequences (a) removal of existing layer, (b) compaction using Roller, (c)
 2 complete surface.




3
 4 (a)

(b)

(c)

3
 4
 5
 6

7 **FIG 12.** Average rut depths of both sections after 2 years.

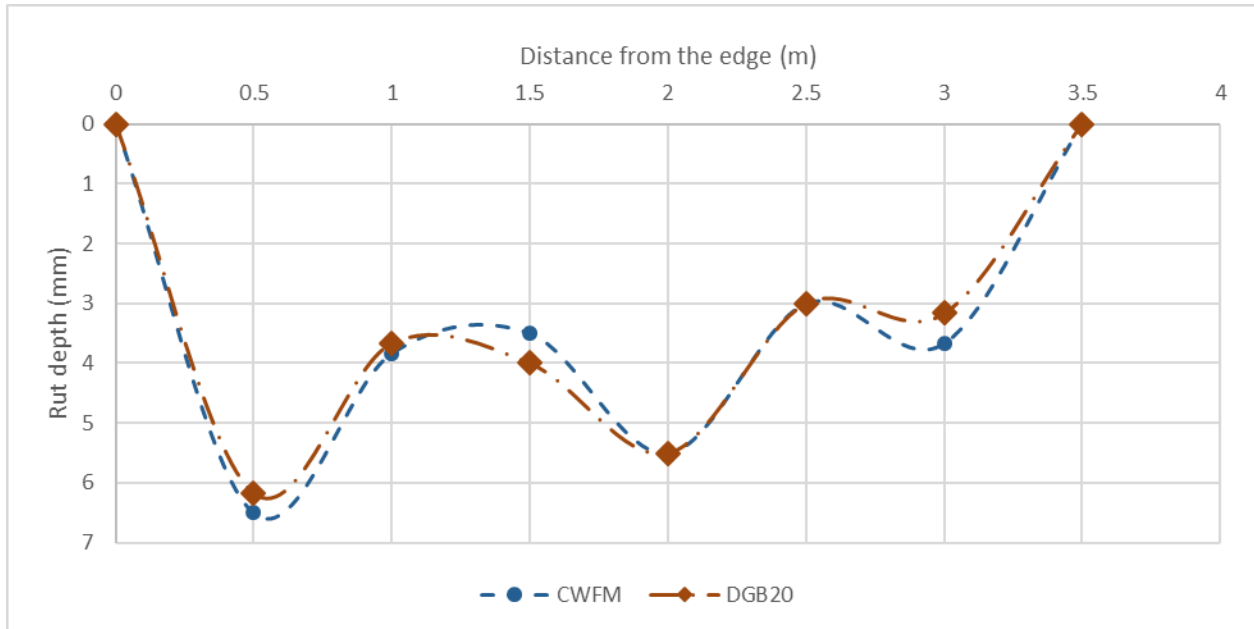

8
 9