



Deposited via The University of York.

White Rose Research Online URL for this paper:

<https://eprints.whiterose.ac.uk/id/eprint/204188/>

Version: Accepted Version

Article:

Hassan, Sharmarke and Dhimish, Mahmoud (2023) Enhancing solar photovoltaic modules quality assurance through convolutional neural network-aided automated defect detection. *Renewable Energy*. 119389. ISSN: 0960-1481

<https://doi.org/10.1016/j.renene.2023.119389>

Reuse

This article is distributed under the terms of the Creative Commons Attribution (CC BY) licence. This licence allows you to distribute, remix, tweak, and build upon the work, even commercially, as long as you credit the authors for the original work. More information and the full terms of the licence here:

<https://creativecommons.org/licenses/>

Takedown

If you consider content in White Rose Research Online to be in breach of UK law, please notify us by emailing eprints@whiterose.ac.uk including the URL of the record and the reason for the withdrawal request.

Enhancing Solar Photovoltaic Modules Quality Assurance through Convolutional Neural Network-Aided Automated Defect Detection

Sharmarke Hassan*, Mahmoud Dhimish

Laboratory of Photovoltaics, School of Physics, Engineering and Technology, University of York, York YO10 5DD, United Kingdom

*Corresponding Author: smh600@york.ac.uk

Abstract

Detecting cracks in solar photovoltaic (PV) modules plays an important role in ensuring their performance and reliability. The development of convolutional neural networks (CNNs) has introduced a game-changing dimension in the detection of defects in PV modules. This paper proposes an automated defect detection method for PV, by leveraging custom-designed CNN to accurately analyse electroluminescence (EL) images, identifying defects such as cracks, mini-cracks, potential induced degradation (PID), and shaded areas. The proposed system achieves a high level of validation accuracy of 98.07%, reducing manual inspection demands, enhancing quality standards, and saving costs. The system was validated in a case study for PV installations faulty with PID, where it identified all defective modules with a high degree of precision of 96.6%, surpassing existing methods. This methodology holds promise for revolutionizing PV industry quality control, improving module reliability, and supporting sustainable solar energy growth.

Keywords: Convolutional Neural Network; Artificial Energy; Photovoltaics; Automated Defect Detection; Electroluminescence Imaging.

1. Introduction

Convolutional neural network (CNN) stands as the most prominent deep learning technique in the field of machine learning. With the advent of this computer vision-based technology, humans can now perform tasks that were previously inconceivable, such as face recognition, automatic disease diagnosis, or autonomous vehicle operation [1]. By enabling machines to interpret images and videos, CNN has significantly transformed the way individuals interact with the world, opening new possibilities for research and various applications.

As a result of learning and performing task effortlessly and intelligently, CNN can execute tasks on par with human beings. It has thus been able to deliver the promised results such as recognition of faces or objects [2], detection of objects or fraud [3], or prediction of weather [4]. Additionally, CNN suggests friends on social media by suggesting individuals who they may already know [5].

35 Moreover, CNN's ability to respond to new situations quickly and effectively is a testament to
36 its advanced artificial intelligence (AI) capabilities. The architectures of CNN are primarily
37 developed by experts with extensive domain knowledge, which makes it challenging for users
38 without domain expertise to utilize them; therefore, there has been a growing interest in
39 automating the architectures to enhance both efficiency and accessibility [6,7].

40 CNN architectures are divided into two main categories: automatic + manual tuning
41 architectures and automated architectures [8-11]. As a result of the first category offering the
42 extra feature of manually adjusting, it is superior to existing architectures incapable of manual
43 tuning, even though individuals without domain knowledge of CNN prefer architectures that
44 are designed to not require manual tuning since no adjustments are necessary.

45 Since PV modules are produced daily, it is becoming increasingly challenging to perform
46 manual inspections to detect defects, and so the need for automated inspections has
47 increased. Therefore, researchers have focused on developing automated inspection
48 methods such as image processing and signal processing [12-15]. As a result, automated
49 inspection methods have been widely studied in recent years, and many successful
50 implementations have been reached. Despite this, the use of CNN as an automated means of
51 defect detection has increased significantly in recent years [16,17]. However, a recent study
52 yielded 93% accuracy when using CNN as an automated technique of defect detection¹⁸. As
53 such, these techniques have become increasingly popular for detecting defects, with CNNs
54 being particularly successful in this regard.

55 Consequently, the CNN detection technique has several advantages that make it superior to
56 conventional methods. The first advantage is that CNN is capable of learning and detecting
57 the various patterns present in EL images. As a second advantage, the CNN technique
58 achieves excellent accuracy and saves time since manual inspection is not required, in
59 addition to the fact that sometimes large quantities of PV are required for inspection. As a
60 third benefit, CNN can prevent hazards since it detects different types of PV defects. Overall,
61 the cumulative effect improves the accuracy of defect detection and the durability and
62 performance of PV modules.

63 CNN is praised for achieving remarkable performance in a wide range of image-related tasks
64 but suffers from several limitations about solar panel inspection. Firstly, the lack of extensive
65 and diverse datasets is a major impediment. Current approaches often rely on datasets
66 containing fewer than 10,000 images, limiting their ability to capture the full spectrum of real-
67 world conditions. Consequently, training CNN models on such insufficient data may limit their
68 capacity to accurately identify patterns and detect cracks across varying scenarios.

69 Moreover, CNNs struggle with generalization in solar panel inspection. Solar panels display a
70 wide range of diversity in design, texture, and manufacturing processes. Additionally,
71 environmental conditions like light intensity and soiling levels vary significantly between
72 installations. CNN models, typically trained on specific datasets, fail to account for this
73 diversity. Consequently, a model trained to detect cracks in one type of solar panel may fail
74 when applied to others, as it lacks the adaptability to recognize patterns unique to different
75 panels. Furthermore, CNNs often operate as "black boxes," lacking interpretability and

76 explain ability. This is a crucial limitation when trust and accountability are paramount. In
77 solar panel inspection, understanding why a model classified a particular cell as cracked is
78 vital. Incorporating interpretability and explain ability mechanisms into CNN models is
79 essential to establish trust, ensuring reliability in critical applications.

80

81 This work represents a novel approach to automated PV defect detection techniques as it
82 consists of two levels of inspection: the cell level inspection and the module level inspection.
83 This is accomplished by inspecting each solar cell separately, and based on the results,
84 determining whether the module has been accepted or rejected based on the percentage of
85 healthy cells. In contrast, the green indicator indicates that a solar cell is healthy or accepted,
86 while the red indicator indicates that a solar cell has been defected.

87 This is achieved by developing four different CNN architectures, and by varying the number
88 of convolutional layers and pooling of architectures, we reach an impressive level of validation
89 accuracy of 98.07%, which is referred to in this paper as Arch 4. The four architectures are
90 trained using a dataset that contains images of healthy and defective solar cells. The
91 architectures are then evaluated based on several metrics, such as accuracy, precision, recall,
92 and specificity. The best performing architecture, Arch 4, is then used to classify the solar cells
93 into healthy and defective categories.

94 Highlighting its uniqueness, the approach presented in the research paper stands out as the
95 sole method with the ability to detect a diverse array of anomalies, including cracks, PID,
96 shaded regions, and breakdowns. This distinctive capability positions the research as a
97 pioneering endeavour, offering a comprehensive solution to quality assessment within the PV
98 industry. The emphasis on this aspect underscores the groundbreaking nature of this work
99 and its potential to significantly advance the field. This work stands out from the rest, offering
100 a comprehensive solution to quality assessment within the PV industry. Its pioneering nature
101 and potential impact make it a groundbreaking achievement in the field.

102 A notable aspect of this research is its two-level inspection strategy, which includes
103 examinations at both the cell and module levels. By carefully assessing individual solar cells
104 and then evaluating overall module health based on the percentage of healthy cells, this
105 approach adds precision that greatly improves defect detection. This innovative approach
106 addresses an evident gap in current knowledge, as previous methods focused on module-
107 level inspections.

108 Furthermore, this research involves the optimization and customization of CNN architectures,
109 leading to an impressive validation accuracy of 98.07% (referred to as Arch 4). This
110 achievement reflects the research team's dedication to advancing automated inspection
111 techniques while enhancing the methods' practicality. In summary, this research introduces
112 an innovative approach to automated PV defect detection and validates its feasibility and
113 effectiveness through extensive empirical testing. By offering a more detailed and precise
114 defect analysis method, this study contributes to PV module quality control development.
115 With an increasing demand for solar energy solutions, this research has the potential to
116 enhance the efficiency, reliability, and sustainability of the solar energy sector.

117 **2. Materials and Methods**


118 **2.1 EL Imaging**

119 The electroluminescence (EL) imaging technique is an effective method to inspect the
120 performance of solar cells [19]. To achieve this, it is imperative to apply a biased current to
121 the cell. In turn, this will cause it to glow, making it easy to detect all defects that the solar
122 cell has, that are not visible to the naked eye [20]. Furthermore, it is a non-destructive testing
123 method, which allows inspection of the entire cell's surface quickly and accurately.

124 Thus, in this study, a Brightspot automation imager was utilised to capture EL images, which
125 were captured using a digital camera with a resolution of 6k x 4k pixels and a focal length of
126 18-55mm, as shown in Figure 1(a), and the main components of Brightspot EL Imaging setup
127 are shown in Figure 1(b). The Brightspot Automation imager was chosen due to its ability to
128 capture high-resolution images with a wide field of view.
129 This allows the capture of more detail and provides a better overall picture of the EL images.
130 Additionally, the digital camera with the 6k x 4k resolution and 18-55mm focal length provides
131 a very sharp image with a wide range of colours and contrast. In addition, the PV module was
132 connected to a power supply to generate a biased current.



133 (a)

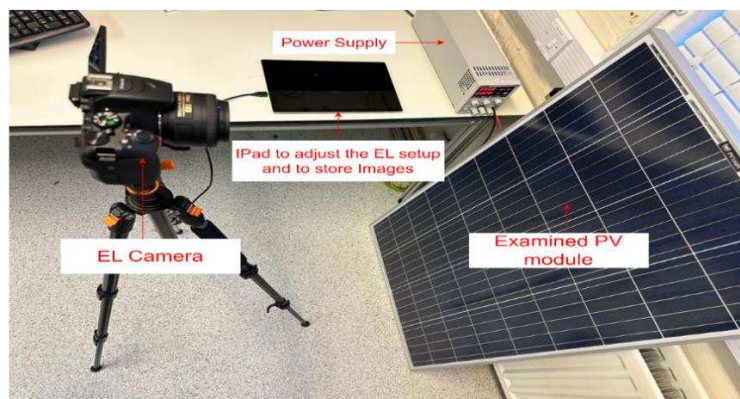

134 (b)

135 Figure 1. (a) EL imaging setup, (b) EL imaging components.

2.2 Image Segmentation

Image segmentation is a computer vision task that entails labelling specific areas of an image based on what is being displayed on the image [21]. To be precise, semantic image segmentation aims to label each pixel in an image with a class corresponding to what is being represented in that image, as the system is predicting the outcome of every pixel [22,23]. This is achieved by using supervised or unsupervised learning algorithms to detect certain features of the image and then assigning a label to each pixel based on those features. For example, these algorithms can be used to recognize objects in the image, and then label each pixel according to the object it belongs to.

The process of labelling an image pixel-by-pixel can be defined as the collection of random variables $\{x_0, \dots, x_n\}$. Where n represents the image's total pixels. Each element $x_i \in L$ takes one of m discrete labels from the set $L = \{1, \dots, m\}$. A convolutional neural network (CNN) models a probability distribution $Q(X|\theta, I)$ over the random variables X , where θ represents the network parameters. Typically, this distribution is modeled as a product of independent marginals, denoted as $Q(X|\theta, I) = \prod_i q_i(x_i|\theta, I)$ [24]. Each of these marginals represents a SoftMax probability. Each marginal $q_i(x_i|\theta, I)$ is parameterized by a set of weights θ_i which are learned by the CNN during training (R). The parameters θ are learned by optimizing the network to minimize a loss function, which is a measure of the difference between the predicted and actual outputs. This functionality is presented in (1) below [24].

$$q_i(x_i|\theta, I) = \frac{\exp(f_i(x_i; \theta, I))}{z_i} \quad (1)$$


Where $z_i = \sum_{l \in L} \exp(f_i(x_i; \theta, I))$ represents the partition function of pixel i . The function f_i represents the numerical score of the neural network.

As a result, in this study, the EL images of the PV panels were segmented into solar cells pixel, and each pixel was examined, segmented into pixels based on conditions, such as healthy, Mini crack, breakdown, PID, and shaded areas, as shown in Figure 2(a). The first pixel segment is characterized as healthy, labelled as 1, and represents every solar cell pixel with no defects. The second segment of solar cells is made up of solar cell pixels with mini cracks and is indicated by 2.


Consequently, the third segment of the solar cells are composed of solar cell pixels with major cracks or breakdowns, which can massively degrade the PV panels' output power, and it is labelled as 3 [25]. The fourth segment of the label is potential-induced degradation (PID). PID is a leading cause of module degradation and is caused by the high voltage generated between the encapsulants and the front glass surface, which is grounded through either the cell frame or the substructure, and it is labelled as 4 (PID) [26]. Lastly, is the shaded area. Shaded is represented as 5 in the colour scheme as shaded areas create uneven current distribution in the busbars, which in turn stresses the cells and consequently higher temperatures would result in power degradation [27].

The pixels were further analysed to determine the percentage of each condition in the PV panel to assess the overall health of the solar cell. It was noted that minor blotches appeared on the solar cells, as shown in Figure 2(b). These spots appeared on the EL because of the

176 camera's calibration/resolution, and they do not have a detrimental effect on the solar cells.
177 Hence, these spots are negligible when examining the condition of the cells.

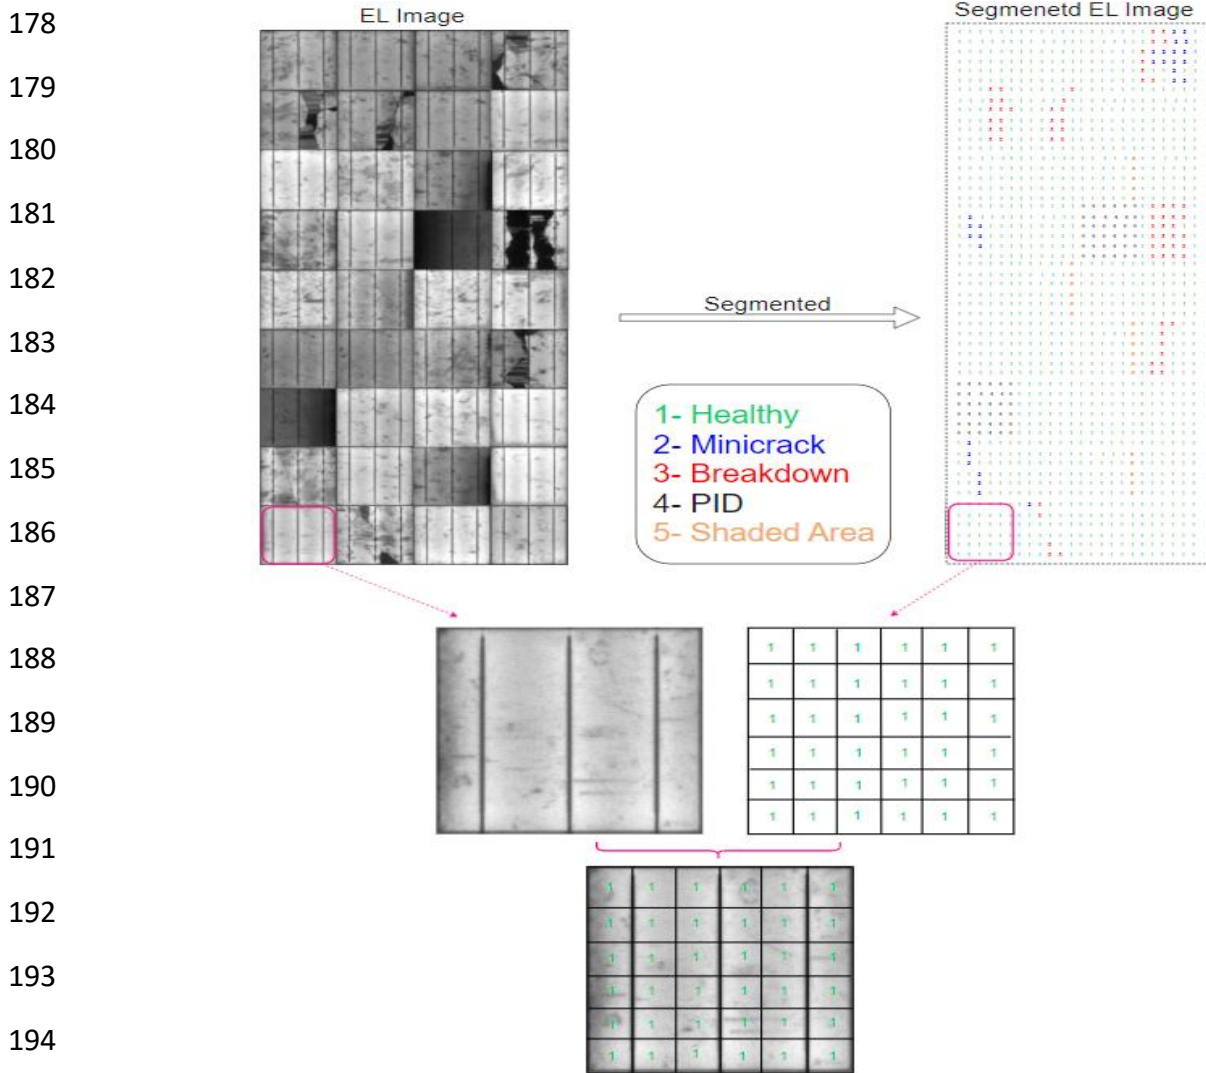

196 (a)

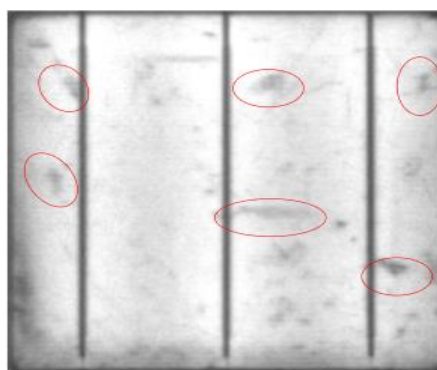

(b)

199 Figure 2. (a) Segmentation processing of PV module EL image, (b) Minor black spots appear
200 in the EL image of the solar cell.

201 **2.3 CNN Architecture**


202 Having completed the segmentation of the image, the subsequent stage is to build a CNN
203 architecture that is suitable for training tasks like this with a high level of validation accuracy.
204 Therefore, there are different layers to employ to build CNN architecture, as shown in Figure
205 3. The first layer is the convolutional layer composed of filters that are learned during the
206 process and are smaller in size than the actual image. This layer later is combined with an
207 activation map. The second layer is the batch Normalization layer, and its main function is to
208 maintain regularity and avoid excess fitting and at the same time to speed up the computation
209 of the CNN. The Rectified Linear Unit (ReLU) is the next layer. Its main function is to remove
210 all negative numbers and replace them with zero. The next layer is the pooling layer, which
211 extracts values from image segments defined by kernels.

212 There are two methods to retrieve the value, either by using max pooling and retrieving the
213 maximum number or by using mean pooling and computing the average. Hence, there is no
214 universal solution, and decisions should be made during training. A fully connected layer in a
215 neural network uses weight matrices to linearly transform input vectors and solve problems,
216 resulting in every possible connection between input and output vectors being present. The
217 CNN network employs the SoftMax function as the activation function in the output layer to
218 predict a probabilistic distribution in multi-class classification problems. The last layer is the
219 classification layer, which applies predefined rules for classifying.

220 Several architectures were developed from scratch, each with its own layers. As shown in
221 Table 1, Arch 1 has two convolutional layers and mean pooling with a learning rate of 0.0001
222 and 20 epochs, and the key parameters of all architectures are summarized in Table 2. Arch 1
223 had a validation accuracy of 81.5%. Our second architecture, referred to as Arch 2, contains
224 two convolutional layers, each with 32 filters, arranged in a connection between a
225 normalization layer and a Relu layer. However, the unique feature of this architecture is its
226 use of max-pooling rather than mean pooling, leading to an accuracy rate of 87.5% for
227 validation accuracy, followed by a third architecture, Arch 3, which has three layers of
228 convolutional layers with 32 filters and double pooling of max and mean, resulting in a
229 validation accuracy of 93.75%. This improved accuracy of Arch 3 is attributed to the double
230 pooling of both max and mean, which is unique to this architecture. During the construction
231 of the architecture, the research team continuously built and tested different architectures
232 (Arch 1-4) until Arch 4 was developed, which achieved a peak validation accuracy of 98.07%.
233 A detailed description of Arch 4 is presented in Figure 3.

234 Choosing Arch 4 was based on the fact that Arch 4 was made up of two double convolutional
235 layers with double max pooling, which resulted in a higher validation accuracy than all the
236 other architectures. Hence, achieving a validation accuracy higher than that of Arch 4 is not
237 feasible, since keeping the training network in place while modifying the Architecture
238 components will drop the validation accuracy. This is because the two double convolutional
239 layers and double max pooling provide an added depth to the network that allows it to
240 accurately identify patterns in the data. By changing the architecture, one essentially strips
241 away the complexity and depth of the network, which inevitably reduces its accuracy.

242

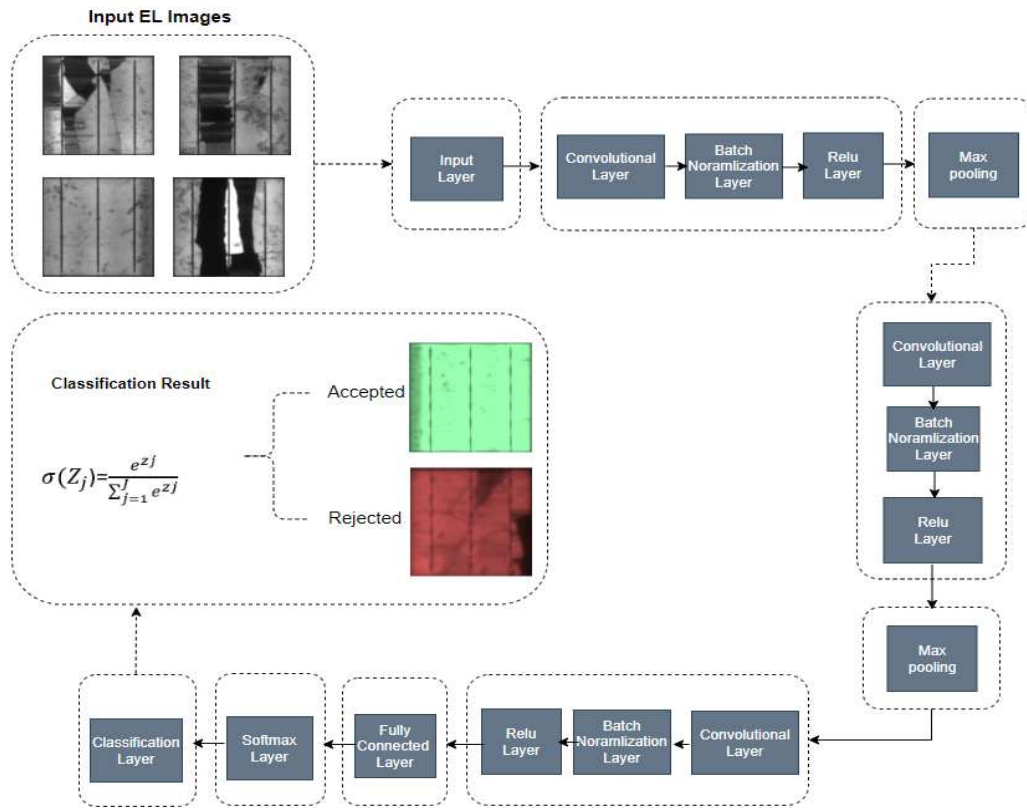

243


244

Figure 3. CNN Network architecture of Arch 4.

Table 1. Summary of the different architectures implemented and tested in this work.

Architecture Name	Description	Validation accuracy
Arch 1	Contains two convolutional layers of 32 filters connected to a normalization layer and a Relu layer by means of mean pooling, with initial input pixels of 227x227x3 pixels.	81.5%
Arch 2	Contains two convolutional layers of 32 filters connected to a normalization layer and a Relu layer by means of max pooling, with initial input pixels of 227x227x3 pixels.	87.5%
Arch 3	With an initial input size of 227x227x3 pixels, this convolutional layer contains three layers of 32 filters connected to a normalization layer and a Relu layer through a double pooling of max and mean.	93.75%
Arch 4	Three convolutional layers containing 32 filters with an initial input size of 227x227x3 pixels is connected through a double max pooling to a normalization layer and a ReLU layer.	98.07%

245 In developing a CNN architecture for solar cell inspection, adjusting parameters such as the
 246 number of epochs, learning rate, and validation accuracy was a major challenge [28]. To
 247 overcome this challenge, the team started with a learning rate of 0.01 and 10 epochs for the
 248 first CNN network, gradually increasing the learning rate to 0.0001 and epochs to 20, resulting
 249 in a maximum validation accuracy of 81.5% for Arch 1. Replicating the mean pooling of Arch
 250 1 with the max pooling of Arch 2 improved the validation accuracy to 87.5%. Adding three
 251 convolution layers with max-mean and max-max pooling for Arch 3 and Arch 4, respectively,
 252 improved the accuracy to 93.75% and 98.07%, respectively, with 20 epochs and a learning
 253 rate of 0.01. Figure 4 compares the validation accuracy of Arch 1 to 4.

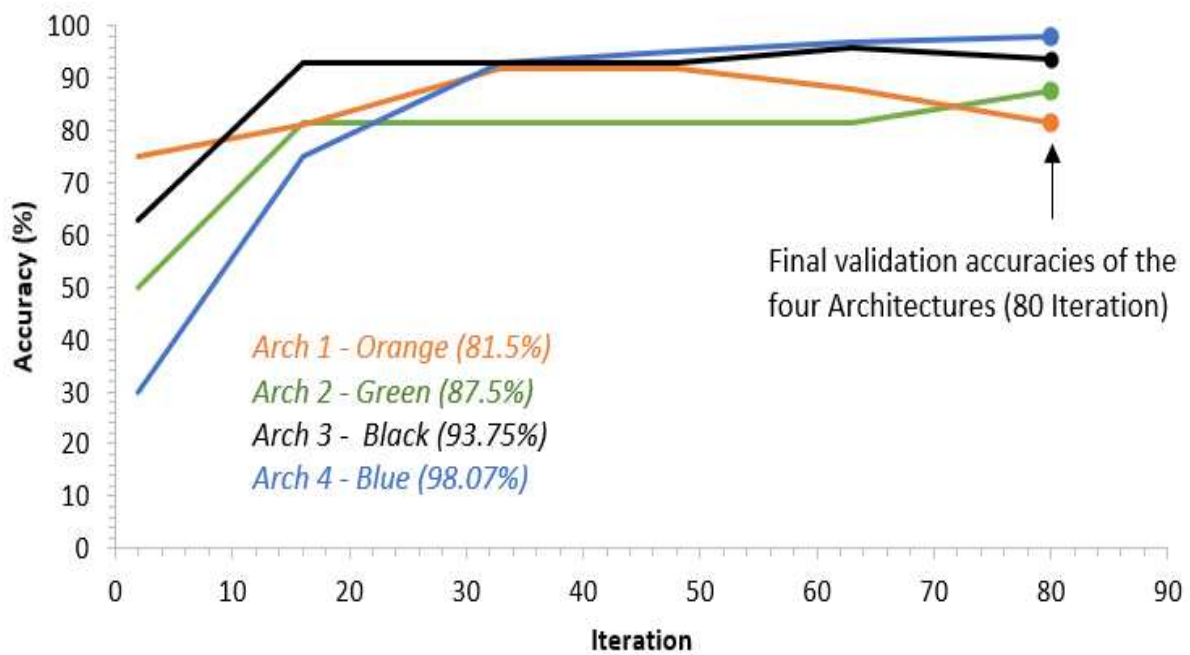

254
255

Figure 4. Validation accuracies of the four different CNN networks.

Table 2. Summary of CNN input parameters for (Arch 1-4).

Parameter	Value	Parameter	Value
Convolutional layers	32 Filters	Epochs	20
Filter size	3,3	Image input Size	227x227x3 Pixels
Mini batch size	16	Learn rate drop factor	0.1
Validation frequency	16	Initial learn Rate	0.0001
Solver	Sgdm	random rotation (Degree)	-90, 90

282 **3. Results**

283 The assessment of the CNN network put forward in this study can be broken down into two
284 distinct sections, in light of its dual-component structure. Specifically, the first component of
285 validation is conducted at the level of individual cells, while the second component focuses
286 on the module level, as the predicted output of the cells directly impacts the overall status of
287 the modules. This approach to validation serves to ensure the reliability and efficacy of the
288 CNN network under consideration while accounting for the complex interactions between its
289 constituent elements.

290 **3.1 Cell Level Prediction**

291 During the solar cell inspection process, each solar cell is examined separately by the trained
292 CNN network. This is done by examining all its pixels and then categorizing them as accepted
293 or rejected. This is done to ensure that each cell meets the quality standards, as shown in
294 Figure 5.

295 Accordingly, four different cells with varying conditions were examined. As shown in Figure
296 6, the first cell was a healthy cell free of defects. In turn, a CNN network was then employed
297 to examine each pixel independently to determine if there are any defects. Based on the
298 findings, it was predicted that the cell was accepted since it met the standard quality,
299 intended to have a cell with less than 14% of defects considered healthy, hence it was
300 displayed as green. In the second case, the CNN network predicted that the cell is unhealthy
301 since it presents a shaded area, and thus rejected it since more than 14% of the cell is
302 defective, resulting in it displaying as red.

303 Due to the defects in the third cell, the CNN predicted it as rejected since most pixels were
304 defective, and it was illustrated as red. A fourth cell, which presented a mini crack, was
305 deemed to be healthy by the CNN network based on the standard quality of a mini crack of
306 28%, which differs significantly from the standard quality for other defects, thus 17% of the
307 mini cracks are rated as healthy and displayed as green.


308 Consequently, the CNN network has shown the capability of detecting different defects in
309 solar cells and predicting them precisely. This makes it a trustworthy way to inspect solar cells,
310 and it could be used on all manufacturing assembly lines. This will contribute to the
311 production of high-quality solar cells and reduce production costs. Moreover, it would help
312 minimize the reliance on manual labour and facilitate in production of a higher quantity of
313 solar cells with improved efficiency. As a result, this could have a significant impact on the
314 renewable energy sector and help lower the cost of renewable energy sources.

315 **3.2 Module Level Prediction**

316 Within this section, the study addresses CNN's predictive capabilities at the module level by
317 assessing individual solar cells and subsequently determining the module's prediction based
318 on established quality standards shown in Figure 5, achieved through an independent
319 examination of each cell. This approach allows for the evaluation of the CNN's performance
320 concerning quality standards and facilitates the identification of potential flaws in the solar

321 modules that can be attributed to individual cells. Examining each cell individually aids in
 322 identifying potential issues that might otherwise be overlooked during module inspection.

323

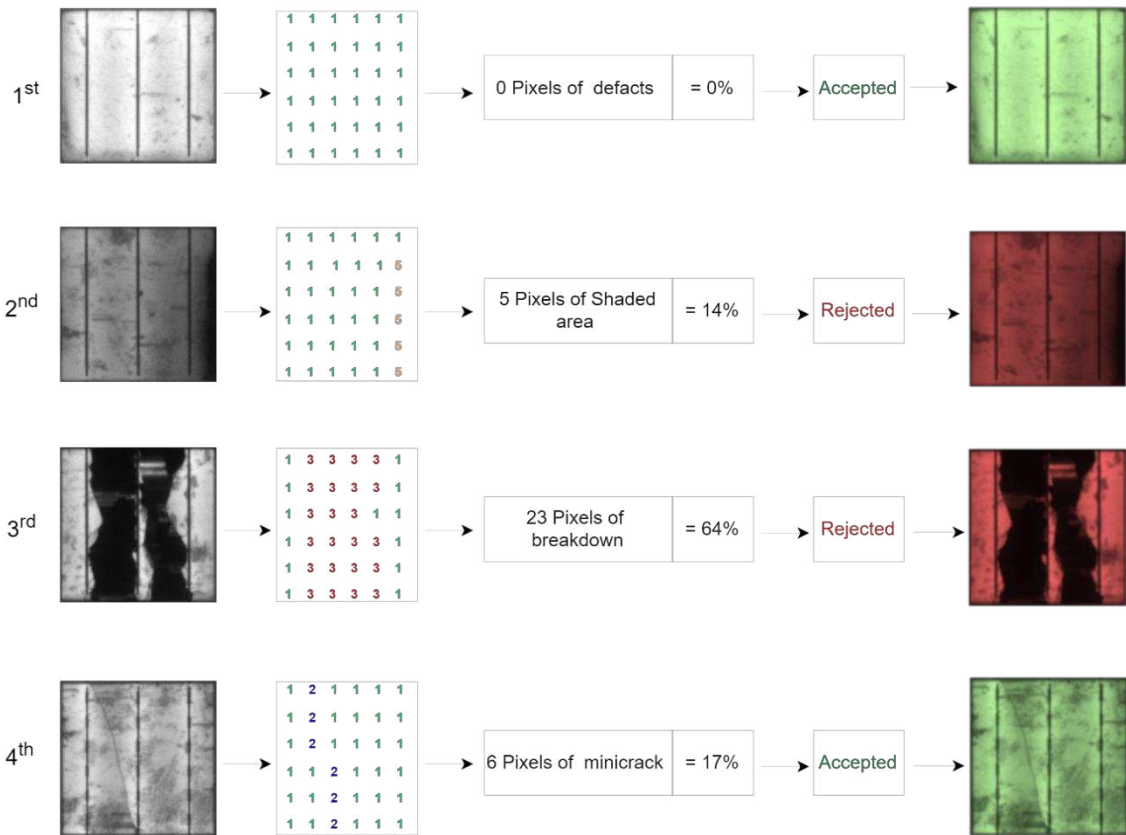


324

325 Figure 6. Cell level prediction (Mix of accepted and rejected cases).

326 To conduct the prediction, a PV module was examined and processed within a CNN network.
 327 As shown in Figure 7, the module is comprised of 36 solar cells, which were assessed
 328 separately using the CNN network. Based on CNN's assessment, 6 of the 36 solar cells on this
 329 module were deemed defective, equalling 17% of the module. As the percentage of defects
 330 is less than 20% of the standard quality rate, the system is referred to as a healthy PV module.
 331 Consequently, the system successfully predicted the PV module's health, while maintaining a
 332 relatively high-quality rating. This means that the CNN network accurately detected defective
 333 solar cells and distinguished them from healthy ones. As a result, it accurately assessed the
 334 overall health of the PV module and determined that it meets the standard quality rate.


335 A second PV module was employed to mark the prediction with a CNN network, as shown in
 336 Figure 8. According to the CNN analysis, the CNN network predicted that 10 of 36 solar cells
 337 of the module were defective, accounting for 28% of the total solar cells. As this defect rate
 338 surpasses the standard quality rate of 20%, the module was predicted to be rejected. The
 339 standard quality rate is based on the expected performance of a PV module, so if the defect
 340 rate surpasses that, it is likely that the module will not be able to meet the necessary
 341 standards for use. As a result, it is rejected.

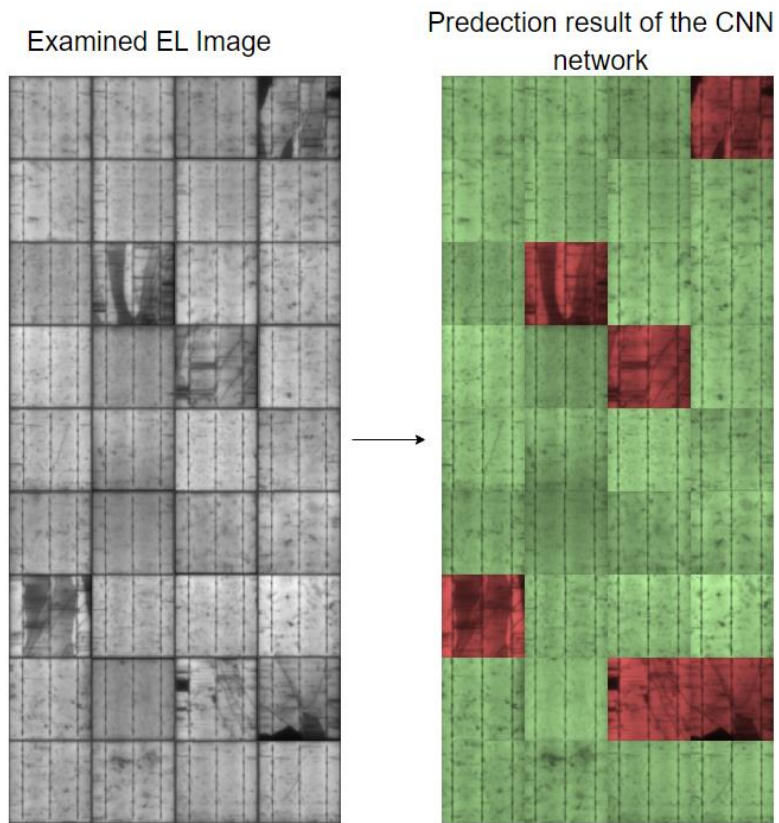

342

343

Figure 7. Module level prediction (accepted case).

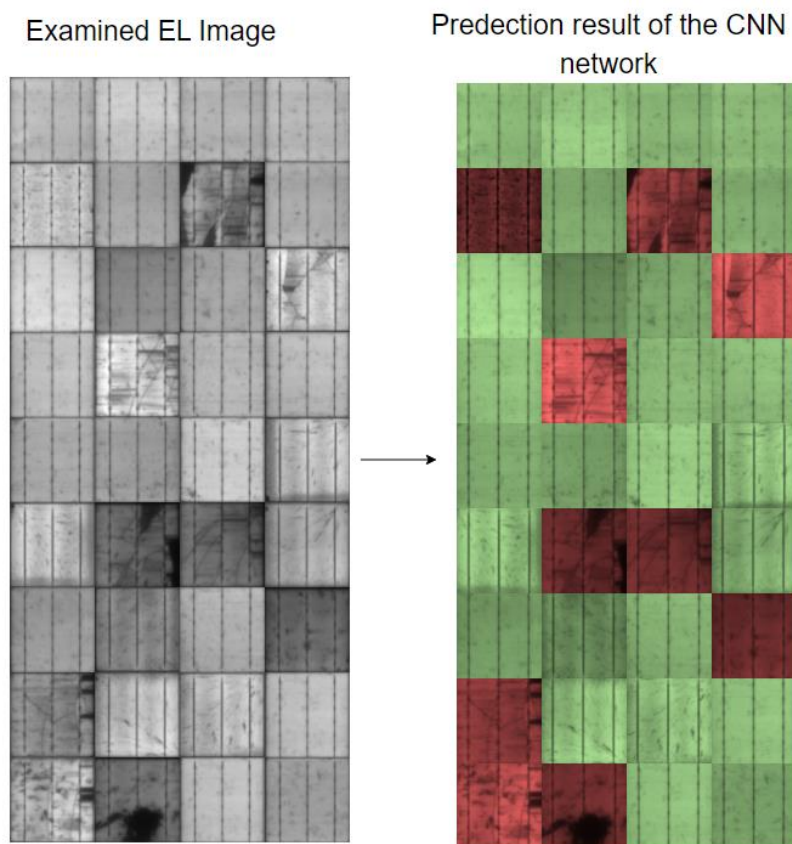

344

345

Figure 8. Module level prediction (rejected case).

3.3 Diverse EL imaging angles


346 Normally, EL imaging takes place by pointing the camera perpendicular to the PV module,
347 however, there may be instances when the camera can't be positioned perpendicular to the
348 PV module due to space limitations, or PV modules are installed on a tilted roof, and therefore
349 it is imperative to take EL images at an angle. In such cases, the camera should be positioned
350 as close as possible to the perpendicular angle and the EL images should be adjusted
351 accordingly to ensure accuracy.
352

353 Considering these factors, three different EL images taken with the same PV module at various
354 angles were examined. as shown in Figure 9. A first look at Figure 9(a) shows the conventional
355 method of capturing EL images; the EL camera is positioned perpendicular to the PV module
356 being examined and the CNN is predicted as being normal since there has been no change in
357 configuration. In addition, the PV module examined during EL camera capture had a tendency
358 to contrast to the right as illustrated in Figure 9(b) and the system predicted the same result
359 as the conventional method.

360 Furthermore, the third exam was conducted by contrasting the EL camera to the left of the
361 Examining PV module using the same camera configuration, as shown in Figure 9(c). However,
362 the system predicted the same results regardless of the camera angle. As a result, it can be
363 concluded that the EL camera capture was able to achieve consistent results, regardless of
364 the orientation of the PV module or the camera configuration. This indicates that the EL
365 camera has excellent consistency in capturing light and that it can accurately detect the
366 orientation of the PV module without any deviations. Furthermore, it also shows that the EL
367 camera is reliable for capturing light from different angles and with different camera
368 configurations.

369 Considering the three different angles in which the proposed CNN tool was examined, it made
370 the same prediction, as shown in Figure 9, indicating that the proposed tool has the capacity
371 to work from a variety of angles, eliminating the need to take the perpendicular angle to
372 utilize the tool. This highlighted the power of the proposed CNN tool to reliably perform its
373 task with great accuracy, regardless of the input angle. The high quality of this PV module
374 serves as a testament to the effectiveness of the CNN network, demonstrating its accuracy in
375 predicting defects with a high degree of accuracy. The results of this study further confirm
376 that CNN networks are highly effective at detecting defects in PV modules, providing a reliable
377 and accurate method for quality assurance. It also confirms the potential of AI for use in the
378 solar industry and other applications.

379 Additionally, this proposed tool has the benefit of examining different solar cells with a variety
380 of busbar technologies, since most modern solar cells are constructed using various busbar
381 (BB) designs, such as 3BB, 4BB and 5BB, so this proposed tool will be able to examine and
382 identify any defects in the solar cell, whether it is a 3BB, 4BB or 5BB. Moreover, this
383 instrument can accurately assess not just the standard 3BB, 4BB and 5BB busbar technology,
384 but also any other type of busbar technology that may be employed in modern solar cells,
385 allowing it to detect any possible defects. This makes it a great tool for ensuring the highest
386 quality standards for solar cells and their production.

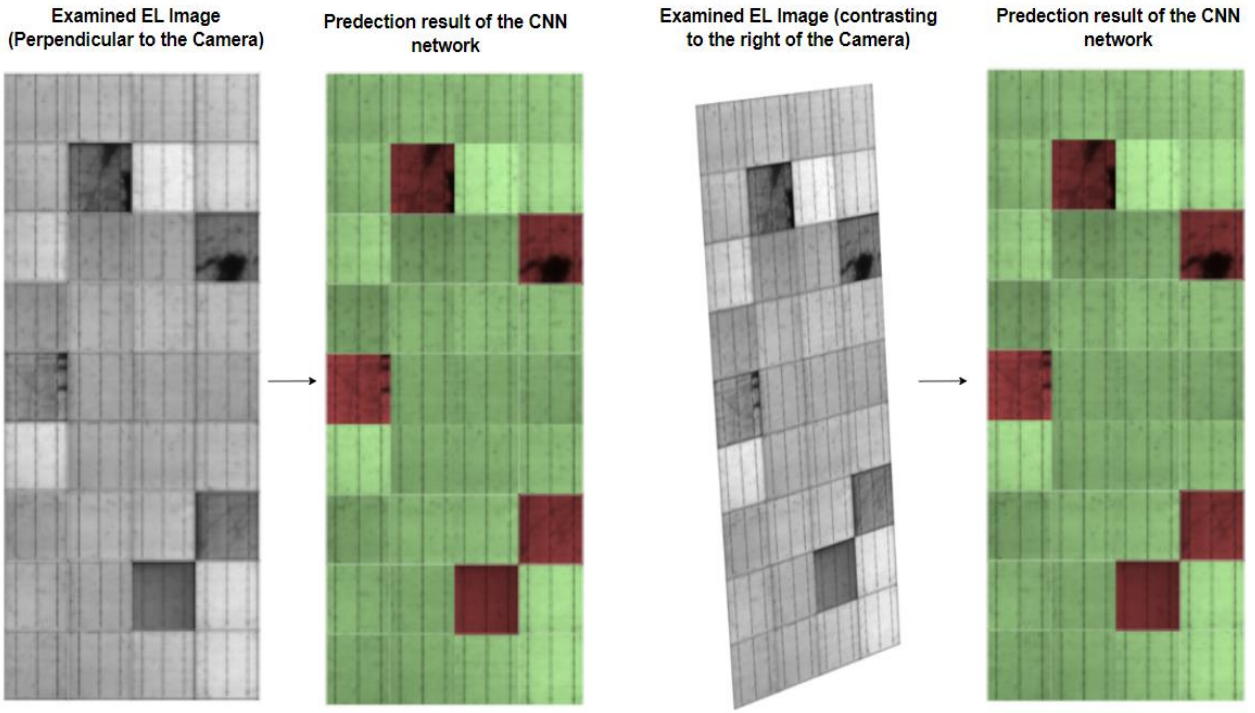


387

388

(a)

(b)

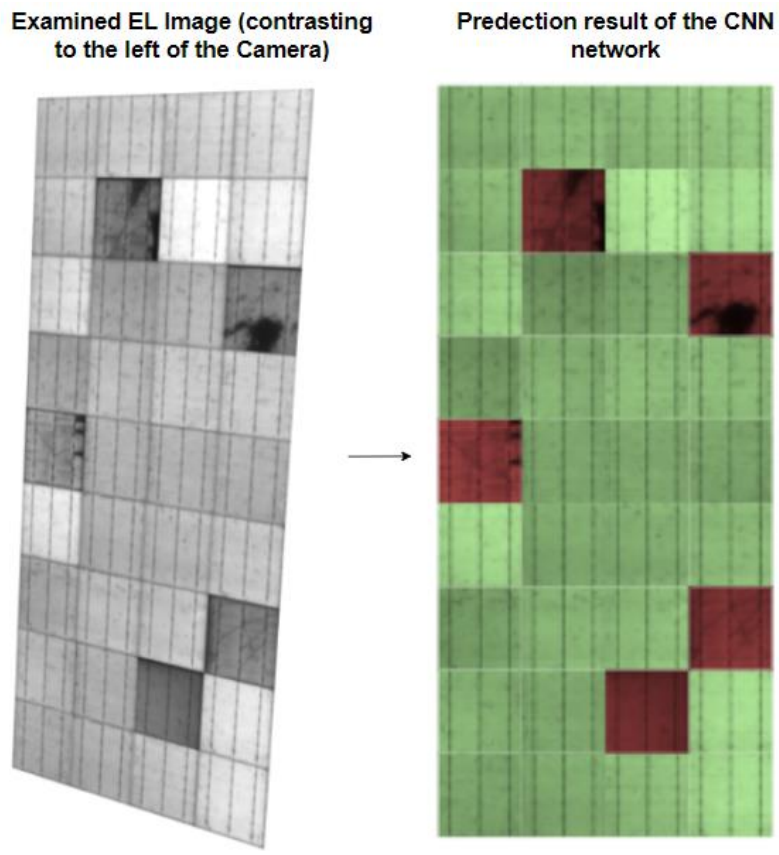

389

390

(c)

391 Figure 9. Predicting PV module level based on different imaging angles. (a) Perpendicular to
 392 the camera, (b) Contrasting to the right of camera, (c) Contrasting to the left of camera.

393 **3.4 Case Study**

394 With the proposed CNN network, the main application is to assess the large scale of PV
395 systems with minimal effort and within a short timeframe, along with a high degree of
396 accuracy. Therefore, a case study was conducted for a PV system. The case study was
397 conducted to validate the CNN network's accuracy. Additionally, it was intended to assess the
398 usefulness of the network in terms of identifying potential faults in the PV system and
399 providing guidance in terms of maintenance and optimization. According to Figure 10, the PV
400 string consists of nine polycrystalline silicon PV modules connected in series, and Table 3
401 summarises the string's main electrical parameters.




402 Figure 10. Examined PV system

403 Table 3. Electrical parameters of the second examined PV string at STC conditions.


Parameter	Value
Power at maximum power point (P_{MPP})	1950 W
Current at maximum power point (I_{MPP})	7.55 A
Voltage at maximum power point (V_{MPP})	258.3 V
Short circuit current (I_{SC})	8.05 A
Open circuit voltage (V_{OC})	331.2 V

404 The EL images of the PV modules were initially captured as illustrated in Figure 11(a), followed
405 by an analysis of all the EL images so that the system can classify them according to the
406 standard qualities shown in Figure 5. Consequently, the CNN network classified the solar cells
407 into green for those without defects and red for those with defects as shown in Figure 11(b).
408 Therefore, all 9 modules were predicted as rejected since the PV string is defective due to PID
409 (potential-induced degradation).

410 As a result, the proposed system can be an extremely useful tool for large-scale PV
411 installations by classifying the solar cells based on standard criteria with the assistance of the
412 CNN, the proposed tool can accurately detect defective cells with high precision. This can
413 significantly reduce the cost of large-scale PV installations by reducing the need for manual
414 inspection and maintenance. Furthermore, the system can also be used to identify any
415 potential problems before they occur, thus further reducing the overall costs associated with
416 a large-scale PV installation.

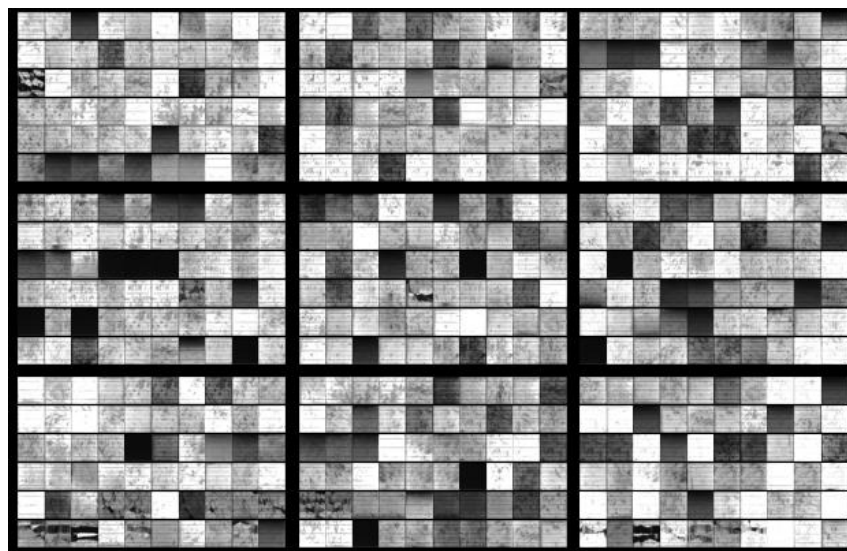

(a)

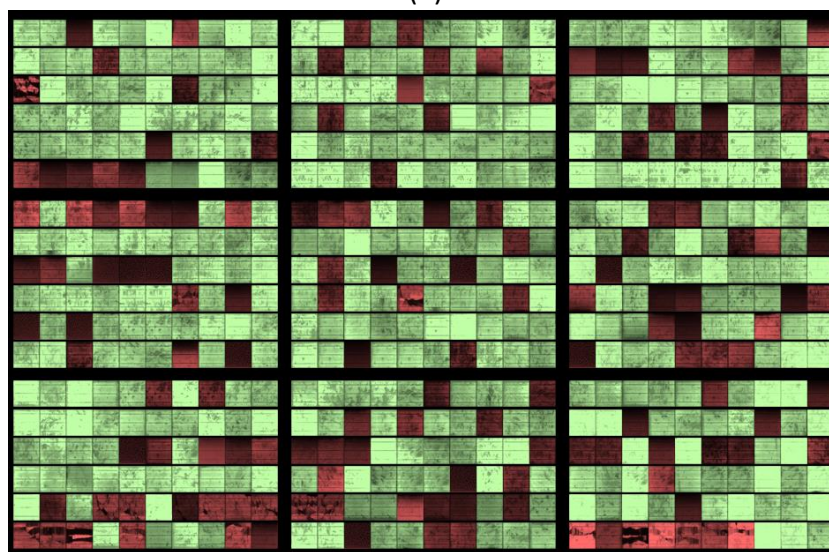

(b)

418 Figure 11. (a) EL image of the Modules, (b) Predicted result of the modules from the CNN
419 network.
420

421 An additional parameter to consider is how well the model performs in terms of predicting
 422 correctly or incorrectly for the data set under consideration, which is done by creating a
 423 confusion matrix table for the data set. The confusion matrix in Table 4 illustrates the results
 424 of the case study, which is made up of 540 solar cells, of which 385 are healthy while 155 are
 425 defective. Based on this, the accuracy and precision of the model are calculated using
 426 equations (1) and (2) to assess its performance, respectively.

427 Specifically, it was found that the accuracy of the model was 95.5%, which indicates that the
 428 model correctly classified 95.5% of all solar cells based on their health or crackability In this
 429 instance, the precision was 96.6%, which means that 96.6% of the solar cells that were
 430 actually defective were categorised as defective by the model, indicating that the CNN model
 431 was very accurate and precise in its prediction of the solar cells.

432 **Table 4.** Confusion matrix of the developed CNN model “Net4”.


		Actual Value	
		Actual No Cracks	Actual Cracks
Predicted Value	Predicted No Cracks	374	11
	Predicted Cracks	13	142

433
$$Accuracy = \frac{TP+TN}{TP+TN+FP+FN} = \frac{374+142}{374+142+13+11} = 95.5\% \quad (2)$$

434
$$Precision = \frac{TP}{TP+FP} = \frac{374}{374+13} = 96.6\% \quad (3)$$

435 The selection of an appropriate loss function for CNN models holds a great deal of significance
 436 as it quantifies the disparity between the predicted output and the actual ground truth data.
 437 The CNN model is carefully trained with adjustments to critical parameters to minimize the
 438 loss function and enhance performance, with the goal of minimising the loss function as part
 439 of the training process. It is designed to enhance the model's ability to accurately predict the
 440 loss function and to significantly increase its overall performance through this optimization
 441 process.

442 As shown in Figure 12, which presents Arch 4, we observe a desirable loss graph with two
 443 lines: red for training loss and blue for validation loss. The convergence and decrease of both
 444 lines indicate that the model reduces prediction errors. Initially, the model showed a slightly
 445 higher loss, but with continuous training, the loss steadily decreased toward zero. This results
 446 in effective learning and a remarkable reduction in loss and error.

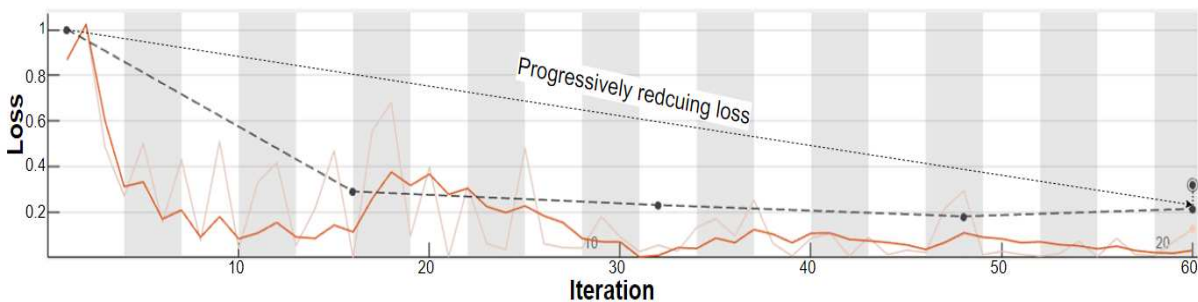

447
 448 **Figure 12.** Arch 4 CNN network learning Loss vs learning iterations (epochs).
 449

450 **3.4 Sensitivity analysis**

451 In the following section, an analysis of sensitivity regarding two pivotal parameters, the data
452 split ratio and the number of training epochs, is presented. Sensitivity analysis serves to
453 discern the effects of parameter variations on the system's performance.

454 The study explored different data split ratios, allocating data for training and validation
455 purposes in varying proportions: 50% training - 50% validation, 55% training - 45% validation,
456 60% training - 40% validation, 65% training - 35% validation, 70% training - 30% validation,
457 75% training - 35% validation and 80% training - 20% validation. Subsequently, the accuracy
458 of the system was evaluated under each configuration. Results from this sensitivity analysis
459 indicated that the configuration employing an 80% training - 20% validation split exhibited
460 the highest accuracy. This allocation appeared to strike an optimal balance between training
461 data volume and validation data representativeness. Deviating from this ratio, either by
462 increasing or decreasing the validation data proportion, was observed to result in decreased
463 accuracy. This finding underscores the significance of the data split ratio as a critical factor in
464 optimising system performance.

465 Additionally, the sensitivity analysis delved into the influence of training epochs by varying
466 the number of epochs employed during the training process. Six different configurations were
467 examined, involving 5, 10, 15, 20, 25 and 30, epochs, as shown in Figure 13. Accuracy
468 measurements were recorded for each configuration. The analysis demonstrated that the use
469 of 20 training epochs yielded the highest accuracy. Importantly, fewer epochs resulted in a
470 decline in accuracy due to inadequate model convergence, while increasing the number of
471 epochs beyond a certain threshold yielded diminishing returns and a corresponding drop in
472 accuracy. This outcome highlights the necessity for a judicious selection of the number of
473 training epochs during model training.


474 In order to provide further clarity regarding the effects of data split ratios and epochs,
475 confusion matrices are presented in the tables 5. These matrices offer a comprehensive
476 breakdown of the system's performance under each configuration, allowing for a more
477 detailed understanding of how variations in these parameters impact the system's
478 classification and prediction capabilities.

479 **Table 5** Sensitivity analysis of two parameters (data split ratio and epoch).

	Epoch 5	Epoch 10	Epoch 15	Epoch 20	Epoch 25	Epoch 30
Ratio 50:50	76.03%	76.93%	77.18%	78.89%	78.10%	77.63%
Ratio 55:45	78.43%	79.90%	80.50%	82.23%	81.66%	81.01%
Ratio 60:40	83.33%	84.19%	85.53%	87.52%	86.47%	85.96%
Ratio 65:35	89.77%	90.96%	92.22%	93.33%	93.02%	92.86%
Ratio 70:30	95.24%	96.64%	97.13%	98.07%	97.86%	97.55%

Ratio 75:25	93.37%	94.83%	95.21%	96.43%	96.11%	95.79%
Ratio 80:20	91.43%	92.09%	93.21	94.04%	93.88%	93.55%

480

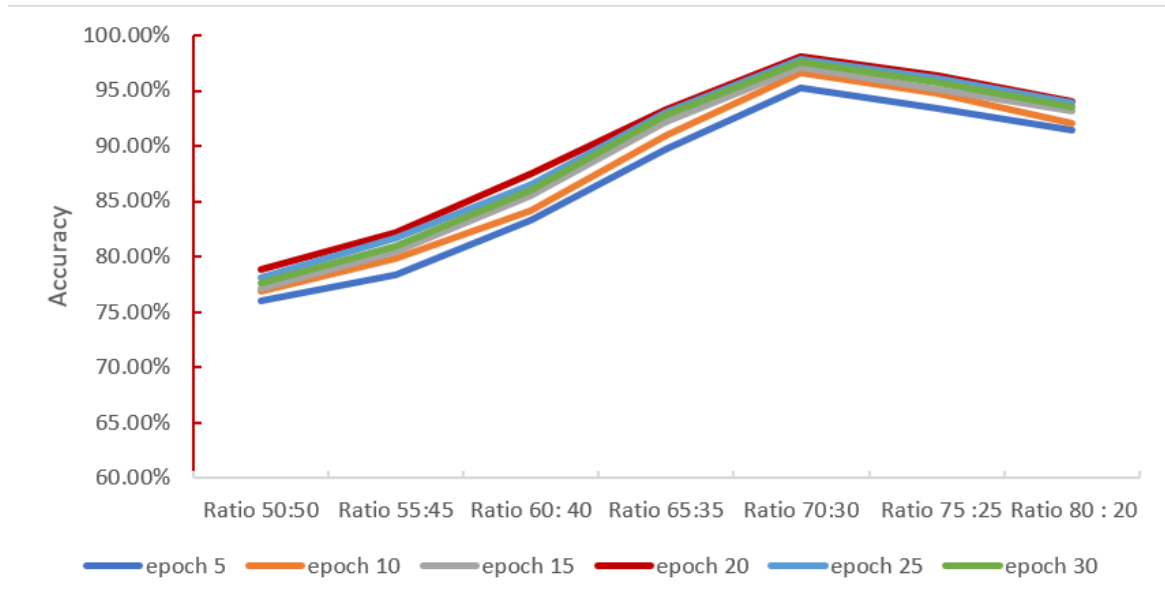

481

482

Figure 13. Accuracy of the sensitives of Epochs vs data split ratio.

483

484

485

486

487

488

489

In summary, the sensitivity analysis conducted in this study underscores the pronounced influence of data split ratios and the number of training epochs on the system's accuracy. Specifically, a data split ratio of 80% training - 20% validation and 20 training epochs produced the most favourable results. It is worth noting that the optimal values for these parameters may vary depending on the specific dataset and problem domain. Consequently, a deliberate and empirical approach to parameter selection is essential for the optimization of model performance.

490

4. Comparative Analysis

491

492

493

494

495

496

497

498

To gauge the feasibility of our proposed method, the research compared the results to several existing automated PV defect detection methods [18, 33-35] currently available in the PV industry. Table 6 provides a summary of the comparison. Several recent automated PV defect detection techniques utilizing the CNN architecture [18,33,34]. Nevertheless, it shares a comment limitation – the existing methods can only inspect at the cell level, and not at the module level as this work does. Additionally, a distinction based on the cell level is the existing methods can only detect cracks, regardless of their severity. However, it is insufficient to detect other defects such as PIDs and shaded areas.

499

500

501

502

Besides these automated PV defect detection methods, there are also automated PV defect detection methods that are based on CNN architectures that are not developed but rely instead on transfer learning to detect PV defects. This is done by using pre-trained CNN architectures that can be tweaked without affecting their genetic composition. Recently, a

503 study has been conducted to inspect PV module level using pre-trained AlexNet architecture
 504 [35]. This method differs in that it is used to inspect conventional PV images, as opposed to
 505 EL image. As a result, detecting defects such as PIDs or minor cracks that are not visible in
 506 conventional PV images will become increasingly challenging.

507 In this study, an automated method was developed for detecting PV defects at both the cell
 508 and module levels. This implies that module inspection is based on a visual assessment of the
 509 individual solar cells and can be accepted or rejected according to the percentage of healthy
 510 solar cells in each module. Moreover, the proposed method is capable of detecting defects
 511 such as cracks, PIDs, and shaded areas, unlike all other methods that are currently available.
 512 As a result, this system can be utilized in two different manners. First the system can be
 513 applied for cell-level inspection in PV assembly lines to inspect solar cells manufactured on
 514 the assembly line. The second application is that module-level inspection can be used to
 515 assess large-scale PV modules thereby minimizing manual labour and saving time while
 516 maintaining a high level of accuracy.

517 In this way, this proposed tool has proven to be highly accurate for the assessment of solar
 518 cells and PV modules and is the only tool available currently that can assess both the cells and
 519 modules simultaneously, in real-time, within a specified timeframe. Furthermore, this
 520 proposed tool can be used to examine PV modules at different angles, for example by taking
 521 an EL image from either the left or right side of the module and obtaining the same prediction
 522 regardless of the angle. This is since the proposed tool utilises CNN, which has the ability to
 523 detect and recognise features in images regardless of their orientation. Additionally, the
 524 proposed tool can be used to examine many PV systems, or planted PV systems, in a timely
 525 and convenient manner. Furthermore, the tool can provide an efficient and cost-effective way
 526 to analyse and compare the performance of numerous PV systems, both installed and
 527 planned.

528 **Table 6.** Comparison between our developed network against several recently develop solar
 529 cell cracks detection algorithms [18, 33-35].

Ref.	Year of Study	Solar cell cracks detection description	Inspection level		Inspected Defects		
			Cell level	Module level	Cracks	PID	Shaded area
[33]	2018	MCCNN: Multi-channel convolutional neural networks are used by connecting several channels of CNNs to a fully connected layer and fusing them together using a random forest model.	✓	X	✓	X	X
[35]	2020	AlexNet-CNN: a method based on CNN transfer					

		learning to detect cracks with pre-trained AlexNet networks	X	✓	✓	X	X
[18]	2019	Light CNN: A CNN architecture composed of four convolutional layers and a regularization scheme based on L2 weights has been developed from scratch	✓	X	✓	X	X
[34]	2022	Gradient Guided Architecture: Lightweight CNN architectures were developed, by connecting gradient guided filter tuning to two convolutional layers and two fully connected layers.	✓	X	✓	X	X
This work	2023	In this study, A CNN architecture was developed from scratch using four different architectures and by varying the number of convolution layers and changing the pooling level to double maximum pooling, we achieved the highest validation accuracy.	✓	✓	✓	✓	✓

530 **5. Conclusions**

531 In conclusion, this study presents an innovative automated PV defect detection method,
532 driven by a robust CNN architecture with an impressive validation accuracy of 98.07%.
533 The methodology involves a comprehensive assessment of EL images at both the cell and
534 module levels, enabling thorough evaluation of PV module health. This system exhibits
535 remarkable versatility, accurately identifying various defects such as cracks, minicracks,
536 PIDs, and shaded areas.

537 The results of this research are promising. The CNN-based model consistently provided
538 precise predictions across diverse solar cell and PV module conditions. The evaluation
539 culminated in a case study involving nine PV modules connected in series, affirming the
540 system's ability to reliably distinguish between healthy and defective modules with a high
541 level of precision, as evidenced by the detailed confusion matrix analysis. However, it is
542 imperative to acknowledge certain limitations inherent to this study. Future research
543 endeavours must address these constraints to further enhance the proposed method's
544 applicability. Notably, improving model interpretability is crucial, and this can be achieved

545 through visualization techniques like Attention mechanisms and Saliency Maps, shedding
546 light on the rationale behind the model's decision-making processes.

547 Furthermore, performance optimization is paramount. Lightweight CNN architectures,
548 quantization, and pruning techniques can significantly accelerate inference speed,
549 particularly when handling larger PV modules. Robustness testing under varying
550 environmental conditions is also a future avenue to explore, ensuring the model's
551 reliability in real-world scenarios. The integration of this automated defect detection
552 system into PV manufacturing assembly lines holds tremendous potential, enabling real-
553 time defect identification and contributing to higher-quality solar cell production. Future
554 research should extend the scope of defect detection to include novel defect types and
555 refine the model's capacity to discern subtler defects.

556 Moreover, the comparative study conducted in this research underscores the system's
557 superiority over existing automated PV defect detection methods. While prior approaches
558 have been limited to cell-level inspection and the detection of specific defect types, the
559 proposed CNN-based system can inspect both cells and modules simultaneously, in real-
560 time, within agreed-upon time frames. This emphasizes its high accuracy and efficiency.
561 In sum, this research serves as a foundational step toward a transformative tool in the PV
562 industry, offering precise and efficient defect detection. By addressing these limitations
563 and exploring these future directions, researchers and industry professionals can ensure
564 the continued evolution and effectiveness of the CNN-based system, thereby advancing
565 the reliability and performance of solar energy systems while reducing costs and
566 improving productivity.

567

568 **Data Availability Statement**

569 The dataset generated and analysed in this study may be available from the corresponding
570 author S.H. on reasonable request.

571 **Acknowledgements**

572 This research was funded by the School of Physics, Engineering, and Technology at the
573 University of York under the project titled "Practical Experimentation on the Deployment of
574 Solar Roads".

575 **Author contributions**

576 Both authors discussed the organization and the content of the manuscript. --. performed the
577 experiments, prepared figures, and wrote the main manuscript text. --. validated the
578 experimental results and revised the manuscript. Both authors have approved the manuscript
579 before submission.

580 **Competing interests**

581 The author declares no competing interests.

582 References

- 583 1. Li, Z., Liu, F., Yang, W., Peng, S. & Zhou, J. A Survey of Convolutional Neural Networks:
584 Analysis, Applications, and Prospects. *IEEE Trans Neural Netw Learn Syst* **33**, 6999–
585 7019 (2022).
- 586 2. Coskun, M., Ucar, A., Yildirim, O. & Demir, Y. Face recognition based on convolutional
587 neural network. *Proceedings of the International Conference on Modern Electrical and*
588 *Energy Systems, MEES 2017* **2018-January**, 376–379 (2017).
- 589 3. Momeny, M. *et al.* Grading and fraud detection of saffron via learning-to-augment
590 incorporated Inception-v4 CNN. *Food Control* **147**, 109554 (2023).
- 591 4. Zhang, L., Huang, Z., Liu, W., Guo, Z. & Zhang, Z. Weather radar echo prediction
592 method based on convolution neural network and Long Short-Term memory
593 networks for sustainable e-agriculture. *J Clean Prod* **298**, 126776 (2021).
- 594 5. Pan, N., Yao, W. & Li, X. Friends Recommendation Based on KBERT-CNN Text
595 Classification Model. *Proceedings of the International Joint Conference on Neural*
596 *Networks* **2021-July**, (2021).
- 597 6. Salama, W. M. & Aly, M. H. Deep learning in mammography images segmentation
598 and classification: Automated CNN approach. *Alexandria Engineering Journal* **60**,
599 4701–4709 (2021).
- 600 7. Jalali, S. M. J., Ahmadian, S., Kavousi-Fard, A., Khosravi, A. & Nahavandi, S. Automated
601 Deep CNN-LSTM Architecture Design for Solar Irradiance Forecasting. *IEEE Trans Syst*
602 *Man Cybern Syst* **52**, 54–65 (2022).
- 603 8. Sun, Y., Xue, B., Zhang, M., Yen, G. G. & Lv, J. Automatically Designing CNN
604 Architectures Using the Genetic Algorithm for Image Classification. *IEEE Trans Cybern*
605 **50**, 3840–3854 (2020).
- 606 9. Kolar, D., Lisjak, D., Pajak, M. & Gudlin, M. Intelligent Fault Diagnosis of Rotary
607 Machinery by Convolutional Neural Network with Automatic Hyper-Parameters
608 Tuning Using Bayesian Optimization. *Sensors* **2021, Vol. 21, Page 2411** **21**, 2411
609 (2021).
- 610 10. Bakhshi, A., Noman, N., Chen, Z., Zamani, M. & Chalup, S. Fast Automatic
611 Optimisation of CNN Architectures for Image Classification Using Genetic Algorithm.
612 *2019 IEEE Congress on Evolutionary Computation, CEC 2019 - Proceedings* 1283–1290
613 (2019) doi:10.1109/CEC.2019.8790197.
- 614 11. Atteia, G., Abdel Samee, N., El-Kenawy, E. S. M. & Ibrahim, A. CNN-Hyperparameter
615 Optimization for Diabetic Maculopathy Diagnosis in Optical Coherence Tomography
616 and Fundus Retinography. *Mathematics* **2022, Vol. 10, Page 3274** **10**, 3274 (2022).
- 617 12. Dhimish, M. & Mather, P. Ultrafast High-Resolution Solar Cell Cracks Detection
618 Process. *IEEE Trans Industr Inform* **16**, 4769–4777 (2020).

- 619 13. Qian, X., Li, J., Cao, J., Wu, Y. & Wang, W. Micro-cracks detection of solar cells surface
620 via combining short-term and long-term deep features. *Neural Networks* **127**, 132–
621 140 (2020).
- 622 14. Parikh, H. R. *et al.* Solar Cell Cracks and Finger Failure Detection Using Statistical
623 Parameters of Electroluminescence Images and Machine Learning. *Applied Sciences*
624 *2020, Vol. 10, Page 8834* **10**, 8834 (2020).
- 625 15. Dhimish, M. & Holmes, V. Solar cells micro crack detection technique using state-of-
626 the-art electroluminescence imaging. *Journal of Science: Advanced Materials and*
627 *Devices* **4**, 499–508 (2019).
- 628 16. Rahman, M. R. *et al.* CNN-based Deep Learning Approach for Micro-crack Detection
629 of Solar Panels. *2021 3rd International Conference on Sustainable Technologies for*
630 *Industry 4.0, STI 2021* (2021) doi:10.1109/STI53101.2021.9732592.
- 631 17. Ahmad, A. *et al.* Photovoltaic cell defect classification using convolutional neural
632 network and support vector machine. *IET Renewable Power Generation* **14**, 2693–
633 2702 (2020).
- 634 18. Akram, M. W. *et al.* CNN based automatic detection of photovoltaic cell defects in
635 electroluminescence images. *Energy* **189**, 116319 (2019).
- 636 19. Hassan, S. & Dhimish, M. Review of Current State-of-the-Art Research on Photovoltaic
637 Soiling, Anti-Reflective Coating, and Solar Roads Deployment Supported by a Pilot
638 Experiment on a PV Road. *Energies* *2022, Vol. 15, Page 9620* **15**, 9620 (2022).
- 639 20. Dhimsih, M. & Mather, P. Development of Novel Solar Cell Micro Crack Detection
640 Technique. *IEEE Transactions on Semiconductor Manufacturing* **32**, 277–285 (2019).
- 641 21. Sultana, F., Sufian, A. & Dutta, P. Evolution of Image Segmentation using Deep
642 Convolutional Neural Network: A Survey. *Knowl Based Syst* **201–202**, 106062 (2020).
- 643 22. Kim, W., Kanazaki, A. & Tanaka, M. Unsupervised Learning of Image Segmentation
644 Based on Differentiable Feature Clustering. *IEEE Transactions on Image Processing* **29**,
645 8055–8068 (2020).
- 646 23. Mahani, G. K. *et al.* Bounding Box Based Weakly Supervised Deep Convolutional
647 Neural Network for Medical Image Segmentation Using an Uncertainty Guided and
648 Spatially Constrained Loss. *Proceedings - International Symposium on Biomedical*
649 *Imaging* **2022-March**, (2022).
- 650 24. Liu, X., Song, L., Liu, S. & Zhang, Y. A Review of Deep-Learning-Based Medical Image
651 Segmentation Methods. *Sustainability* *2021, Vol. 13, Page 1224* **13**, 1224 (2021).
- 652 25. Aghaei, M. *et al.* Review of degradation and failure phenomena in photovoltaic
653 modules. *Renewable and Sustainable Energy Reviews* **159**, 112160 (2022).

- 654 26. Dhimish, M. & Tyrrell, A. M. Power loss and hotspot analysis for photovoltaic modules
655 affected by potential induced degradation. *npj Materials Degradation* 2022 6:1 **6**, 1–8
656 (2022).
- 657 27. Dhimish, M. & Lazaridis, P. I. An empirical investigation on the correlation between
658 solar cell cracks and hotspots. *Scientific Reports* 2021 11:1 **11**, 1–11 (2021).
- 659 28. Garbin, C., Zhu, X. & Marques, O. Dropout vs. batch normalization: an empirical study
660 of their impact to deep learning. *Multimed Tools Appl* **79**, 12777–12815 (2020).
- 661 29. Dhimish, M., D’Alessandro, V. & Daliento, S. Investigating the Impact of Cracks on
662 Solar Cells Performance: Analysis Based on Nonuniform and Uniform Crack
663 Distributions. *IEEE Trans Industr Inform* **18**, 1684–1693 (2022).
- 664 30. Dhimish, M., Holmes, V., Mehrdadi, B. & Dales, M. The impact of cracks on
665 photovoltaic power performance. *Journal of Science: Advanced Materials and Devices*
666 **2**, 199–209 (2017).
- 667 31. Dhimish, M., Holmes, V., Dales, M. & Mehrdadi, B. Effect of micro cracks on
668 photovoltaic output power: case study based on real time long term data
669 measurements. *Micro Nano Lett* **12**, 803–807 (2017).
- 670 32. Dhimish, M. Micro cracks distribution and power degradation of polycrystalline solar
671 cells wafer: Observations constructed from the analysis of 4000 samples. *Renew*
672 *Energy* **145**, 466–477 (2020).
- 673 33. Ying, Z., Li, M., Tong, W. & Haiyong, C. Automatic Detection of Photovoltaic Module
674 Cells using Multi-Channel Convolutional Neural Network. *Proceedings 2018 Chinese*
675 *Automation Congress, CAC 2018* 3571–3576 (2019) doi:10.1109/CAC.2018.8623258.
- 676 34. Hussain, M., Chen, T., Titrenko, S., Su, P. & Mahmud, M. A Gradient Guided
677 Architecture Coupled With Filter Fused Representations for Micro-Crack Detection in
678 Photovoltaic Cell Surfaces. *IEEE Access* **10**, 58950–58964 (2022).
- 679 35. Zyout, I. & Oatawneh, A. Detection of PV Solar Panel Surface Defects using Transfer
680 Learning of the Deep Convolutional Neural Networks. 1–4 (2020)
681 doi:10.1109/ASET48392.2020.9118384.