

This is a repository copy of *Room-temperature intrinsic ferromagnetism in epitaxial CrTe₂ ultrathin films*.

White Rose Research Online URL for this paper:

<https://eprints.whiterose.ac.uk/id/eprint/173779/>

Version: Accepted Version

Article:

Zhang, Xiaoqian, Lu, Qiangsheng, Liu, Wenqing et al. (14 more authors) (2021) Room-temperature intrinsic ferromagnetism in epitaxial CrTe₂ ultrathin films. *Nature Communications*. 2492. ISSN: 2041-1723

<https://doi.org/10.1038/s41467-021-22777-x>

Reuse

Items deposited in White Rose Research Online are protected by copyright, with all rights reserved unless indicated otherwise. They may be downloaded and/or printed for private study, or other acts as permitted by national copyright laws. The publisher or other rights holders may allow further reproduction and re-use of the full text version. This is indicated by the licence information on the White Rose Research Online record for the item.

Takedown

If you consider content in White Rose Research Online to be in breach of UK law, please notify us by emailing eprints@whiterose.ac.uk including the URL of the record and the reason for the withdrawal request.

Room-temperature intrinsic ferromagnetism in epitaxial CrTe₂ ultrathin films

Xiaoqian Zhang,^{1,2#} Qiangsheng Lu,^{2#} Wenqing Liu,^{1,3#} Wei Niu,⁴ Jiabao Sun,³ Jacob Cook,² Mitchel Vaninger,² Paul. F. Miceli,² David J. Singh,^{2,5} Shang-Wei Lian,⁶ Tay-Rong Chang,^{6,7} [Xiaoqing He](#),^{8,9} Jun Du,¹⁰ Liang He,^{1*} Rong Zhang,^{1*} Guang Bian,^{2*} Yongbing Xu^{1,11*}

¹Jiangsu Provincial Key Laboratory of Advanced Photonic and Electronic Materials, School of Electronic Science and Engineering, Nanjing University, Nanjing 210093, China

²Department of Physics and Astronomy, University of Missouri, Columbia, Missouri 65211, USA

³Department of Electronic Engineering, Royal Holloway University of London, Egham, Surrey TW20 0EX, UK

⁴New Energy Technology Engineering Laboratory of Jiangsu Province & School of Science, Nanjing University of Posts and Telecommunications, Nanjing 210023, China

⁵Department of Chemistry, University of Missouri, Columbia, Missouri 65211, USA

⁶Department of Physics, National Cheng Kung University, Tainan 701, Taiwan

⁷Center for Quantum Frontiers of Research and Technology (QFort), Tainan 701, Taiwan

⁸[Electron Microscopy Core Facility, University of Missouri, Columbia, Missouri 65211, USA](#)

⁹[Department of Mechanical and Aerospace Engineering, University of Missouri, Columbia, MO 65211, USA](#)

¹⁰National Laboratory of Solid State Microstructures and Department of Physics, Nanjing University, Nanjing 210093, China

¹¹York-Nanjing Joint Centre (YNJC) for spintronics and nano engineering, Department of Electronic Engineering, The University of York, YO10 3DD, United Kingdom

[#]These authors contribute equally to this work.

*Correspondence and requests for materials should be addressed to Y.X. (ybxu@nju.edu.cn), G.B.

(biang@missouri.edu), L.H. (heliang@nju.edu.cn), R.Z. (rzhang@nju.edu.cn)

Abstract:

While the discovery of two-dimensional (2D) magnets opens the door for fundamental physics and next-generation spintronics, it is technically challenging to achieve the room-temperature ferromagnetic (FM) order in a way compatible with potential device applications. Here, we report the growth and properties of single- and few-layer CrTe₂, a van der Waals (vdW) material, on bilayer graphene by Molecular beam epitaxy (MBE). Intrinsic ferromagnetism with a Curie temperature (T_C) up to 300 K, an atomic magnetic moment of $\sim 0.21 \mu_B/\text{Cr}$ and perpendicular magnetic anisotropy (PMA) constant (K_u) of $4.89 \times 10^5 \text{ erg/cm}^3$ at room temperature in these few-monolayer films have been unambiguously evidenced by superconducting quantum interference device and X-ray magnetic circular dichroism. This intrinsic ferromagnetism has also been identified by the splitting of majority and minority band dispersions with $\sim 0.2 \text{ eV}$ at Γ point using angle-resolved photoemission spectroscopy. The FM order is preserved with the film thickness down to a monolayer ($T_C \sim 200 \text{ K}$), benefiting from the strong PMA and weak interlayer coupling. The successful MBE growth of 2D FM CrTe₂ films with room-temperature ferromagnetism opens a new avenue for developing large-scale 2D magnet-based spintronics devices.

Two-dimensional (2D) layered magnets exhibit novel phases of quantum matter with abrupt transition in the magnon density of states in atomically thin layers. In a three-dimensional (3D) system, the magnon density of states are consecutive and chiefly determined by exchange interactions. Therefore, a magnetic phase transition could occur at a finite temperature. By contrast, the long-range magnetic order in 2D systems is fragile against thermal fluctuations according to the Mermin-Wagner theorem^{1,2}. The magneto-anisotropy in 2D ferromagnets opens up a large spin-wave excitation gap, quenches thermal fluctuations³⁻⁹ and thus stabilizes the long-range magnetic order in 2D regime. In contrast to defect or dopant induced magnetism, the ferromagnetism occurring in a stoichiometric compound is defined as intrinsic ferromagnetism¹⁰.

While the presence of 2D crystals with intrinsic magnetism has been well established, the intrinsic ferromagnetic (FM) order in the discovered magnetic van der Waals (vdW) materials is generally fragile with a low Curie temperature (T_C). It mainly results from the enhanced spin fluctuation in reduced dimensions or the relatively weak exchange interactions. Note that the interlayer bonding strength in vdW compounds is 2–3 orders of magnitude weaker than that of traditional 3D materials⁴, which leads to a low T_C in the bulk form already. It motivates research efforts to enhance the robustness of 2D FM order. The first route is doping a FM host with specific elements, which normally results in a limited increase of T_C but unavoidable clusters and/or disorders from dopants^{11,12}. The second one is constructing heterostructures with FM (or ferrimagnetic) metals (or insulators), in which the FM order can be enhanced by proximity effects^{13,14}. For instance, the $(\text{Fe}_3\text{GeTe}_2/\text{MnTe})_3$ superlattices possess an enhanced coercive field as a result of the proximity effect¹². However, the penetration depth of proximity effect is usually very small (<5 nm), hindering an effective manipulation of magnetic order. The third method is doping 2D magnets with electrons via electrolyte gating, and thereby modulating the T_C of ferromagnetism. For example, the T_C of an atomically thin Fe_3GeTe_2 flake is successfully raised to even room temperature¹⁵. Nevertheless, particular device geometry and gating are required by this

means. Apart from the issues mentioned above, most of the 2D magnetic materials reported so far are thin flakes exfoliated from bulk with typical size of several micrometers, which greatly limits the practical applications of those 2D magnets in spintronics. Therefore, there is a pressing need for the realization of stoichiometric 2D materials with intrinsic robust ferromagnetism (e.g. high T_C and strong perpendicular anisotropy) and, importantly, compatibility with large-scale solid state device applications.

Molecular beam epitaxy (MBE) growth is significant as it provides the opportunity to obtain nominally stoichiometric single-crystalline films, explore the role of physical dimensionality as well as fabricate heterostructures and superlattices in a way compatible with conventional microelectronics techniques. One remarkable work is the strong FM order in ML VSe₂ epitaxial film with in-plane easy axis and a large magnetic moment ($\sim 15 \mu_B/V$) persisting to even above room temperature, as characterized by magneto-optical Kerr effect (MOKE) and vibrating sample magnetometry (VSM)¹⁶. However, according to the theoretical calculations, the magnetic moment of ML VSe₂ mostly comes from V ions with an atomic value of $\sim 0.6 \mu_B$ ¹⁷, which is completely contradictory to the experimentally observed large magnetic moment¹⁶, raising doubts about this presumed FM phase. Most recently, Wong *et al.* has provided the evidence of spin frustration with absence of a long-range magnetic order in ML VSe₂ films from complementary temperature- and field-dependent susceptibility measurements¹⁸, in stark contrast to the previous study. Moreover, the electronic structure and X-ray magnetic circular dichroism (XMCD) measurements of ML VSe₂ conducted by Feng *et al.* reveal no signatures of FM order¹⁹. These studies suggest that the existence of 2D FM order in VSe₂ remains to be further confirmed. Therefore, layer-controlled growth of stoichiometric large-scale 2D FM films with strong perpendicular magnetic anisotropy (PMA) and direct proof for the intrinsic ferromagnetism by unambiguous techniques would be mandatory. Notably, an above-room-temperature T_C has been reported in 1T-CrTe₂ in its bulk form²⁰. Very recently, above-room-temperature ferromagnetism has been observed in the exfoliated thin flakes of CrTe₂ (10 nm, or ~ 17

ML)^{21,22}. Their properties were found to be rather similar to that of the bulk with in-plane anisotropy, but with enhanced coercivity compared with its bulk counterpart. However, the magnetic response (e.g., T_C and PMA) of CrTe₂ epitaxial thin films with thickness down to ML limit has not been explored so far.

In this work, we succeed in synthesizing mono- and few-layer CrTe₂ films by MBE and observed intrinsic long-range 2D ferromagnetism. The robust ferromagnetism and strong PMA of CrTe₂ films persist up to 300 K, as evidenced by both superconducting quantum interference device (SQUID) and XMCD characterizations. In addition, the splitting of the majority and minority bands (~ 0.2 eV at Γ point) with distinct photon-energy responses has been observed by *in-situ* angle-resolved photoemission spectroscopy (ARPES) measurements, suggesting the magnetic band structure of CrTe₂ with spin-splitting. Furthermore, the CrTe₂ thin films retain a robust ferromagnetism with high T_C down to a ML, indicating a weak dimensionality effect. These results establish CrTe₂ ultrathin films as a promising 2D ferromagnet for exotic low-dimensional spintronics applications.

CrTe₂ is a layered trigonal crystal structure with a unit cell of a hexagonal Cr layer sandwiched between Te layers, as schematically illustrated in Fig. 1a. In our experiment, a bilayer graphene on SiC substrate was used to support a layer-by-layer growth of CrTe₂ films. The optical image of a single-crystal CrTe₂ film with large size (~ 4 mm $\times$ 5 mm) is shown in the inset of Fig. 1b. The microscopic topography taken from the surface of a few-layer CrTe₂ film by *in-situ* scanning tunneling microscopy (STM) shows atomically flat terrace (Fig. 1b). Figure 1c exhibits the step height between adjacent layers with a uniform value of 6.14 Å, which is consistent with the thickness of the unit cell of CrTe₂ crystal in 1T phase. One of the atomic resolution image taken by STM on the same sample is presented in Fig. 1e, showing the hexagonal lattice structure. The lattice constant obtained from the line profile in Fig. 1f is 3.81 Å, which is very close to the corresponding bulk CrTe₂ lattice parameter (3.79 Å)²⁰. STM measurements carried out on several CrTe₂ thin films with different thicknesses (mono- to few-layer) show similar terraces, indicating the layer-by-layer growth mode and

homogeneously well-structured thin films (see Supplementary Fig. 1).

There are various stable stoichiometries reported for chromium chalcogenides [e.g., $\text{CrTe}^{23,24}$, $\text{Cr}_2\text{Te}_3^{25,26}$, and $\text{Cr}_5\text{Te}_8^{27,28}$] depending on the Cr vacancies that occur in intercalation. However, none of them belongs to layered compounds with interlayer vdW gap, except for CrTe_2 . The layered surface morphology with a uniform step height characterized by STM suggests that the films are in a single phase with vdW gap. The atomic-resolution high-angle annular dark-field scanning transmission electron microscopy (HAADF-STEM) images show the $\sqrt{3}a \times a$ arrangement, revealing that CrTe_2 thin films correspond to the 1T phase with an octahedral (O_h) symmetry (see Supplementary Fig. 2). Both TEM and STM characterizations manifest the epitaxial nature and crystallographic orientation of as-grown CrTe_2 films. A typical X-ray diffraction (XRD) 2θ - ω scan was employed to further identify the crystal structure (Fig. 1d). The diffraction pattern with perpendicular constant $c = 6.13 \text{ \AA}$ is matched to the (001) crystal planes of 1T-type hexagonal structure explored experimentally ($a = 3.79 \text{ \AA}$, $c = 6.10 \text{ \AA}$)²⁰, rather than those of the 2H phase ($a = 3.49 \text{ \AA}$, $c = 13.64 \text{ \AA}$)²⁹. We note that the magnetic exchange coupling is sensitive to the lattice parameters. For example, bulk 1T- CrSe_2 with lattice constants of $a = 3.39 \text{ \AA}$ and $c = 5.92 \text{ \AA}$ shows an antiferromagnetic (AFM) order³⁰, in contrast to the FM phase in CrTe_2 . With STM, TEM and XRD characterizations, the formation of CrTe_2 films with 1T phase and their single-crystalline nature has been confirmed. The reflectivity curves show Laue fringes, attesting to the structural coherence of the film. The chemical states and band structure of the as-synthesized samples were determined by X-ray absorption spectroscopy (XAS) and ARPES as included in the following part, respectively, which further identify the metallic 1T-phase in these few-layer CrTe_2 films.

Magnetic properties of CrTe_2 thin films with both in-plane and out-of-plane configurations were examined by SQUID, as shown in Fig. 2. The temperature dependent magnetization (M - T) curves of CrTe_2 thin films with different thicknesses under an out-of-plane magnetic field of 1000 Oe were measured, as shown in Fig. 2a. It shows a general trend of decreasing with the increase of temperature, demonstrating

a FM nature. It indicates that the T_C is close to the room temperature with the specific values depending on the thickness. The magnetization of 7 ML CrTe₂ film is still observable at 300 K, indicating the FM order at room temperature. The magnetization curve exhibits a long “tail” near T_C , which is commonly observed in ferromagnets^{4,11,31}. It can be explained by a positive-feedback mean-field modification of the classical Brillouin magnetization theory³².

The magnetization-magnetic field (M - H) hysteresis loops acquired from the 7 ML CrTe₂ film at different temperatures are included in Fig. 2b and 2c. The sharp distinction between out-of-plane (Fig. 2b) and in-plane (Fig. 2c) M - H loops demonstrates a strong out-of-plane anisotropy of the magnetization with a large PMA constant ($K_u = \frac{H_k M_s}{2}$) of 5.63×10^6 erg/cm³ at 20 K. The K_u in CrTe₂ thin films is comparable to the typical PMA systems such as Co/Pd and Co/Pt (see Supplementary Table 1)³³⁻³⁶, which is vital for obtaining 2D FM order and is also considerably desirable for vdW heterostructures-based spintronics. The film also exhibits rather large coercivities (e.g., ~1000 Oe at 20 K), indicative of a hard magnetic phase. Well-defined hysteresis loops are observed at elevated temperatures up to 300 K (Fig. 2d) with the easy axis along the out-of-plane direction and hard axis along the in-plane one. The existence of PMA in the ultrathin 7 ML film is confirmed, supporting the FM order at room temperature. The in-plane magnetic hysteresis loops, similar to those reported in the FM vdW Cr₂Ge₂Te₆ thin films³⁷ and typical PMA systems such as Mn_{2.5}Ga³⁸ and Co/Pt³⁹, can be attributed to the shape anisotropy favoring in-plane easy axis for thin films^{40,41}. Control experiments on the field dependent magnetization of SiC/graphene substrate show a typical diamagnetic behavior (see Supplementary Fig. 4). Therefore, the possibility of magnetic contribution from magnetic impurities in the substrate can be ruled out. In order to clarify the thickness dependence of the magnetic properties, we have measured the field dependent magnetization curves of 3 ML and 5 ML CrTe₂ thin films under out-of-plane and in-plane configuration (Supplementary Fig. 5). The squarish FM hysteresis loops in the out-of-plane magnetic field suggest the robust FM order with the easy axis perpendicular to the thin films. At 10 K, the magnetic moments of 3 ML and

5 ML CrTe₂ are found to be 2.81 μ_B/Cr and 2.83 μ_B/Cr , respectively, which are comparable with the theoretical value ($\sim 3 \mu_B/\text{Cr}$)⁴². With in-plane and out-of-plane M - H loops, the PMA constants of 3 ML and 5 ML CrTe₂ films are determined to be $6.6 \times 10^6 \text{ erg/cm}^3$ and $6.5 \times 10^6 \text{ erg/cm}^3$ at 10 K, respectively. These results demonstrate that the MBE-grown CrTe₂ few-layer films possess robust FM properties, which is essential for the applications of FM devices. Compared with other 2D magnets from literature^{3,4,11,12,15,20,43-48}, the CrTe₂ films perform a relatively high T_C (above room temperature) and strong magnetic anisotropy with a few atomic layers. Notably, a large K_u ($4.89 \times 10^5 \text{ erg/cm}^3$) is maintained at 300 K, comparable to the bulk value of CrGeTe₃ at 1.8 K ($4.7 \times 10^5 \text{ erg/cm}^3$)⁴⁹. The strong PMA in CrTe₂ few-layer films is different from the in-plane anisotropy observed in bulk CrTe₂²⁰ and exfoliated flakes (thicker than 10 nm)²¹. Here, the thickness dependent magnetic anisotropy suggests that the reduced symmetry at the interface plays an important role in determining the PMA in CrTe₂ thin films⁵⁰. As the magnetic film thickness approaches a few nm, the interfacial magnetism and inversion symmetry breaking give rise to the PMA⁵¹. This is a consequence of magneto-crystalline anisotropy from spin-orbit interactions, that apparently have a stronger effect in the more anisotropic film limit^{33,41,50}. In addition, based on density functional theory (DFT) calculations, it has been found that the FM Cr-Cr intrasublattice exchange interactions dominate in CrTe₂ thin films, and the total energy minima is at perpendicular direction⁵². In general, the magnetic moments of CrTe₂ thin films are aligned in the perpendicular direction, due to the magneto-crystalline anisotropy and the anisotropy of exchange interactions.

To examine the local electronic character and magnetic ground states of CrTe₂ films, XAS and XMCD measurements at the Cr $L_{2,3}$ absorption edges were performed, as schematically shown in Fig. 3a. This element-specific magnetic characterization technique can also exclude any possible magnetic impurities. The XAS spectra of Cr present multiplet structures around photon energies of 575 eV and 584 eV (Fig. 3b), which stem from the excitations from Cr $2p_{3/2}$ and Cr $2p_{1/2}$ core levels, respectively. A small peak ($\sim 2 \text{ eV}$ away from L_3 peak of Cr) marked with the black arrow comes from

Te $5d_{5/2}$ core level, which slightly overlaps with the peak of Cr $2p_{3/2}$ with almost no magnetic contribution⁵³. A small peak at the higher energy side (marked with orange arrow) of the main feature in Fig. 3b is related to the distribution of atomic multiplet. Due to the O_h coordination, the $3d$ orbitals of Cr split into e_g and t_{2g} states with energy separation of nominal $10 Dq$. The t_{2g} states are lower in energy than the e_g states. In this case, the Cr^{3+} (d^3) configuration with half-filled t_{2g} states causes the reduction of free energy⁵⁴, which is in good agreement with the reported theoretical value of magnetic moment, $3 \mu_B/Cr$ atom⁴². The observed XAS spectral line shape is in line with that of spinel $Cu(Cr,Ti)_2Se_4$ polycrystals with trivalent Cr cations on O_h sites⁵⁵, further providing a spectroscopic fingerprint of 1T-type $CrTe_2$ with predominately Cr^{3+} cations. In this case, approximately three electrons are removed from the Cr atoms, and distributed over the Te.

The Cr $L_{2,3}$ XMCD spectra in the bottom panel of Fig. 3b highlight the emergence of intrinsic ferromagnetism from Cr atoms. XMCD and XAS measurements were repeated at elevated temperatures, and the dichroism of 7 ML thin film at Cr L_3 edge is evident up to 300 K. The characteristic peaks in the spectra remain at the same energy as the temperature rises, despite the attenuation of intensity. For greater clarity, partial enlarged left- and right-circularly polarized XAS of Cr L_3 edge at 200 K, 250 K and 300 K are exhibited in Fig. 3c. There is an obvious difference between the XAS under distinct X-ray helicity even at 300 K, directly confirm the intrinsic FM order coming from the Cr^{3+} cations in the $CrTe_2$ films. The XMCD spectra have been analyzed in terms of element-specific magnetic moments according to the sum rules^{56,57}. The spin moment (m_s) and orbital moment (m_l) can be obtained by sum rule:

$$m_s = -n_h \frac{6 \int_{L_3} (\sigma^- - \sigma^+) dE - 4 \int_{L_{2,3}} (\sigma^- - \sigma^+) dE}{\int_{L_{2,3}} (\sigma^- + \sigma^+) dE} \times SC - \langle T_z \rangle$$

$$m_l = -\frac{4}{3} n_h \frac{\int_{L_{2,3}} (\sigma^- - \sigma^+) dE}{\int_{L_{2,3}} (\sigma^- + \sigma^+) dE}$$

where n_h , SC and $\langle T_z \rangle$ are the number of d holes, spin correction factor (estimated to

be 2.0 ± 0.2 for Cr)^{13,58} and the averaged magnetic dipole term, respectively. Based on the trivalent Cr, we assume $n_h = 7$. The magnetic dipole term, $\langle T_z \rangle$ can be neglected due to its rather small contribution (<5%) in the Cr t_{2g}^3 configuration. An arctangent step-like function was employed in the fitting of the threshold of XAS spectra in order to exclude the nonmagnetic contribution^{59,60}.

The calculated m_s and m_l from 5 to 300 K are summarized in Fig. 3d. The derived m_s demonstrates a Curie-like behavior. A remarkably large value of m_s ($2.85 \pm 0.10 \mu_B/\text{Cr}$) is found at 5 K. The m_s retains a sizable value of $0.82 \pm 0.10 \mu_B/\text{Cr}$ at 250 K and drops to $0.21 \pm 0.05 \mu_B/\text{atom}$ at 300 K, confirming a FM phase transition near this temperature. On the other hand, m_l is relatively small of around $0.08 \pm 0.05 \mu_B/\text{atom}$, consistent with a half-filled t_{2g} level in O_h crystal field of 1T-CrTe₂. The orbital moment plays an important role in the magneto-crystalline anisotropy and the perpendicular orientation of the moments that underlies the FM order in this 2D system. Notably, the atomic magnetic moment of CrTe₂ is determined to be $\sim 3 \mu_B/\text{atom}$, which is the largest possible moment of Cr according to the Hund's rule. The observed FM behavior cannot be attributed to the Cr clusters, since Cr is AFM and therefore would give a zero XMCD intensity.

The magnetic response of 1 ML CrTe₂ film is worth exploring. It is difficult to detect magnetization in such ultrathin films by SQUID, since the magnetic signal of 1 ML CrTe₂ is too weak compared with an overwhelmingly larger background signal from the substrate and beyond the resolution of SQUID. Therefore, we did element-specific XMCD characterization of 1 ML CrTe₂ film (Fig. 4a). There is a noticeable difference in the XAS spectra between left- and right-handed circularly polarized setups (Fig. 4b). Although the dichroism is small compared with 7 ML sample, the clear XMCD signals appear near the absorption peaks. It suggests that the intrinsic ferromagnetism of 1 ML CrTe₂ film originates from the spin polarization of Cr 3d electrons. Accurate calculation of the magnetic moment remains a challenge since the contribution of Te capping layer to the XAS spectra is so large for 1 ML sample. The XMCD percentage increases with the reduced temperature (Fig. 4c), in line with a

typical FM behavior. The nonzero XMCD percentage persists when temperature approaches 200 K and disappears above 250 K, indicating that 1 ML CrTe₂ has a T_C of ~200 K. The T_C can be obtained by using a critical power-law function $\alpha(1-T/T_C)^\beta$ to fit M - T curves without the inclusion of the paramagnetic tail⁶¹. In order to investigate the dimensionality effect of the ferromagnetism in CrTe₂ stemming from thermal fluctuation, we plot the thickness dependent T_C obtained from XMCD and SQUID measurements in Fig. 4d. The T_C of CrTe₂ decreases mildly as the film thickness is reduced, in contrast to the other known 2D magnets such as Cr₂Ge₂Te₆⁴ and Fe₃GeTe₂¹⁵ (Supplementary Fig. 10). The high T_C in the 2D limit demonstrates the robustness of ferromagnetism in the epitaxial CrTe₂ thin films.

The electronic band structure of CrTe₂ thin films has been mapped by ARPES with two different photon energies of 21.2 eV and 40.8 eV at 107 K. The band dispersions of 7 ML CrTe₂ measured at $h\nu = 21.2$ eV along high symmetry crystallographic direction M- Γ -K in the surface Brillouin zone are shown in Fig. 5a. Near the Γ point, the main features include two hole-like valence bands aligned close to the Fermi level, which shares identity with the typical features of 1T-ZrTe₂⁶². Near the M point, there are two electron pockets with bottom locating at -1.2 eV and -1.8 eV, respectively. The Fermi surface map shows two circular pockets centered at Γ point surrounded by six triangular pockets at K points. Below the Fermi level, the pockets around K points begin to merge with the expanded pockets at Γ point (Supplementary Fig. 11). The well-defined band structure indicates the high structural quality of the MBE-fabricated films.

The origin of the band dispersions has been investigated by first-principle DFT calculations based on CrTe₂ slab¹⁸. The mean free path of photoelectrons excited by photons of 21.2 eV and 40.8 eV is between 0.5 and 1 nm. Therefore, to compare with the experimental spectra, we simulated the band structure with a surface weight of each Bloch wavefunction. The higher intensity in the image means greater weight of wavefunction near the slab surface. Figure 4b shows the calculated spin-polarized band structure, with the majority and minority spin bands plotted in blue and red, respectively. Both magnetization and spin orbit coupling (SOC) are taken into account in the

calculation, and the magnetic moments are set along out-of-plane direction. To better illustrate the spin contribution to electronic structure, the calculated minority band (left) and majority band (right) are separately plotted in Supplementary Fig. 12. According to the orbital and surface projection analysis of the band structure, the metallicity is a consequence of the hybridization of Te-5*p* and Cr-3*d* orbitals crossing the Fermi level at the center of the Brillouin zone (see Supplementary Fig. 13), which is confirmed by the calculated density of states (see Supplementary Fig. 14). The hybridization of Te and Cr states is also verified in previous DFT calculations²⁰. There is an overall agreement between the experimental (Fig. 5a) and calculated band dispersions (Fig. 5b), except for the absence of two hole pockets from minority band near Γ point.

To compare experiment and theory in greater detail, the dispersion of hole pockets detected by different photon energies is plotted in Fig. 5c and Fig. 5d. Note that the two hole pockets near the Fermi level in Fig. 5c are mainly from the majority bands. Interestingly, the minority hole pocket shows up in the spectrum taken at $h\nu = 40.8$ eV (Fig. 5d) while the majority ones disappear. It suggests the emission from the minority spin pockets was suppressed in the measurement at $h\nu = 21.2$ eV as a consequence of matrix element effect⁶³. The band dispersion can be traced by fitting the peak position in the momentum distribution curves (MDC), as marked by blue and red dashed lines in Fig. 5c and 5d, respectively. Combining the band structure near Fermi energy (E_F) taken by He I α and He II α photons together, as shown in Fig. 5e, the electronic structure is clearly metallic in both the majority and minority spin channels, and agrees well with DFT calculations. Relatively small renormalizations are needed to match with ARPES results, indicating moderate-to-weak correlations. The experimental band structure of CrTe₂ is in sharp contrast with the band structure calculated without the inclusion of spin polarization (Supplementary Fig. 15), where hole pockets near E_F are degenerate at Γ point as in the cases of VTe₂⁶⁴ and VSe₂^{18,19}. There are no exchange splitting of band dispersion in MBE grown VSe₂ films, indicating the absence of ferromagnetism^{18,19}. By contrast, the splitting of majority and minority bands (~ 0.2 eV at Γ point) in CrTe₂ films corroborates the FM ground state, which highlights the unique

interplay of ferromagnetism and electronic structure in CrTe₂. In addition, the calculated magnetic moment of Cr is 2.89 μ_B /atom, in good agreement with the SQUID and XMCD measurements. For a comparison with the ARPES spectra, we also calculated the electronic band structure of 2H-CrTe₂. The low-energy bands of 2H-CrTe₂ are different from those observed in the ARPES spectra and the calculated 1T-CrTe₂ band structure (see Supplementary Fig. 17). Another significant difference between 1T and 2H phase is that the 1T-CrTe₂ exhibits a FM ground state along *c*-axis, while the 2H-CrTe₂ is PM as a result of the fully occupied d_{z^2} orbital of tetravalent Cr. The observed FM band structure and FM properties corroborate the 1T phase of the epitaxial CrTe₂ films.

We have further studied the thickness dependence of hole pocket features. The evolution of the band structure for the films with a thickness ranging from 1 ML to 15 ML is shown in Fig. 5f. For the 1 ML film, there are two parabolic bands with a maximum above and below the Fermi level, respectively. When film thickness increases to 2 ML, one of the parabolic band overlaps with another one near the Fermi level, sharing similar feature with the case of few-layer ZrTe₂⁶² and HfTe₂⁶⁵. With further increasing the film thickness, the Fermi level moves towards the valence band with the band shape invariant. To understand the thickness-dependent electronic structure, we carried out first-principles calculations of 1T-CrTe₂ with different thicknesses (see Supplementary Fig. 18). There is an excellent agreement between our experiment and theory. In particular, the hole-like band near E_F and a relatively flat Cr 3*d* orbital band are similar to that of calculated 1T-CrTe₂ with the inclusion of spin polarization. For the 1 ML film, the two parabolic hole pockets are well reproduced by the majority spin projections of the bands, which highlights the FM nature. These results demonstrate that the epitaxial 1T structure and ferromagnetism have been established since 1 ML deposition, in line with the corresponding STM images. The layer-by-layer growth mode of the CrTe₂ ultrathin films enables us to further explore the fabrication of thin-film electronic devices, exploiting the interplay between electronic structure and extraordinary magnetic properties in the future.

To summarize, we have successfully synthesized high-quality mono- to few-layer CrTe₂ via MBE method, for the first time. The epitaxial CrTe₂ ultrathin films with thickness up to 7 ML possess room-temperature intrinsic ferromagnetism, large magnetic moments ($\sim 3 \mu_B/\text{atom}$), strong perpendicular anisotropy and magnetic spin-split band structure. The high T_C is preserved with the thickness down to one ML due to the strong magnetic anisotropy and the weak interlayer coupling. The FM CrTe₂ films can be employed as a spin injector when hybridized with other 2D materials such as topological insulator and topological semimetals for exploring novel spin physics. At the same time, this work provides a tremendous potential for the future 2D magnet-based spintronics technologies, as the films can readily reach wafer size with MBE growth technique.

Methods

Growth of CrTe₂/bilayer graphene/SiC(0001) heterostructures. CrTe₂ thin films were grown on a bilayer graphene/SiC substrate in an integrated MBE-STM ultrahigh vacuum (UHV) system with base pressure below 2×10^{-10} mbar. The bilayer graphene was prepared by annealing a 6H SiC(0001) substrate at 1150 °C for 20 seconds and repeating 30 times. Then, high-purity Cr and Te were evaporated from an electron-beam evaporator and a standard Knudsen cell, with flux of 0.1 Å/min and 6 Å/min, respectively. The temperature of substrate was kept at 375 °C during the growth. The deposition rate of CrTe₂ was ~ 0.73 Å/min as monitored by a quartz oscillator. In order to protect the thin film from contamination and oxidation during XRD, SQUID, XAS and XMCD measurements, a Te capping layer (~ 5 nm) was deposited on sample surface after growth.

Characterizations. High-resolution XRD was performed using MoK $_{\alpha 1}$ radiation (0.70926 Å) which was obtained from a flat perfect crystal Ge monochromator that produced a line beam having angular divergence of in the scattering plane and out of the scattering plane. The measurements were performed by specular reflection and the

data were modeled using the reflection amplitudes from the substrate, graphene layers, layers of CrTe₂ and its structure factor. The TEM samples were prepared by a lift-out method in a ThermoFisher Scientific Scios focused ion beam (FIB) instrument at room temperature, and imaged in the ThermoFisher Scientific G2 Tecnai F30 FEG high resolution TEM operated at 300 kV. The SiC substrate was tilted to the [100] zone axis and the lattice fringes from both the graphene and the SiC can be clearly resolved. Great care has been taken to reduce the beam damage on the thin film samples both during the FIB lift out and during the sample tilting and high-resolution image acquisition process. The magnetization measurements were performed by using a Quantum Design SQUID magnetometer with magnetic field up to 7 T.

X-ray Absorption Spectroscopy and Magnetic Circular Dichroism. The measurements were performed on beamline I10 at Diamond Light Source, U.K., with 100% circularly polarized X-ray perpendicular to the sample plane and parallel to the magnetic field. XAS measurements with total electron yield (TEY) mode were carried out from 5 K to 300 K. By flipping the X-ray helicity at fixed magnetic field of 1 T, we obtained XMCD by taking the difference of XAS, $\sigma^- - \sigma^+$.

Angle-resolved Photoemission Spectroscopy and Scanning Tunneling Microscopy. After the growth, the CrTe₂ films were in-situ transferred under ultra-high vacuum to the ARPES stage. ARPES measurements were performed at 107 K using a SPECS PHOIBOS 150 hemisphere analyzer with a SPECS UVS 300 helium discharge lamp (He I α = 21.2 eV and He II α = 40.8 eV). The energy resolution is 40 meV under 107 K. The size of the beam spot on the sample was ~ 1.5 mm. We didn't find any change in the observed ARPES spectra when changing the beam position on the sample surface (~ 5 mm $\times$ 4 mm), indicative of the homogeneity of grown samples. The topography of the sample surface was mapped *in-situ* by an Aarhus STM housed in the growth chamber.

First-principles calculations. First-principles calculations with DFT were performed by using the Vienna ab Initio Simulation Package (VASP) package. We used the Perdew-Burke-Ernzerhof (PBE) form of the exchange correlation functional. All the calculations were performed with a plane-wave cut-off energy of 300 eV on the $11 \times 11 \times 1$ Monkhorst–Pack k-point mesh. The super cell includes CrTe₂ layers with varying thicknesses and a vacuum layer of about 20 Å, in order to avoid interactions between the neighboring slabs. CrTe₂ with an in-plane lattice constant of 3.81 Å was used. The atomic positions and the out-of-plane lattice constant were optimized by the conjugate gradient method. Calculations of the band structures were performed with the inclusion SOC.

Acknowledgments

G.B. is supported by the US National Science Foundation (NSF-DMR#1809160). This work is also supported by the National Key Research and Development Program of China (No. 2016YFA0300803, No. 2017YFA0206304), the National Basic Research Program of China (No. 2014CB921101), the National Natural Science Foundation of China (No. 61427812, 11774160, 11574137, 61474061, 61674079, 11904174), Jiangsu Shuangchuang Program, the Natural Science Foundation of Jiangsu Province of China (No. BK20140054, BK20190729), NUPTSF (Grant No. NY219024), the Natural Science Foundation of the Jiangsu Higher Education Institutions of China (19KJB510047), UK EPSRC (EP/S010246/1), leverhulme Trust (LTSRF1819\15\12), and Royal Society (IEC\NSFC\181680). Diamond Light Source is acknowledged to I10 under proposal MM22532. T.-R.C. is supported by the Young Scholar Fellowship Program from the Ministry of Science and Technology (MOST) in Taiwan, under a MOST grant for the Columbus Program MOST108-2636- M-006-002, National Cheng Kung University, Taiwan, and National Center for Theoretical Sciences, Taiwan. This work is also partially supported by the MOST, Taiwan, Grant MOST107-2627-E-006-001 and by Higher Education Sprout Project, Ministry of Education to the Headquarters of University Advancement at National Cheng Kung University (NCKU).

Author contributions

Y.X., G.B., R.Z. and L.H. planned the project. X.Z. and Q.L. synthesized CrTe₂ thin films. Q.L., X.Z. and J.C. conducted the ARPES and STM experiments and analyzed the data. W.L., J.S., W.N. and J.D. performed XMCD and SQUID measurements and analyzed the data. Q.L., S.-W.L., T.-R.C. and D.J.S did the DFT calculations. P.M. and M.V. conducted XRD measurements. [X.H. performed the TEM characterizations.](#) X.Z., Q.L., D.J.S and G.B. wrote the paper. All the authors discussed the results and commented on the manuscript.

Conflict of Interest

The authors declare no conflict of interest.

References

- 1 Mermin, N. D. & Wagner, H. Absence of Ferromagnetism or Antiferromagnetism in One- or Two-Dimensional Isotropic Heisenberg Models. *Phys. Rev. Lett.* **17**, 1133-1136 (1966).
- 2 Gibertini, M., Koperski, M., Morpurgo, A. F. & Novoselov, K. S. Magnetic 2D materials and heterostructures. *Nat. Nanotechnol.* **14**, 408-419 (2019).
- 3 Huang, B. *et al.* Layer-dependent ferromagnetism in a van der Waals crystal down to the monolayer limit. *Nature* **546**, 270-273 (2017).
- 4 Gong, C. *et al.* Discovery of intrinsic ferromagnetism in two-dimensional van der Waals crystals. *Nature* **546**, 265-269 (2017).
- 5 Song, T. *et al.* Giant tunneling magnetoresistance in spin-filter van der Waals heterostructures. *Science* **360**, 1214–1218 (2018).
- 6 Zhong, D. *et al.* Van der Waals engineering of ferromagnetic semiconductor heterostructures for spin and valleytronics. *Sci. Adv.* **3**, e1603113 (2017).
- 7 Seyler, K. L. *et al.* Ligand-field helical luminescence in a 2D ferromagnetic insulator. *Nat. Phys.* **14**, 277-281 (2017).
- 8 Wang, Z. *et al.* Electric-field control of magnetism in a few-layered van der Waals ferromagnetic semiconductor. *Nat. Nanotechnol.* **13**, 554-559 (2018).
- 9 Jiang, S., Shan, J. & Mak, K. F. Electric-field switching of two-dimensional van der Waals magnets. *Nat. Mater.* **17**, 406-410 (2018).
- 10 Shabbir, B. *et al.* Long range intrinsic ferromagnetism in two dimensional materials and dissipationless future technologies. *Appl. Phys. Rev.* **5**, 041105 (2018).
- 11 May, A. F., Calder, S., Cantoni, C., Cao, H. & McGuire, M. A. Magnetic structure and phase stability of the van der Waals bonded ferromagnet $\text{Fe}_{3-x}\text{GeTe}_2$. *Phys. Rev. B* **93**, 014411 (2016).
- 12 Liu, S. *et al.* Wafer-scale two-dimensional ferromagnetic Fe_3GeTe_2 thin films grown by molecular beam epitaxy. *Npj 2D Mater. Appl.* **1**, 30 (2017).
- 13 Liu, W. *et al.* Enhancing magnetic ordering in Cr-doped Bi_2Se_3 using high- T_C ferrimagnetic insulator. *Nano Lett.* **15**, 764-769 (2015).
- 14 He, Q. L. *et al.* Tailoring exchange couplings in magnetic topological-insulator/antiferromagnet heterostructures. *Nat. Mater.* **16**, 94-100 (2017).
- 15 Deng, Y. *et al.* Gate-tunable room-temperature ferromagnetism in two-dimensional Fe_3GeTe_2 . *Nature* **563**, 94-99 (2018).
- 16 Bonilla, M. *et al.* Strong room-temperature ferromagnetism in VSe_2 monolayers on van der Waals substrates. *Nat. Nanotechnol.* **13**, 289-293 (2018).
- 17 Ma, Y. D. *et al.* Evidence of the Existence of Magnetism in Pristine VX_2 Monolayers ($X = \text{S}, \text{Se}$) and Their Strain-Induced Tunable Magnetic Properties. *ACS nano* **6**, 1695 (2012).
- 18 Wong, P. K. J. *et al.* Evidence of Spin Frustration in a Vanadium Diselenide Monolayer Magnet. *Adv. Mater.* **31**, 1901185 (2019).
- 19 Feng, J. *et al.* Electronic Structure and Enhanced Charge-Density Wave Order of Monolayer VSe_2 . *Nano Lett.* **18**, 4493-4499 (2018).
- 20 Freitas, C. D. *et al.* Ferromagnetism in layered metastable $1T\text{-CrTe}_2$. *J. Phys.: Condens. Matter* **27**, 176002 (2015).
- 21 Sun, X. *et al.* Room temperature ferromagnetism in ultra-thin van der Waals crystals of $1T\text{-CrTe}_2$. *Nano Res.* **13**, 3358-3363 (2020).

- 22 Purbawati, A. *et al.* In-plane magnetic domains and Neel-like domain walls in thin flakes of the room temperature CrTe₂ van der Waals ferromagnet. *ACS Appl. Mater. Inter.* **12**, 30702-30710 (2020).
- 23 Kanazawa, K. *et al.* Structural and magnetic properties of hexagonal Cr_{1-δ}Te films grown on CdTe(001) by molecular beam epitaxy. *J. Cryst. Growth* **415**, 31-35 (2015).
- 24 Zhao, D. *et al.* Observation of unconventional anomalous Hall effect in epitaxial CrTe thin films. *Nano Res.* **11**, 3116-3121 (2017).
- 25 Chen, J. *et al.* Evidence for Magnetic Skyrmions at the Interface of Ferromagnet/Topological-Insulator Heterostructures. *Nano Lett.* **19**, 6144-6151 (2019).
- 26 Roy, A. & Guchhait, S. Perpendicular Magnetic Anisotropy and Spin Glass-like Behavior in Molecular Beam Epitaxy Grown Chromium Telluride Thin Films. *ACS nano* **9**, 3772-3779 (2015).
- 27 Wang, Y. *et al.* Magnetic anisotropy and topological Hall effect in the trigonal chromium tellurides Cr₅Te₈. *Phys. Rev. B* **100**, 024434 (2019).
- 28 Liu, Y. & Petrovic, C. Anomalous Hall effect in the trigonal Cr₅Te₈ single crystal. *Phys. Rev. B* **98**, 195122 (2018).
- 29 Bastos, C. M. O., Besse, R., Da Silva, J. L. F. & Sipahi, G. M. Ab initio investigation of structural stability and exfoliation energies in transition metal dichalcogenides based on Ti-, V-, and Mo-group elements. *Phys. Rev. Mater.* **3**, 044002 (2019).
- 30 Freitas, D. C. Antiferromagnetism and ferromagnetism in layered 1T-CrSe₂ with V and Ti replacements. *Phys. Rev. B* **87**, 014420 (2013).
- 31 Li, Y. F. *et al.* Electronic structure of ferromagnetic semiconductor CrGeTe₃ by angle-resolved photoemission spectroscopy. *Phys. Rev. B* **98**, 125127 (2018).
- 32 Harrison, R. G. Calculating the spontaneous magnetization and defining the Curie temperature using a positive-feedback model. *J. Appl. Phys.* **115**, 033901 (2014).
- 33 Ikeda, S. *et al.* A perpendicular-anisotropy CoFeB-MgO magnetic tunnel junction. *Nat. Mater.* **9**, 721-724 (2010).
- 34 Wu, Y., Xu, X. G., Miao, J. & Jiang, Y. Perpendicular Magnetic Anisotropy in Co-Based Full Heusler Alloy Thin Films. *Spin* **5**, 1540012 (2016).
- 35 Richter, N. *et al.* Temperature-dependent magnetic anisotropy in the layered magnetic semiconductors CrI₃ and CrBr₃. *Phys. Rev. Mater.* **2**, 024004 (2018).
- 36 Yakushiji, K. *et al.* Ultrathin Co/Pt and Co/Pd superlattice films for MgO-based perpendicular magnetic tunnel junctions. *Appl. Phys. Lett.* **97**, 232508 (2010).
- 37 Mogi, M. *et al.* Ferromagnetic insulator Cr₂Ge₂Te₆ thin films with perpendicular remanence. *APL Mater.* **6**, 091104 (2018).
- 38 Wu, F. *et al.* Epitaxial Mn_{2.5}Ga thin films with giant perpendicular magnetic anisotropy for spintronic devices. *Appl. Phys. Lett.* **94** (2009).
- 39 Emori, S. & Beach, G. S. D. Optimization of out-of-plane magnetized Co/Pt multilayers with resistive buffer layers. *J. Appl. Phys.* **110** (2011).
- 40 Lado, J. L. & Fernández-Rossier, J. On the origin of magnetic anisotropy in two dimensional CrI₃. *2D Mater.* **4**, 035002 (2017).
- 41 Lau, Y.-C. *et al.* Giant perpendicular magnetic anisotropy in Ir/Co/Pt multilayers. *Phys. Rev. Mater.* **3**, 104419 (2019).
- 42 Otero Fumega, A., Phillips, J. & Pardo, V. Controlled Two-Dimensional Ferromagnetism in 1T-

- CrTe₂: The Role of Charge Density Wave and Strain. *J. Phys. Chem. C* **124**, 21047-21053 (2020).
- 43 Xing, W. *et al.* Electric field effect in multilayer Cr₂Ge₂Te₆: a ferromagnetic 2D material. *2D Mater.* **4**, 024009 (2017).
- 44 Zhang, X. *et al.* Magnetic anisotropy of the single-crystalline ferromagnetic insulator Cr₂Ge₂Te₆. *Jpn. J. Appl. Phys.* **55**, 033001 (2016).
- 45 Liu, B. J. *et al.* Critical behavior of the quasi-two-dimensional semiconducting ferromagnet CrSiTe₃. *Sci. Rep.* **6**, 33873 (2016).
- 46 May, A. F. *et al.* Ferromagnetism Near Room Temperature in the Cleavable van der Waals Crystal Fe₅GeTe₂. *ACS nano* **13**, 4436-4442 (2019).
- 47 McGuire, M. A. *et al.* Magnetic behavior and spin-lattice coupling in cleavable van der Waals layered CrCl₃ crystals. *Phys. Rev. Mater.* **1**, 014001 (2017).
- 48 Tan, C. *et al.* Hard magnetic properties in nanoflake van der Waals Fe₃GeTe₂. *Nat. Commun.* **9**, 1554 (2018).
- 49 Zeisner, J. *et al.* Magnetic anisotropy and spin-polarized two-dimensional electron gas in the van der Waals ferromagnet Cr₂Ge₂Te₆. *Phys. Rev. B* **99**, 165109 (2019).
- 50 Dieny, B. & Chshiev, M. Perpendicular magnetic anisotropy at transition metal/oxide interfaces and applications. *Rev. Mod. Phys.* **89**, 025008 (2017).
- 51 Lee, A. J. *et al.* Interfacial Rashba-Effect-Induced Anisotropy in Nonmagnetic-Material-Ferrimagnetic-Insulator Bilayers. *Phys. Rev. Lett.* **124**, 257202 (2020).
- 52 Fujisawa, Y. *et al.* Tailoring magnetism in self-intercalated Cr_{1+δ}Te₂ epitaxial films. *Phys. Rev. Mater.* **4**, 114001 (2020).
- 53 Ye, M. *et al.* Carrier-mediated ferromagnetism in the magnetic topological insulator Cr-doped (Sb,Bi)₂Te₃. *Nat. Commun.* **6**, 8913 (2015).
- 54 Hu, T., Li, R. & Dong, J. Characterization of few-layer 1T-MoSe₂ and its superior performance in the visible-light induced hydrogen evolution reaction. *J. Chem. Phys.* **139**, 174702 (2013).
- 55 Noh, H. J. *et al.* Valence values of the cations in selenospinel Cu(Cr,Ti)₂Se₄. *EPL* **78**, 27004 (2007).
- 56 Chen, C. T. *et al.* Experimental confirmation of the X-ray magnetic circular dichroism sum rules for iron and cobalt. *Phys. Rev. Lett.* **75**, 152-155 (1995).
- 57 van der Laan, G. & Thole, B. T. Strong magnetic x-ray dichroism in 2*p* absorption spectra of 3d transition-metal ions. *Phys. Rev. B* **43**, 13401-13411 (1991).
- 58 Liu, W. *et al.* Atomic-Scale Magnetism of Cr-Doped Bi₂Se₃ Thin Film Topological Insulators. *ACS nano* **9**, 10237-10243 (2015).
- 59 Liu, W. Q. *et al.* Atomic-Scale Interfacial Magnetism in Fe/Graphene Heterojunction. *Sci. Rep.* **5**, 11911 (2015).
- 60 Liu, W. *et al.* Experimental Observation of Dual Magnetic States in Topological Insulators. *Sci. Adv.* **5**, eaav2088 (2019).
- 61 Fei, Z. *et al.* Two-dimensional itinerant ferromagnetism in atomically thin Fe₃GeTe₂. *Nat. Mater.* **17**, 778-782 (2018).
- 62 Tsipas, P. *et al.* Massless Dirac Fermions in ZrTe₂ Semimetal Grown on InAs(111) by van der Waals Epitaxy. *ACS nano* **12**, 1696-1703 (2018).
- 63 Belopolski, I. *et al.* Discovery of topological Weyl fermion lines and drumhead surface states in a room temperature magnet. *Science* **365**, 1278-1281 (2019).
- 64 Wang, Y., Ren, J. & Li, J. Evidence of charge density wave with anisotropic gap in monolayer

- VTe₂ film. *arXiv* **1905**, 13446 (2019).
- 65 Amini-Araghi-Giamini, S. *et al.* Molecular beam epitaxy of thin HfTe₂ semimetal films. *2D Mater.* **4**, 015001 (2016).

Figures

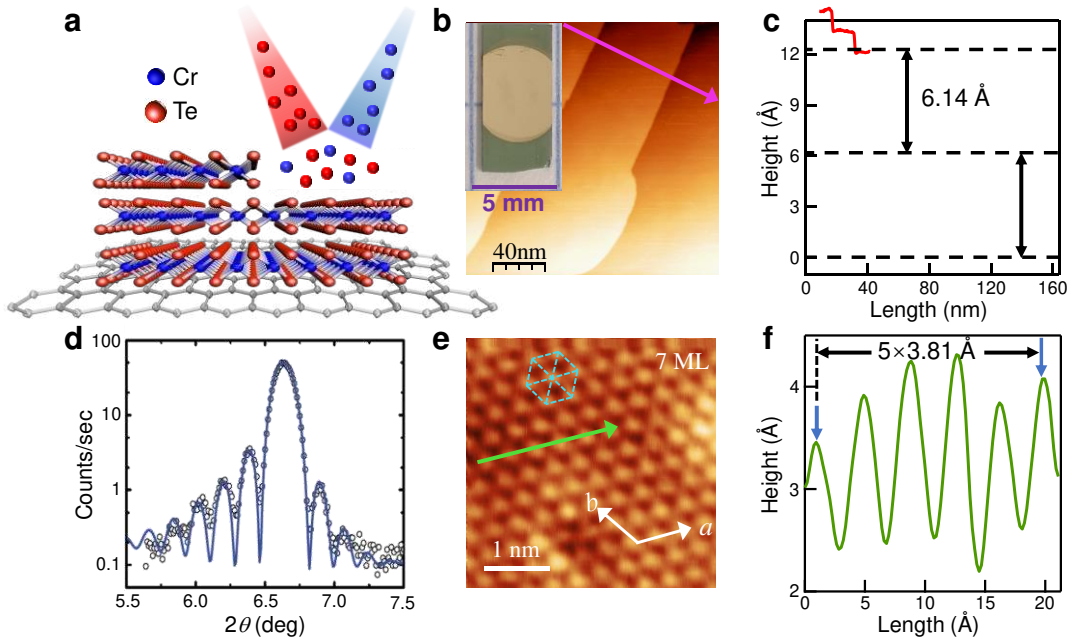


Fig. 1 Crystal structure and STM characterizations of epitaxially grown CrTe₂ thin films. **a** Schematic illustration of MBE growth process of CrTe₂ films on graphene. **b** The STM topology image (200 × 200 nm²) of a 7 ML CrTe₂ fabricated on graphene/SiC. $U = +1$ V, $I_t = 200$ pA. Inset on the left is an optical image. **c** The line-scan profile taken along the pink line in **b**, with an average step height of ~6.14 Å. **d** XRD spectrum showing Laue fringes around the (001) CrTe₂ reflections. The solid fitting curve indicates the thickness of 39 layers, the roughness of 2 layers and the lattice constant $c = 6.13$ Å. **e** Atomically resolved STM image (4 × 4 nm²) with a hexagonal structure. $U = -1.5$ mV, $I_t = -440$ pA. **f** The line-scan along the green arrow in **e**, showing a lattice periodicity of ~3.81 Å.

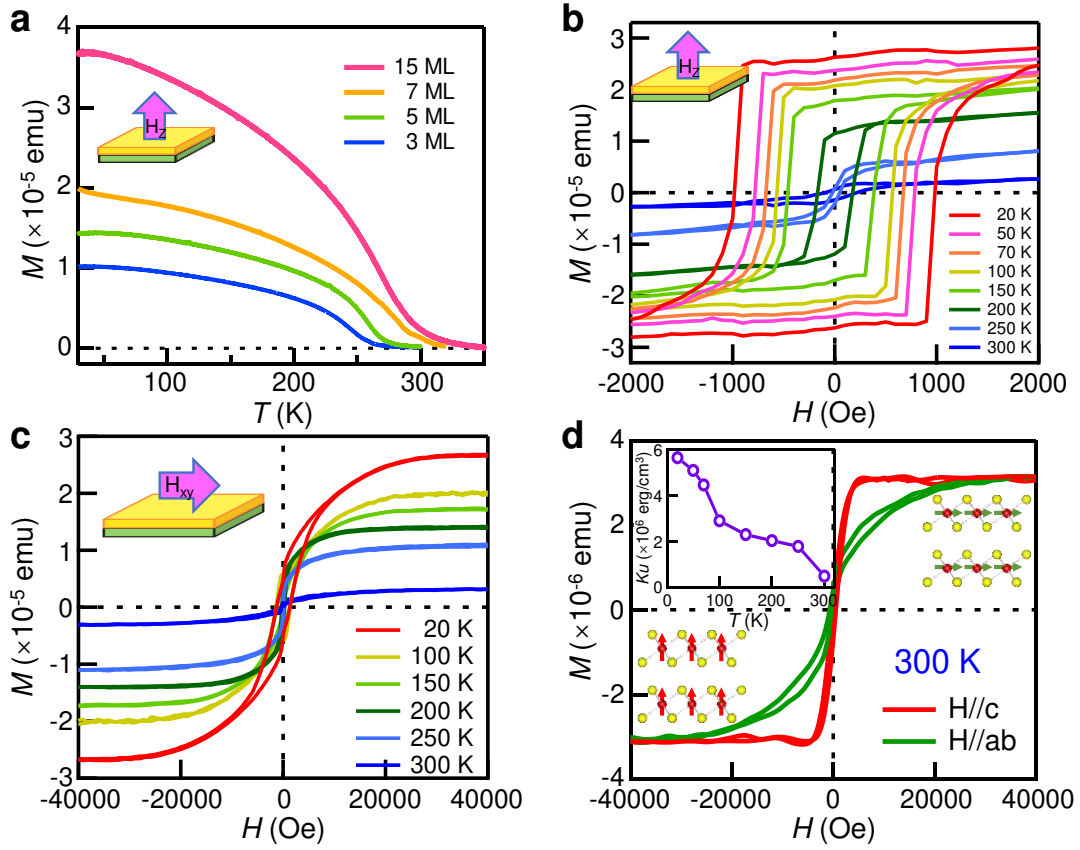


Fig. 2 SQUID measurements of the CrTe₂ films. **a** Temperature dependent magnetization curves of the films with various thicknesses under field-cooled mode. The magnetic field is applied along the out-of-plane direction with a magnitude of 1000 Oe. The high T_C is preserved with thickness decreasing to 3 ML. **b**, **c** Magnetic hysteresis loops of 7 ML CrTe₂ at different temperatures with external fields along the perpendicular (**b**) and parallel orientation (**c**) with respect to sample plane, indicating a strong out-of-plane magnetic anisotropy. **d** Enlarged hysteresis loops of 7 ML CrTe₂ at 300 K, where the intrinsic ferromagnetism and PMA still maintains. Top inset: temperature dependence of K_u for 7 ML CrTe₂, where the K_u is preserved at 300 K, despite the lower intensity with the increase of temperature.

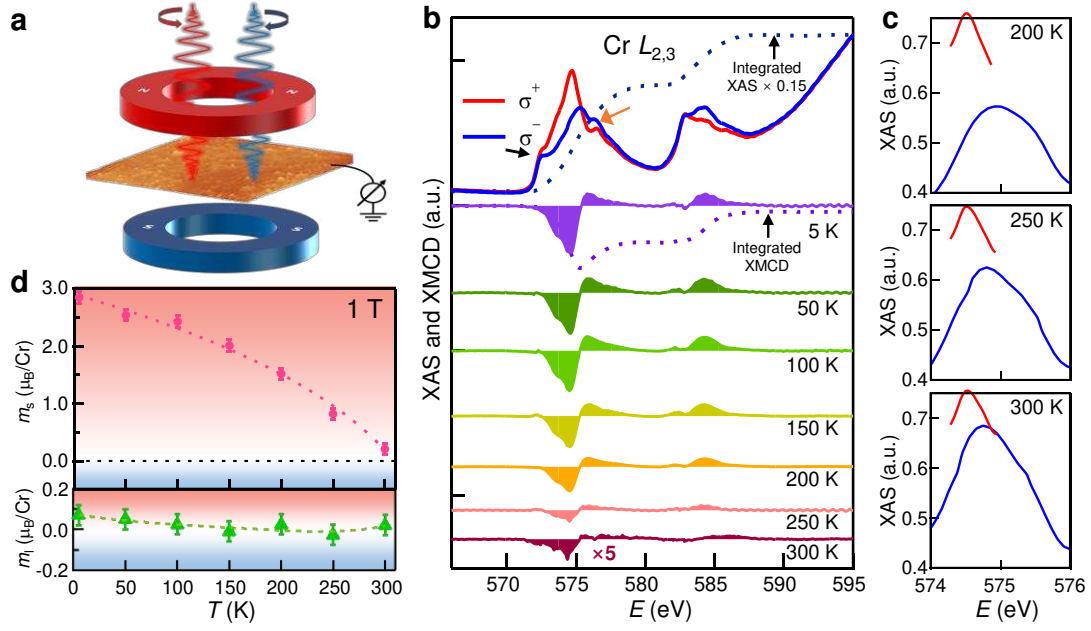


Fig. 3 XAS and XMCD characterization of 7 ML CrTe₂ films. **a** Schematic geometry of XMCD experimental setup. **b** Typical pairs of XAS and XMCD spectra of 7 ML CrTe₂ from 5 K to 300 K and the integrals at 5 K, where the dichroism at Cr L_3 edge can be traced to 300 K (spectra at different temperatures are offset for clarity). **c** The partially enlarged XAS of Cr L_3 edge at 200 K, 250 K, and 300 K, where the differences between left- and right-circularly polarized XAS are evident. **d** m_s and m_l versus temperature derived from **b** using sum rules.

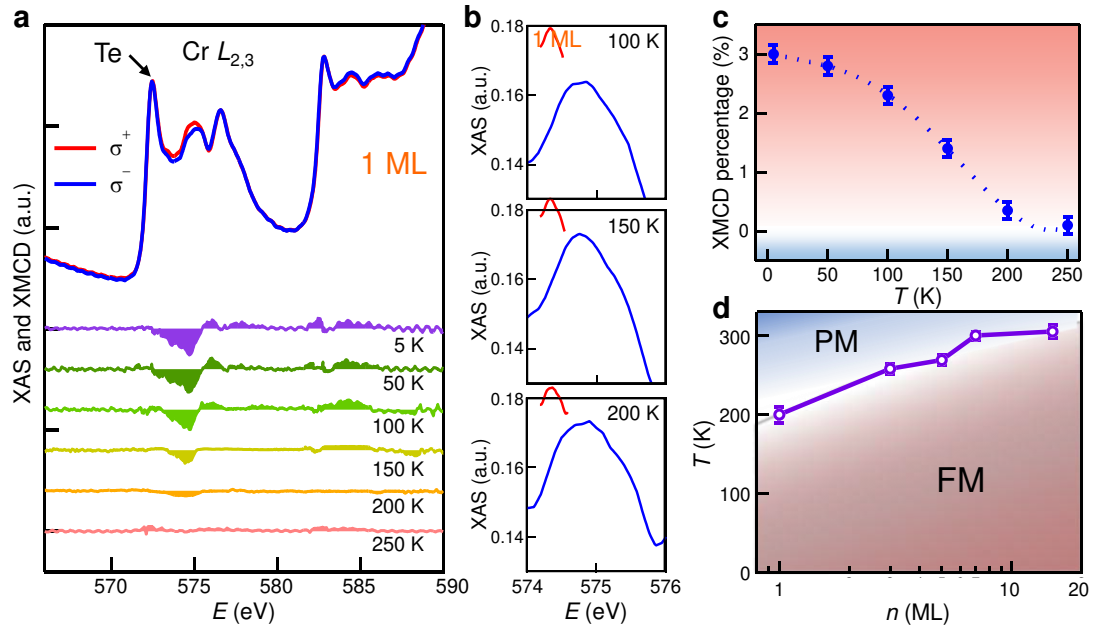


Fig. 4 XAS and XMCD characterization of CrTe₂ films with thickness of monolayer. **a** Typical pairs of XAS and XMCD spectra of 1 ML CrTe₂ thin film at various temperatures, where the dichroism at Cr L_3 edge can be traced to 200 K. **b** The partial enlarged XAS spectra near the Cr L_3 edge, where the difference between left- and right-circularly polarized XAS is evident. **c** XMCD percentage as a function of temperature derived from **a**. **d** Compiled thickness–temperature phase diagram with the T_C obtained from XMCD and SQUID measurements.

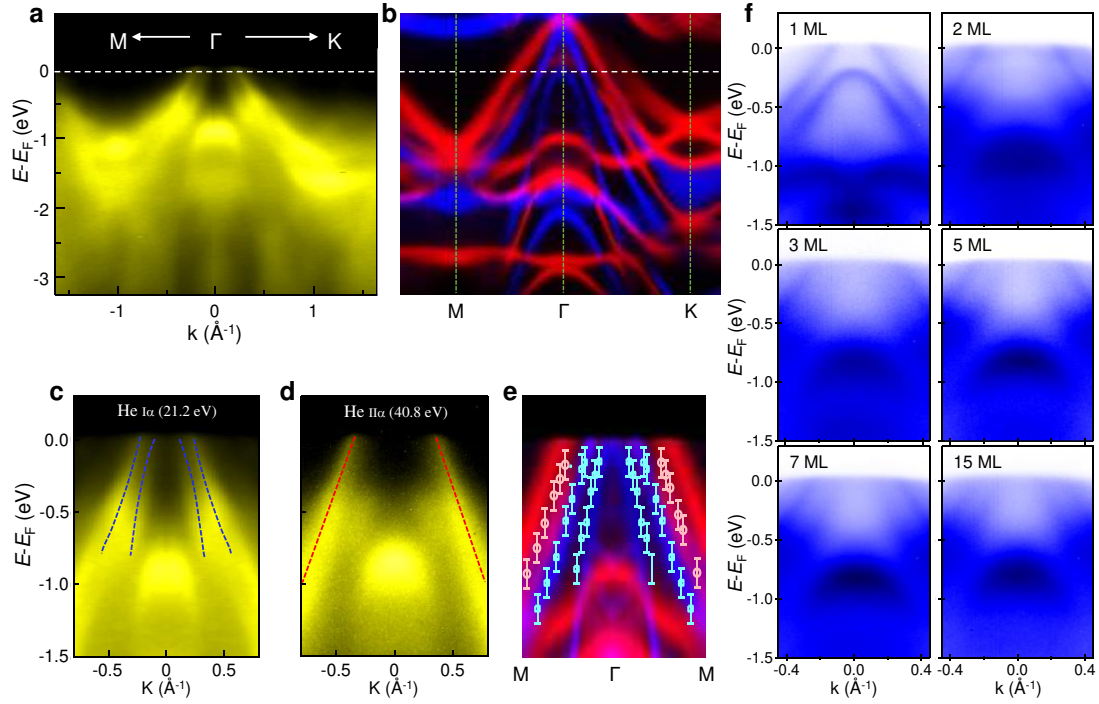


Fig. 5 Band structure of CrTe₂ ultrathin films. **a, b** Plots of valence-band dispersion (**a**) and the first-principles calculations (**b**) of 7 ML CrTe₂ with the inclusion of spin polarization along the high symmetry direction M-Γ-K. The minority and majority spin bands are plotted in red and blue colors, respectively. The major features seen in the left panel are well reproduced in the right one. **c-e** Comparison of the valence-band dispersion near the Fermi level taken by He Iα (21.2 eV) (**c**), He IIα photons (40.8 eV) (**d**) with theoretical bands (**e**) along the high symmetry direction M-Γ-M. The blue and red dashed lines indicate the position of hole pockets measured by He Iα and He IIα photons, respectively. The light blue/red markers and error bars represent the position of MDC peaks. **f** ARPES intensity maps of 1 ML, 2 ML, 3 ML, 5 ML, 7 ML and 15 ML, respectively. The spectra of various thicknesses were taken along the high symmetry direction M-Γ-M.