



This is a repository copy of *Gold nanoparticle decorated single walled carbon nanotube nanocomposite with synergistic peroxidase like activity for D-alanine detection.*

White Rose Research Online URL for this paper:
<http://eprints.whiterose.ac.uk/105451/>

Version: Accepted Version

Article:

Haider, W., Hayat, A., Raza, Y. et al. (3 more authors) (2015) Gold nanoparticle decorated single walled carbon nanotube nanocomposite with synergistic peroxidase like activity for D-alanine detection. RSC Advances, 5 (32). pp. 24853-24858.

<https://doi.org/10.1039/c5ra01258a>

Reuse

Unless indicated otherwise, fulltext items are protected by copyright with all rights reserved. The copyright exception in section 29 of the Copyright, Designs and Patents Act 1988 allows the making of a single copy solely for the purpose of non-commercial research or private study within the limits of fair dealing. The publisher or other rights-holder may allow further reproduction and re-use of this version - refer to the White Rose Research Online record for this item. Where records identify the publisher as the copyright holder, users can verify any specific terms of use on the publisher's website.

Takedown

If you consider content in White Rose Research Online to be in breach of UK law, please notify us by emailing eprints@whiterose.ac.uk including the URL of the record and the reason for the withdrawal request.



eprints@whiterose.ac.uk
<https://eprints.whiterose.ac.uk/>

RSC Advances



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

1 **Gold nanoparticles decorated single walled carbon nanotubes nanocomposite**
2 **with synergistic peroxidase like activity for D-alanine detection**

3 Waqar Haider^a, Akhtar Hayat^{b*}, Yousuf Raza^c, Aqif anwar^b, Ihtesham-Ur- Rehman^d,
4 Jean Louis Marty^e

5 ^aDepartment of Chemistry, Government College University Faisalabad, Pakistan

6 ^bInterdisciplinary Research centre in Biomedical Materials (IRCBM), COMSATS, Lahore,
7 Pakistan

8 ^cInstitute of Chemical Sciences, Bahauddin Zakariya University, Multan, Pakistan

9 ^dThe Kroto Research Institute North Campus University of Sheffield Broad Lane Sheffield, UK

10 ^eIMAGES, Universite de Perpignan Via Domitia, France

11 *Corresponding author; akhtarhayat@ciitlahore.edu.pk

12

13 **Abstract**

14 In this report, gold nanoparticles decorated single walled carbon nanotubes
15 (SWCNTs) nanocomposite was shown to possess synergistic intrinsic peroxidase like
16 activity and enhanced affinity towards H₂O₂ oxidation. The gold nanoparticles decorated
17 SWCNTs nanocomposite were characterized by high catalytic activity, enhanced stability
18 of gold nanoparticles and improved dispersion of SWCNTs. Subsequently, this
19 nanocomposite was proved to be a novel peroxidase mimetic with great potential to
20 catalyze oxidation of 3,3',5,5'-tetramethylbenzidine (TMB) in the presence of H₂O₂ to
21 yield a blue color product. As a proof of concept, gold nanoparticles decorated SWCNTs
22 composite was used as a robust nanoprobe for the detection of D-alanine with improved
23 analytical characteristics. Taking into account the valuable intrinsic peroxidase activity of
24 nanohybrid, the present work may find widespread applications in the field of sensors and
25 biosensors for diverse applications.

26 **Keywords:** SWCNTs/gold particle nanocomposite; peroxidase like activity;
27 synergic effect; D-alanine detection; colorimetric assays

28

29 **1. Introduction**



30 Natural enzymes have remained a topic of great interest for researchers owing to their
31 catalytic properties, and as well as substrate specificity. However, the catalytic activity of natural
32 enzymes is directly influenced by different parameters such as temperature, acidity and
33 inhibitors¹. Their significance is further limited due to their high cost and time consuming
34 preparation, purification and storage steps¹⁻⁴. Thus, more attention is paid to the discovery and
35 development of new enzyme mimics during the last few years. The peroxide enzymes mimics
36 such as cyclodextrin⁵, porphyrin⁶, hemin^{7, 8}, DNAzyme⁹, and hematin¹⁰ were largely used as
37 catalysts for the determination of H₂O₂.

38 During recent years, the growing field of nanotechnology has resulted in the development
39 of a variety of nanomaterial with improved catalytic properties due to their large surface-to-
40 volume ratio¹¹. The enzyme mimics of transition metal oxides and sulfides such as graphene
41 oxide¹², cupric oxide¹³, V₂O₅ nanowires¹⁴, Fe₃O₄³, BiFeO₃¹⁵, polymer-coated CeO¹⁶ and FeS
42 nanostructures¹⁷ have been successfully integrated to impart intrinsic peroxidase activity for
43 sensing applications. Moreover, hybrid nanocomposite materials with well-defined structure
44 have been investigated to realize the synergic effect by combining the properties of two materials
45 or to achieve cooperatively enhanced performance for various applications. In this context, a
46 variety of inorganic nanomaterials have been incorporated with different supports to achieve
47 nanohybrids of desired functionalities. Typically, some of these nanocomposites have been

48 explored to possess synergistic peroxidase like activity to replace the natural enzyme¹⁸. There is
49 a great interest to design and fabricate new nanomaterials with enzyme like activities, and to
50 subsequently use them for sensing applications.

51 Recent studies have demonstrated the catalytic activity of carbon nanotubes even in the
52 absence of catalytic factors¹⁹. The intrinsic peroxidase like activity of SWCNTs has received
53 much attention to design biofuel cells and biosensors of novel characteristics. Similarly, noble
54 metal nanomaterials such as gold and silver having several to tons of metal atoms have become
55 emerging area of scientific research due to their optical properties, biocompatibility and low
56 toxicity. Interestingly, recent work by Wang et al has explored the peroxidase like activity of
57 gold nanoparticles for xanthine detection²⁰. Therefore, in the light of superiority of SWCNTs and
58 gold nanoparticles, the decoration of gold nanoparticles on SWCNTs was expected to possess
59 new and enhanced catalytic properties that cannot be achieved by either component alone. To the
60 best of our knowledge, the peroxidase like activity of SWCNTs/gold nanoparticles
61 nanocomposite has not been explored in the literature so far. To demonstrate the feasibility of
62 nanocomposite, the synergistic peroxidase like properties of the gold nanoparticles decorated
63 SWCNTs nanocomposite were further employed for the determination of D-alanine detection. D-
64 alanine belongs to D-amino acids family. Each amino acid exists in two isomeric forms based on
65 the possibility of forming two different enantiomers around the central carbon atom. The two
66 isomeric forms are known as D- and L-forms analogous to right handed and left handed
67 configurations. L-amino acids are produced in the cell and subsequently incorporated into the
68 proteins. L-amino acid oxidase is used to catalyze the reaction of L-aminoacids, while D-amino
69 acids are converted by the D-amino acid oxidase. D-amino acids (DAAs) are known to have
70 important physiological roles in central nervous system²¹ and insulin regulation²². Besides this,

71 their concentration is monitored due to the correlation of DAAs with several diseases. Therefore,
72 it is of vital importance to detect concentration of DAAs in biological samples with great
73 precision and accuracy. Various analytical methodologies have been employed to monitor level
74 of DAAs which includes High Performance Liquid Chromatography, Gas Chromatography and
75 electrochemical detection methods.²³ Alternatively, colorimetric methods based on the use of D-
76 amino acids oxidase can be employed for monitoring of DAAs. D-amino acids oxidase oxidizes
77 amino acids into imino acid and H₂O₂ in the presence of oxygen. The peroxidase catalytic
78 oxidation of generated H₂O₂ in the presence of TMB results in the formation of a blue colored
79 product that can be monitored for colorimetric detection of DAAs. Herein, we have proposed a
80 new, simple and sensitive method for the colorimetric determination of DAAs in which the
81 combined catalytic effect of gold NPs and CNTs was used for the quantification of H₂O₂ instead
82 of commonly used natural enzyme. (see eq. 1 & 2).



85 D-alanine was selected as a model DAA to demonstrate the applicability of proposed
86 nanocomposite as peroxidase mimetic. The proposed method can be very easily extended for the
87 detection of other D-amino acids, as D-amino acids oxidase is a generic enzyme for D-amino
88 acids oxidation. The same chemistry could also be integrated to other H₂O₂ colorimetric
89 detection based sensing methodologies.

90 **2. Experimental**

91 **2.1 Chemical and apparatus**

92 D-amino acids oxidase (DAAO), D alanine, 3,3',5,5'-Tetramethylbenzidine (TMB) and
93 hydrogen peroxide (H_2O_2) solution were obtained from Sigma Aldrich. Chitosan, Single Walled
94 Carbon Nanotubes (SWNC) and acetic acid were also purchased from Sigma Aldrich.
95 Chloroauric acid ($\text{HAuCl}_4 \cdot 3\text{H}_2\text{O}$) and all other chemicals were purchased from Fisher scientific.
96 Interfering compounds including uric acid, ascorbic acid, glycine and glucose were purchased
97 from Sigma. All chemical were of analytical grade and used as received. Working solutions were
98 achieved by serial dilution of the stock solution. All solutions were made using deionized water.
99 96 Well Microplates were obtained from Greiner bio-one. Colorimetric measurements were
100 performed with a lab systems Multiskan EX micro titer plate reader. UV/Vis Spectrophotometer
101 (Perkin-Elmer Lambda) was used to characterize the proposed reaction.

102 2.2 Synthesis of SWCNTs-gold nanocomposite

103 SWCNTs-gold nanocomposite synthesis was performed with the dissolution of chitosan
104 powder in acetic acid solution with stirring for 1h at room temperature to achieve a completely
105 dispersed solution. Afterwards, 10 mg of SWCNTs were added in 20 mL of chitosan solution,
106 and resulting mixture was sonicated for 2h prior to 10 min of centrifugation to obtain the well
107 dispersed SWCN. Further, 1 mL of 25 mM HAuCl_4 was added to the above obtained dispersion
108 under intense stirring for 10 min. The mixture was heated up to 80°C , until the color of the
109 solution was stabilized and did not change²⁴. The synthesized SWCNTs-gold nanocompoiste
110 was subsequently employed in the construction of H_2O_2 and D-alanine biosensors to replace the
111 commonly used Horseredish peroxidase (HRP) enzyme.

112 2.3 Measurement of SWCNTs-gold nanocomposite activity towards H_2O_2

113 TMB solution was used to determine the reactivity of SWCNTs-gold nanocomposite.
114 Experiments were carried out using 10 μL of nanocomposite in a reaction medium containing
115 H_2O_2 and TMB. The oxidation reaction by nanocompiste was characterized by a blue color
116 product (diimine, one electron oxidation product) with an absorption wavelength of 652 nm. In
117 order to achieve the concentration dependence response, and to determine the nanocomposite
118 sensitivity, H_2O_2 in the range of 0.5 to 25 μM was incubated in the reaction mixture and
119 absorption values were used to draw a calibration curve. Kinetic measurements were carried out
120 by measuring the absorbance at various times, and were subsequently used to obtain the kinetic
121 parameters.

122 2.4 Bioassay for D-alanine measurement

123 D-alanine detection was carried out as follows: firstly, 85 μL of DAAO solution and 85
124 μL of D-alanine solution with varying concentration strength were mixed in the wells of 96
125 microplates and incubated for a time period of 30 min at room temperature. Then 20 μL of TMB
126 and 10 μL of SWCNTs-gold nanocomposites were successively added to the D-alanine reaction
127 solution. Finally the mixed solution was incubated for a time period of 20 min at room
128 temperature for standard curve measurements. D-alanine contents were determined in fruit Juice
129 samples to demonstrate the applicability of the proposed method for real sample analysis.

130 3. Results and Discussion

131 To obtain an insight on the peroxidase like activity of SWCNTs and gold nanocomposite,
132 catalytic oxidation of H_2O_2 in the absence or presence of chromogenic substrate TMB was
133 investigated. SWCNTs and gold particle nanocomposite resulted in excellent catalytic properties
134 for the oxidation of H_2O_2 in the presence of TMB. As can be seen from Fig. 1, the reaction for

135 the oxidation of TMB did not proceed in the absence of catalysts, demonstrating the suitability of
136 composite for H₂O₂ detection. In the contrary, the presence of SWCNTs and gold nanoparticles
137 composite significantly increased the rates of reaction and a deep blue colored solution was
138 observed with an absorption wavelength of 652 nm (Fig 1). However, the SWCNTs and gold
139 nanocomposite system resulted in negligible color change under same experimental conditions in
140 the presence of TMB. These above findings suggest that SWCNTs and gold particles composite
141 possess peroxidase like activity that can be explored to construct H₂O₂ based biosensors to
142 replace the natural enzyme.

143 3.1 Optimization of analytical parameters

144 Like natural enzymes, the catalytic activity of artificial enzymes was also dependent on
145 the amount of nanocomposite, concentration of TMB, H₂O₂ and pH of the reaction mixture. The
146 maximum catalytic activity of the nanocomposite was achieved under following optimal
147 experimental conditions: pH 7.0, room temperature, 10 μ L of nanocomposite, 400 μ M TMB and
148 30 mM H₂O₂ (supporting information, Fig S1). These results are in close proximity to the
149 previously described values for other NP-based peroxidase mimetics and HRP. After
150 optimization of these initial parameters, optimal conditions were employed to perform the
151 subsequent assays.

152 For assessing the catalytic mechanism and acquiring kinetic parameters, the catalytic
153 activity of SWCNTs and gold particles nanocomposites was carried out by enzyme kinetics
154 methodology in the presence of TMB and H₂O₂. Experiments were performed under varying
155 concentration of one substrate and constant concentration of other substrate. Michaelis-Menton
156 curves were obtained for varying concentrations of two substrates (supporting information, Fig
157 2a and 2b for TMB and H₂O₂ respectively). The kinetic parameters such as maximum initial

158 velocity (V_m) and Michaelis-Menton (K_m) were calculated from the Lineweaver-Burk plots and
159 are listed in the table 1. The comparison of kinetic parameters revealed that the K_m value of
160 SWCNTs and gold nanocomposite towards H_2O_2 was 64 folds lower than that of SWCNTs and
161 39 times lower as compared to gold nanoparticles. These results provide evidence that a lower
162 concentration of H_2O_2 is needed for nanocomposite as compared to SWCNTs and gold
163 nanoparticles to achieve the maximum catalytic activity. K_m value is a representative of the
164 enzyme affinity towards substrate conversion. The decreased K_m value is directly related to
165 better catalytic efficiency towards H_2O_2 oxidation, suggesting that SWCNTs and gold particles
166 nanocomposite has more affinity for H_2O_2 as compared to SWCNTs and gold nanoparticles. The
167 enhanced affinity can be related to the improved peroxidase like activity of nanocomposite, and
168 subsequently, this novel material may find wide spread applications in various fields. The
169 enhanced enzyme like activity of gold nanoparticles decorated single walled carbon nanotubes
170 may be attributed to the improved stabilization and dispersion of the nanocomposite in the
171 detection medium. It can be predicted that the electronic structure of SWCNTs is preserved upon
172 gold nanoparticles coating, leading to a synergistic effect. The other phenomena such as Au NPs
173 co-tunneling effects and the Au NPs-induced energy-band modulation of the SWCNTs may also
174 contribute to improve the biomimetic properties of nanocomposite against hydrogen peroxide
175 oxidation²⁵.

176

177

178

179

180 **Table 1** A comparison of the K_m and V_m values

Catalyst	K_m [mM]		V_m [10^{-8} MS $^{-1}$]	
	TMB	H ₂ O ₂	TMB	H ₂ O ₂
SWCNTs /Gold particle Nanocomposite	0.48	0.65	14.2	5.8
HRP ²⁶	0.434	3.7	10	8.71
Carbon nanotubes ²⁷	0.02	41.42	-	-
Gold nanocluster ²⁰	0.00253	25.3	6.23	7.21

181

182 To further evaluate the process of SWCNTs and gold nanocomposite catalysis,

183 experiments were performed over a wide range of TMB and H₂O₂ concentrations. The double

184 reciprocal of velocity against one of the component concentrations were achieved while the

185 concentrations for other substrates were fixed. The catalytic activity of SWCNTs/gold particles

186 nanocomposite was investigated for different concentrations of H₂O₂ under optimal experimental

187 conditions. The absorbance of reaction mixture increased with the increasing concentration of

188 H₂O₂. Similarly, the reaction rate of TMB with H₂O₂ was observed at varying concentration of

189 TMB. As provided in the supporting information (Fig 2c and 2d) , the slopes of the lines are

190 parallel , revealing a ping pong mechanism and indicating the proposed nanocomposite binds and

191 reacts with the first substrate and then releases the first product prior to its reaction with other

192 substrate.

193 3.2 Assays for detection of hydrogen peroxide and D-Amino acids

194 Based on the intrinsic and synergic peroxidase like properties of SWCNTs/gold particles

195 nanocomposite, a simple colorimetric method to detect H₂O₂ and D-alanine employing the

196 catalyzed color reaction was designed. As the absorbance of TMB is proportional to the

197 concentration of H_2O_2 , it can be a facile approach to quantitatively measure H_2O_2 at 652 nm.
198 Figure 3a represents the calibration curve for varying concentrations of H_2O_2 ranging from 0.5
199 μM to 25 μM . The color variation can be seen as inset of Fig 3a, indicating that this approach
200 can offer a convenient way to monitor H_2O_2 by naked eye with a visual limit of detection of 1.5
201 μM . The analytical parameters including linearity, limits of detection and precision were carried
202 out under optimal experimental conditions. Figures of merit are included in the Supplementary
203 table 1.

204 DAA's detection is of vital importance in the clinical analysis, and generally
205 DAAO is used to catalyze the oxidation of DAAs to produce imino acids and hydrogen peroxide
206 in the presence of oxygen. In the proposed work, SWCNTs/gold particles nanocomposite was
207 used to catalyze H_2O_2 in the presence of TMB to obtain a blue color product. The color
208 variation/intensity from the converted TMB can be monitored for the indirect measurement of
209 DAA. The obtained results for DAA detection with our nanocomposite are presented in
210 supplementary table 1, while figure 3b presents the calibration curve along with visual inset. The
211 response was linearly proportional to DAA concentration from 0.1 μM to 25 μM , with a
212 detection limit of 0.05 μM . The obtained limit of detection was lower than the LOD of
213 previously reported method for DAA detection²⁸. The naked color changes were also obvious to
214 monitor the level of DAA. Furthermore, the specificity of the proposed method was
215 demonstrated against common interfering compounds including uric acid, ascorbic acid, glycine
216 and glucose. As can be seen from the Fig 3, the absorbance of these interfering compounds was
217 not obvious even when they were used at much elevated concentration as compared to DAA.
218 These results show that the proposed nanocomposite based colorimetric method has very good

219 selectivity for DAA detection, which is attributed to the specificity of DAAO towards DAA
220 catalysis.

221 In order to demonstrate the applicability of the SWCNTs/gold particles
222 nanocomposite as a peroxidase mimetic, the developed approach was used to detect DAA in the
223 fruit juice samples. The obtained results with recovery values are included in the Table 2. The
224 average recovery values for three DAA spiked concentrations were from 95 % to 98%. Similarly
225 the precision of the method was also presented in the table 2. The relative standard deviation
226 values were obtained for each concentration level. Good recovery values and good precision
227 values for DAA detection based on proposed nanocomposite reveals that the peroxidase like
228 activity based colorimetric approach was useful to reduce the matrix effect of fruit sample. It is
229 obvious that the proposed method may find spread applications in various fields particularly in
230 sensor and biosensor field. In comparison with previously reported nanomaterials based oxidase
231 mimics^{18, 29-36}, SWCNTs/gold particle nanocomposite has the best analytical characteristics in
232 terms of sensitivity and linear range. The analytical performance of our purposed methods is
233 comparable to the assay based on BSA-stabilized gold nanoparticles oxidase like activity²⁰.
234 However, the gold nanoparticles assays suffer from aggregation phenomena, and require specific
235 experimental conditions. Table 3 provides a comparison between the analytical performance of
236 our purposed method and previously reported assays with peroxidase like activity (**Table3**).

237

238

239

240

241 **Table 2.** Recovery percentages obtained with designed colorimetric assay

DAA added ($\mu\text{mol/L}$)	DAA found ($\mu\text{mol/L}$)	R.S.D %	R.E %	R%
0.15	0.143	5	4.66	95.33
5	4.89	3.2	2.2	97.8
12.5	12.1	3.4	3.2	96.8

242 R.S.D % = relative standard deviation percentage; R.E % = relative error percentage; R% = recovery
 243 percentage.

244 **Table 3.** A comparison between the analytical performance of our proposed method and
 245 previously reported oxidase like mimics towards H_2O_2 detection

Sr No	Nanomaterial	Limit of detection ($\mu\text{mol/L}$)	Linear range ($\mu\text{mol/L}$)	Ref
1	Graphene oxide- Fe_2O_3 magnetic nanocomposite	0.32	1-50	18
2	MWCNT-PBin	0.1	1-1500	29
3	PtPd nano dendrites supported on graphene nanosheets	0.1	0.5-150	31
4	BSA-stabilized Au nanocluster	0.02	0.5 – 20	20
5	Au@Pt core/shel nanorods	44	44-1000	30
6	$\text{Co}_3\text{O}_4/\text{rGO}$ nanocomposite	1	1-100	32
7	Fe_3O_4 magnetic nanoparticles	3	5 -100	33
8	Chitosan stabilized silver nanoparticles	0.1	5-200	34
9	Positively charged gold nanoparticles	0.5	2 -200	35
10	Porphyrin- Fe_2O_3 nanocomposite	1.07	5-80	36
11	Gold nanoparticles decorated SWCNTs	0.08	0.5-25	Present work

246

247 4. Conclusion

248 We have reported a new combination of artificial enzyme for colorimetric determination
249 of D amino acids through the catalytic oxidation of H₂O₂. In the proposed method, the
250 synergistic effect of gold nanoparticles and SWCNTs has shown excellent intrinsic peroxidase
251 activity which is much higher than the sum of individual catalytic effect of both nanomaterials.
252 The rate of oxidation of TMB was dependent on time, pH, the concentrations of H₂O₂ and TMB
253 and the catalyst. The method showed good sensitivity, selectivity and linearity for the
254 determination of D-amino acid in the range of 0.1 – 25 μM. The enzyme-like catalysis is proved
255 to be a good competitor of natural enzymes due to robustness and good stability under rigorous
256 experimental reaction conditions. Moreover the assay is simple and cheap, making it suitable and
257 applicable for various applications in different domains.

258

259

260

261

262

263

264

265

266

267

268

269

270

271 **References**

- 272 1. Y. Tao, Y. Lin, Z. Huang, J. Ren and X. Qu, *Advanced materials*, 2013, **25**, 2594-2599.
- 273 2. Y. Jv, B. Li and R. Cao, *Chemical communications*, 2010, **46**, 8017-8019.
- 274 3. Y. L. Dong, H. G. Zhang, Z. U. Rahman, L. Su, X. J. Chen, J. Hu and X. G. Chen,
275 *Nanoscale*, 2012, **4**, 3969-3976.
- 276 4. E. Shoji and M. S. Freund, *Journal of the American Chemical Society*, 2001, **123**, 3383-
277 3384.
- 278 5. Z. Liu, R. Cai, L. Mao, H. Huang and W. Ma, *Analyst*, 1999, **124**, 173-176.
- 279 6. M. Sono, M. P. Roach, E. D. Coulter and J. H. Dawson, *Chemical Reviews*, 1996, **96**,
280 2841-2888.
- 281 7. Q. Wang, Z. Yang, X. Zhang, X. Xiao, C. K. Chang and B. Xu, *Angewandte Chemie*
282 *International Edition*, 2007, **46**, 4285-4289.
- 283 8. L. Fruk and C. M. Niemeyer, *Angewandte Chemie International Edition*, 2005, **44**, 2603-
284 2606.
- 285 9. G. Pelossof, R. Tel-Vered, J. Elbaz and I. Willner, *Analytical chemistry*, 2010, **82**, 4396-
286 4402.
- 287 10. G. Zhang and P. K. Dasgupta, *Analytical chemistry*, 1992, **64**, 517-522.
- 288 11. C. Burda, X. Chen, R. Narayanan and M. A. El-Sayed, *Chemical Reviews*, 2005, **105**,
289 1025-1102.

- 290 12. Y. Song, K. Qu, C. Zhao, J. Ren and X. Qu, *Advanced materials*, 2010, **22**, 2206-2210.
- 291 13. L. Hong, A. L. Liu, G. W. Li, W. Chen and X. H. Lin, *Biosensors & bioelectronics*,
292 2013, **43**, 1-5.
- 293 14. R. André, F. Natálio, M. Humanes, J. Leppin, K. Heinze, R. Wever, H. C. Schröder, W.
294 E. G. Müller and W. Tremel, *Advanced Functional Materials*, 2011, **21**, 501-509.
- 295 15. W. Luo, Y.-S. Li, J. Yuan, L. Zhu, Z. Liu, H. Tang and S. Liu, *Talanta*, 2010, **81**, 901-
296 907.
- 297 16. A. Asati, S. Santra, C. Kaittanis, S. Nath and J. M. Perez, *Angewandte Chemie*
298 *(International ed. in English)*, 2009, **48**, 2308-2312.
- 299 17. Z. Dai, S. Liu, J. Bao and H. Ju, *Chemistry – A European Journal*, 2009, **15**, 4321-4326.
- 300 18. Y.-l. Dong, H.-g. Zhang, Z. U. Rahman, L. Su, X.-j. Chen, J. Hu and X.-g. Chen,
301 *Nanoscale*, 2012, **4**, 3969-3976.
- 302 19. Y. Song, X. Wang, C. Zhao, K. Qu, J. Ren and X. Qu, *Chemistry – A European Journal*,
303 2010, **16**, 3617-3621.
- 304 20. X.-X. Wang, Q. Wu, Z. Shan and Q.-M. Huang, *Biosensors and Bioelectronics*, 2011, **26**,
305 3614-3619.
- 306 21. J. S. Bains and S. H. R. Oliet, *Trends in Neurosciences*, 2007, **30**, 417-424.
- 307 22. K. Hamase, A. Morikawa, S. Etoh, Y. Tojo, Y. Miyoshi and K. Zaitzu, *Analytical*
308 *sciences : the international journal of the Japan Society for Analytical Chemistry*, 2009,
309 **25**, 961-968.
- 310 23. C. H. Nieh, Y. Kitazumi, O. Shirai and K. Kano, *Biosensors & bioelectronics*, 2013, **47**,
311 350-355.

- 312 24. H.-J. Jiang, Y. Zhao, H. Yang and D. L. Akins, *Materials Chemistry and Physics*, 2009,
313 **114**, 879-883.
- 314 25. H. Liu, L. Yang, L. Yu, F. Meng, X. Yu and J. Liu, *Journal of Materials Chemistry*,
315 2012, **22**, 6139-6147.
- 316 26. L. Gao, J. Zhuang, L. Nie, J. Zhang, Y. Zhang, N. Gu, T. Wang, J. Feng, D. Yang, S.
317 Perrett and X. Yan, *Nat Nano*, 2007, **2**, 577-583.
- 318 27. R. Cui, Z. Han and J.-J. Zhu, *Chemistry – A European Journal*, 2011, **17**, 9377-9384.
- 319 28. S. Lata, B. Batra, P. Kumar and C. S. Pundir, *Analytical Biochemistry*, 2013, **437**, 1-9.
- 320 29. T. Wang, Y. Fu, L. Chai, L. Chao, L. Bu, Y. Meng, C. Chen, M. Ma, Q. Xie and S.
321 Yao *Chemistry – A European Journal*, 2014, **20**, 2623-2630.
- 322 30. X. H. Jianbo Liu, Shuai Hou, Tao Wen, Wenqi Liu, Xing Zhu, Jun-Jie Yinc, Xiaochun
323 Wu, *Sensors and Actuators B: Chemical*, 2012, **166-167**, 708-714.
- 324 31. B. S. Xiaomei Chena, Zhixiong Cai, Xi Chen, Munetaka Oyama, *Sensors and Actuators*
325 *B: Chemical*, 2014, **201**, 286-292.
- 326 32. H. C. Jianxin Xie, Huan Jiang, Yujin Chen, Wenbing Shi, Huzhi Zheng, Yuming Huang,
327 *Analytica Chimica Acta*, 2013, **796**, 92-100.
- 328 33. H. Wei and E. Wang, *Analytical Chemistry*, 2008, **80**, 2250-2254.
- 329 34. H. Jiang, Z. Chen, H. Cao and Y. Huang, *Analyst*, 2012, **137**, 5560-5564.
- 330 35. Y. Jv, B. Li and R. Cao, *Chemical Communications*, 2010, **46**, 8017-8019.
- 331 36. H. L. Qingyun Liu, Qingru Zhao, Renren Zhu, Yanting Yang, Qingyan Jia, Bing Bian,
332 Linhai Zhuo, *Materials Science and Engineering: C*, 2014, **41**, 142–151.

333

334

335

336

337

338

339

Figure Captions

340 **Figure 1.** UV/Visible spectra and color evolution of different reaction systems; (a) H_2O_2 +
341 nanocomposite; (b) TMB + nanocomposite; (c) H_2O_2 + TMB+ nanocomposite

342 **Figure 2.** Steady state kinetic assay of the proposed nanocomposite ; a) TMB concentration was
343 varied under fixed concentration of H_2O_2 and nanocomposite; b) H_2O_2 concentration was varied
344 under same concentration of TMB and H_2O_2 ; c and d) double reciprocal plot of nanocomposite
345 activity with the concentration of one substrate fixed and the other varied

346 **Figure 3.** The calibration plots for ; a) H_2O_2 and b) D-alanine detection: Inset; images of end
347 colored product under varying concentration of two analytes

348 **Figure 4.** Selectivity analysis for D-alanine detection with following analyte concentration; 5
349 μM D-alanine and 1 mM for the rest of interfering compounds

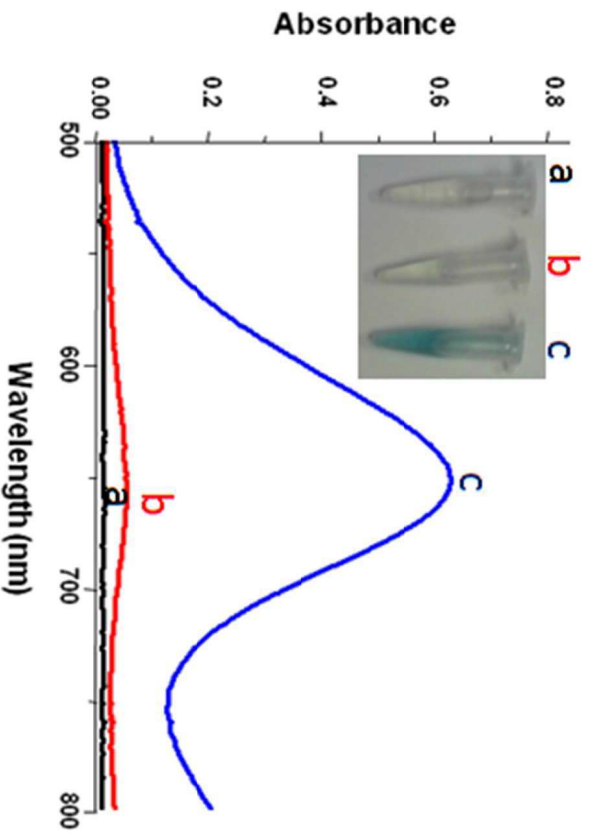


Figure 1

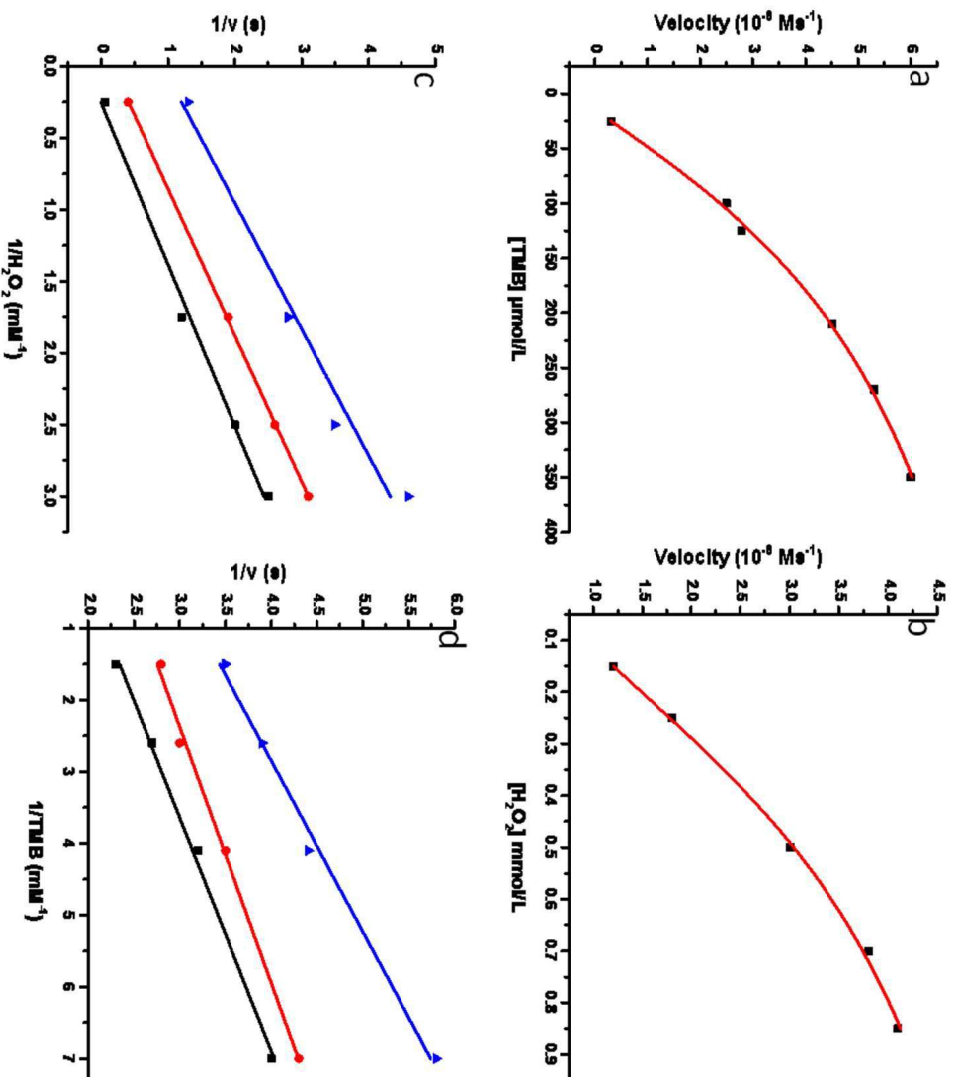


Figure 2

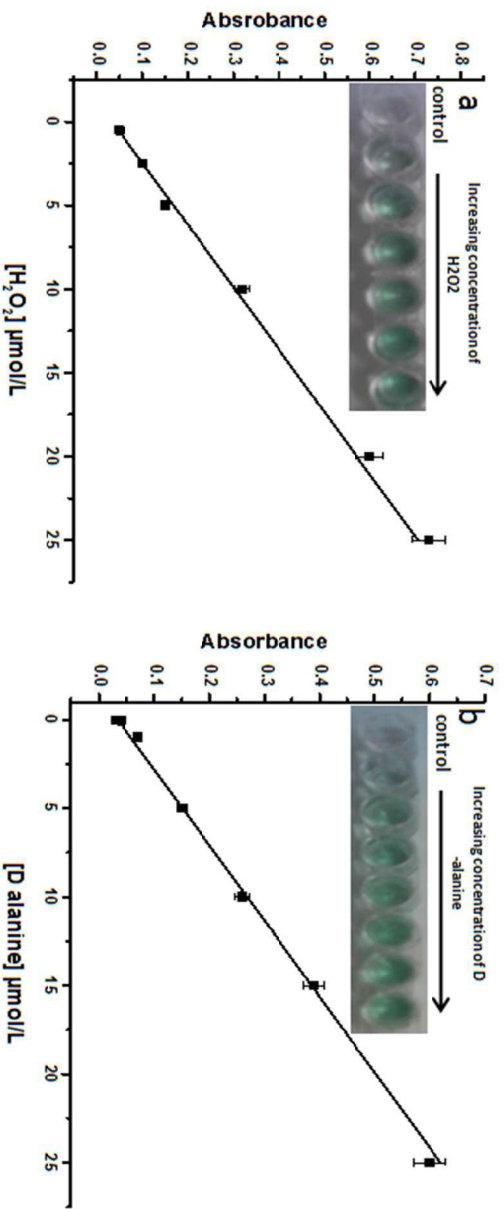


Figure 3

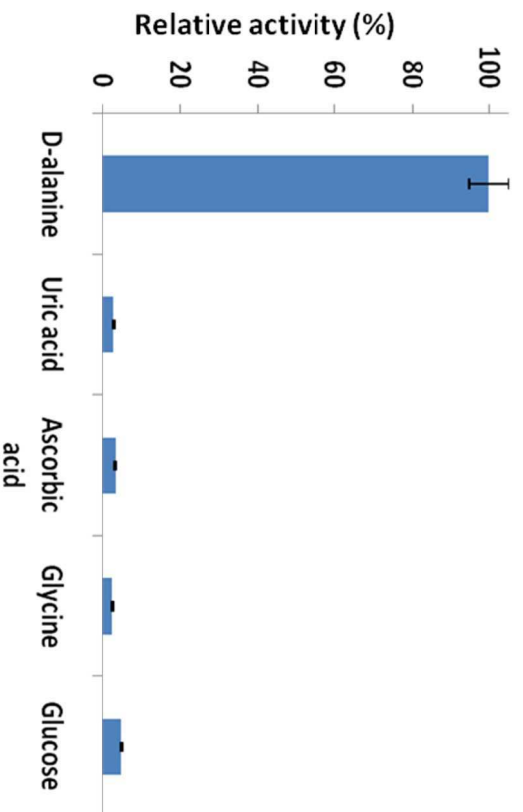


Figure 4