

This is a repository copy of *Effects of interactions on the relaxation processes in magnetic nanostructures*.

White Rose Research Online URL for this paper:

<https://eprints.whiterose.ac.uk/111324/>

Version: Accepted Version

---

**Article:**

Atkinson, Lewis J., Ostler, Thomas A. [orcid.org/0000-0002-1328-1839](https://orcid.org/0000-0002-1328-1839), Hovorka, O. et al. (7 more authors) (2016) Effects of interactions on the relaxation processes in magnetic nanostructures. *Physical Review B*. 134431. pp. 1-8. ISSN 2469-9969

<https://doi.org/10.1103/PhysRevB.94.134431>

---

**Reuse**

Items deposited in White Rose Research Online are protected by copyright, with all rights reserved unless indicated otherwise. They may be downloaded and/or printed for private study, or other acts as permitted by national copyright laws. The publisher or other rights holders may allow further reproduction and re-use of the full text version. This is indicated by the licence information on the White Rose Research Online record for the item.

**Takedown**

If you consider content in White Rose Research Online to be in breach of UK law, please notify us by emailing [eprints@whiterose.ac.uk](mailto:eprints@whiterose.ac.uk) including the URL of the record and the reason for the withdrawal request.

# The effects of interactions on the relaxation processes in magnetic nanostructures

Lewis J. Atkinson<sup>1†\*</sup>, Thomas A. Ostler<sup>2†‡</sup>, O. Hovorka<sup>3</sup>, K.K Wang<sup>4</sup>, B. Lu<sup>4</sup>,  
G.P Ju<sup>4</sup>, J. Hohlfeld<sup>5</sup>, B. Bergman<sup>6</sup>, B. Koopmans<sup>6</sup> and Roy W. Chantrell<sup>1</sup>

<sup>1</sup>*Department of Physics, University of York, Heslington, York YO105DD United Kingdom.*

<sup>2</sup>*Département de Physique, Université de Liège (B5), B-4000 Liège, Belgium*

<sup>3</sup>*Engineering and the Environment, University of Southampton, Southampton SO16 7QF, United Kingdom*

<sup>4</sup>*Seagate Technology, 47010 Kato Road, Fremont, CA 94538, USA*

<sup>5</sup>*Seagate Technology, 7801 Computer Avenue, Bloomington, MN 55435, USA*

<sup>6</sup>*Department of Applied Physics, Technische Universiteit Eindhoven, P.O. Box 513, 5600 MB Eindhoven, NL*

<sup>†</sup>*These authors contributed equally to this work*

<sup>\*</sup>*e-mail: lja503@york.ac.uk and*

<sup>‡</sup>*email: thomas.ostler@ulg.ac.be*

Controlling the relaxation of magnetisation in magnetic nanostructures is key to optimizing magnetic storage device performance. This relaxation is governed by both intrinsic and extrinsic relaxation mechanisms and with the latter strongly dependent on the interactions between the nanostructures. In the present work we investigate laser induced magnetization dynamics in a broad band optical resonance type experiment revealing the role of interactions between nanostructures on the relaxation processes of granular magnetic structures. The results are corroborated by constructing a temperature dependent numerical micromagnetic model of magnetization dynamics based on the Landau-Lifshitz-Bloch equation. The model predicts a strong dependence of damping on the key material properties of coupled granular nanostructures in good agreement with the experimental data. We show that the intergranular magnetostatic and exchange interactions provide a large extrinsic contribution to the damping. Finally we show that the mechanism can be attributed to an increase in spinwave degeneracy with the ferromagnetic resonance mode as revealed by semi-analytical spinwave calculations.

## I. INTRODUCTION

Over the last few decades the demand for information storage has increased at unprecedented rates. This has driven forward huge advances in the areal density of hard disk drives (HDD) based on magnetic storage. These increases have led to hard drive (granular) media containing much smaller grains located in smaller areas. In an ideal scenario the ability to control the magnetic orientation of individual grains would be possible without the effects of interactions between them. However, in structured magnetic materials at the nanoscale this ideal can never be reached. In reality the nanostructures are coupled. This coupling can arise from a number of mechanisms; the long-ranged dipole-dipole field; direct exchange between grains through magnetic impurities across the interstitial region<sup>1</sup>; or via superexchange via oxides in the interstitial boundary layer. The role of interactions in relaxation processes in magnetic materials has long been studied<sup>2-6</sup> in magnetic materials, though it is often very difficult to determine individual mechanisms by which the system relaxes.

The key measurable quantity that governs the relaxation of the magnetization is the effective damping. This parameter determines the dynamics of the magnetization after an external stimulus and, importantly for granular magnetic media, it governs the speed at which a bit can be reversed. A large value of damping is desirable to speed up the writing process and reduce transition noise in Perpendicular Magnetic Recording (PMR) and

to reduce the dc noise arising from back-switching during the Heat Assisted Magnetic Recording (HAMR) process. Although its effect on recording performance is significant, the origin of damping is poorly understood. Mo *et. al.*<sup>6</sup> carried out a detailed analysis of FMR data on CoCrPt perpendicular media, concluding that the intrinsic damping from magnon-electron scattering was as low as 0.004, over an order of magnitude smaller than the values usually obtained for the total damping. Mo *et al* ascribe the major contribution to the damping as arising from inhomogeneity line broadening and grain boundary two-magnon scattering. However, another extrinsic candidate contribution to damping arises from the effects of intergranular interactions. In the present work we investigate the effects of magnetostatic and exchange interactions on the effective damping of perpendicular media. It is shown that the interactions give rise to an increase in damping which is due to the presence of long-ranged dipole-dipole spin wave modes. The introduction of exchange interaction results in a stiffening of the magnetization and a consequent reduction in damping, demonstrated experimentally for a series of CoCrPt granular media, and verified by micromagnetic modelling. We furthermore use a simplified model of spinwaves<sup>2</sup> to show that the interplay between the magnetostatic interactions and intergranular exchange determines the number of spinwave modes with finite k-vectors that share the k=0 (ferromagnetic resonance) frequency (the degeneracy), which is well known to affect the damping<sup>2</sup>.

## II. EXPERIMENTAL RESULTS

To determine the damping from the numerical model and experimentally we use an optical ferromagnetic resonance (FMR) method. In an optical FMR experiment, a magnetic field is used to force the magnetic moments away from their equilibrium. An optical pulse is applied, heating the sample, and thus leading to a new equilibrium position for the magnetization. The initial/new equilibrium configuration arises due to the minimisation of the competing anisotropy, exchange, demagnetising and Zeeman energies at the starting/final temperature. The rapid increase in temperature caused by the laser induces precession of those moments around a new position due to thermally induced changes in the energy contributions. The resulting dynamics can then be analysed to determine effective parameters governing the relaxation process. This technique has been applied to a wide range of materials and structures<sup>7-10</sup>. In particular optical FMR is the preferred method for measuring the damping and resonance frequencies in materials with a strong magnetocrystalline anisotropy<sup>11</sup>, due to the high fields required to drive the system to resonance in a typical ferromagnetic resonance experiment<sup>12</sup>. Interestingly, the two methods were shown to give the same values of the damping by Clinton and co-workers in Ref. 7.

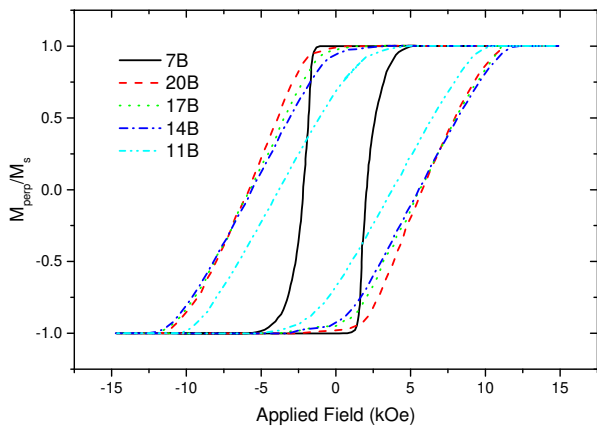


Figure 1. (Color online) Hysteresis loops for the series of CoPt with variable exchange. Increasing exchange leads to increasingly square loops as expected.

We have carried out measurements on a series of CoPt perpendicular media in which the exchange coupling was varied by changing the oxygen content in the intergranular layers. The applied field is applied perpendicular to the sample plane (in the z-direction). The variation of the exchange coupling is immediately apparent in the measured hysteresis loops as shown in Fig. 1, where it can be seen that increasing oxygen

content gives rise to increasingly sheared loops as the intergranular exchange is reduced, due to the distribution of switching fields and the fact that the reduced exchange leads to a less coherent reversal mechanism.

From the hysteresis properties we determine the exchange field using  $N * 4\pi M_s - H_{int}$ , where  $N$  is a demagnetizing factor, usually anywhere between 0.75 to 0.85 Ref. 13, and  $H_{int}$  is the mean interaction field measured using FORC<sup>14</sup>.

We have carried out measurements of the effective damping constant using the optically pumped FMR technique<sup>15</sup> in order to investigate the dependence of the effective damping constant on the exchange. The magnetic moments are forced away from the equilibrium position using a 0.8kOe field at a 45 degree angle from the out of plane anisotropy axis. A 10.8mW laser is used to heat the media and excite the magnetisation into precession. An example of the time resolved magnetisation data obtained is given in figure 2 which includes an example (inset) of the fit to the data that was used to determine the damping of the system.

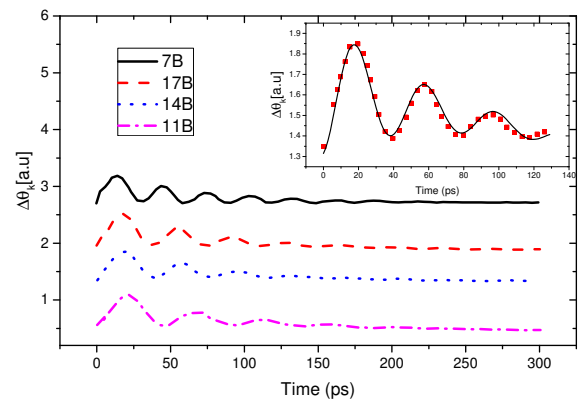


Figure 2. (Color online) A example of a time resolved magnetisation trace determined experimentally. Also showing in the inset an example of the fit to data that was used to extract the damping, where the raw data is shown as points and fitted function is shown as a line.

The results are shown in fig. 3, which shows the dependence of the measured Gilbert damping constant on the exchange field. The values of the damping are calculated by fitting the transverse magnetisation components to a decaying oscillating function,  $m_y(t) = A \cos(\omega t) \exp(-t/\tau)$ , where the fitting parameters are;  $A$ , the amplitude;  $\omega$ , the resonance frequency; and  $\tau$ , the relaxation rate. The damping is then  $\alpha = 1/\tau\omega$ .

A non-monotonic dependence of  $\alpha$  on  $H_{ex}$  is clear. In order to interpret the experiments in terms of the intergranular interactions we have also measured the zero field cluster size using the method of Nemoto *et. al.*<sup>13</sup>.

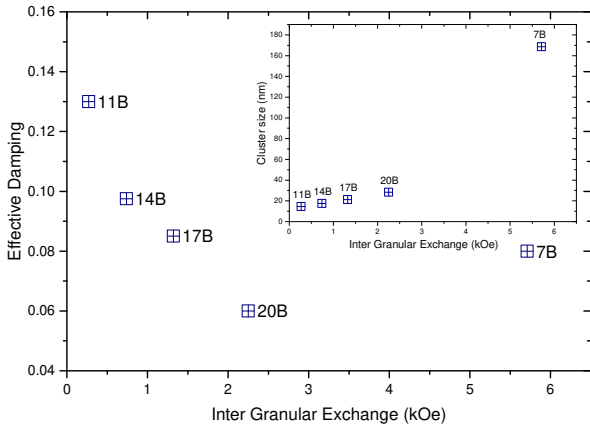


Figure 3. (Color online) Dependence of the measured Gilbert damping constant on the exchange field. A non-monotonic dependence of  $\alpha$  on  $H_{ex}$  is clear. (Inset) Variation of the cluster size with exchange field determined using the method given in Ref. 13 and described in the text.

The results are given in the inset of Fig. 3. Importantly, it is found that for the sample with the highest exchange coupling there is a large increase in the correlation length. This is consistent with the form of the hysteresis loop shown in Fig. 1, where the sample exhibits a very square loop consistent with magnetization by nucleation and propagation of quasi-domains.

### III. NUMERICAL MODEL

To corroborate the effects of increasing intergranular exchange we have constructed a dynamic numerical model of granular media using the Landau-Lifshitz-Bloch (LLB) equation<sup>16</sup> combined with a voronoi construction of the grains typical for magnetic media. The interactions between the grains are calculated based on the interaction distances and lengths between the grains and included into the LLB model, both of which we describe in the following.

#### A. Landau-Lifshitz-Bloch Model

The LLB equation of motion describes the time evolution of a magnetic macrospin. The equation allows for longitudinal relaxation of the magnetization, and was derived by Garanin<sup>16</sup> within a Mean Field approximation from the classical Fokker-Planck equation for atomic spins interacting with a heat bath. Models based on the resulting expressions have been shown to be

consistent with atomistic spin dynamics simulations<sup>17</sup>, as well as comparisons with experimental observations, for example, in laser induced demagnetization<sup>18</sup> and domain wall mobility measurements in Yttrium Iron Garnet crystals close to the Curie point<sup>19</sup> ( $T_c$ ). The equation is similar to the Landau-Lifshitz-Gilbert (LLG) equation<sup>20</sup>, with precessional and relaxation terms, but with an extra term that deals with changes in the magnitude of the magnetization:

$$\begin{aligned} \dot{\mathbf{m}}_i = & -\gamma[\mathbf{m}_i \times \mathbf{H}_i^{\text{eff}}] + \frac{\gamma\alpha_{\parallel}}{m_i^2} (\mathbf{m}_i \cdot \mathbf{H}_i^{\text{eff}}) \mathbf{m}_i \\ & - \frac{\gamma\alpha_{\perp}}{m_i^2} [\mathbf{m}_i \times [\mathbf{m}_i \times \mathbf{H}_i^{\text{eff}}]], \end{aligned} \quad (1)$$

where  $\mathbf{m}_i$  is a spin polarisation. The spin polarisation tends towards equilibrium,  $m_e$ , which is a temperature dependent input parameter (discussed below).  $\alpha_{\parallel}$  and  $\alpha_{\perp}$  are dimensionless longitudinal and transverse damping parameters.  $\gamma$  is the gyromagnetic ratio taken to be the free electron value. The LLB equation is valid for finite temperatures and even above  $T_c$ , though the damping parameters and effective fields are different below and above  $T_c$ . For the transverse damping parameter:

$$\alpha_{\perp} = \begin{cases} \lambda \left(1 - \frac{T}{3T_c}\right) & T < T_c \\ \lambda \frac{2T}{3T_c} & T \geq T_c \end{cases} \quad (2)$$

and for the longitudinal:

$$\alpha_{\parallel} = \lambda \frac{2T}{3T_c} \quad \text{for all } T. \quad (3)$$

For a single particle the effective field  $\mathbf{H}_i^{\text{eff}} = -\frac{1}{M_s^0} \frac{\delta f}{\delta \mathbf{m}_i}$  with free energy density  $f$ ,

$$\begin{aligned} f_i = & -M_s(0)\mathbf{B} \cdot \mathbf{m}_i + \frac{M_s(0)}{2\tilde{\chi}_{\perp}} (m_{i,x}^2 + m_{i,y}^2) \\ & + \frac{M_s(0)}{8\tilde{\chi}_{i,\parallel} m_{i,e}^2} (m_i^2 - m_{i,e}^2)^2 \\ & - M_s(0)^2 \sum_{j,i \neq j} V_i V_j \frac{3(\mathbf{m}_i \cdot \mathbf{e}_{ij})(\mathbf{m}_j \cdot \mathbf{e}_{ij}) - \mathbf{m}_i \cdot \mathbf{m}_j}{r_{ij}^3}, \end{aligned} \quad (4)$$

is given by<sup>16</sup>

$$\mathbf{H}_i^{\text{eff}} = \mathbf{B} + \mathbf{H}_{A,i} + \frac{1}{2\tilde{\chi}_{i,\parallel}} \left( 1 - \frac{m_i^2}{m_{i,e}^2} \right) \mathbf{m}_i + \mathbf{H}_{e,i} + \mathbf{H}_{\text{dip},i} \quad (5)$$

where  $\mathbf{B}$  represents an external magnetic field,  $\mathbf{H}_{\text{dip},i}$  is the dipolar field and  $\mathbf{H}_{A,i} = -(m_i^x \mathbf{e}_i^x + m_i^y \mathbf{e}_i^y) / \tilde{\chi}_\perp$  an anisotropy field.  $M_s(0)$  is the saturation magnetisation (magnetisation at 0K),  $V_i$  represents the volume of grain  $i$ . Here, the susceptibilities  $\tilde{\chi}_l$  are defined by  $\tilde{\chi}_l = \partial m_l / \partial H_l$ .  $\mathbf{H}_e$  is the (intergranular) exchange field, which we assume is based on the contact area between the grains, arising from the Voronoi construction, as discussed below. In these equations,  $\lambda$  is a microscopic parameter which characterizes the coupling of the individual, atomistic spins with the heat bath (the intrinsic damping). We choose the value of  $\lambda$  to be 0.05 for this work. It is worth pointing out that we expect the results and conclusions presented here to be qualitatively the same for all values of the damping. The calculation of the dipolar field is truncated at 8 grain diameters to reduce the  $N^2$  calculation over all pairwise interactions. The long-ranged contribution is then treated within a mean-field approximation.

For application of the LLB equation one has to know the spontaneous equilibrium magnetisation  $m_e(T)$ , the perpendicular ( $\tilde{\chi}_\perp(T)$ ) and parallel ( $\tilde{\chi}_\parallel(T)$ ) susceptibilities beforehand. In this work, the input functions are based on that of Ref. 17 for FePt and scaled to give the correct Curie temperature. For the transverse susceptibility (that determines the anisotropy) the function is scaled to give an anisotropy constant of  $13.5 \times 10^6 \text{ erg/cc}$ . The functions are scaled in the same manner as that of Ref. 21:

$$M_s(T) = \frac{M_s(0)}{M_s^{\text{FePt}}(0)} M_s^{\text{FePt}} \left( \frac{T_C^{\text{FePt}}}{T_C} T \right), \quad (6)$$

$$\chi_\parallel(T) = \frac{M_s(0)}{M_s^{\text{FePt}}(0)} \chi_\parallel^{\text{FePt}} \left( \frac{T_C^{\text{FePt}}}{T_C} T \right), \quad (7)$$

$$\chi_\perp(T) = \frac{M_s(0)}{2K(0)} \chi_\perp^{\text{FePt}} \left( \frac{T_C^{\text{FePt}}}{T_C} T \right). \quad (8)$$

## B. Granular Model

The model of the magnetic nanostructures is based on a Voronoi construction which creates structures and grain size dispersions similar to those produced in magnetic hard disk drives (see Fig. 5). The seed points for the Voronoi algorithm are based on a 2D hexagonal structure with the points moved by a random value, linearly, to generate structural disorder. This results in a log-normal distribution of grain volumes,  $V_i$ , as seen experimentally.

The average grain diameter in our numerical simulations is 8nm with a thickness of 8nm. The standard deviation in the grain diameter is 2.63nm. In the present work we assume no dispersion in the anisotropy easy axes of the grains and we numerically simulate a system approximately  $700\text{nm} \times 700\text{nm}$  laterally, corresponding to 7558 grains. Furthermore, we do not assume a spatial variation of the anisotropy strength per grain, though the voronoi construction gives a volume distribution giving rise to a variation of energy barrier,  $KV$ . This means that to first order the extrinsic contributions, from anisotropy, to the damping are zero to first order<sup>2</sup>.

The IGE is formulated on the basis of the contact area between grains as was implemented in Ref. 22. Considering neighbouring grains  $k$  and  $l$ . The exchange energy between them can be written

$$E_{\text{exch}}^{kl} = -N_{kl} J_{kl} \hat{\mathbf{s}}_k \cdot \hat{\mathbf{s}}_l, \quad (9)$$

where  $N_{kl}$  is the number of atoms in the contact area between ( $k, l$ ). Assuming a film of uniform thickness  $t$ ,  $N_{kl} = L_{kl} t / a^2$ , where  $L_{kl}$  is the contact length between the grains and  $a$  is the lattice constant. The exchange field on grain  $k$  due to  $l$  is therefore

$$\mathbf{H}_e^{kl} = -\frac{\partial E_{\text{exch}}^{kl}}{\partial \boldsymbol{\mu}_k} = \frac{L_{kl} J_{kl}}{a^2 M_s A_k} \hat{\mathbf{s}}_l. \quad (10)$$

$A_k$  is the area of the face of grain  $k$  in the plane of thin film and  $L_{kl}$  is the contact length between grains  $k$  and  $l$ . In addition, we allow for some dispersion in the  $J_{kl}$  by generating a normal distribution with a given width. We now write Eq. 10 in terms of reduced parameters (relative to the median values  $L_m, A_m, J_m$ )

$$\mathbf{H}_e^{kl} = H_{\text{exch}} \left( \frac{J_{kl}}{J_m} \right) \left( \frac{L_{kl}}{L_m} \right) \left( \frac{A_m}{A_k} \right) \hat{\mathbf{s}}_l, \quad (11)$$

where  $H_{\text{exch}} = J_m L_m / (a^2 M_s A_m)$ . In practice  $H_{\text{exch}}$  is set by the requirement that the average exchange at saturation has a certain value  $H_{\text{exch}}^{\text{sat}}$ , which is the more accessible value experimentally, that is

$$H_{\text{exch}}^{\text{sat}} = N^{-1} H_{\text{exch}} \sum_k \sum_{l \in n.n.} \left( \frac{J_{kl}}{J_m} \right) \left( \frac{L_{kl}}{L_m} \right) \left( \frac{A_m}{A_k} \right). \quad (12)$$

We have verified that the model gives consistent static results by initially simulating hysteresis loops for a range of intergranular exchange. Qualitatively Fig. 4 shows increasingly square loops with increasing intergranular exchange.

There are some expected quantitative differences between the experimental and numerically determined loops that primarily arise from the fact that the Landau-Lifshitz-Bloch equation is integrated numerically as a function of time, however, the total simulation time is orders of magnitude lower than those measured experimentally.

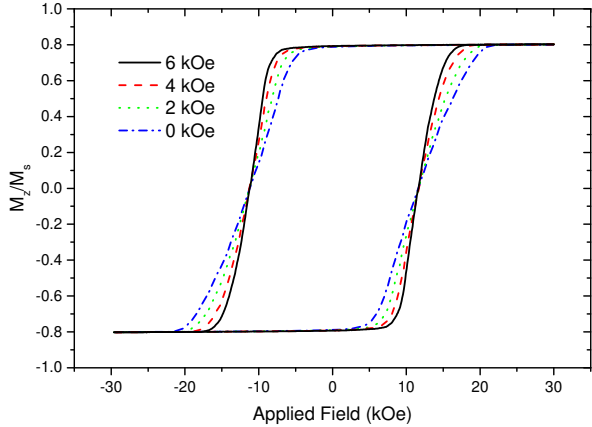


Figure 4. (Color online) Numerically calculated hysteresis curves for a range of intergranular exchange constants in good qualitative agreement with the experimental hysteresis loops (Fig. 1).

Furthermore, the numerical simulations do not take into account the detailed variations in the experimental structure, saturation magnetization, anisotropy or grain size variations. Not taking these specific aspects into account allows us to use the numerical model to interpret the experimental results without these extra degrees of freedom.

During the simulations of optically induced FMR we apply a magnetic field in the  $x$ - $z$  plane at an angle  $\theta$  which we take to be at  $45^\circ$  from the  $z$  axis of magnitude 10kOe. The anisotropy is assumed to be uniaxial and points out of the plane of the sample. The large angle at which we apply the field gives rise to large amplitude precession giving excellent fits to the magnetisation (discussed below). Even in the presence of the field at  $45^\circ$ , the large anisotropy ensures that the magnetisation lies strongly out-of-plane. In our optical FMR approach we assume a square pulse in temperature rising from ambient to 600K for 400ps, returning to ambient after the pulse. In a real optical FMR experiment on the picosecond timescale the laser generates a hot electron distribution that can reach temperatures of thousands of Kelvin<sup>23</sup>. Subsequently, the hot electrons reach a quasi-equilibrium state with the phonons at the same temperature. Depending on the relaxation time of the magnetic system the spin system will reach equilibrium with this quasi-equilibrium at around 0.1-1 picoseconds<sup>24</sup>, though this can be considerably longer for pure rare earth metals<sup>25</sup>. For metallic ferromagnets, the changes in the magnetisation occur on a much faster timescale than the resulting precession (see inset of Fig. 6, thus we probe the dynamics at the temperature after the pulse. Experimentally the long cooling-time to the initial temperature occurs by transfer of energy out of the

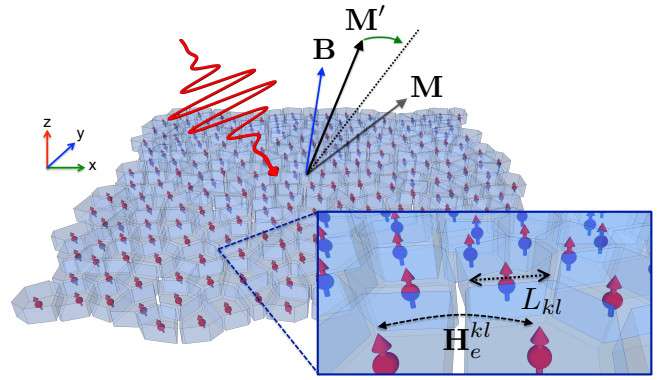


Figure 5. (Color online) Schematic of the set-up of the simulations. The anisotropy is perpendicular to the plane with the applied field at an angle  $\theta$  to the plane. The magnetization equilibrates to  $\mathbf{M}$  before the laser pulse is applied. The laser pulse results in relaxation of the magnetization by precession to the new orientation,  $\mathbf{M}'$ .

magnetic material to the substrate and the surroundings via phonon processes on the nanosecond time-scale.

Using the LLB model, we have investigated the effects of varying the saturation magnetisation and IGE on the damping of our granular material after excitation with a heat pulse. As discussed above, the change in temperature alters the equilibrium position, which causes the magnetization to precess back the initial state. An example of the resulting dynamics within the LLB model is shown in Fig. 6 (points). On the picosecond timescale the magnetization is quickly reduced, in agreement with experimental<sup>26-28</sup> and numerical results<sup>28-30</sup> so that the quenching and recovery of the anisotropy field is much faster than the timescale of the precessional dynamics.

Using the numerical model we first calculate the damping as a function of the saturation magnetization, as presented in Fig. 7, for a range of values of the IGE. The values for the damping are calculated as with the experimental data.

Figure 7 shows a strong variation and a subtle combination of contributions from magnetostatic and exchange interactions. Consider first the case  $H_{\text{exch}}^{\text{sat}} = 0$ . From Fig. 7 it can be seen that there is a very strong dependence of effective damping on  $M_s$ , specifically an increase of around a factor of 2.5 for  $M_s$  values around those of Co and Fe. For low values of  $M_s$  the damping for all values of IGE converge to the value of the input damping due to the very low contribution from the demagnetizing fields.

The variation of damping with IGE, determined numerically, is shown in Fig. 8 and is consistent with the experimentally observed decrease (Fig. 3) in damping with increasing intergranular exchange. For low values of the saturation magnetization the value of the damping shows very little variation and remains close to the value

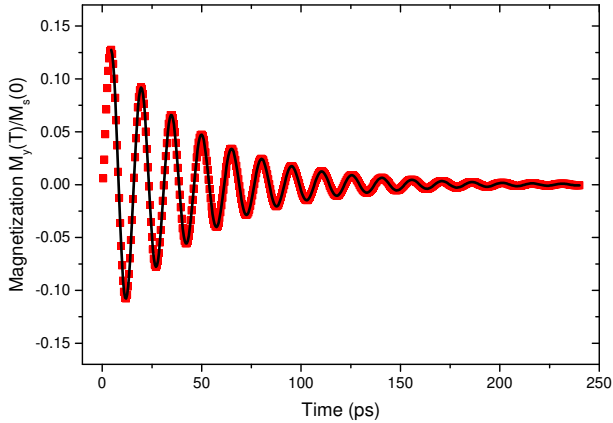


Figure 6. (Color online) Example of the transverse magnetization dynamics after a heat pulse (points) with a fit to the dynamics (lines).

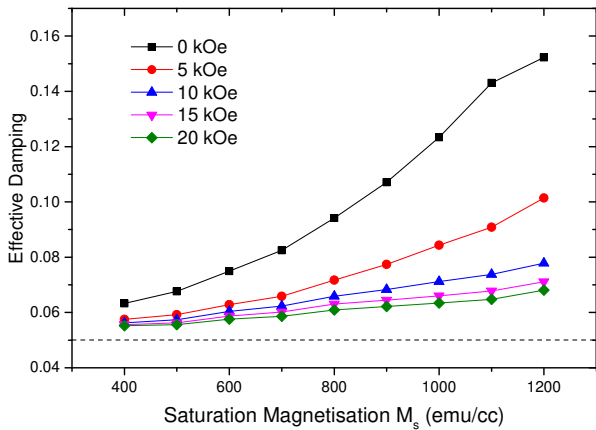


Figure 7. (Color online) Damping as a function of saturation magnetization for a range of values of the intergranular exchange,  $H_{\text{exch}}^{\text{sat}}$ .

for the intrinsic damping used for the calculations. For larger values of  $M_s$  there is a much larger variation with IGE where there is a strong interplay between the demagnetizing energy and the IGE.

Overall, the numerical simulations are consistent with the experimental data for small exchange fields, where the effective damping is seen to decrease with  $H_{\text{ex}}$ . However, the model does not reproduce the increase in damping for the sample with the largest exchange (see Fig. 3). This is likely related to the dramatic increase in the measured cluster size for this particular sample as shown in the inset of Fig. 3. For this sample, the oxide concentration was reduced to zero, and it is

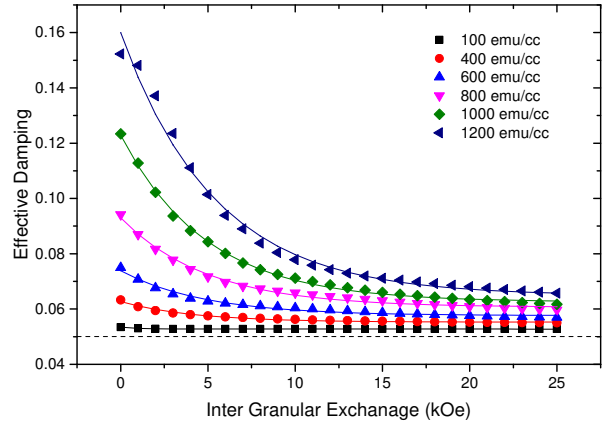


Figure 8. (Color online) Damping as a function of intergranular exchange for a range of values of saturation magnetization. For low values of  $M_s$  the value of the damping varies very little and remains around the value of the input damping parameter. As  $M_s$  increases, the variation with intergranular exchange becomes much greater as the interplay between the demagnetizing fields and exchange becomes important.

possible that the determined exchange field is an underestimate. The large cluster size and the form of the hysteresis loop for this sample is indicative of a change to a nucleation/propagation mechanism which is not observed in the model calculations for values of  $H_{\text{ex}}$  up to 5kOe. For a very strongly exchange coupled sample it is likely that additional damping mechanisms will arise from interaction of the domain walls with defects and impurities resulting in the increase in Gilbert damping at large exchange fields.

#### IV. SEMI-ANALYTICAL SPINWAVE MODEL

So far we have presented numerical and experimental results that show good agreement on the effects of interactions on the damping in granular media, however, the underlying mechanism remains somewhat ambiguous. In the following we ascribe the reduction in damping due to increasing intergranular exchange as arising from a reduction in the degeneracy of finite  $k$ -vectors with the frequency of the  $k=0$  (ferromagnetic resonance) mode (see schematic inset of Fig. 9). In general, the presence of defects, inhomogeneities, boundaries, etc. can act as scattering centres leading to the energy transfer from the uniform magnetization precession into degenerate spinwave modes. A reduction in this degeneracy reduces the number of possible spinwave modes that can be scattered to or from. The process involves the annihilation of a zero-wavenumber

magnon and the creation of a nonzero-wavenumber magnon. The consequence of this process is that the magnetization precession undergoes rapid relaxation (damping)<sup>31</sup>. Reducing this degeneracy will then result in a reduced damping. We conclude that the reduction of two-magnon scattering processes is dominating the reduction in damping due to increased intergranular exchange. To elucidate this we follow the method of McMichael<sup>2,3,32</sup>.

In the present work we only briefly outline the method of determining the frequencies of the spinwave modes. In Refs. 2, 3, and 32 the Landau-Lifshitz-Gilbert equation is linearised. The resulting linearised components of the magnetization and fields are written in Fourier space through:

$$b(\mathbf{r}) = \int \frac{d\mathbf{k}}{(2\pi)^2} b(\mathbf{k}) \exp(i\mathbf{k} \cdot \mathbf{r}) \quad (13)$$

where  $b$  represents the magnetization or the fields. The effective field has contributions from the Zeeman, demagnetising, anisotropy and exchange terms and is written in terms of a sum over the magnetization multiplied with a kernel,  $G$  and is translationally invariant. Due to the  $\mathbf{r} - \mathbf{r}'$  term, on-site terms would be represented by delta functions multiplied by a scalar. The Fourier components of the field are then written:

$$\mathbf{H}_{eff}(\mathbf{r}) = \int d\mathbf{r}' G(\mathbf{r} - \mathbf{r}') \mathbf{m}(\mathbf{r}'). \quad (14)$$

where  $h_{\mathbf{k}}$  are the elements of the normalized stiffness tensor:

$$h_{\theta\theta,\mathbf{k}} = M_s^{0-1} [H_i + Dk^2 + M_s^0(1 - N_k) \sin^2(\theta_k)] \quad (15a)$$

$$h_{\phi\phi,\mathbf{k}} = M_s^{0-1} [H_i + Dk^2 + M_s^0 N_k \cos^2(\phi) + M_s^0(1 - N_k) \sin^2(\phi) \cos^2(\theta_k)] \quad (15b)$$

$$h_{\theta\phi,\mathbf{k}} = M_s^{0-1} [M_s^0(1 - N_k) \cos(\theta_k) \times \sin(\theta_k) \sin(\phi)] \quad (15c)$$

$$h_{\phi\theta,\mathbf{k}} = h_{\theta\phi,\mathbf{k}} \quad (15d)$$

where  $Dk^2 = (2A/\mu_0 M_s)k^2$  is the exchange field for a spinwave with wavevector  $\mathbf{k}$ , assuming that the wavelengths of interest are much larger than the lattice spacing.  $A$  is the exchange stiffness and  $H_i = B \cos(\phi - \phi_H) - (M_s^0 - H_k) \sin^2(\phi)$  is the ‘‘internal field’’ consisting of the component of; the applied field  $B$  (at an angle  $\phi_H$  to the plane) parallel to the magnetization, which is at an angle,  $\phi$ , to the plane; the static part of the demagnetization field; and the anisotropy field  $H_k$ . The  $k$ -dependent demagnetization factor for a film of thickness  $d$  is given by:

$$N_k = \frac{1 - e^{-kd}}{kd} \quad (16)$$

The susceptibility tensor,  $\chi_{\mathbf{k}}(\omega)$ , can be obtained from the linearised LLG equations of motion. For an applied field with spatial frequency  $\mathbf{k}$  and angular frequency  $\omega$ , the transverse susceptibility tensor is given by:

$$\chi_{\mathbf{k}}(\omega) = \frac{1}{Z_{\mathbf{k}}} \begin{bmatrix} h_{\phi\phi,\mathbf{k}} + \frac{i\alpha\omega}{\omega_M} & -h_{\theta\phi,\mathbf{k}} + \frac{i\alpha\omega}{\omega_M} \\ -h_{\phi\theta,\mathbf{k}} - \frac{i\alpha\omega}{\omega_M} & h_{\theta\theta,\mathbf{k}} + \frac{i\alpha\omega}{\omega_M} \end{bmatrix} \quad (17a)$$

$$Z_{\mathbf{k}} = h_{\theta\theta,\mathbf{k}} h_{\phi\phi,\mathbf{k}} - h_{\theta\phi,\mathbf{k}} h_{\phi\theta,\mathbf{k}} - (1 + \alpha^2) \left( \frac{\omega}{\omega_M} \right)^2 + i\alpha \left( \frac{\omega}{\omega_M} \right) (h_{\theta\theta,\mathbf{k}} + h_{\phi\phi,\mathbf{k}}), \quad (17b)$$

where  $\omega_M = \gamma M_s^0$ . The dispersion relation is obtained by noting that  $|Z_{\mathbf{k}}|$  is minimum and the susceptibility is in resonance when

$$\omega = \omega_{\mathbf{k}} = \frac{\omega_M}{\sqrt{1 + \alpha^2}} [h_{\theta\theta,\mathbf{k}} h_{\phi\phi,\mathbf{k}} - h_{\theta\phi,\mathbf{k}} h_{\phi\theta,\mathbf{k}}]^{1/2}. \quad (18)$$

To make a consistent comparison between the LLB numerical model and the spinwave model we use the values of  $M_s$ , anisotropy, thickness ( $d$ ), applied field and applied field angle that are the same in both cases. Furthermore, the angles of the magnetization ( $\phi$ ) from the film plane are taken directly from the numerical simulations at equilibrium after the pulse (from the end of the numerical simulation). Using the physical parameters that enter into the LLB model we have calculated the spinwave properties of the numerically simulated samples using equations 15, 16, 17 and 18 and determined the degeneracy of those modes with the  $k=0$  mode. This plays an important role in the damping arising from inhomogeneities<sup>2</sup> due to non-uniformities that are present in granular media. We note that the value of the exchange stiffness that enters into the equations is in the correct range<sup>4</sup> for granular media but it is not trivial to relate the intergranular exchange field in the LLB with the long-wavelength exchange,  $A$  used in the spinwave model. We note here that the presented form of the semi-analytical spinwave model does not take into account inhomogeneous line broadening effects, thus contains contributions only from inhomogeneities which arise in the LLB model from the distribution of the grain volumes. The results of the semi-analytical spinwave model are shown in Fig. 9 and show a decreasing trend with increasing exchange stiffness.

We can conclude that the two-magnon scattering process is the leading term in our reduction in damping with intergranular exchange and is strongly affected by the interactions due to intergranular exchange and the demagnetising fields. This is supported by the fact that the LLB model does not include any specific detail about the grain boundaries or dispersions in the anisotropy axes or on-site magnitudes, though does take into account different demagnetising fields, size distribution etc., so there is inevitably a distribution in the cone-angle of the macrospins. Therefore, scattering with impurities cannot occur. The role of grain-to-grain



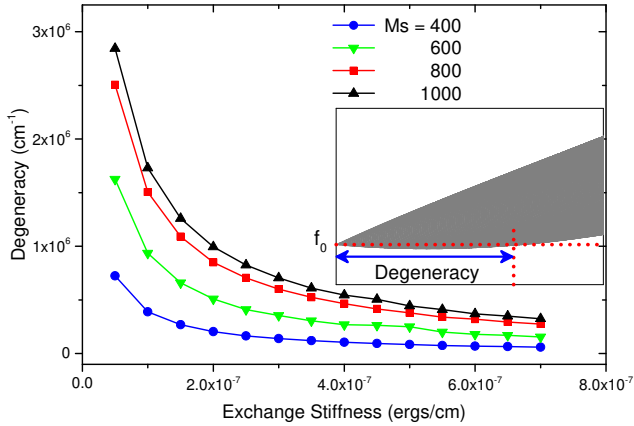


Figure 9. (Color online) Spinwave degeneracy as a function of exchange stiffness for a range of values of saturation magnetisation. There is clearly a direct correlation between the degeneracy and the damping shown in Fig. 3 and a similar trend for fixed exchange stiffness and varying  $M_s$ .

scattering due to slight dispersions in the anisotropy axes is zero in our LLB model as we assume perfectly aligned anisotropy axes. Similarly, we assume that our grains are uniform single macrospins and therefore grain-boundary scattering cannot contribute to this two-magnon scattering process. In terms of a macrospin picture, the decreased damping can be explained by a stiffening of the system resulting in a more coherent precession so that demagnetizing effects become less important and the system as a whole acts more like a single macrospin.

## V. CONCLUSION

In summary we have carried out an investigation of the effects of intergranular interactions on the effective damping constant of perpendicular media. Experiments show a non-monotonic variation of the damping with

increasing exchange strength. Contributions to the experimental damping constant due to inhomogeneous line broadening cannot be ruled out, however, these are expected to be consistent between samples; the major effect of reducing the thickness of the grain boundaries is the variation in the exchange coupling as shown in the hysteresis behavior. We have constructed a realistic model of granular media using the Landau-Lifshitz-Bloch model. By simulating the optical FMR technique to probe relaxation processes we have determined how the damping is affected by the key parameters governing the interactions (exchange and saturation magnetisation). The model calculations show a decrease of effective damping with increasing exchange, consistent with the experimental data for small exchange. It is argued that the increase in damping for the largest exchange field, arising in a film without exchange coupling, is due to the onset of a different reversal mechanisms involving domain nucleation and propagation. For practical perpendicular recording media, which are more exchanged decoupled, the decrease in damping with exchange strength predicted by the model calculations is the most likely scenario. Further investigations of the phenomenon using spin wave theory provide further insight and ascribe the reduction in damping due to increasing intergranular exchange as arising from a reduction in the degeneracy of finite  $k$ -vectors with the frequency of the  $k=0$  (ferromagnetic resonance) mode. These calculations show a direct correlation between the degeneracy and the damping shown by the numerical model with a similar trend for fixed exchange stiffness and varying  $M_s$ . Our numerical calculations do not include extrinsic contributions to damping due to variations in on-site quantities, such as anisotropy or saturation magnetisation, thus we have shown that it is possible to describe the decrease in damping with intergranular exchange based on the effects of intergranular exchange and demagnetising fields, thus we conclude that their contribution is large.

This work was supported by the European Commission under contract No. 281043, *Femtospin*. The financial support of the Advanced Storage Technology Consortium is gratefully acknowledged. T. A. Ostler gratefully acknowledges the Marie Curie incoming BeIPD-COFUND fellowship program at the University of Liège.

<sup>1</sup> V. Sokalski, D. E. Laughlin, and J.-G. Zhu, *Applied Physics Letters* **95**, 102507 (2009).

<sup>2</sup> R. D. McMichael, *Journal of Applied Physics* **95**, 7001 (2004).

<sup>3</sup> R. McMichael and P. Krivosik, *IEEE Transactions on Magnetics* **40**, 2 (2004).

<sup>4</sup> P. Krone, M. Albrecht, and T. Schrefl, *Journal of Magnetism and Magnetic Materials* **323**, 432 (2011).

<sup>5</sup> A. Butera, *The European Physical Journal B* **52**, 297 (2006).

<sup>6</sup> N. Mo, J. Hohlfeld, M. ul Islam, C. S. Brown, E. Girt, P. Krivosik, W. Tong, A. Rebei, and C. E. Patton, *Applied Physics Letters* **92**, 022506 (2008).

<sup>7</sup> T. W. Clinton, N. Benatmane, J. Hohlfeld, and E. Girt, *Journal of Applied Physics* **103**, 075546 (2008).

<sup>8</sup> S. Kalarickal, N. Mo, P. Krivosik, and C. Patton, *Physical Review B* **79**, 094427 (2009).

<sup>9</sup> A. Mekonnen, M. Cormier, A. V. Kimel, A. Kirilyuk, A. Hrabec, L. Ranno, and T. Rasing, *Physical Review Letters* **107**, 117202 (2011).

- <sup>10</sup> X. Zou, J. Wu, P. K. J. Wong, Y. B. Xu, R. Zhang, Y. Zhai, C. Bunce, and R. W. Chantrell, *Journal of Applied Physics* **109**, 07D341 (2011).
- <sup>11</sup> J. Becker, O. Mosendz, D. Weller, A. Kirilyuk, J. C. Maan, P. C. M. Christianen, T. Rasing, and A. Kimel, *Applied Physics Letters* **104**, 152412 (2014).
- <sup>12</sup> T. A. Ostler, M. O. A. Ellis, D. Hinzke, and U. Nowak, *Physical Review B* **90**, 094402 (2014), arXiv:1407.1174.
- <sup>13</sup> H. Nemoto, I. Takekuma, H. Nakagawa, T. Ichihara, A. R., and H. Y., *J Magn. Magn. Mater.* **320**, 3144 (2008).
- <sup>14</sup> C. R. Pike, A. P. Roberts, and K. L. Verosub, *J. Appl. Phys.* **85** (1999).
- <sup>15</sup> M. van Kampen, C. Jozsa, J. T. Kohlhepp, P. LeClair, L. Lagae, W. J. M. de Jonge, and B. Koopmans, *Physical Review Letters* **88**, 227201 (2002).
- <sup>16</sup> D. A. Garanin, *Physical Review B* **55**, 3050 (1997).
- <sup>17</sup> N. Kazantseva, D. Hinzke, U. Nowak, R. Chantrell, U. Atxitia, and O. Chubykalo-Fesenko, *Physical Review B* **77**, 184428 (2008).
- <sup>18</sup> J. Mendil, P. Nieves, O. Chubykalo-Fesenko, J. Walowski, T. Santos, S. Pisana, and M. Münzenberg, *Scientific reports* **4**, 3980 (2014), arXiv:1306.3112.
- <sup>19</sup> J. Kötzler, D. Garanin, M. Hartl, and L. Jahn, *Physical Review Letters* **71**, 177 (1993).
- <sup>20</sup> T. Gilbert, *IEEE Transactions on Magnetics* **40**, 3443 (2004).
- <sup>21</sup> K. M. Lebecki and U. Nowak, *Journal of Applied Physics* **113**, 023906 (2013).
- <sup>22</sup> Y. Peng, X. W. Wu, J. Pressesky, G. P. Ju, W. Scholz, and R. W. Chantrell, *Journal of Applied Physics* **109**, 123907 (2011).
- <sup>23</sup> J. Chen, D. Tzou, and J. Beraun, *International Journal of Heat and Mass Transfer* **49**, 307 (2006).
- <sup>24</sup> I. Radu, C. Stamm, A. Eschenlohr, F. Radu, R. Abrudan, K. Vahaplar, T. Kachel, N. Pontius, R. Mitzner, K. Holldack, A. Föhlich, T. A. Ostler, J. Mentink, R. Evans, R. W. Chantrell, A. Tsukamoto, A. Itoh, A. Kirilyuk, A. Kimel, and T. Rasing, *SPIN* **5**, 1550004 (2015).
- <sup>25</sup> B. Koopmans, G. Malinowski, F. Dalla Longa, D. Steiauf, M. Fähnle, T. Roth, M. Cinchetti, and M. Aeschlimann, *Nature materials* **9**, 259 (2010).
- <sup>26</sup> E. Beaurepaire, J.-C. Merle, A. Daunois, and J.-Y. Bigot, *Physical Review Letters* **76**, 4250 (1996).
- <sup>27</sup> I. Radu, K. Vahaplar, C. Stamm, T. Kachel, N. Pontius, H. A. Dürr, T. A. Ostler, J. Barker, R. F. L. Evans, R. W. Chantrell, A. Tsukamoto, A. Itoh, A. Kirilyuk, T. Rasing, A. V. Kimel, and H. a. Dürr, *Nature* **472**, 205 (2011).
- <sup>28</sup> K. Vahaplar, A. Kalashnikova, A. V. Kimel, D. Hinzke, U. Nowak, R. Chantrell, A. Tsukamoto, A. Itoh, A. Kirilyuk, and T. Rasing, *Physical Review Letters* **103**, 117201 (2009).
- <sup>29</sup> T. A. Ostler, J. Barker, R. F. L. Evans, R. W. Chantrell, U. Atxitia, O. Chubykalo-Fesenko, S. El Moussaoui, L. Le Guyader, E. Mengotti, L. J. Heyderman, F. Nolting, A. Tsukamoto, A. Itoh, D. Afanasiev, B. A. Ivanov, A. M. Kalashnikova, K. Vahaplar, J. Mentink, A. Kirilyuk, T. Rasing, and A. V. Kimel, *Nature communications* **3**, 666 (2012).
- <sup>30</sup> U. Atxitia, J. Barker, R. W. Chantrell, and O. Chubykalo-Fesenko, *Physical Review B - Condensed Matter and Materials Physics* **89**, 224421 (2014), arXiv:arXiv:1308.0993v1.
- <sup>31</sup> L. Lu, Z. Wang, G. Mead, C. Kaiser, Q. Leng, and M. Wu, *Applied Physics Letters* **105**, 012405 (2014).
- <sup>32</sup> R. D. McMichael, D. J. Twisselmann, and A. Kunz, *Physical Review Letters* **90**, 227601 (2003).