

This is a repository copy of *Augmentation of the insufficient tissue bed for surgical repair of hypospadias using acellular matrix grafts:A proof of concept study*.

White Rose Research Online URL for this paper:

<https://eprints.whiterose.ac.uk/171247/>

Version: Accepted Version

Article:

Morgante, Debora, Radford, Anna, Abbas, Syed K. et al. (3 more authors) (2021) Augmentation of the insufficient tissue bed for surgical repair of hypospadias using acellular matrix grafts:A proof of concept study. *Journal of Tissue Engineering*. ISSN 2041-7314

<https://doi.org/10.1177/2041731421998840>

Reuse

Items deposited in White Rose Research Online are protected by copyright, with all rights reserved unless indicated otherwise. They may be downloaded and/or printed for private study, or other acts as permitted by national copyright laws. The publisher or other rights holders may allow further reproduction and re-use of the full text version. This is indicated by the licence information on the White Rose Research Online record for the item.

Takedown

If you consider content in White Rose Research Online to be in breach of UK law, please notify us by emailing eprints@whiterose.ac.uk including the URL of the record and the reason for the withdrawal request.

Augmentation of the Insufficient Tissue Bed for Surgical Repair of Hypospadias using Acellular Matrix Grafts: A Proof of Concept study.

Journal:	<i>Journal of Tissue Engineering</i>
Manuscript ID	JTE-Nov-20-0161.R2
Manuscript Type:	Original Article
Date Submitted by the Author:	n/a
Complete List of Authors:	Morgante, Debora; University of York, Jack Birch Unit, Department of Biology & York Biomedical Research Institute ; Hull York Medical School; Leeds Teaching Hospitals NHS Trust, Paediatric Urology Radford, Anna; University of York, Jack Birch Unit, Department of Biology & York Biomedical Research Institute ; Hull York Medical School; Leeds Teaching Hospitals NHS Trust, Paediatric Urology Abbas, Syad; Leeds Teaching Hospitals NHS Trust Ingham, Eileen; University of Leeds, IMBE Subramaniam, Ramnath; Leeds Teaching Hospitals NHS Trust, Paediatric Urology Southgate, Jennifer; University of York, Jack Birch Unit, Department of Biology & York Biomedical Research Institute
Keywords:	Acellular Matrix, Biomaterial, Surgery, Hypospadias repair, Tissue integration
Abstract:	<p>Acellular matrices produced by tissue decellularisation are reported to have tissue integrative properties. We examined the potential for incorporating acellular matrix grafts during procedures where there is an inadequate natural tissue bed to support an enduring surgical repair. Hypospadias is a common congenital defect requiring surgery, but associated with long-term complications due to deficiencies in the quality and quantity of the host tissue bed at the repair site.</p> <p>Biomaterials were implanted as single on-lay grafts in a peri-urethral position in male pigs. Two acellular tissue matrices were compared: full-thickness porcine acellular bladder matrix (PABM) and commercially-sourced cross-linked acellular matrix from porcine dermis (Permacol™). Anatomical and immunohistological outcomes were assessed 3 months post-surgery.</p> <p>There were no complications and surgical sites underwent full cosmetic repair. PABM grafts were fully incorporated, whilst Permacol™ grafts remained palpable. Immunohistochemical analysis indicated a non-inflammatory, remodelling-type response to both biomaterials. PABM implants showed extensive stromal cell infiltration and neovascularisation, with a significantly higher density of cells ($p < 0.001$) than Permacol™, which showed poor cellularisation and partial encapsulation.</p> <p>This study supports the anti-inflammatory and tissue-integrative nature of non-crosslinked acellular matrices and provides proof-of-principle for incorporating acellular matrices during surgical procedures, such as in primary complex hypospadias repair.</p>

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60



1
2
3
4
5 **Augmentation of the Insufficient Tissue Bed for Surgical Repair of**
6
7
8 **Hypospadias using Acellular Matrix Grafts: A Proof of Concept Study.**
9

10
11
12 **Debora Morgante MD^{1,2,3,\$,%}, Anna Radford PhD^{1,2,3,\$,%}, Syed K. Abbas DVM⁴,**
13
14 **Eileen Ingham PhD⁵, Ramnath Subramaniam FRCS, PhD^{3*}, Jennifer Southgate**
15
16
17 **PhD^{1*}**
18
19

20
21 ¹Jack Birch Unit of Molecular Carcinogenesis, Department of Biology and York
22
23 Biomedical Research Institute, University of York, Heslington, York YO10 5DD, UK
24

25
26 ²Hull York Medical School, John Hughlings Jackson Building, University Rd,
27
28 Heslington, York YO10 5DD, UK
29

30
31 ³Paediatric Urology, Leeds Teaching Hospitals NHS Trust, Leeds General Infirmary,
32
33 Leeds LS1 3EX, UK
34

35
36
37 ⁴Central Biomedical Services, University of Leeds, Leeds LS2 9JT, UK
38

39
40 ⁵School of Biomedical Sciences, Institute of Medical & Biological Engineering,
41
42 University of Leeds, Leeds LS2 9JT, UK
43
44

45
46 [%]Current address: Hull University Teaching Hospitals NHS Trust, Hull Royal
47
48 Infirmary, Kingston upon Hull HU3 2JZ, UK
49

50
51 ^{*, \$} equal contributions
52

53
54 **Corresponding Author:**
55

56
57 Professor Jennifer Southgate, Jack Birch Unit, Department of Biology, Heslington,
58
59 York YO10 5DD, UK. Tel: +44 (0)1904 328705. e-mail: j.southgate@york.ac.uk
60

Abstract

Acellular matrices produced by tissue decellularisation are reported to have tissue integrative properties. We examined the potential for incorporating acellular matrix grafts during procedures where there is an inadequate natural tissue bed to support an enduring surgical repair. Hypospadias is a common congenital defect requiring surgery, but associated with long-term complications due to deficiencies in the quality and quantity of the host tissue bed at the repair site.

Biomaterials were implanted as single on-lay grafts in a peri-urethral position in male pigs. Two acellular tissue matrices were compared: full-thickness porcine acellular bladder matrix (PABM) and commercially-sourced cross-linked acellular matrix from porcine dermis (Permacol™). Anatomical and immunohistological outcomes were assessed 3 months post-surgery.

There were no complications and surgical sites underwent full cosmetic repair. PABM grafts were fully incorporated, whilst Permacol™ grafts remained palpable. Immunohistochemical analysis indicated a non-inflammatory, remodelling-type response to both biomaterials. PABM implants showed extensive stromal cell infiltration and neovascularisation, with a significantly higher density of cells ($p < 0.001$) than Permacol™, which showed poor cellularisation and partial encapsulation.

This study supports the anti-inflammatory and tissue-integrative nature of non-crosslinked acellular matrices and provides proof-of-principle for incorporating acellular matrices during surgical procedures, such as in primary complex hypospadias repair.

Introduction

Decellularised tissue matrices offer a promising natural biomaterial in surgical situations where there is either an inherent lack of a tissue bed for repair, or where the healthy tissue bed is compromised by trauma or fibrotic scarring. One such need is encountered in surgical repair for hypospadias. With reported frequencies of 0.3 to 7.0 per 1000 live births, hypospadias is one of the most common genitourinary birth defects, requiring revision in as many as 1 in 300 boys (reviewed ^{1, 2}). Hypospadias is associated with the development of a foreshortened urethra resulting in an aberrantly-positioned external orifice (meatus) on the ventral aspect of the penis. Surgical repair is the mainstay treatment for the majority of infants with hypospadias, but can require multiple procedures and is frequently associated with unsatisfactory results and complications, including the formation of urethral fistulas, stenosis and dehiscence or rupture of the repair. The underlying pathophysiology of many complications is the inherent lack of healthy host vascularised tissue, with tension on these inadequate tissues resulting in poor healing and dehiscence of the wound ³. Retrospective reviews of patient outcome following two-stage repair for severe hypospadias have reported complication rates from 58 to 68% ^{2, 4, 5}. Fistulas and strictures are particularly difficult to manage due to a lack, or poor quality of tissue at the site of repair.

Post-operative complications increase with the severity of the anomaly ⁶ and patients with severe hypospadias often require extra tissue to repair the urethra (reviewed ¹). Autologous free tissue grafts have been used clinically for urethral reconstruction, including skin from genital and extra-genital regions ^{7, 8}, with buccal mucosa the most commonly used ⁹⁻¹¹. Problems most commonly associated with the use of

1
2
3 autologous free tissue grafts include graft size, donor site morbidity and graft
4
5 contracture ¹². Preclinical studies aimed at improving hypospadias repair outcomes
6
7 by applying novel biomaterials and tissue-engineering techniques have met limited
8
9 success (reviewed ²). Such approaches have included the use of biomaterials of
10
11 synthetic or natural derivation, either unseeded or cell-seeded in both flat and
12
13 tubularised configurations in rabbits, dogs or rats (80 preclinical studies reviewed in
14
15 ¹³). A range of acellular biological scaffolds derived from allogeneic and xenogeneic
16
17 sources using different decellularisation processes have been used in these pre-
18
19 clinical studies including porcine small intestinal submucosa (SIS, Surgisis®),
20
21 Alloderm®, decellularised bladder submucosa and decellularised urethra ¹³. Due to
22
23 a lack of controlled preclinical studies, however, the efficacy of these approaches
24
25 has been difficult to determine. Although pre-clinical studies in animals have tended
26
27 to suggest better results and reduced complications when acellular matrices are
28
29 combined with cells, such findings have not been confirmed in the limited number of
30
31 clinical studies (reviewed ¹³). However, a major confounder is the tendency to test
32
33 novel approaches clinically only after standard surgical procedures have failed.
34
35
36
37
38
39
40 The ideal biomaterial to enhance urethral tissue repair would provide a suitable
41
42 template to replicate the biological and biomechanical functional properties of the
43
44 host tissue by allowing progressive ingrowth of periurethral tissue components,
45
46 without inducing an adverse host response that would lead to fibrosis and
47
48 contracture. The size of the defect and the extent to which endogenous cells can
49
50 infiltrate and organise within a graft material have been reported as key limitations.
51
52 In male rabbits, a 0.5 cm tubularised decellularised matrix of porcine bladder
53
54 submucosa was reported to be the maximum length able to support normal tissue
55
56 formation ¹⁴. However, it is important to highlight that different decellularisation
57
58
59
60

1
2
3 methods are utilised by different research groups and different protocols can have
4
5 varying effects on the extent of cell and DNA removal, composition of the
6
7 extracellular matrix and biomechanical attributes of the resultant biological scaffold
8
9 matrix resulting in variations in the potential for constructive tissue remodelling ^{15, 16}.
10
11 We have developed propriety decellularisation processes using low concentration
12
13 sodium dodecyl sulphate (0.1% (w/v) SDS) and proteinase inhibitors for the
14
15 production of a range of porcine and human tissue specific biological scaffolds
16
17 including cardiac valves ^{17, 18}, dermis ¹⁹, arteries ²⁰ and musculoskeletal tissues ^{21, 22}.
18
19 Importantly, these processes preserve the biomechanical and biological tissue
20
21 properties. Preclinical ²³ and clinical ²⁴⁻²⁷ studies have clearly demonstrated the
22
23 utility of this approach. We have adapted this process for full thickness porcine
24
25 bladder to create an acellular porcine bladder biomaterial (PABM) particularly aimed
26
27 at urological applications ²⁸. Using an ex vivo model in which human urinary tract
28
29 tissue was combined with PABM in organ culture, we have previously associated
30
31 host M2-polarised CD163+ tissue macrophages with the pioneering events of cellular
32
33 infiltration and integration at the tissue:decellularised biomaterial interface ²⁹.
34
35 It is reported that Permacol™ (aka Pelvicol™), a commercial cross-linked collagen
36
37 acellular matrix derived from porcine dermis and licenced for surgical use, may
38
39 reduce the complications of primary complex hypospadias repair when used as a
40
41 peri-urethral graft ³. In the off-label study, it was suggested that the graft supported
42
43 the urethroplasty as a splint, but there was no scope for the histological outcome to
44
45 be assessed. Our previous in vitro studies have indicated that unlike PABM ²⁹,
46
47 Permacol™ lacks cell integrative properties ³⁰. In order to help inform future clinical
48
49 development, the aim of this study was to evaluate gross and histological outcomes
50
51 of incorporating PABM or Permacol™ as peri-urethral grafts in an experimental large
52
53
54
55
56
57
58
59
60

1
2
3 animal model. The male juvenile pig was chosen as the animal species because of
4 the anatomical size and physiological similarity to male children. The cellular
5 response to the implanted scaffolds at three months was studied using CD163 (M2
6 macrophages) with progenitor markers of haematopoietic (CD34), leucocyte (CD45)
7 and myofibroblast (SMA) lineages to assess the cell-integrative properties of non-
8 cross-linked and cross-linked natural biomaterial matrices.
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

For Peer Review

Materials & Methods

Biomaterials

For PABM production, pig bladders were collected from a local abattoir (Traves & Son Ltd, Escrick) on ice in Transport Medium consisting of Hank's balanced salt solution (Gibco) containing 10 mM HEPES pH 7.6 (Gibco) and 20 kallikrein inhibiting units/ml aprotinin (Trasylol®, Nordic Pharma)³¹. PABM, a full-thickness porcine acellular bladder matrix, was produced aseptically using the decellularisation procedure described by²⁸, including a terminal disinfection stage with peracetic acid. PABM was batch-tested by histology and Hoechst 33258 staining of sections from multiple samples to confirm the absence of cells or double-stranded DNA. Contact cytotoxicity tests conducted in vitro as described²⁸ confirmed both sterility and absence of toxic by-products.

Permacol™ was purchased from Medtronic (Watford, UK).

Animal husbandry, analgesia and anaesthesia

Large White Landrace Hybrid male pigs 14 weeks old of approximately 15 - 20 kg weight were ear-tagged for identification and housed in pairs with unlimited access to water. Assessment of the animals was performed at least twice daily and animals were weighed every two weeks.

All experimental procedures were approved by the local Animal Welfare and Ethical Review Body and were conducted at the University of Leeds animal surgical facility under a project licence granted by the UK Home Office, in accordance with the Animal Scientific Procedures Act 1986. Details to fulfil the essential and

1
2
3 recommended ARRIVE 2.0 guidelines for reporting animal studies is available as
4
5 Supplementary Information.
6
7

8 Food was withheld 16 hours prior to surgery. Initial sedation was performed using
9
10 intramuscular Midazolam 0.32mg/kg (Hypnovel Roche, UK) and Azeperone 2.25
11
12 mg/kg (Stresnil Elanco Animla Health). An over-the-needle cannula (18g Venflon)
13
14 was inserted and secured in an ear vein. In some animals, where combination of
15
16 Midazolam and Azeperoine did not produce enough sedation to allow intravenous
17
18 catheterisation, 2.5% isoflurane in oxygen was delivered via a snout mask for no
19
20 more than 1 minute attached to an anaesthetic machine. This deepened the state of
21
22 sedation enough to allow intravenous catheterisation of an ear vein. Following
23
24 intravenous catheterisation, general anaesthesia was induced by intravenous
25
26 injection of Propofol 4.0 mg/kg or to effect (Propofol Plus, Zoetis UK Limited). A 7-8
27
28 mm ID endo-tracheal tube (Sims Portex Limited) was introduced and anaesthesia
29
30 maintained using Isoflurane (2.0 – 3.0% in oxygen).
31
32
33
34
35

36 An eye lubricant was applied and the skin was prepared for aseptic surgery using
37
38 5% Chlorhexidine (Vetasept, Animalcare Limited). A long acting antibiotic injection,
39
40 Amoxicillin 15mg/kg body weight (Ampoxyphen LA 150mg/ml Suspension for
41
42 Injection, MSD Animal Ltd.) and a non-steroidal anti-inflammatory drug, Carprofen
43
44 4mg/kg body weight (Rimadyl small animal solution for injection, Zoeist UK Ltd.)
45
46 were given subcutaneously as separate injections before the start of the surgery.
47
48

49 During the surgical procedure, 0.9% NaCl (Vitevax 1 9mg/ml, Dechra Veterinary
50
51 Products) was infused via the ear vein cannula at a rate of 40 ml/kg body weight.
52
53
54

55 At the end of the surgical procedure, 3 ml of local anaesthetic (0.5 % Marcaine,
56
57 AstraZeneca UK) was infiltrated locally and an opioid analgesic Buprenorphine 20
58
59 µg/kg body weight (Vetergesic 0.3 mg/ml solution for injection, CEVA Animal Health
60

1
2
3 Ltd) was administered as intramuscular injection to provide postoperative pain relief.
4
5 Further post-operative analgesia was dependent on animal behaviour and was
6
7 provided either by Buprenorphine or Carprofen alone.
8
9

10 Humane euthanasia involved sedation with Midazolam and Azeperone as described
11
12 above followed by an overdose of barbiturate (phentobarbital sodium 200mg/ml
13
14 solution; Euthatal, Merial Animal Health Ltd).
15
16
17
18
19

20 21 *Implantation of PABM and Permacol™ as on-lay urethral free graft*

22
23 Surgery was performed on 12 pigs (mean weight 16.59 kg \pm 1.25 SD), with six
24
25 animals receiving implants of PABM and six of Permacol™. The study was designed
26
27 so that procedures were carried out on half the animals (three PABM and three
28
29 Permacol™) followed by a five month gap in order to enable the first series to be
30
31 analysed and inform the second series.
32
33

34
35 Under anaesthesia and complete aseptic conditions, a 5 cm midline incision was
36
37 made caudally, approximately 5 cm from the preputial sac. The peri-urethral plane
38
39 was opened and a 3.0 by 1.5 cm² graft of PABM or Permacol™ was positioned and
40
41 secured with eight to ten dissolvable Vicryl™ (polyglactin 910; Ethicon) sutures,
42
43 consistent with the surgical procedure reported in children³². Two non-dissolvable
44
45 polypropylene (Prolene™, Ethicon) sutures were placed at either end of the graft in
46
47 the opened superficial fascia in order to mark the implant site. The rest of the
48
49 superficial fascia was closed using Vicryl™ interrupted sutures. Skin closure was
50
51 achieved using absorbable suture in a continuous closure. Two further Prolene™
52
53 sutures were placed as external markers of the closure to enable location of the
54
55 implant site after three months.
56
57
58
59
60

1
2
3 Euthanasia was performed three months post-operatively as planned and, following
4 external inspection, implants with surrounding tissues were removed for analysis.
5
6 Guided by the marker sutures, incisions were made and the graft and surrounding
7
8 tissues removed en bloc, extending from the subcutaneous fat to the deep aspect of
9
10 the penile shaft. During tissue collection from the first cohort of pigs, free movement
11
12 of the penile shaft within the sheath of surrounding fascia and peri-urethral tissues
13
14 made it difficult to register the orientation of the graft in relation to the penile
15
16 structures for histology. To overcome this during tissue collection from the second
17
18 set of pigs, the penile shaft and surrounding tissues were clamped before cutting
19
20 through these structures beyond the site of the clamps. Clamps were replaced by
21
22 sutures once the tissue was removed from the animal and prior to fixation.
23
24
25
26
27
28
29
30

31 *Histology & Immunohistochemistry evaluation: qualitative and quantitative analysis*

32
33 Harvested tissues were divided in two to enable separate fixation in 10% (v/v)
34 formalin in phosphate buffered saline and in zinc salts. Equivalent samples of non-
35
36 implanted PABM and Permacol™ were processed in parallel. Following fixation,
37
38 tissues were processed routinely into paraffin wax and 5 µm sections were collected
39
40 onto slides. Standard haematoxylin and eosin staining was performed to evaluate
41
42 the position and histological appearance of grafts and peri-urethral tissues. Staining
43
44 with DNA intercalating Hoechst 33258 (0.1 µg/ml) was performed to assess tissue
45
46 and graft cellularity.
47
48
49
50

51
52 Immunohistochemistry was performed, in some cases on serial sections, to identify
53
54 the nature of the cell populations surrounding or infiltrating the implants. For this
55
56 purpose, antibodies were selected against CD34 (haematopoietic progenitor
57
58 marker), CD45 (leucocyte/macrophage lineage marker), CD163
59
60

1
2
3 (monocytes/macrophages of an M2 tissue-remodelling phenotype), MAC387
4
5 (recently infiltrated macrophages) and anti-smooth muscle actin (SMA expressed by
6
7 myofibroblasts and smooth muscle cells of vascular structures). Antibodies were
8
9 selected on the basis of immunoreactivity against paraffin wax-embedded porcine
10
11 tissues as listed in Table 1. All antibodies were titrated for use, with appropriate
12
13 positive and negative (irrelevant and no primary antibody) controls included in all
14
15 series. All antibody labelling was performed on zinc-fixed tissues without antigen
16
17 retrieval, except in the case of anti-CD34, where formalin-fixed paraffin wax-
18
19 embedded sections were used.
20
21
22
23

24 For zinc-fixed tissue sections, blocking of all free avidin/biotin sites (kit from Vector
25
26 Laboratories) and secondary antibody binding sites (10 % (v/v) rabbit serum; Dako)
27
28 was performed before incubation overnight at 4⁰C with primary antibody. The
29
30 secondary antibody, biotinylated rabbit anti-mouse immunoglobulin (Dako) was pre-
31
32 incubated with 10 % (v/v) swine serum (Dako) to eliminate cross-reactivity with
33
34 porcine tissue. Bound antibody was detected using the Vectastain® ABC kit (Vector
35
36 Laboratories), with 3,3'-diaminobenzidine (DAB; SigmaFAST™
37
38 3,3'-diaminobenzidine tablets) as chromogen.
39
40
41
42

43 For formalin-fixed sections, endogenous peroxidase was blocked with 3 % (v/v)
44
45 hydrogen peroxide, then antigen retrieval was performed by microwave boiling in 1
46
47 mM ethylenediamine tetra-acetic acid (pH 8.0) for 10 minutes. Secondary antibody
48
49 binding sites were blocked with 2.5 % (v/v) horse serum (Dako) before incubation
50
51 overnight at 4⁰C with primary (anti-CD34) antibody. Bound primary antibody was
52
53 detected using an Amplifier™ antibody, followed by ImmPRESS™ Excel amplified
54
55 horseradish peroxidase (HRP) polymer reagent and ImmPACT™ DAB EqV
56
57
58
59
60

1
2
3 substrate as the chromogen (ImmPRESS™ Excel Amplified HRP Polymer Staining
4
5 Kit; Vector Laboratories).

6
7
8 Following labelling, all sections were counterstained in Mayer's haematoxylin,
9
10 dehydrated and mounted in 1,3-diethyl-8-phenylxanthine (DPX; Sigma-Aldrich).

11
12
13 Immunohistology was analysed to characterise and quantify the extent and type of
14
15 cellularisation and tissue integration versus host reaction to the two implanted
16
17 biomaterials (PABM and Permacol™). The analysis focused on the extent of cellular
18
19 integration (cell type and density), presence and extent of any encapsulation
20
21 process, and the number and distribution of immunolabelled cells. For analysis,
22
23 labelled slides were scanned on a Zeiss Axioscan Microscope and the resulting CZI
24
25 image files were subjected to supervised semi-automated analysis using
26
27 StrataQuest software (version 6.0.0.123) on the TissueGnostic image analysis
28
29 platform (Vienna, Austria). The auto-detection function was used to set the colour
30
31 intensity of the master marker (nuclear haematoxylin) and DAB label to identify the
32
33 different cell type-associated markers. Five non-overlapping 0.1 x 0.1 mm² regions
34
35 of interest (ROIs) were defined within each implanted biomaterial (PABM and
36
37 Permacol™) and nuclei were detected automatically within the five equal-sized
38
39 ROIs. Following optimisation, the same conditions were applied to all image files.
40
41
42
43
44
45 Raw data were imported into GraphPad Prism for statistical evaluation.
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Results

Survival and health of surgical recipients

The procedure is illustrated schematically in Figure 1 (A-D). Surgery proceeded according to plan with biomaterials positioned as onlay urethral grafts (Figure 1 E-G). All pigs survived the immediate and long-term post-operative period with no complications; voiding was normal and there were no episodes of urinary retention, urinary tract or wound infections. Upon termination at three months, the body weight of the animals ranged from 55-62 kg (mean 56.12 kg). Gross anatomy, as examined at the time of dissection and harvesting of tissue around the graft, was similar to control animals, with no substantial scarring, fibrosis or encapsulation. Macroscopically PABM grafts appeared fully integrated and could only be identified from the positioning of the non-absorbable marker sutures (Figure 1H), whilst Permacol™ grafts remained readily apparent (Figure 1I).

Extent and patterns of cellularisation

Following dissection and histological evaluation, the biomaterial implants were identified in all 12 animals, as illustrated in Figure 2A-B. Samples of non-grafted PABM or Permacol™ processed in parallel for haematoxylin and eosin (H&E) stain and immunohistochemistry revealed multidirectional collagen bundles and an absence of cells that provided a morphological reference for identifying the implanted grafts.

Histologically, there was no widespread inflammation associated with any graft and there was no detection of any MAC387⁺ cells, which would have been indicative of recently infiltrated macrophages. In one Permacol™ graft, a small localised reaction

1
2
3 of giant cells within a thin capsule was found coincident with the Prolene™ marker
4 suture and provided an internal control for the potential for foreign body reaction. In
5 addition, occasional foci of lymphocytes were observed at the edges of Permacol™
6 samples which, based on location, frequency and distribution, related to the position
7 of the Vicryl™ absorbable sutures used to attach the grafts.
8
9

10
11 Varying extents of cellularisation were apparent within the implant sections analysed
12 from the 12 grafts. Implanted PABM grafts revealed cells present uniformly
13 throughout the implant (Figure 2C). There was evidence of vascularisation at the
14 periphery and within the graft. This was highlighted by α SMA immunolabelling, which
15 was detected on vascular elements as well as by a majority of cells within the PABM
16 grafts (Figure 2E). In the case of PABM implants, there were no lymphocytic
17 aggregates found and no evidence of any encapsulation-like reaction around the
18 periphery of the implant (Figure 2F). An absence of cellularisation was typical of
19 Permacol™ grafts, where cells accumulated at the edge of the implant and showed
20 very limited, sparse infiltration (Figure 2D). Where present, cells showed a tendency
21 to infiltrate along natural pathways within the Permacol™ grafts, sparsely infiltrating
22 between collagen bundles (H&E shown in Figure 2D). Evidence of a partial
23 encapsulation-like reaction, where cells accumulated at the interface between the
24 Permacol™ graft and host tissue, was apparent in some regions). This partial
25 encapsulation reaction exclusive to the Permacol™ implants was particularly evident
26 when sections were immunolabelled with antibodies to α SMA (Figure 2F). As
27 measured from scans of all six Permacol implants, the capsule involved between 6%
28 and 44% (min-max range) of the perimeter of the visualised implanted biomaterial
29 (mean \pm SD: 19.5% \pm 12.59, n=6). The average thickness of the identified capsule
30 was 216 μ m \pm 96 (mean \pm SD, n=6; min – max range: 20 – 500 μ m).
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

The nature and abundance of infiltrating cell populations

An objective quantitative analysis of immunohistochemically-labelled tissue sections was carried out. Total cell counts confirmed significantly higher cell densities in PABM than in Permacol™ implanted grafts (Figure 3). The cell count per ROI is shown for each animal to illustrate the extent of variation between animals and across the grafts (Figure 3A). The density of infiltrating cells expressed as the mean total number of cells per mm² ± SEM was 5309 ± 78 for PABM versus 906 ± 32 for Permacol™ (n=6 animals per group; Figure 3B). This difference was statistically significant ($p < 0.0001$, determined using Welch's t-test).

To determine if, separate from the total cell count, there were shifts in the relative proportions of the different major cell types infiltrating PABM and Permacol™, the percentages of cells expressing CD34, CD45, CD163 and αSMA was examined. Whereas percentages of cells expressing αSMA, CD45 and CD163 were assessed in serial sections, the antibody to CD34 required a different tissue fixation to be immunoreactive and hence was counted in equivalent but non-related areas. The relative quantification revealed 40% CD34: 20% CD163: 40% αSMA positive cells in PABM, compared to 40% CD34: 20% CD163: 40% CD45 positive cells in Permacol™. In other words, although both biomaterials were infiltrated by cells expressing CD34+ and/or CD163+ cells in a similar ratio, the remaining 40% of the infiltrating population showed a significant switch from predominantly CD45+ in Permacol™ to αSMA+ in PABM (Figure 4).

Discussion

The aim of hypospadias repair is to provide a good cosmetic and functional outcome, resulting in a penis devoid of ventral curvature and the patient being able to pass urine from the tip of the penis with a good stream. Our study investigated the concept that an acellular matrix graft inserted into a peri-urethral position would become tissue-integrated, augmenting a deficient tissue bed on the ventral aspect and reducing the potential for surgical complications. By being positioned peri-urethrally, our approach differs in surgical approach from other studies where acellular matrices, either alone or seeded with cells, have been used as inlay grafts in urethral reconstruction in both animal and human studies (reviewed ¹³).

In this present study aimed at acquiring proof-of-concept evidence towards clinical translation, we have demonstrated that implanting decellularised acellular tissue matrices into the peri-urethral stroma in a large animal surgical model is well-tolerated and does not provoke an inflammatory response. We compared two porcine matrices that varied in their different surgical handling characteristics from highly compliant (PABM) to stiff (Permacol™). The handling differences are supported by mechanical evidence, as the Young's modulus for Permacol™, reported to be 50-100 MPa ³³, is considerably higher than the 2-3 MPa we found for native porcine bladder ³⁴, albeit that some stiffening occurs following decellularisation ²⁸. Nevertheless, how different tissue derivations and/or processing affects biomaterial properties and influences implantation outcomes is an incomplete science. Bladder and dermal matrices both contain collagens type I and III, but whereas type III collagen is associated in the bladder with healthy compliance ³⁵, in the dermis it is associated with rigidity and scarring ³⁶, reflecting negative

1
2
3 implications for (dermal) scaffold design ³⁷. This highlights the need for further basic
4 studies to inform intelligent design, alongside empirical, translation-focused studies
5 of the type reported here.
6
7
8
9

10 Externally, both porcine-derived biomaterials used gave acceptable results.

11
12 Nevertheless, there were important biological differences in the host response to the
13 two materials. Implants of PABM had become fully incorporated within the three-
14 month period to leave no macroscopic residue. Histologically, the marked PABM
15 graft region was extensively vascularised and completely infiltrated by cells. This
16 agrees with independent reports of non-cross-linked matrices in terms of superior
17 host tissue integration and cellular infiltration accompanied by neovascularisation ³⁸,
18 ³⁹. By contrast, Permacol™ implants persisted macroscopically and the bulk material
19 remained acellular at three months. Permacol™ is terminally-sterilised by gamma
20 radiation and chemically cross-linked by hexamethylene diisocyanate ⁴⁰, the latter
21 producing stable urea groups by the interaction of amine groups with isocyanate ⁴¹.
22 Cross-linking is known to limit scaffold degradation ⁵ and to inhibit host cells from
23 infiltrating matrix grafts, including Permacol™ . Although we might predict acellular
24 matrix properties to reflect tissue-specific differences, it seems axiomatic that
25 observed differences in results between Permacol™ and PABM were dominated by
26 the influence of cross-linking. Supporting this point, we have shown previously that
27 cells fail to infiltrate PABM cross-linked by gamma-radiation ²⁹.
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49

50 Cells expressing α SMA+ were present both as vascular smooth muscle cells in
51 association with blood vessels and as spindle-shaped myofibroblasts. The
52 myofibroblasts were present either within the PABM or in the case of Permacol™, at
53 the neo-vascularised interface of the biomaterial and native host tissue where they
54 formed an incomplete capsule-like structure. An encapsulation response to
55
56
57
58
59
60

1
2
3 Permacol™ has been described in some studies ^{38, 42}, albeit with exceptions ⁴³. The
4
5 myofibroblast is recognised as an essential effector of both healthy tissue
6
7 regeneration through matrix remodelling and pathological fibrosis, although how this
8
9 balance is regulated is not fully understood (reviewed ^{44, 45}). Our observations
10
11 suggest that the physical cross-linking of the matrix might define whether recruited
12
13 myofibroblasts formed a boundary at the edge of the implant or infiltrated the matrix.
14
15
16 Given the difference in extent of cellular infiltration into Permacol™ and PABM, we
17
18 were interested in whether there was any relative shift in infiltrating cell types.
19
20 Historically, any evaluation of cellularisation in implanted biomaterials has been
21
22 performed using qualitative or semi-quantitative approaches. In the field of histology
23
24 and immunohistochemistry, it is well known that different observers see and report
25
26 the same tissue sample differently ⁴⁶⁻⁴⁸. To overcome this limitation, we performed
27
28 an objective quantitative analysis of immunohistochemically-labelled biomaterials
29
30 three months post-implantation. Although restricted by the limited availability of
31
32 reliable porcine-reactive antibodies, we were nevertheless able to examine the major
33
34 infiltrating cell lineages as identified by expression of CD34 (to identify progenitor
35
36 cells of multiple lineages, particularly haematopoietic (reviewed ⁴⁹); CD45 (as a pan-
37
38 leucocyte marker); CD163 (macrophages of M2 phenotype) and α SMA (vascular and
39
40 other smooth muscle cells, including myofibroblasts). These different markers
41
42 revealed that after 3 months, both implanted biomaterials contained a similar
43
44 proportion of CD34+ and CD163+ cells, making up about 60% of the total cellular
45
46 infiltrate. The presence of CD163-expressing cells further indicated that both
47
48 acellular collagen matrices promoted a remodelling, regenerative (M2), rather than
49
50 inflammatory (M1) macrophage response, as observed previously with PABM in
51
52 human ex vivo studies ²⁹. The remainder 40% infiltrating population was different
53
54
55
56
57
58
59
60

1
2
3 between matrices, being constituted by spindle-shaped α SMA+ cells in PABM
4
5 versus diffuse lymphoid CD45+ cells in Permacol™. This reveals key differences in
6
7 recellularisation biology and outcome between the two matrices, discussed below.
8
9
10 Irrespective of matrix tissue derivation (bladder or dermal) or cross-linked status,
11
12 neither acellular matrix tested provoked an acute reactive or rejection response upon
13
14 implantation. Nevertheless, the presence of a diffuse infiltrating CD45+ population in
15
16 Permacol™ was indicative of a low level, chronic inflammatory state, as was
17
18 reinforced by the presence of enhanced acute local reactions at permanent and
19
20 resorbable suture sites. Thus, although implanted acellular matrices were not
21
22 themselves inflammatory and promoted an M2-type macrophage phenotype, the
23
24 PABM was the more benign material, possibly as a result of being non-cross-linked.
25
26 The absence of innate immune-activating signals in PABM fits with our previous
27
28 observations using a novel ex vivo human tissue:PABM interface model, where early
29
30 (<10 day) “pioneering” cellular events involved recruitment of tissue-resident
31
32 macrophages and polarisation to an M2 CD163+ remodelling phenotype²⁹. The
33
34 ability of PABM as a non-cross-linked allogeneic material to promote a fully
35
36 integrative response perforce rests on the quality of matrix production, including
37
38 absence of innate immune-inducing “danger” signals such as DNA. This clearly
39
40 needs stringent quality-control during batch production if the material is to be taken
41
42 forward for clinical use. This also raises the question of sterilisation, as most terminal
43
44 sterilisation methods involve cross-linking, such as by gamma-radiation, which our
45
46 previous results indicate may impact negatively on tissue integrative properties²⁹.
47
48
49 The availability of PABM and Permacol™ as biomaterials with contrasting properties
50
51 of host integration/remodelling versus persistence may suit different surgical
52
53 applications. The process of chemical cross-linking results in a product that remains
54
55
56
57
58
59
60

1
2
3 rigid but flexible and resistant to degradative processes and therefore maintains
4 strength and 3D structure. This resilience of Permacol™ was exploited by Springer
5 and Subramaniam to support urethral repair where Permacol™ was incorporated as
6 a peri-urethral splint in 12 boys undergoing urethrocutaneous fistula repair (10) or
7 redo urethroplasty (2) ³². Apart from one instance of late wound infection, no
8 recurrence of fistula or stricture was noticed in the cohort at a median follow up of
9 2.5 years. The results supported the principle of managing complications from
10 hypospadias surgery by incorporating a suitable biomaterial into the surgical
11 procedure when local tissues are insufficient or inadequate. The clinical nature of the
12 study meant that outcomes were observational only, with no possibility of obtaining
13 follow-up histological evidence of the extent or nature of any tissue integration. Our
14 present study highlights the importance of studying histological outcomes in a
15 clinically-relevant in vivo model, as the eventual fate of the cross-linked implant
16 material in the clinical study ³² is unknown. On a related point, our study
17 demonstrates that even in the case of natural non-cross-linked tissue matrices, the
18 complete remodelling and integration events take place over a longer timescale than
19 the three months typically reported for in vivo models.

20
21 In addition to its superior integration, other benefits of PABM are its compliance,
22 malleability and ability to hold sutures. In accordance with the recognised ideal
23 characteristics of a biomaterial for urethral use (reviewed ⁵⁰), PABM provided a
24 functional strong and supple scaffold when placed in the peri-urethral plane in a
25 simple porcine urethroplasty model. From its characteristics, it is predicted that in
26 primary hypospadias repair, where insufficient native tissue is available, PABM may
27 fulfil an unmet surgical and clinical need as a scaffold for augmentation of the native
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 tissue in order to prevent subsequent complications, such as urethral fistulae and
4
5 strictures.
6
7

8 In conclusion, this study provides proof of principle evidence that implanted acellular
9
10 matrices become readily incorporated, meaning they may be useful to augment an
11
12 inadequate tissue bed to support primary surgical repair. In the particular case of
13
14 hypospadias, the successful incorporation of an onlay graft of acellular matrix during
15
16 the primary surgery may improve the quality of repair, leading to reduced
17
18 complications. It is clear that natural acellular tissue matrices offer promising new
19
20 biomaterials to support reconstructive and regenerative surgery, but that many of
21
22 their advanced physical and biological properties are negatively affected by cross-
23
24 linking as a result of conventional chemical- or radiation-induced terminal sterilisation
25
26 procedures. If natural acellular matrices are to meet their full clinical potential it is
27
28 important to evaluate the safety/efficacy outcomes from both ex vivo ²⁹ and in vivo
29
30 studies and use these to define new criteria for the regulated production of such
31
32 materials for clinical use.
33
34
35
36
37
38
39
40

41 **Acknowledgments**

42
43 We thank Dr Karen Hogg (Bioscience Technology Facility, Department of Biology,
44
45 University of York) for assistance with TissueGnostics analysis, Dr Amy Glover
46
47 (Research Technician) for histology and immunohistochemistry support and Maria
48
49 Caballero (Erasmus overseas student) for her help with histology analysis.
50
51

52
53 The research work described here was funded through the Medical Technologies
54
55 Innovation and Knowledge Centre (phase 2 - Regenerative Devices), funded by the
56
57 EPSRC under grant number EP/N00941X/1 as Proof of Concept awards: PoC023
58
59 and PoC045 and partially by Grow MedTech's Proof of Feasibility programme
60

1
2
3 supported by UKRI Research England's Connecting Capability Fund [project code:
4 CCF11-7795]. AR was supported by the European Society of Paediatric Urology.
5
6 AR and DM were registered as PhD students with the Hull York Medical School. JS
7
8 is supported by a programme grant from York Against Cancer. The work leading to
9
10 the development of PABM was originally funded by the Biotechnology and Biological
11
12 Sciences Research Council (BBSRC) on grants E20352 and BB/E527220/1.
13
14
15
16
17
18
19

20 **Data Availability.**

21
22 The raw/processed data required to reproduce the findings is available on request.
23
24
25
26
27
28

29 **Declaration of Conflicting Interests**

30
31
32 Eileen Ingham is a shareholder and consultant to Tissue Regenix Group PLC. The
33
34 authors confirm that there are no other known conflicts of interest associated with
35
36 this publication and there has been no significant financial support for this work that
37
38 could have influenced its outcome.
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

References

1. Abbas TO, Mahdi E, Hasan A, et al. Current Status of Tissue Engineering in the Management of Severe Hypospadias. *Front Pediatr* 2017; 5: 283. 2018/02/07. DOI: 10.3389/fped.2017.00283.
2. Faure A, Bouty A, Nyo YL, et al. Two-stage graft urethroplasty for proximal and complicated hypospadias in children: A retrospective study. *J Pediatr Urol* 2016; 12: 286 e281-286 e287. 2016/03/30. DOI: 10.1016/j.jpuro.2016.02.014.
3. Springer A and Subramaniam R. Preliminary experience with the use of acellular collagen matrix in redo surgery for urethrocutaneous fistula. *Urology* 2012; 80: 1156-1160. 2012/09/22. DOI: 10.1016/j.urology.2012.06.058.
4. McNamara ER, Schaeffer AJ, Logvinenko T, et al. Management of Proximal Hypospadias with 2-Stage Repair: 20-Year Experience. *J Urol* 2015; 194: 1080-1085. 2015/05/13. DOI: 10.1016/j.juro.2015.04.105.
5. Stanasel I, Le HK, Bilgutay A, et al. Complications following Staged Hypospadias Repair Using Transposed Preputial Skin Flaps. *J Urol* 2015; 194: 512-516. 2015/02/24. DOI: 10.1016/j.juro.2015.02.044.
6. Long CJ, Chu DI, Tenney RW, et al. Intermediate-Term Followup of Proximal Hypospadias Repair Reveals High Complication Rate. *J Urol* 2017; 197: 852-858. 2016/11/15. DOI: 10.1016/j.juro.2016.11.054.
7. Altarac S, Papes D and Bracka A. Two-stage hypospadias repair with inner preputial layer Wolfe graft (Aivar Bracka repair). *BJU Int* 2012; 110: 460-473. 2012/07/11. DOI: 10.1111/j.1464-410X.2012.11304.x.
8. Schwentner C, Seibold J, Colleselli D, et al. Single-stage dorsal inlay full-thickness genital skin grafts for hypospadias reoperations: extended follow up. *J Pediatr Urol* 2011; 7: 65-71. 2010/02/23. DOI: 10.1016/j.jpuro.2010.01.016.
9. Cruz-Diaz O, Castellan M and Gosalbez R. Use of buccal mucosa in hypospadias repair. *Curr Urol Rep* 2013; 14: 366-372. 2013/05/21. DOI: 10.1007/s11934-013-0334-9.
10. Duckett JW, Coplen D, Ewalt D, et al. Buccal mucosal urethral replacement. *J Urol* 1995; 153: 1660-1663. 1995/05/01.
11. Stein R, Schroder A and Thuroff JW. Surgical atlas: Primary hypospadias repair with buccal mucosa. *BJU Int* 2006; 97: 871-889. 2006/03/16. DOI: 10.1111/j.1464-410X.2006.06119.x.
12. Barbagli G, Vallasciani S, Romano G, et al. Morbidity of oral mucosa graft harvesting from a single cheek. *Eur Urol* 2010; 58: 33-41. 2010/01/29. DOI: 10.1016/j.eururo.2010.01.012.
13. Versteegden LRM, de Jonge P, IntHout J, et al. Tissue Engineering of the Urethra: A Systematic Review and Meta-analysis of Preclinical and Clinical Studies. *Eur Urol* 2017; 72: 594-606. 2017/04/08. DOI: 10.1016/j.eururo.2017.03.026.

14. Dorin RP, Pohl HG, De Filippo RE, et al. Tubularized urethral replacement with unseeded matrices: what is the maximum distance for normal tissue regeneration? *World J Urol* 2008; 26: 323-326. 2008/08/07. DOI: 10.1007/s00345-008-0316-6.
15. Crapo PM, Gilbert TW and Badylak SF. An overview of tissue and whole organ decellularization processes. *Biomaterials* 2011; 32: 3233-3243. 2011/02/08. DOI: 10.1016/j.biomaterials.2011.01.057.
16. Keane TJ, Swinehart IT and Badylak SF. Methods of tissue decellularization used for preparation of biologic scaffolds and in vivo relevance. *Methods* 2015; 84: 25-34. 2015/03/21. DOI: 10.1016/j.ymeth.2015.03.005.
17. Booth C, Korossis SA, Wilcox HE, et al. Tissue engineering of cardiac valve prostheses I: development and histological characterization of an acellular porcine scaffold. *J Heart Valve Dis* 2002; 11: 457-462. 2002/08/02.
18. Vafae T, Thomas D, Desai A, et al. Decellularization of human donor aortic and pulmonary valved conduits using low concentration sodium dodecyl sulfate. *J Tissue Eng Regen Med* 2018; 12: e841-e853. 2016/12/13. DOI: 10.1002/term.2391.
19. Hogg P, Rooney P, Ingham E, et al. Development of a decellularised dermis. *Cell Tissue Bank* 2013; 14: 465-474. 2012/08/10. DOI: 10.1007/s10561-012-9333-1.
20. Wilshaw SP, Rooney P, Berry H, et al. Development and characterization of acellular allogeneic arterial matrices. *Tissue Eng Part A* 2012; 18: 471-483. 2011/09/17. DOI: 10.1089/ten.tea.2011.0287.
21. Jones G, Herbert A, Berry H, et al. Decellularization and Characterization of Porcine Superflexor Tendon: A Potential Anterior Cruciate Ligament Replacement. *Tissue Eng Part A* 2017; 23: 124-134. 2016/11/04. DOI: 10.1089/ten.TEA.2016.0114.
22. Stapleton TW, Ingram J, Katta J, et al. Development and characterization of an acellular porcine medial meniscus for use in tissue engineering. *Tissue Eng Part A* 2008; 14: 505-518. 2008/03/29. DOI: 10.1089/tea.2007.0233.
23. Paniagua Gutierrez JR, Berry H, Korossis S, et al. Regenerative potential of low-concentration SDS-decellularized porcine aortic valved conduits in vivo. *Tissue Eng Part A* 2015; 21: 332-342. 2014/08/27. DOI: 10.1089/ten.tea.2014.0003.
24. da Costa FD, Santos LR, Collatusso C, et al. Thirteen years' experience with the Ross Operation. *J Heart Valve Dis* 2009; 18: 84-94. 2009/03/24.
25. Greaves NS, Benatar B, Baguneid M, et al. Single-stage application of a novel decellularized dermis for treatment-resistant lower limb ulcers: positive outcomes assessed by SIAscopy, laser perfusion, and 3D imaging, with sequential timed histological analysis. *Wound Repair Regen* 2013; 21: 813-822. 2013/10/19. DOI: 10.1111/wrr.12113.
26. Greaves NS, Lqbal SA, Morris J, et al. Acute cutaneous wounds treated with human decellularised dermis show enhanced angiogenesis during healing. *PLoS One* 2015; 10: e0113209. 2015/01/21. DOI: 10.1371/journal.pone.0113209.
27. Kimmel H and Gittleman H. Retrospective observational analysis of the use of an architecturally unique dermal regeneration template (Derma Pure®) for the treatment of hard-to-heal wounds. *Int Wound J* 2017; 14: 666-672. 2016/09/14. DOI: 10.1111/iwj.12667.

- 1
2
3 28. Bolland F, Korossis S, Wilshaw SP, et al. Development and characterisation of a full-
4 thickness acellular porcine bladder matrix for tissue engineering. *Biomaterials* 2007; 28: 1061-
5 1070. 2006/11/10. DOI: 10.1016/j.biomaterials.2006.10.005.
6
7 29. Bullers SJ, Baker SC, Ingham E, et al. The human tissue-biomaterial interface: a role for
8 PPARgamma-dependent glucocorticoid receptor activation in regulating the CD163+ M2
9 macrophage phenotype. *Tissue Eng Part A* 2014; 20: 2390-2401. 2014/02/20. DOI:
10 10.1089/ten.TEA.2013.0628.
11
12 30. Kimuli M, Eardley I and Southgate J. In vitro assessment of decellularized porcine
13 dermis as a matrix for urinary tract reconstruction. *BJU Int* 2004; 94: 859-866. 2004/10/13.
14 DOI: 10.1111/j.1464-410X.2004.05047.x.
15
16 31. Southgate J, Hutton KA, Thomas DF, et al. Normal human urothelial cells in vitro:
17 proliferation and induction of stratification. *Lab Invest* 1994; 71: 583-594. 1994/10/01.
18
19 32. Springer A and Subramaniam R. Split dorsal dartos flap transposed ventrally as a bed
20 for preputial skin graft in primary staged hypospadias repair. *Urology* 2012; 79: 939-942.
21 2012/03/03. DOI: 10.1016/j.urology.2012.01.006.
22
23 33. Cavallo JA, Greco SC, Liu J, et al. Remodeling characteristics and biomechanical
24 properties of a crosslinked versus a non-crosslinked porcine dermis scaffolds in a porcine
25 model of ventral hernia repair. *Hernia* 2015; 19: 207-218. 2013/03/14. DOI: 10.1007/s10029-
26 013-1070-2.
27
28 34. Korossis S, Bolland F, Southgate J, et al. Regional biomechanical and histological
29 characterisation of the passive porcine urinary bladder: Implications for augmentation and
30 tissue engineering strategies. *Biomaterials* 2009; 30: 266-275. 2008/10/18. DOI:
31 10.1016/j.biomaterials.2008.09.034.
32
33 35. Aitken KJ and Bägli DJ. The bladder extracellular matrix. Part I: architecture,
34 development and disease. *Nat Rev Urol* 2009; 6: 596-611. 2009/11/06. DOI:
35 10.1038/nrurol.2009.201.
36
37 36. Tanaka Y, Matsuo K, Yuzuriha S, et al. Differential long-term stimulation of type I
38 versus type III collagen after infrared irradiation. *Dermatol Surg* 2009; 35: 1099-1104.
39 2009/05/15. DOI: 10.1111/j.1524-4725.2009.01194.x.
40
41 37. Khan U and Bayat A. Microarchitectural analysis of decellularised unscarred and
42 scarred dermis provides insight into the organisation and ultrastructure of the human skin
43 with implications for future dermal substitute scaffold design. *J Tissue Eng* 2019; 10:
44 2041731419843710. 2019/06/28. DOI: 10.1177/2041731419843710.
45
46 38. Butler CE, Burns NK, Campbell KT, et al. Comparison of cross-linked and non-cross-
47 linked porcine acellular dermal matrices for ventral hernia repair. *J Am Coll Surg* 2010; 211:
48 368-376. 2010/08/31. DOI: 10.1016/j.jamcollsurg.2010.04.024.
49
50 39. Macleod TM, Williams G, Sanders R, et al. Histological evaluation of Permacol as a
51 subcutaneous implant over a 20-week period in the rat model. *Br J Plast Surg* 2005; 58: 518-
52 532. 2005/05/18. DOI: 10.1016/j.bjps.2004.12.012.
53
54 40. Khor E. Methods for the treatment of collagenous tissues for bioprotheses.
55 *Biomaterials* 1997; 18: 95-105. 1997/01/01. DOI: 10.1016/s0142-9612(96)00106-8.
56
57
58
59
60

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
41. Damink LHHO, Dijkstra PJ, Vanluyn MJA, et al. Cross-Linking of Dermal Sheep Collagen Using Hexamethylene Diisocyanate. *J Mater Sci-Mater M* 1995; 6: 429-434.
42. Valentin JE, Badylak JS, McCabe GP, et al. Extracellular matrix bioscaffolds for orthopaedic applications. A comparative histologic study. *J Bone Joint Surg Am* 2006; 88: 2673-2686. 2006/12/05. DOI: 10.2106/JBJS.E.01008.
43. de Castro Bras LE, Proffitt JL, Bloor S, et al. Effect of crosslinking on the performance of a collagen-derived biomaterial as an implant for soft tissue repair: a rodent model. *J Biomed Mater Res B Appl Biomater* 2010; 95: 239-249. 2010/09/30. DOI: 10.1002/jbm.b.31704.
44. Hinz B. The role of myofibroblasts in wound healing. *Curr Res Transl Med* 2016; 64: 171-177. 2016/12/13. DOI: 10.1016/j.retram.2016.09.003.
45. Pakshir P and Hinz B. The big five in fibrosis: Macrophages, myofibroblasts, matrix, mechanics, and miscommunication. *Matrix Biol* 2018; 68-69: 81-93. 2018/02/07. DOI: 10.1016/j.matbio.2018.01.019.
46. Rhodes A, Jasani B, Balaton AJ, et al. Immunohistochemical demonstration of oestrogen and progesterone receptors: correlation of standards achieved on in house tumours with that achieved on external quality assessment material in over 150 laboratories from 26 countries. *J Clin Pathol* 2000; 53: 292-301. 2000/05/24. DOI: 10.1136/jcp.53.4.292.
47. Sirota RL. Error and error reduction in pathology. *Arch Pathol Lab Med* 2005; 129: 1228-1233. 2005/10/04. DOI: 10.1043/1543-2165(2005)129[1228:EAERIP]2.0.CO;2.
48. Taylor CR. An exaltation of experts: concerted efforts in the standardization of immunohistochemistry. *Hum Pathol* 1994; 25: 2-11. 1994/01/01. DOI: 10.1016/0046-8177(94)90164-3.
49. Sidney LE, Branch MJ, Dunphy SE, et al. Concise review: evidence for CD34 as a common marker for diverse progenitors. *Stem Cells* 2014; 32: 1380-1389. 2014/02/06. DOI: 10.1002/stem.1661.
50. O'Brien FJ. Biomaterials & scaffolds for tissue engineering. *Mater Today* 2011; 14: 88-95. DOI: Doi 10.1016/S1369-7021(11)70058-X.

Table 1. Primary porcine-reactive monoclonal antibodies used for immunohistochemistry.

Antigen	Distribution	Antibody clone	Supplier	Concentration
CD34	Haematopoietic, vascular and other lineages	EP373Y	Abcam	1:1000
CD45	Leucocyte lineage marker	K252-1E4	Serotec	1:150
CD163	Expressed by monocytes and macrophages of M2 tissue-remodelling phenotype	2A10/11	Serotec	1:200
SMA	Vascular structures & myofibroblasts	1A4	Sigma	1:4000
MAC387	Recently tissue infiltrating monocytes and macrophages	MAC387	AbD Serotec	1:150

All immunohistochemistry was performed on serial zinc-fixed tissue sections with exception of anti-CD34 which was applied to antigen-retrieved tissue sections from formalin-fixed paraffin wax-embedded tissues processed in parallel.

Figure Captions

Figure 1. Surgical placement of biomaterial implant (PABM or Permacol™) within the peri-urethral fascia. Surgery was performed on 12 Large White Landrace Hybrid male pigs 14 weeks old and mean weight of 16.59 kg (± 1.25 (SD)). Six animals received implants of PABM and six of Permacol™.

A-D: Schematic of the surgical procedure. An incision (red dashed line in A) was made approximately 5 cm caudally from the preputial sac. The superficial adipose tissue was dissected (B) to reveal the peri-urethral tissues and fascia. The fascia was opened (B) in order that either PABM or Permacol™ could be sutured in place using eight Vicryl™ sutures, with two non-absorbable 3'0 Prolene® marker sutures positioned at either end of the graft (C). Subcutaneous fat was then opposed followed by skin closure (D) achieved with 5'0 Monocryl (Ethicon) or Vicryl™ continuous suture with two external Prolene® marker sutures at the caudal and cranial end of incision (D).

E-G: Intraoperative stages from surgery reflecting schematic parts B and C with insertion in part C of PABM (F) or Permacol™ (G).

H-I: At harvest, the grafted tissue area was removed “en-bloc” for histological analysis using the delineating permanent marker sutures as guides for PABM (H) and Pelvicol (I). Note: in H arrows highlight the persistence of Permacol™; in I, asterisks highlight the position of permanent sutures used to mark the position of the graft.

Scale bar 1 cm.

1
2
3 **Figure 2:** Histology of on-lay graft implants after 3 months, showing PABM (left
4 column) or Permacol™ (right column).
5
6
7

8 **A-D:** H&E-stained sections of peri-urethral penile tissue showing PABM and
9 Permacol™ implants at low power (**A & B**), with boxes (green) marking the position of
10 implant regions illustrated at higher magnification in **C & D** (by H&E) and **E & F** (by
11 IHC) to examine differences in the extent of cellularisation of each biomaterial. Note
12 the extensive infiltration by cells in PABM (**C**) marked by haematoxylin-stained nuclei
13 (blue dots), compared to the absence of cells across the Permacol™ graft (pink) in
14 **D**. Immunolabelling with anti- α SMA indicates differences in distribution of vessels
15 and α SMA+ cells between PABM (**E**) and Permacol™ (**F**) implants. PABM implants
16 showed extensive cellular infiltration and neovascularisation, whereas Permacol™
17 implants showed cells and vessels retained along the edges of the implant. Note
18 partial encapsulation evident along one edge of Permacol™ (**F**).
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Figure 3: Implant cell density.

A: Scatter plot for number of cells detected within the biomaterial implant for each animal displayed individually, showing mean and SD. Using tissue analysis software, nuclei were detected automatically within 20 non-overlapping equal-sized regions of interest (ROIs) for each PABM and Permacol™ implant. Data are displayed for the individual animals to show the variance within and across grafts. Filled symbols represent PABM data and empty symbols represent Permacol™ data.

B: Combined data from all animals displayed as mean number of cells per mm² (\pm SEM) in PABM versus Permacol™ (5309 ± 78 vs 906 ± 32 ; $p < 0.0001$; $n = 6$ animals per group).

1
2
3 **Figure 4: Distribution of infiltrating cell types in implants.**
4

5
6 **A:** Immunohistochemistry of Permacol™ and PABM implants labelled with antibodies
7
8 against CD34, CD45, CD163 and α SMA to identify lineages of infiltrating host cell
9
10 populations. Scale bar 100 μ m.
11
12

13 **B:** Quantification of the relative proportion of different cell types in PABM and
14
15 Permacol™ samples identified using cell type lineage markers. Supervised
16
17 automated image analysis using StrataQuest software was used to quantify cell
18
19 numbers from 5 individual ROIs per implant for each marker. Data expressed as
20
21 mean \pm SD.
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

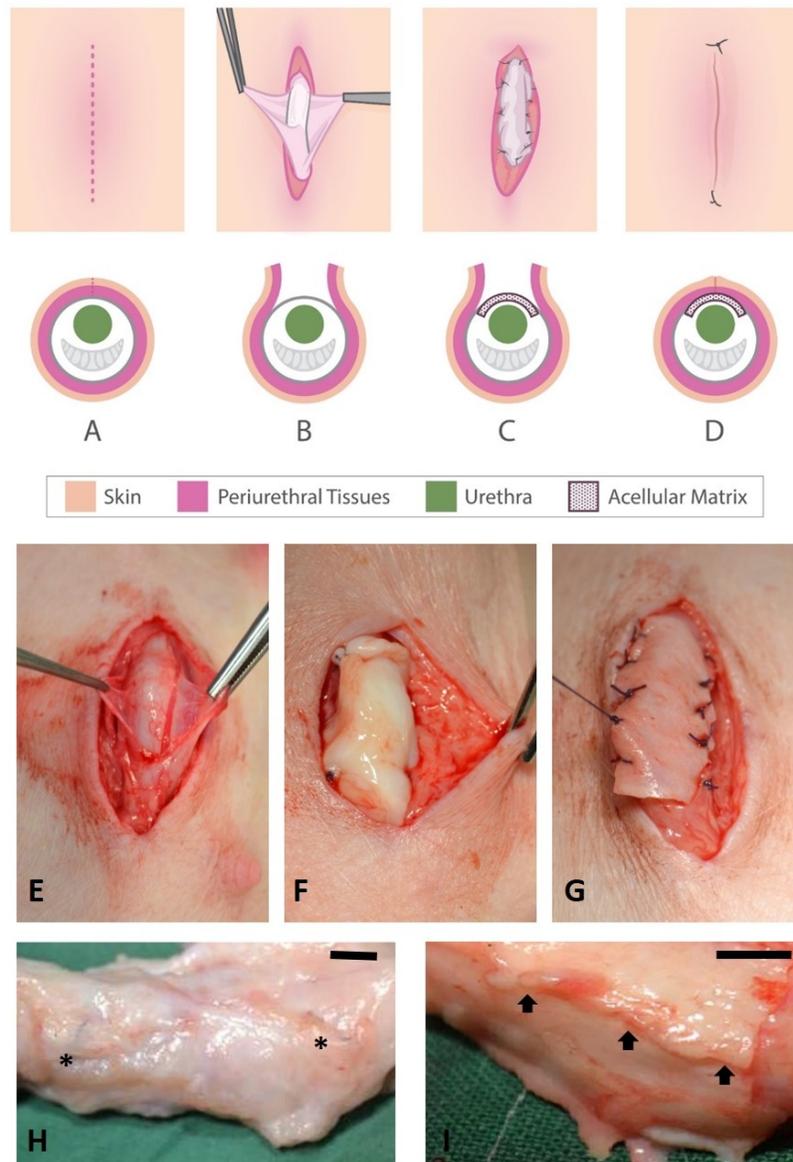


Figure 1. Surgical placement of biomaterial implant (PABM or Permacol™) within the peri-urethral fascia.

Surgery was performed on 12 Large White Landrace Hybrid male pigs 14 weeks old and mean weight of 16.59 kg (± 1.25 (SD)). Six animals received implants of PABM and six of Permacol™.

A-D: Schematic of the surgical procedure. An incision (red dashed line in A) was made approximately 5 cm caudally from the preputial sac. The superficial adipose tissue was dissected (B) to reveal the peri-urethral tissues and fascia. The fascia was opened (B) in order that either PABM or Permacol™ could be sutured in place using eight Vicryl™ sutures, with two non-absorbable 3/0 Prolene® marker sutures positioned at either end of the graft (C). Subcutaneous fat was then opposed followed by skin closure (D) achieved with 5/0 Monocryl (Ethicon) or Vicryl™ continuous suture with two external Prolene® marker sutures at the caudal and cranial end of incision (D).

E-G: Intraoperative stages from surgery reflecting schematic parts B and C with insertion in part C of PABM (F) or Permacol™ (G).

H-I: At harvest, the grafted tissue area was removed "en-bloc" for histological analysis using the delineating permanent marker sutures as guides for PABM (H) and Pelvicol (I). Note: in H arrows highlight the

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

persistence of Permacol™; in I, asterisks highlight the position of permanent stutures used to mark the position of the graft.

Scale bar 1 cm.

157x221mm (150 x 150 DPI)


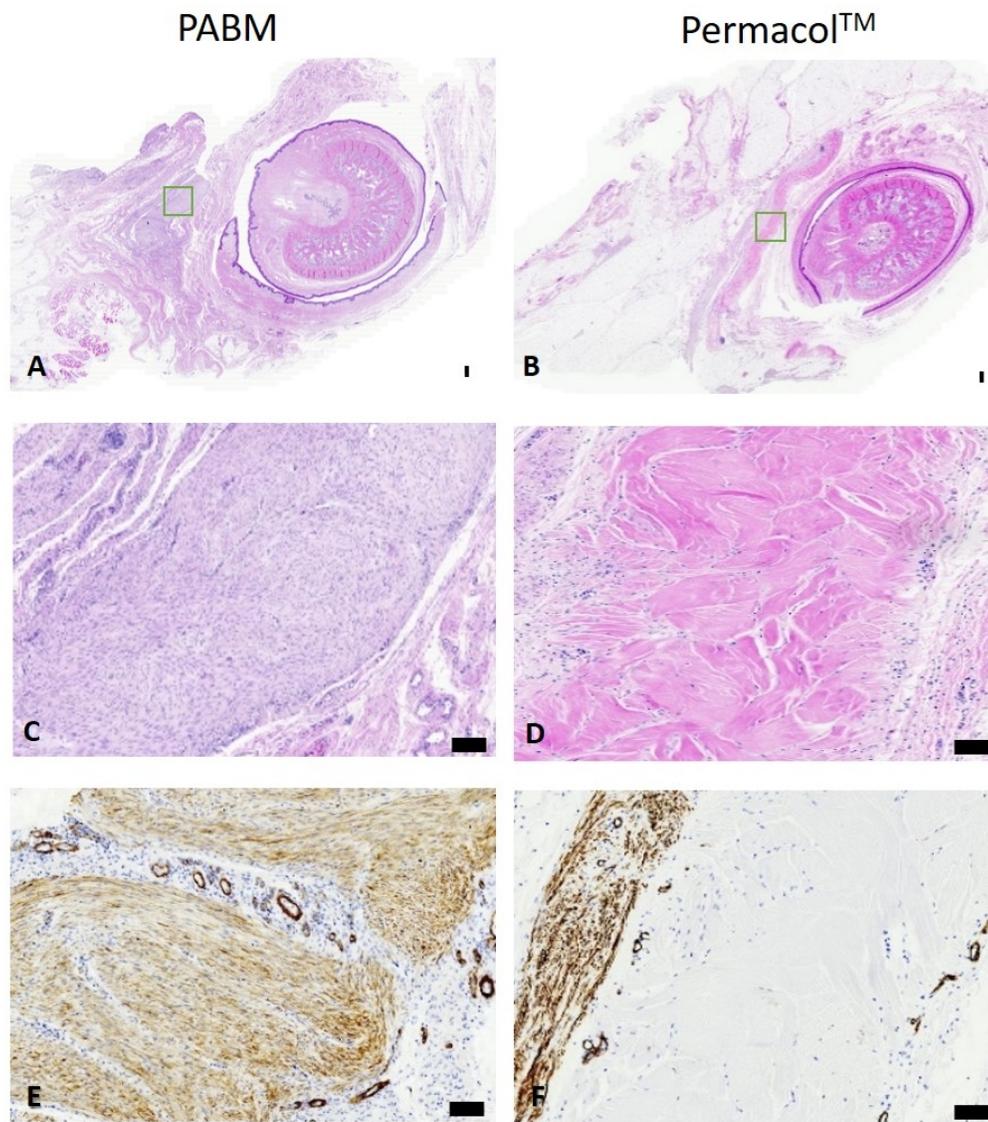


Figure 2: Histology of on-lay graft implants after 3 months, showing PABM (left column) or Permacol™ (right column).

A-D: H&E-stained sections of peri-urethral penile tissue showing PABM and Permacol™ implants at low power (A & B), with boxes (green) marking the position of implant regions illustrated at higher magnification in C & D (by H&E) and E & F (by IHC) to examine differences in the extent of cellularisation of each biomaterial. Note the extensive infiltration by cells in PABM (C) marked by haematoxylin-stained nuclei (blue dots), compared to the absence of cells across the Permacol™ graft (pink) in D. Immunolabelling with anti- α SMA indicates differences in distribution of vessels and α SMA+ cells between PABM (E) and Permacol™ (F) implants. PABM implants showed extensive cellular infiltration and neovascularisation, whereas Permacol™ implants showed cells and vessels retained along the edges of the implant. Note partial encapsulation evident along one edge of Permacol™ (F).

150x174mm (150 x 150 DPI)

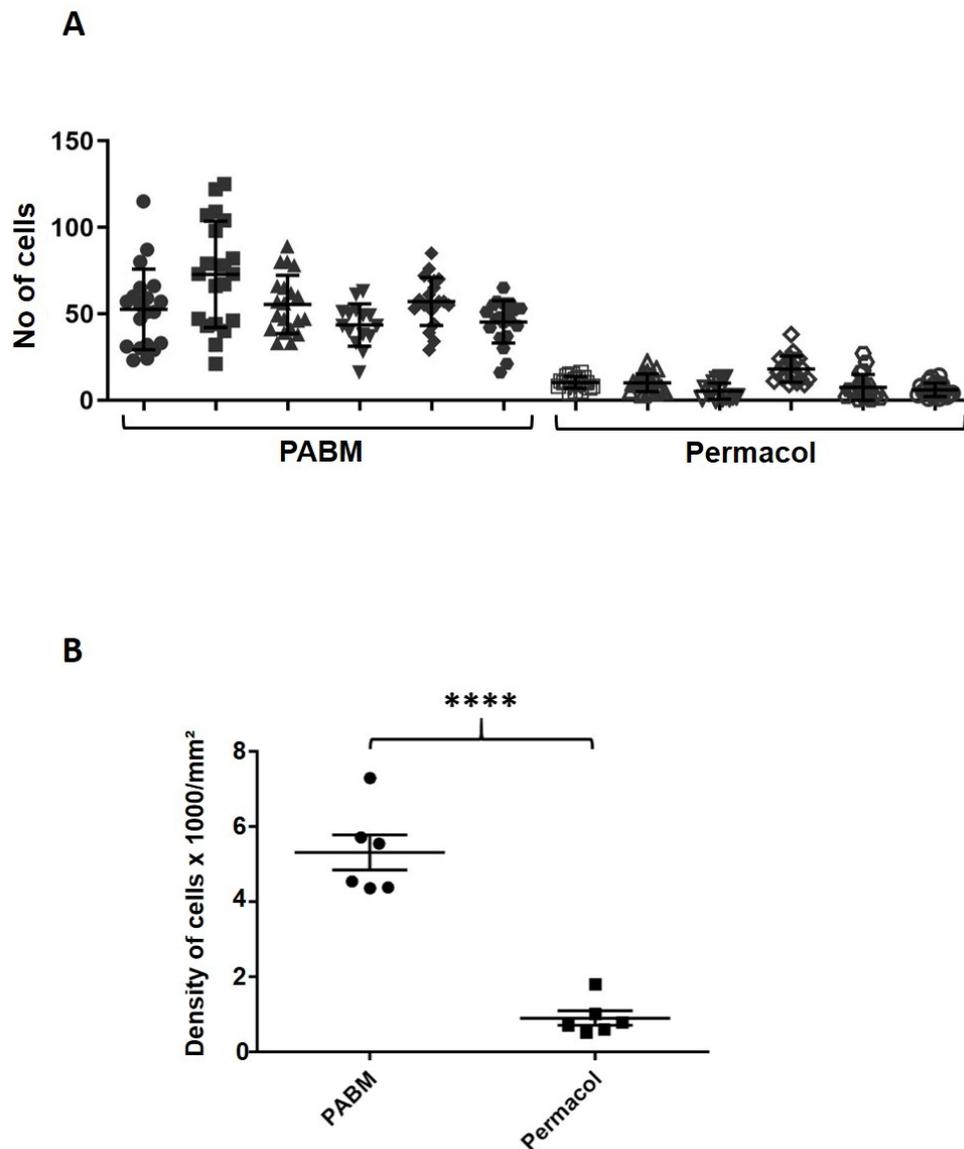


45 Figure 3: Implant cell density.


46 A: Scatter plot for number of cells detected within the biomaterial implant for each animal displayed
 47 individually, showing mean and SD. Using tissue analysis software, nuclei were detected automatically
 48 within 20 non-overlapping equal-sized regions of interest (ROIs) for each PABM and Permacol™ implant.
 49 Data are displayed for the individual animals to show the variance within and across grafts. Filled symbols
 represent PABM data and empty symbols represent Permacol™ data.

50 B: Combined data from all animals displayed as mean number of cells per mm² (± SEM) in PABM versus
 51 Permacol™ (5309 ± 78 vs 906 ± 32; p<0.0001; n = 6 animals per group).

52 168x200mm (150 x 150 DPI)

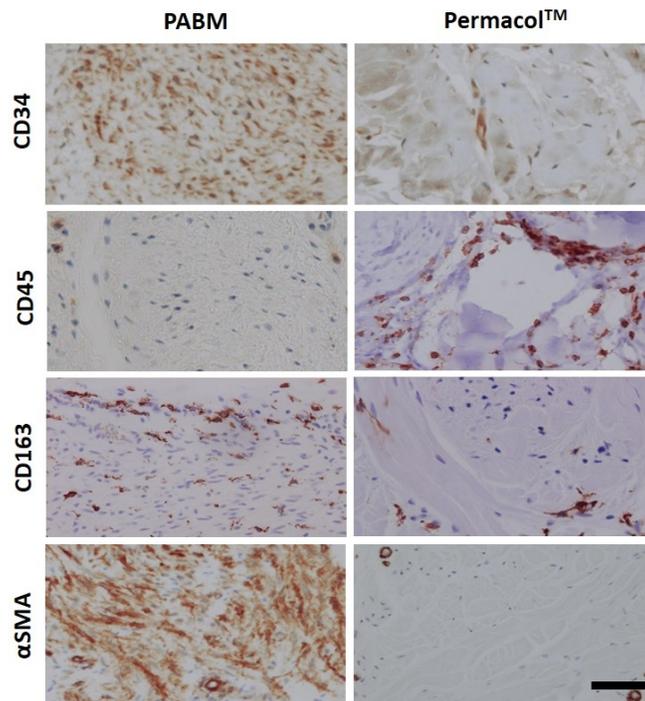

A

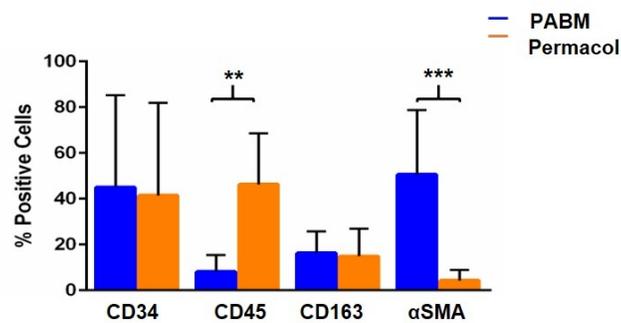

B

42
43
44
45

Figure 4: Distribution of infiltrating cell types in implants.

46 A: Immunohistochemistry of Permacol™ and PABM implants labelled with antibodies against CD34, CD45, CD163 and αSMA to identify lineages of infiltrating host cell populations. Scale bar 100 μm.

47
48 B: Quantification of the relative proportion of different cell types in PABM and Permacol™ samples identified using cell type lineage markers. Supervised automated image analysis using StrataQuest software was used to quantify cell numbers from 5 individual ROIs per implant for each marker. Data expressed as mean ± SD.

49
50
51
52
53
54
55
56
57
58
59
60

130x226mm (150 x 150 DPI)

ARRIVE guidelines 2.0. <https://arriveguidelines.org/>

Essential 10		
1a	The groups being compared	We developed a porcine experimental model of urethroplasty to study the effect of incorporating an onlay free graft of acellular matrix at the repair site. We compared two acellular matrices: 1) PABM (Porcine Acellular Bladder Matrix a non-crosslinked, full thickness matrix) and 2) Permacol™ (a commercial porcine dermis-derived acellular matrix that is licensed for human use and has previously been used as an off-label product in a small clinical series undergoing hypospadias repair).
1b	The experimental unit	Single animal
2a	Experimental units allocated to each group and total number in each experiment; total number of animals used	Twelve large white hybrid (LWH) pigs were used in the experimental study with a total of six animals implanted with PABM and six with Permacol.
2b	How sample size was decided	A maximum of 6 pigs could be housed at any one time
3a	Inclusion or exclusion criteria and data points during the analysis	<p>Only male pigs were used - both sexes of animal were not used because the study was targeted for a condition that does not occur in females.</p> <p>All animals included in the study remained healthy and none were excluded at any stage of the study</p>
3b	Any animals not included in the analysis and why.	NA
3c	Report exact value of n in each group	12 animals total in 2 groups of n=6 each.
4a	Randomisation of animals to control and treatment groups	<p>Six animals were implanted with PABM and six with Permacol™. The animals were divided into two groups of six with three pigs having PABM and the other Permacol™ implanted into the peri-urethral tissues. The surgery for first and second groups took place ~five months apart.</p> <pre> graph TD A["6 pigs 3 Permacol 3 PABM"] --> B["3 months"] B --> C["Histological evaluation"] C --> D["6 pigs 3 Permacol 3 PABM"] D --> E["3 months"] E --> F["Histological evaluation"] C --> G["Combined immunohistochemical assessment"] F --> G </pre>

4b	Strategy to minimise experimental confounders	Surgery was performed in two batches of 6 to limit any inherent bias that may have ensued by implanting only Permacol™ or PABM first, thereby improving the surgical procedure used for the second batch of six.
5a	Blinding – who was aware of group allocation during allocation, conduct, outcome and data analysis	To perform blinded analysis, labelled slides were scanned on a Zeiss Axioscan Microscope and the resulting CZI image files were subjected to semi-automated supervised analysis using StrataQuest software (version 6.0.0.123) on the TissueGnostic image analysis platform (Vienna, Austria). Five non-overlapping 0.1 x 0.1 mm ² regions of interest (ROIs) were defined within each implanted biomaterial (PABM and Permacol™) and nuclei were detected automatically within the five equal-sized ROIs. Following optimisation, the same conditions were applied to all image files.
6a	Define outcome measures	Weight gain; Normal voiding function; External palpability; Histological evaluation of capsule formation; inflammation; cellularisation by density & cell type.
7a	Statistical methods and software	Raw data were imported into GraphPad Prism for statistical evaluation using descriptive statistics.
8a	Species, strain, gender, age, weight	Large white hybrid (LWH) male animals averaging 16.59 kg ± 1.25.
9a	Experimental procedures – what, where, when and why	During the surgical implantation of the grafts, the peri-urethral plane was opened. The graft was secured with eight dissolvable Vicryl™ (polyglactin 910; Ethicon) sutures. Two Prolene® (polypropylene; Ethicon) non-dissolvable “marker” sutures were placed at either end of the opened superficial fascia to the graft to enable localisation of the implant site. The rest of the superficial fascia and subcutaneous fat (where necessary) was closed using Vicryl™ interrupted sutures. Skin closure was achieved using Vicryl™ or Monocryl® in a continuous closure. Two further Prolene® sutures were placed as external markers of the closure to enable successful location of the site at 3 months.
10a	Summary/descriptive stats for each experimental group plus variance	<p>Upon termination at three months, the body weight of the animals ranged from 55-62 kg (mean 56.12 kg).</p> <p>In the Permacol group only, there was a partial encapsulation reaction involving between 6% and 44% (min-max range) of the perimeter of the visualised implanted biomaterial (mean ±SD: 19.5% ± 12.59, n=6). The average thickness of the identified capsule was 216 μm ± 96 (mean ± SD, n=6; min-max range: 20 - 500 μm).</p> <p>The density of infiltrating cells expressed as the mean total number of cells per mm² ± SEM was 5309 ± 78 for PABM versus 906 ± 32 for Permacol™ (n=6 animals per group; p < 0.0001 using Welch t test).</p>

		Relative quantification revealed 40% CD34: 20% CD163: 40% α SMA positive cells in PABM, compared to 40% CD34: 20% CD163: 40% CD45 positive cells in Permacol™. Thus, although both biomaterials were infiltrated by cells expressing CD34+ and/or CD163+ cells in a similar ratio, the remaining 40% of the infiltrating population showed a significant switch from predominantly CD45+ in Permacol™ to α SMA+ in PABM.
--	--	--

	Recommended set	
11	Abstract	<p>Acellular matrices produced by tissue decellularisation are reported to have tissue integrative properties. We examined the potential for incorporating acellular matrix grafts during procedures where there is an inadequate natural tissue bed to support an enduring surgical repair. Hypospadias is a common congenital defect requiring surgery, but associated with long-term complications due to the poor quality/quantity of underlying tissue bed at the repair site.</p> <p>Biomaterials were implanted as single on-lay 3.0 by 1.5 cm² grafts of PABM or Permacol™ in a peri-urethral position in male pigs. Two acellular tissue matrices were compared: full-thickness porcine acellular bladder matrix (PABM) and commercially-sourced cross-linked acellular matrix from porcine dermis (Permacol™). Anatomical and immunohistological outcomes were assessed 3 months post-surgery.</p> <p>There were no complications and surgical sites underwent full cosmetic repair. PABM grafts were fully incorporated, whilst Permacol™ grafts remained manipulatable. Immunohistochemical analysis indicated a non-inflammatory, remodelling-type response to both biomaterials. PABM implants showed extensive stromal cell infiltration and neovascularisation, with a significantly higher density of cells ($p < 0.001$) than Permacol™, which showed poor cellularisation and partial encapsulation.</p> <p>This study supports the anti-inflammatory and tissue-integrative nature of non-cross-linked acellular matrices and provides proof-of-principle for incorporating acellular matrices during surgical procedures, such as in primary complex hypospadias repair.</p>
12a	Background, rationale and experimental approach	<p>Background</p> <p>There is a clinical need in urology to identify biomaterials that can be used for reconstructive surgery of the lower urinary tract, including the bladder and urethra. Hypospadias is one of the most common birth defects in males (1 in 300) and is associated with development of an abnormal urethra. Surgical repair is performed for a majority of infants with hypospadias, but repair of severe hypospadias may require</p>

<p>1 2 3 4 5 6 7 8 9 10 11 12 13 14 15 16 17 18 19 20 21 22 23 24 25 26 27 28 29 30 31 32 33 34 35 36 37 38 39 40 41 42 43 44 45 46 47 48 49 50 51 52 53 54 55 56 57 58 59 60</p>		<p>multiple procedures and is frequently associated with unsatisfactory results, including the formation of urethral fistulas in up to 20% of cases. These fistulas may be persistent and difficult to manage due to a lack of, or poor quality, tissue at the site of repair. Success rates for fistula repair with multiple attempts is unsatisfactory (between 66.6% and 92%) and recurrence rates are highest with simple closure.</p> <p>Rationale Our rationale was that natural biomaterials may support surgical repair and if incorporated in primary hypospadias cases could reduce the incidence of complications.</p> <p>Experimental procedures.</p> <p>Anaesthesia Food but not water was withheld for 18 hours prior to surgery. Initial sedation was performed using intramuscular Hypnovel (0.3 mg/kg) (Roche) and Stresnil (1.2 mg/kg) (Elanco). The animal was left for 20-30 minutes in a quiet and calm environment before transportation to the anaesthetic room on a trolley. Induction of anaesthesia was achieved by utilising a snout mask containing an isoflurane-soaked. Isoflurane 2.5 % in oxygen was then used for maintenance of anaesthesia and delivered via the snout mask attached to an anaesthetic machine. The electrocardiogram, pulse, blood pressure and oxygen saturation of the animal was continuously monitored during the surgical procedure. Eyes were protected using Lacri-lube® (Allergan-Actavis). An over-the-needle intravenous cannula (22 G) was introduced into an ear vein and secured with Micropore™ (3M). The animal was given AmoxyPen LA (MSD Animal Health) (15 mg/kg) and Rimadyl (Zoetis) (2 mg/kg), a non-steroidal anti-inflammatory agent</p> <p>Positioning for surgery The anaesthetised animal was placed supine on the operating table. Skin on the lower abdomen was shaved. A plate electrode (Conmed) was placed onto shaved flank skin and attached to the diathermy machine. The animal's skin was prepared with Chlorhexidine solution (Vetasept-Animal Care). The animal was draped using 307 x 254cm SterriDrapes with incise pouch (3M). The monopolar diathermy pen (Ambu) was attached to the diathermy machine.</p> <p>Surgical Basics: A 5cm midline incision was made, approximately 5cm from the preputial sac, caudally using a size 15 disposable scalpel (Swann Morton). The peri-urethral tissues were opened using blunt dissection. Bleeding was stopped, when necessary using monopolar diathermy.</p>
---	--	---

		<p>Post-operative care:</p> <p>At skin closure 3ml of 0.5 % Marcaine local anaesthetic was infiltrated locally. In addition, Vetergesic (0.3 mg), an opioid analgesic was administered to provide postoperative pain relief. The animal was transferred from the operating table to trolley and then to a pen with fresh bedding and sawdust. The animal was allowed to recover in a quiet environment in isolation until up on all four limbs and drinking water. Once this was achieved the animal was placed in a pen with another animal and food made available.</p> <p>Schedule 1</p> <p>The process of euthanasia began with sedation of the animal using Hypnovel and Stresnil. An ear vein was cannulated and barbiturate was administered intravenously to overdose.</p>
12b	Relevance to humans	In order to be relevant to children, a large surgical model was required to test surgical compatibility and provide an adequate model in terms of anatomical size.
13	Objectives	<p>The aim was to develop a large experimental model equivalent to anatomical size to children, in which to test surgical compatibility and examine the potential use of PABM in paediatric urology. The following experimental objectives were investigated:</p> <ul style="list-style-type: none"> - To determine the cellular integration properties of PABM when surgically implanted in vivo as a free onlay graft in a peri-urethral position - To compare the integration of non-crosslinked PABM with that of a commercially-available crosslinked decellularised dermal matrix (Permacol™)
14	Ethical statement	All experimental procedures were approved by the local Animal Welfare and Ethical Review Body and were conducted at the University of Leeds animal surgical facility under a project licence granted by the UK Home Office, in accordance with the Animal Scientific Procedures Act 1986 under project licence (PPL70/7930).
15	Housing and husbandry	Large White Hybrid (LWH) male pigs were transported to the animal surgical facility for seven days quarantine. Numbered ear tags were used to aid individual identification. The animals were inspected for signs of disease by a vet and the facility's technical staff and animals were housed together in pens, with appropriate clean bedding.
16	Animal care and monitoring	All animals were monitored and evaluated at least twice/day. The animals were weighed every two weeks over the full period and feeding regime altered accordingly. Food was available up to twice a day, with the amount varying according to weight gain and behaviour. Access to water was unlimited.
17	Interpretation/scientific implications	Implanting an acellular tissue matrix into the peri-urethral stroma in a large animal surgical model is safe and does not provoke an inflammatory response. Superficially, both the porcine-derived biomaterials used gave outwardly acceptable

		<p>results. Nevertheless, there were important biological differences in the host response to the two materials. Implants of PABM had become fully incorporated within the three-month period to leave no macroscopic residue. Histologically, the marked PABM graft region was extensively vascularised and completely infiltrated by cells. This agrees with independent reports of non-cross-linked matrices in terms of superior host tissue integration and cellular infiltration accompanied by neovascularisation. By contrast, Permacol™ implants persisted macroscopically and the bulk material remained acellular at three months. This is consistent with other studies using cross-linked biomaterials, including changes we ourselves have noted following PABM crosslinking.</p>
18	Generalisability/translation	<p>The experiments were performed in a surgical model of relevant scale and provide support to the principle of managing complications from hypospadias surgery by incorporating a suitable biomaterial into the surgical procedure when local tissues are insufficient or inadequate. By providing histological evidence of the extent and nature of tissue integration outcomes when different biomaterials are used, the results add important insight to small scale clinical studies where outcomes have been observational only.</p>
19	protocol registration	NA
20	Data Access	<p>Access to the raw histological qualitative and quantitative data required to reproduce the findings is available on request from the corresponding author.</p>
21	Declaration of interests	<p>The work was partially funded through the Medical Technologies Innovation and Knowledge Centre (phase 2 - Regenerative Devices), funded by the EPSRC under grant number EP/N00941X/1 as Proof of Concept awards: PoC023 and PoC045. AR was supported by the European Society of Paediatric Urology. JS is supported by a programme grant from York Against Cancer. The work leading to the development of PABM was originally funded by the Biotechnology and Biological Sciences Research Council (BBSRC) on grants E20352 and BB/E527220/1.</p> <p>Eileen Ingham is a shareholder and consultant to Tissue Regenix Group PLC. The authors confirm that there are no other known conflicts of interest associated with this publication and there has been no significant financial support for this work that could have influenced its outcome.</p>