



This is a repository copy of *Interfacial morphology between ramie fibers and phenolic resins : effects of plasma treatment and cure cycle.*

White Rose Research Online URL for this paper:
<https://eprints.whiterose.ac.uk/184499/>

Version: Accepted Version

Article:

Hamad, S.F., Fei, T., Hayes, S.A. et al. (2 more authors) (2022) Interfacial morphology between ramie fibers and phenolic resins : effects of plasma treatment and cure cycle. *Journal of Composite Materials*, 56 (6). pp. 889-897. ISSN 0021-9983

<https://doi.org/10.1177/00219983211065549>

Hamad SF, Fei T, Hayes SA, Foreman JP, Rodenburg C. Interfacial Morphology between Ramie Fibers and Phenolic Resins: Effects of Plasma Treatment and Cure Cycle. *Journal of Composite Materials*. 2022;56(6):889-897. doi:10.1177/00219983211065549. © 2022 The Author(s). Article available under the terms of the CC-BY-NC-ND licence (<https://creativecommons.org/licenses/by-nc-nd/4.0/>).

Reuse

This article is distributed under the terms of the Creative Commons Attribution-NonCommercial-NoDerivs (CC BY-NC-ND) licence. This licence only allows you to download this work and share it with others as long as you credit the authors, but you can't change the article in any way or use it commercially. More information and the full terms of the licence here: <https://creativecommons.org/licenses/>

Takedown

If you consider content in White Rose Research Online to be in breach of UK law, please notify us by emailing eprints@whiterose.ac.uk including the URL of the record and the reason for the withdrawal request.



eprints@whiterose.ac.uk
<https://eprints.whiterose.ac.uk/>

Interfacial morphology between ramie fibers and phenolic resins: effects of plasma treatment and cure cycle

Sameer F. Hamad^{1,2*}, Teng Fei¹, Simon A. Hayes³, Joel P. Foreman¹, Cornelia Rodenburg¹

¹*Department of Materials Science and Engineering, the University of Sheffield, Sheffield S1 3JD, UK*

²*College of Engineering, University of Misan, Maysan 62001, Iraq*

³*Department of Multidisciplinary Engineering Education, the University of Sheffield, Sheffield S3 7RD, UK*

Correspondence to: Sameer F. Hamad (E-mail: sfhamad4@uomisan.edu.iq or sfhamad3@gmail.com)

Abstract: Natural fiber reinforced-polymer composites offer many advantages over conventional composite materials, such as availability, low cost, inexpensive, lightweight, and high specific mechanical properties. However, the applications of these materials are still limited due to the challenges in achieving a good interface between the fibers and matrix. This is highly influenced by the fiber surface characteristics and the polymer matrix properties. Therefore, in this study, the surface characteristics of ramie fibers were modified using low-pressure plasma treatment in order to improve their interface to the phenolic resin. Furthermore, the effects of using two different curing cycles (acid cure and thermal cure) on the properties of short ramie fiber-phenolic composites were also investigated. A new method for making mats of random short ramie fibers was developed and used for the fabrication of composites containing plasma-treated fibers. The flexural properties of all composites were tested and the obtained fracture surfaces were investigated using LV-SEM. The results indicate that both plasma treatment and cure cycle conditions influence the fiber-matrix interface, and consequently the flexural properties of the composites.

Keywords: Ramie fibers; phenolic resin; low pressure plasma treatment; curing conditions; fiber-matrix interfacial morphology.

1. Introduction

The use of natural plant fibers such as ramie, flax, jute, hemp, kenaf, and sisal as reinforcements in the polymer composites has recently received great attention in various

engineering applications. This is due to their excellent mechanical characteristics such as flexibility, high toughness, high specific modulus, and specific strength as well as their low cost, low density, recyclability, and renewability [1]–[8]. Such properties make plant fiber composites one of the high-performance group of materials with both economic and environmental benefits [9]. However, the properties and performance of these materials are highly influenced by the properties of the individual components (fibers and matrix) and their surface adhesion properties as well as the method of composite fabrication [7][10]–[12].

Among natural plant fibers, ramie fibers are widely used as a reinforcement in polymer composites due to their favourable properties such as high crystallinity, commercial availability [13]–[15], and being one of the stronger natural textile fibers [16][17]. Nonetheless, ramie fibers present some disadvantages such as poor wettability, incompatibility with some types of polymer matrices, and low moisture resistance [9]. However, it is possible to overcome some of these challenges via surface modification making fibers more compatible with some polymer matrices [9][10]. In a previous study, it was found that the 2 min of low pressure plasma treatment of ramie fibers resulted in a nanoscale surface roughness without affecting or changing the fiber bulk properties [18]. Such results are expected to increase the fiber surface area and hence improve the fiber-matrix interface. Therefore, here we investigate the effects of plasma treatment on the fiber-matrix interface in a random short ramie fiber-phenolic resin composite system, before and after plasma treatment.

In this system, some degree of interaction is expected to exist between the hydrophilic ramie fibers and polar hydroxyl groups present in the structure of phenolic resins [19][20]. This can be considered as an advantage that phenolic resins possess when compared to thermoplastic matrices which are generally hydrophobic [21]. Moreover, composites based on phenolic resins as a matrix tend to yield low levels of combustion products and smoke under both

smouldering and flaming fire conditions and are superior in terms of other flammability properties to epoxy, polyester, and vinyl ester-based composites [22][23]. However, the curing process of phenolic resin is complex and usually involves several types of reactions. One of the main issues is the generation of water and formaldehyde as by-products of the crosslinking reaction of the phenolic resin with the consequent formation of voids [11][24]–[27]. The curing conditions (cure cycle) are very important in controlling the void content, size, and distribution in the final cured resin. In an earlier study, the authors found that the use of a short cure cycle (3-4 hrs) with the addition of a fast action acid catalyst (Phencat 10), a homogenous void size and distribution can be achieved in the final cured resin. On the other hand, a microvoid free phenolic resin was achieved with the use of a long cure cycle (4 days) without the addition of a curing agent [28]. Thus, in this work, the authors investigated the effects of the above two cure cycles on the microstructural and mechanical properties of random short ramie fiber-reinforced phenolic resin composites.

Finally, the process of mixing short fibers into thermosetting resins has generally been based on mechanical stirring or blending, a process which has a tendency to cause fiber damage and fiber agglomeration, as well as the likelihood of forming air bubbles [29]. To overcome this problem, the authors reported a method in which the effect of plasma treatment can also be utilised to hold the short ramie fibers together as a mat after compacting them.

Therefore, in this study, the untreated and plasma treated random short ramie fiber mat-reinforced phenolic thermoset matrix composites were fabricated. The effects of the plasma treatment on the interface between fibers and matrix were investigated. The structural and mechanical properties of the prepared composites were optimised via the use of two different curing cycles. Low Voltage Scanning Electron Microscopy (LV-SEM) was used to observe the interface morphology of the prepared composites. Flexural tests were also performed for

all prepared composites, in order to find a composite fabrication procedure that leads to optimisation of the mechanical properties.

2. Experimental Methods

2.1. Materials

Ramie fibers (*Boehmeria nivea*) were supplied by Wild Fibres, UK and used as received for the experiments. The polymer matrix was a commercial resole phenolic resin (Cellobond J2027X) which was kindly supplied by Caleb Technical Products Ltd., UK. The curing agent used was Phencat 10 (fast action acid catalyst) which was also supplied by Caleb Technical Products Ltd., UK.

2.2. Low pressure plasma surface treatment

Low pressure plasma surface treatment was performed using a Diener Electronic Zepto plasma surface cleaner with 40 kHz power supply frequency and chamber size of 2.6 Litre (borosilicate glass cylindrical chamber). The fibers were first cut and prepared into a length of about 8-10 mm. The fibers were then placed inside the plasma chamber and the chamber was evacuated to 0.1 mbar. The ambient air was used as a process gas. Plasma was generated at power of 100 W and a chamber pressure of 0.3 mbar. Ramie fibers were treated for 2 minutes in two different steps (see Section 2.3).

2.3. Fabrication of composites

Generally, short fibre-polymer composites are fabricated using techniques such as hand layup, injection moulding, and press-moulding using a sheet moulding compound (SMC) [30]. The untreated short ramie fibers were laid down in a PTFE mould (with dimensions of 12.7 mm wide×56 mm long×1.6 mm thick) and then a load (5 kg) was placed on it for 5 minutes, which reduced any significant movement of the fibers. Whereas, when using plasma treated fibers, the mats were prepared as follows. Fibers which had been plasma treated for 1 minute were placed in the PTFE mould and then a load (5 kg) was placed on it for 5 minutes

to provide compaction. After that, the plasma treated mats (Figure 1) were treated for a second minute and then returned to the PTFE mould.

Thereafter, two types of phenolic resins were used to make the composites, being cured either using the curing agent (short cure cycle (4 hrs)) or with the application of heat only, using a long cure cycle (4 days) [28]. In the case of using curing agent, fast action acid catalyst was used with a mixing ratio of 5 wt% of the resin. The prepared resins were then poured on to the fiber mats where they were observed to wet and infiltrate all the free space. The composites were placed in the autoclave to be cured using the two different curing cycles depending on the resin type. The employed curing cycles were reported elsewhere [28]. The materials will be referred to as ‘composite acid cured’ and ‘composite thermal cured’. The content of ramie fibers for the composites as mixed, prior to cure, were 10%, 15%, and 20 % by weight. The fiber volume fraction was not measured after cure due to the difficulty in using burn-off or acid digestion methods in natural fiber composites. For more details about the fabrication process of the composites, see supplementary information.

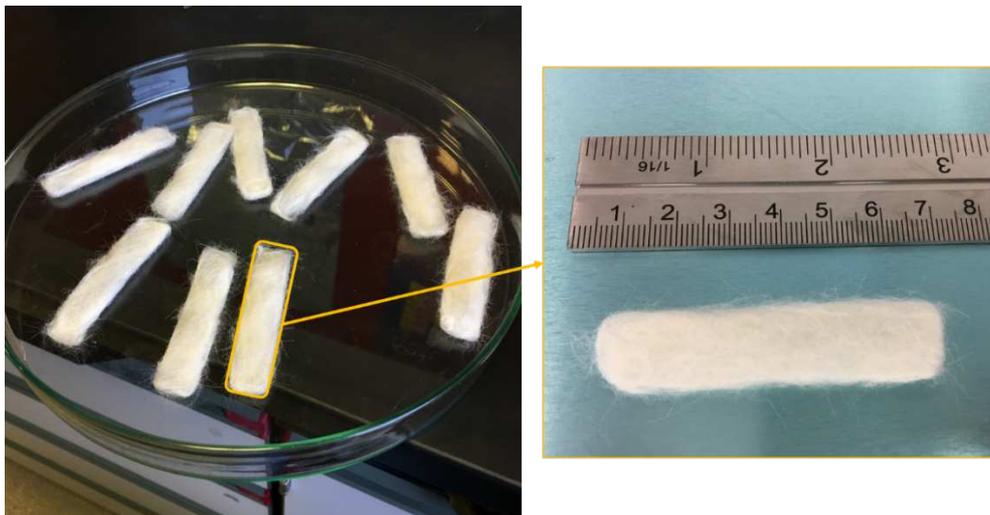


Figure 1. Mats of plasma treated random short ramie fibers.

2.4. Flexural properties

The flexural properties of the composites were determined using a Lloyd TA500 tensometer. The test was conducted according to the ASTM D790 at a crosshead speed of 2.0 mm/min. The tests were performed at room temperature (22 ± 3 °C). The bending results (strength and modulus) for each composite were calculated using an average of seven specimens per test condition.

2.5. Scanning electron microscopy

Fracture surface morphology of the composites after flexural testing was examined using low voltage Scanning Electron Microscopy (FEI Nova Nano SEM 450). Low accelerating voltage (1 kV) was used to avoid sample surface charging and damage with typical vacuum pressure of 10^{-5} mbar, and a working distance of approximately 4mm. Secondary electron images were collected using two detectors: Everhart-Thornley Detector (ETD) for low magnification images and Through Lens Detector (TLD) to obtain high magnification images.

3. Results and discussion

3.1. Flexural properties

The flexural properties (modulus and strength) of the pure phenolic and its composites (short ramie fibers-phenolic resin composites) produced using short cure cycle (acid cured) and long cure cycle (thermal cured) are presented in Figure 2. The average flexural modulus of the pure phenolic resin (acid cured) was 2.3 GPa. With the use of plasma treated ramie fibers, the average flexural modulus of the composite was linearly increased with increasing fiber content (Figure 2a). This is because ramie fibers are relatively stiff (Young's modulus of 31 GPa) [18] compared to phenolic resin (flexural modulus of 2.3 GPa). However, the composite based on 15 wt% untreated fibers shows a reduction in the average flexural modulus of approximately 12%, compared to the plasma treated composite. This indicates better incorporation of the plasma treated ramie fibers into phenolic resin than the untreated fibers.

In terms of the flexural strength of the acid cured composites (Figure 2b), the plasma treated fiber composite showed higher flexural strength than that of the untreated fiber composite. This could be due to the continuous void free zone around the plasma treated fibers, as observed by the LV-SEM in Figure 4e in Section 3.3. Thus, the stress concentration points around the plasma treated fibers were less than in the case of the untreated fibers. However, both materials (untreated and plasma treated fiber composites with 15 wt% fiber content) show clear decreasing strength compared to that of pure phenolic resin. This is consistent with other work on natural fiber-phenolic composites [31]. It is well known that the fiber-matrix interface plays an important role in determining the final mechanical properties of the composites, as transferring the stress between the fiber and matrix occurs through the interface region. The properties mainly depend on the degree of interfacial adhesion between fibers and matrix. The maximum stress level can be maintained across the interface without disruption if a high interfacial strength is achieved [32]. However, the LV-SEM micrographs in Section 3.3 (Figure 4) showed that the interfacial bonding between the fibers and matrix was very poor, as well as revealing the presence of microvoids along the interface for both materials (untreated and plasma treated fiber composites). Furthermore, unfilled lumen was clearly observed in some samples, resulting in more defects in the final composite structure. The presence of these defects in the composite could act as a stress concentration point in the polymer matrix, and consequently being sites of crack initiation and fiber-matrix debonding before final composite failure [33]. All of this could explain the reason why the acid cured composites showed lower flexural strength than the pure phenolic resin.

In contrast, the flexural properties (modulus and strength) of the thermal cured composites (Figures 2c and d) showed higher values compared to those of the acid cured composites. For instance, the average flexural modulus of the pure phenolic resin (thermal cured) was 3.2 GPa (Figure 2c) compared to 2.3 GPa for the acid cured system. This was increased to 4.9 GPa,

when 15 wt% of plasma treated fibers was added to phenolic resin which is an improvement of approximately 34% over the pure phenolic resin (thermal cured). This is in contrast to the composite produced using the short cure cycle (acid cured) with 15 wt% fiber, where the improvement in the modulus was only 17% over the pure phenolic. More importantly, unlike when using the short cure cycle, the flexural strength of the composite produced using the long cure cycle was maintained in the same range as that of the pure phenolic resin (thermal cured) as shown in Figure 2d.

All the above can be attributed to the resin characteristics. As observed and discussed in Section 3.3, the formation of microvoids in the cured resin when using the short cure cycle was predominantly along the fiber-matrix interface, resulting in a relatively poor interfacial bond. In addition, when using plasma treated fibers, a non-homogenous distribution of the microvoids was observed around the fibers. It has been shown in a previous study that the non-homogenous distribution of the microvoids in the cured resin resulted in a reduction in the mechanical properties compared to those with a homogenous microvoids distribution [28]. This is in contrast to the composites produced using the long cure cycle, which showed void free structure suggesting a better interfacial bond between the fiber and matrix. Thus, the flexural properties of the thermal cured phenolic composites were higher than those of the acid cured phenolic composites.

However, it is also important to point out that when using the long cure cycle, the flexural modulus and flexural strength of the plasma treated fiber composites were higher than those of the untreated fiber composites (Figures 2c and d). As mentioned above, the mechanical properties of the final composites are highly influenced by the nature of the interfacial bond between the fiber and matrix. In general, the interfacial bond between natural fibers and polymer matrices is influenced by mechanical interlocking, chemical bonding and physical interactions between the two components [32]. The presence of the non-cellulosic compounds

(e.g. waxes and pectins) on the surface of untreated ramie fibers could act as a barrier for the mechanical/chemical interlocking between the ramie fibers and phenolic resin. This is corroborated by a less than ideal coverage of the fibers by the resin, as indicated by the LV-SEM observations in Figure 6a-c. Thus, the stress transfer between the fibers and matrix was inefficient when using untreated ramie fibers, and consequently led to the early failure of the composites. This is in contrast to the interfacial bonding between ramie fibers and the phenolic resin which had higher coverage when using plasma treated fibers than when using untreated fibers (as indicated by the LV-SEM micrographs in Figure 6d-f in Section 3.4). Thus, the stress was likely to be more efficiently transferred between the fibers and matrix through the plasma treated interface, resulting in higher flexural properties. Therefore, the differences in the flexural properties between the two composites (untreated and plasma treated fibers) can be attributed to the effects of the plasma treatment on the surface morphology/chemistry of ramie fibers, indicating an improved fiber-matrix interface.

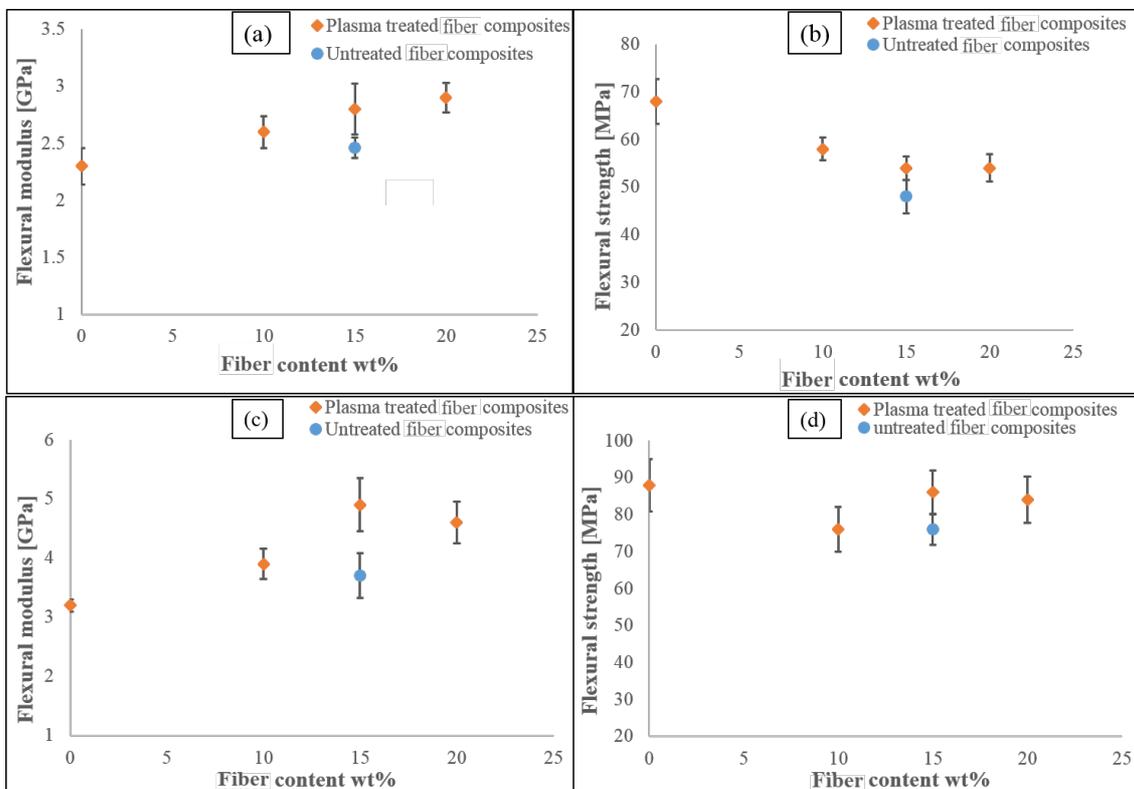


Figure 2: The flexural properties of the untreated and plasma treated short ramie fibers-phenolic composites as a function of fiber content: (a) and (b) flexural modulus and flexural strength respectively of acid cured composites, (c) and (d) flexural modulus and flexural strength respectively of thermal cured composites.

3.2. Composite fiber distribution

An overview of LV-SEM micrographs obtained from fractured surfaces of untreated and plasma treated short ramie fiber-reinforced phenolic composites are shown in Figure 3. These micrographs reveal the ramie fiber distribution in the phenolic resin. In both untreated (Figure 3a) and plasma treated (Figure 3b) systems, the ramie fibres are well dispersed in the resin and there are no signs of fiber agglomerations. This indicates that the method of composite fabrication, based on short fiber mats, was successful.

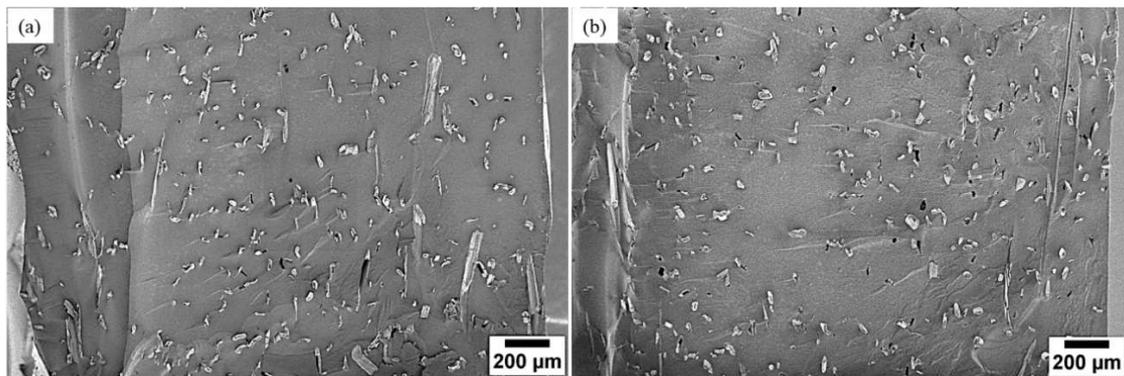


Figure 3. Overview LV-SEM micrographs of the flexural fractured surfaces of (a) untreated short ramie fibers-phenolic resin composite and (b) plasma treated short ramie fibers-phenolic resin composite.

3.3. Fiber-matrix interface morphology-acid cured composites

The fiber-matrix interfacial bonding is of great importance in short fiber composites. This is partly due to the length of short fibers being of the same order of magnitude as the critical fiber length for efficient stress transfer between fiber and matrix. Consequently, small changes in the interfacial bonding between fibers and matrix affect the reinforcement efficiency quite dramatically [34].

Therefore, a detailed view of the fiber-matrix interface morphology of the untreated and plasma treated fiber composites, cured using short cure cycle are investigated and presented in Figure 4. In Figure 4a (untreated fiber), dense and homogenous coverage of the phenolic fracture surface with spherical features with an average diameter of $0.52\pm 0.15\ \mu\text{m}$ were observed. These features can be attributed to the trapped water present as result of the condensation reactions which release formaldehyde and water as by-products. With the use of the acid catalyst, the crosslinking rate of the phenol and formaldehyde is relatively fast, therefore, the by-products generated will be less capable of diffusing into the surrounding matrix, resulting in a homogenous distribution of voids in the final cured resin [28]. A higher magnification LV-SEM image of the fiber-matrix interface (Figure 4b) also reveals microvoids along the fiber-matrix interface. Furthermore, these microvoids were locally varied around the fiber, leading to localised void free zones as shown in Figure 4a and b. As discussed previously, this may be due to the inhomogeneous coverage of the fibers by waxes and pectins. In addition, Figure 4c shows a fiber lumen, which is an inherent feature of natural fibers. This particular lumen is unfilled and therefore is a void within the composite system which occupies volume but will support no load. The unfilled lumen could be due to the poor interaction between the fibers and matrix or due to a high viscosity resin. The viscosity of the resin is visibly increased after the addition of fast action acid catalyst and thus the filling of untreated fiber lumens with this phenolic resin may be limited.

However, when using plasma treated fibers, the microvoids along the fiber-matrix interface are larger compared to those of the untreated fibers, as shown in Figure 4d. Moreover, plasma treated fibers tend to be surrounded by a void free zone, followed by a ring of larger voids and then a zone with a homogenous void size distribution (Figure 4e). To further confirm this, a histogram of the void diameter distribution around the untreated and plasma treated fibers are shown in Figures 5c and f for the micrographs shown in Figures 5a and d. When

using untreated fibers the average void diameter is 0.64 ± 0.2 μm with a relatively narrow distribution of void diameters. Conversely, when using plasma treated fibers the average void diameter is higher at 1.13 ± 0.3 μm , with a relatively broad distribution of void diameters. It seems likely that the differences in void size and distribution are a direct consequence of the altered fiber surface chemistry after plasma treatment. For instance, the FTIR analysis in a previous study showed that the absorbed water in the crystalline cellulose of ramie fibers was decreased gradually with plasma treatment [18]. This was attributed to the temperature effect of the plasma during the treatment and also to bond cleavage forming free radicals [35][36]. This would lead to fibers with a lower moisture content and more functional groups on the fiber surface capable of hydrogen bonding, resulting in more interaction with the water in the resin. The water generated during the polymerisation reaction can exist as bounded water (hydrogen bonded to the polymer network), or discrete pockets of free water (leading to voids) [37]. Either of these types of water can interact with the fibers, though this will be more likely to occur with the free water.

The observations in Figure 4 can be explained by considering the water generated as by-products in the phenolic resin during cure and how this interact with plasma treated fibers. Some of this water will be absorbed by the fibers and some will coalesce to form voids at the fiber-matrix interface. When using plasma treated fibers, the water at the fiber-matrix interface can more readily absorb. This scenario is also consistent with the presence of a distinct void free zone around the fiber. Beyond the void free zone, the generated water coalesces, but as a result of the fast cross-linking rate it is unable to diffuse before the gel point is reached, leading to a larger average void size in this area. Furthermore, the void free zones might also prevent the diffusion of the voids into the fibers because of the high density of this area. In contrast, when using untreated fibers, the average void size is smaller and no distinct continuous void free zone around the fiber is observed. This could be attributed to the

higher level of water in the untreated fibers that could only attract and interact with the water close by and also due to the inhomogeneous coverage of ramie fiber by waxes and pectins.

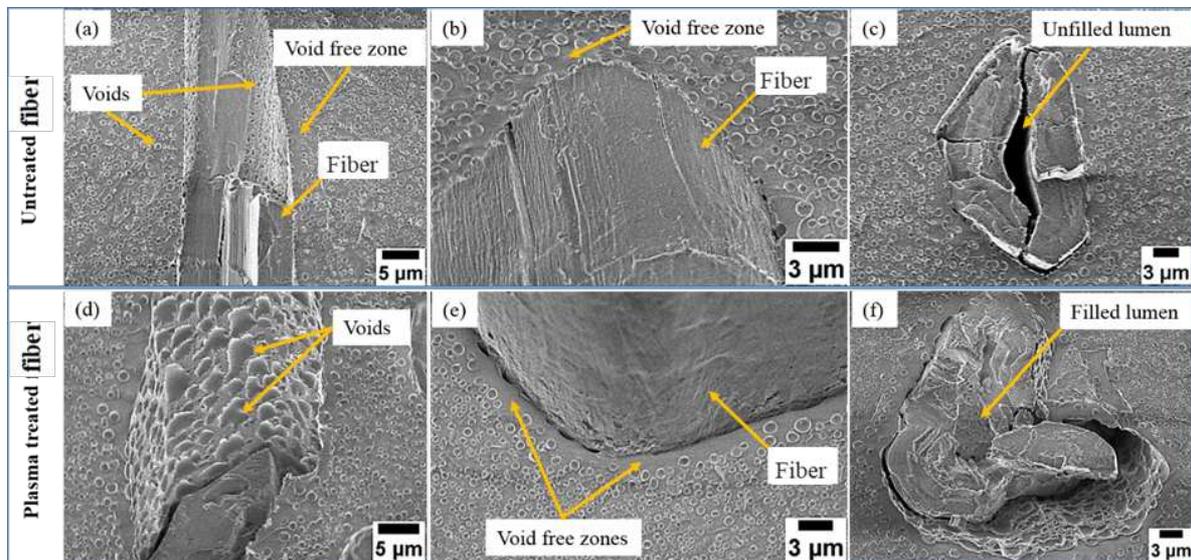


Figure 4. LV-SEM micrographs of the fiber-matrix interface of (a) (b) (c) untreated ramie fiber-phenolic resin composites and (d) (e) (f) 2 min plasma treated ramie fibers-phenolic resin composites at different magnifications. The composites were cured using short cure cycle (acid cured).

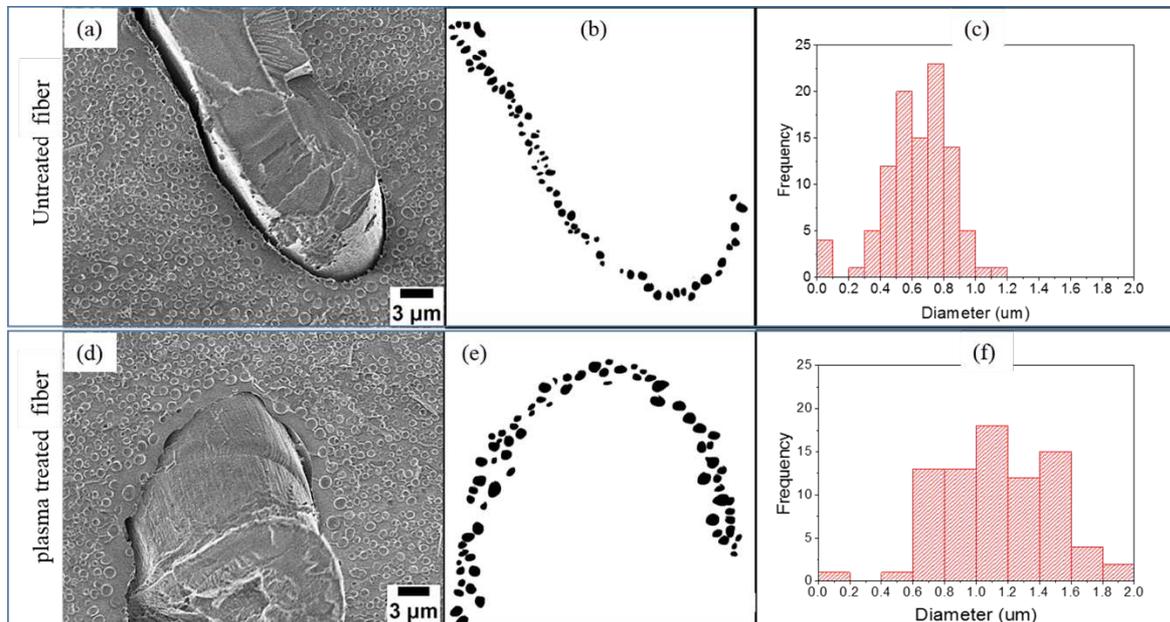


Figure 5: LV-SEM micrographs of the fiber-matrix interface of (a) untreated ramie fiber-phenolic resin composites and (d) 2 min plasma treated ramie fibers-phenolic resin composites. (b) and (e) Binary images showing the voids distribution around the fibres in (a) and (d) respectively. (c) and (f) Histogram of voids diameter distribution derived from the binary images in (b) and (e) respectively. The composites were cured using short cure cycle.

3.4. Fiber-matrix interface morphology-thermal cured composites

The LV-SEM micrographs of the untreated and plasma treated fiber composites made using the long cure cycle (thermal cured) are shown in Figure 6. During flexural testing, the composite will be loaded in tension and compression with the neutral line running between the two. When the sample is subjected to a flexural load from above it will bend, resulting in compressive stresses on top of the sample and tensile stresses on the bottom. The neutral line is the transition between the compressive and tensile zones [38][39]. For a reliable comparison of the interfacial bonding between the untreated and plasma treated fiber composites, all the LV-SEM micrographs in this study were collected from the tensile side of the neutral line. In contrast to the phenolic resin cured using the short cure cycle (Figure 4a), a homogenous fracture surface which was free of microvoids was observed for the phenolic resin cured using the long cure cycle. This was attributed to the time available for the water to diffuse away from the polymer network before the gel point of the resin is reached [28]. If this is long enough, as when using the long cure cycle (4 days), the formation of microvoids in the cured resin can be minimised.

In terms of the fiber-matrix interface, the LV-SEM micrographs of the untreated fiber composites show relatively low fiber coverage, suggesting relatively poor interfacial adhesion (Figures 6a-c). The fibers are clearly debonded and pulled out from the resin (Figures 6a-c) with a noticeable gap between the fiber and matrix. In addition, the fiber surface shows relatively few signs of adhering polymer as shown in Figure 6b (indicated by arrows).

However, in the case of using plasma treated fibers (Figures 6d-f), the fibers are broken off near the matrix surface with a relatively short fiber pull out. Moreover, it can be seen in Figures 6d and e, that the fiber-matrix interface is almost continuous and the fiber surface appears to have a relatively high level of resin coverage. This is likely to play an important

role with regards to the mechanical properties of the composite (see Section 3.1) as the degree of adhesion between the fibers and matrix governs load transfer. Another difference between the untreated and plasma treated fibers is that the fiber lumen shown in Figure 6f is clearly filled with resin. Whilst not shown in Figure 6, the majority of the visible fiber lumens were also filled with resin, though it is not possible to assess how deep the lumens are filled.

All the above can be attributed to changes in the surface morphology and surface chemistry of the fibers before and after plasma treatment. In terms of the fiber surface morphology, it has been observed that the surface of the untreated ramie fiber was smooth and almost homogenous on the nanoscale [18]. This was attributed to the primary amorphous layer of ramie fibers that consists of waxes, pectin, and proteinaceous materials [40]. This is in contrast to the plasma treated fibers, where 2 mins of low pressure plasma treatment produced ramie fibers with a rougher surface and a greater exposure of crystalline cellulose microfibrils in comparison to the untreated fibers [18]. Such changes are expected to increase the fiber surface interfacial area and also improve the mechanical interlocking between the fibers and matrix. In terms of the chemical changes, it has been proven that the low pressure plasma treatment was effective in removing the non-cellulosic compounds such as amorphous hemicellulose and waxes from the surface of ramie fibers after 2 min of treatment [18]. This could increase the surface reactivity of the fibers and consequently improve the chemical bonding between the fibers and matrix.

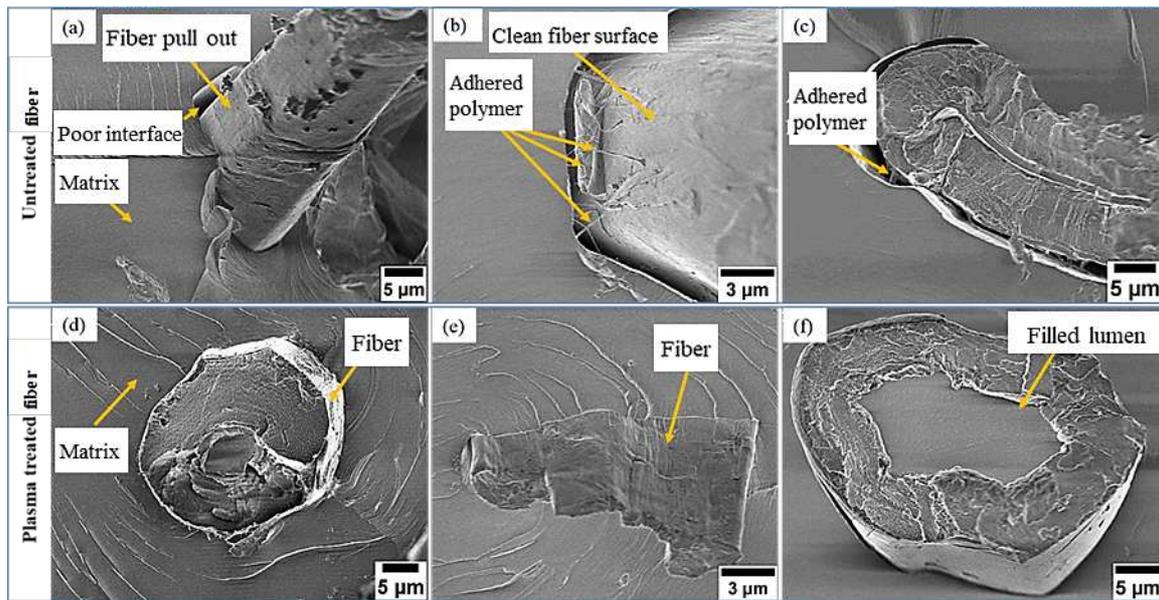


Figure 6: LV-SEM micrographs of the fiber-matrix interface of (a) (b) (c) untreated ramie fiber-phenolic resin composites and (d) (e) (f) 2 min plasma treated ramie fibers-phenolic resin composites at different magnifications. The composites were cured using long cure cycle (thermal cured).

4. Conclusions

Mats of random short ramie fibers were successfully fabricated utilising the effects of plasma treatment to improve the compatibility between the fibers themselves. Furthermore, when using plasma treated fibers as the reinforcement in phenolic resin composites, the Young's modulus was clearly improved in both composites (acid cured and thermal cured). However, this is not the case in terms of the flexural strength for both composites. It has been shown that the flexural strength was gradually decreased for the plasma treated fiber composites (acid cured) whereas in the case of the thermal cured composites, the flexural strength was maintained in the range of the pure phenolic resin. This was attributed to the formation of voids along the fiber-matrix interface in the case of acid cured composites. Therefore, it can be concluded that plasma treatment of ramie fibers is more effective when used in combination with a longer cure cycle (thermal cure) which results in fewer voids.

Acknowledgement

Sameer F. Hamad gratefully acknowledge the Iraqi Ministry of Higher Education and Scientific Research and its representative in the UK, the Iraqi Cultural Attaché for the financial support. C. Rodenburg thanks the Engineering and Physical Sciences Research Council (EPSRC) for funding under EP/N008065/1. Joel P. Foreman thanks Peter Willson at Caleb Technical Products for providing the resin.

References

- [1] L. Yan, "Effect of alkali treatment on vibration characteristics and mechanical properties of natural fabric reinforced composites," *J. Reinf. Plast. Compos.*, vol. 31, no. 13, pp. 887–896, 2012.
- [2] H. Alamri and I. M. Low, "Microstructural, Mechanical, and Thermal Characteristics of Recycled Cellulose Fiber-Halloysite-Epoxy Hybrid Nanocomposites," *Polym. Compos.*, pp. 589–600, 2012.
- [3] J. D. Megiatto, E. C. Ramires, and E. Frollini, "Phenolic matrices and sisal fibers modified with hydroxy terminated polybutadiene rubber: Impact strength, water absorption, and morphological aspects of thermosets and composites," *Ind. Crops Prod.*, vol. 31, no. 1, pp. 178–184, 2010.
- [4] M. Haq, R. Burgueño, A. K. Mohanty, and M. Misra, "Hybrid bio-based composites from blends of unsaturated polyester and soybean oil reinforced with nanoclay and natural fibers," *Compos. Sci. Technol.*, vol. 68, no. 15–16, pp. 3344–3351, 2008.
- [5] M. M. Kabir, H. Wang, K. T. Lau, and F. Cardona, "Chemical treatments on plant-based natural fibre reinforced polymer composites: An overview," *Compos. Part B*, vol. 43, no. 7, pp. 2883–2892, 2012.
- [6] Q. T. H. Shubhra *et al.*, "Characterization of plant and animal based natural fibers reinforced polypropylene composites and their comparative study," *Fibers Polym.*, vol. 11, no. 5, pp. 725–731, 2010.
- [7] S. Marais *et al.*, "Unsaturated polyester composites reinforced with flax fibers: Effect of cold plasma and autoclave treatments on mechanical and permeation properties," *Compos. Part A Appl. Sci. Manuf.*, vol. 36, no. 7, pp. 975–986, 2005.
- [8] D. M. Matoke, G. M.; Owido, S.F.; Nyaanga, "Effect of Production Methods and Material Ratios on Physical Properties of the Composites," *Am. Int. J. Contemp. Res.*, vol. 2, no. 2, pp. 208–213, 2012.
- [9] Y. Li, S. Manolache, Y. Qiu, and M. Sarmadi, "Effect of atmospheric pressure plasma treatment condition on adhesion of ramie fibers to polypropylene for composite," *Appl. Surf. Sci.*, vol. 364, pp. 294–301, 2016.
- [10] E. Bozaci *et al.*, "Effects of the atmospheric plasma treatments on surface and mechanical properties of flax fiber and adhesion between fiber-matrix for composite materials," *Compos. Part B Eng.*, vol. 45, no. 1, pp. 565–572, 2013.

- [11] J. M. Laza, J. L. Vilas, M. Rodriguez, M. T. Garay, F. Mijangos, and L. M. Leon, "Analysis of the crosslinking process of a phenolic resin by thermal scanning rheometry," *J. Appl. Polym. Sci.*, vol. 83, pp. 57–65, 2002.
- [12] A. Ticoalu, T. Aravinthan, and F. Cardona, "A review of current development in natural fiber composites for structural and infrastructure applications," in *Southern Region Engineering Conference*, 2010, no. November, pp. 1–5.
- [13] X. Liu and L. Cheng, "Influence of plasma treatment on properties of ramie fiber and the reinforced composites," *J. Text. Inst.*, vol. 31, no. 15, pp. 1723–1734, 2017.
- [14] Q. Zhang, Y. Jiang, L. Yao, Q. Jiang, and Y. Qiu, "Hydrophobic surface modification of ramie fibers by plasma-induced addition polymerization of propylene," *J. Adhes. Sci. Technol.*, vol. 29, no. 8, pp. 691–704, 2015.
- [15] C. Xu, Y. Gu, Z. Yang, M. Li, Y. Li, and Z. Zhang, "Mechanical properties of surface-treated ramie fiber fabric/epoxy resin composite fabricated by vacuum-assisted resin infusion molding with hot compaction," *J. Compos. Mater.*, vol. 50, no. 9, pp. 1189–1198, 2016.
- [16] G. Koronis, A. Silva, and A. P. Soares Dias, "Development of green composites reinforced with ramie fabrics: Effect of aging on mechanical properties of coated and uncoated specimens," *Fibers Polym.*, vol. 15, no. 12, pp. 2618–2624, 2014.
- [17] S. N. Pandey, "Ramie fibre: Part II. Physical fibre properties. A critical appreciation of recent developments," *Text. Prog.*, vol. 39, no. 4, pp. 189–268, 2007.
- [18] S. F. Hamad, N. Stehling, S. A. Hayes, J. P. Foreman, and C. Rodenburg, "Exploiting Plasma Exposed, Natural Surface Nanostructures in Ramie Fibers for Polymer Composite Applications," *Materials (Basel)*, vol. 12, pp. 1–15, 2019.
- [19] J. D. Megiatto, C. G. Silva, E. C. Ramires, and E. Frollini, "Thermoset matrix reinforced with sisal fibers: Effect of the cure cycle on the properties of the biobased composite," *Polym. Test.*, vol. 28, no. 8, pp. 793–800, 2009.
- [20] J. D. Megiatto, F. B. Oliveira, D. S. Rosa, C. Gardrat, A. Castellan, and E. Frollini, "Renewable resources as reinforcement of polymeric matrices: Composites based on phenolic thermosets and chemically modified sisal fibers," *Macromol. Biosci.*, vol. 7, no. 9–10, pp. 1121–1131, 2007.
- [21] J. D. Megiatto, C. G. Silva, D. S. Rosa, and E. Frollini, "Sisal chemically modified with lignins: Correlation between fibers and phenolic composites properties," *Polym. Degrad. Stab.*, vol. 93, no. 6, pp. 1109–1121, 2008.
- [22] J. Brown and Z. Mathys, "Plasma surface modification of advanced organic fibres: Part V Part V Effects on themechanical properties of aramid/phenolic composites," *J. Mater. Sci.*, vol. 32, pp. 2599–2604, 1997.
- [23] E. C. Ramires and E. Frollini, "Tannin-phenolic resins: Synthesis, characterization, and application as matrix in biobased composites reinforced with sisal fibers," *Compos. Part B*, vol. 43, no. 7, pp. 2851–2860, 2012.
- [24] M. Asim, N. Saba, M. Jawaid, M. Nasir, M. Pervaiz, and O. Y. Alothman, "A review on Phenolic resin and its Composites," *Curr. Anal. Chem.*, vol. 14, pp. 1–13, 2018.
- [25] J. C. Munoz, H. Ku, F. Cardona, and D. Rogers, "Effects of catalysts and post-curing

- conditions in the polymer network of epoxy and phenolic resins: Preliminary results,” *J. Mater. Process. Technol.*, vol. 202, no. 1–3, pp. 486–492, 2008.
- [26] H. S. L. Ku, F. Cardona, M. Trada, and G. Vigier, “Flexural properties of sawdust reinforced phenolic composites: Pilot study,” *J. Appl. Polym. Sci.*, vol. 114, no. 3, pp. 1927–1934, 2009.
- [27] C. Kaynak and C. C. Tasan, “Effects of production parameters on the structure of resol type phenolic resin/layered silicate nanocomposites,” *Eur. Polym. J.*, vol. 42, no. 8, pp. 1908–1921, 2006.
- [28] S. F. Hamad *et al.*, “Optimizing size and distribution of voids in phenolic resins through the choice of catalyst types,” *J. Appl. Polym. Sci.*, vol. 48249, pp. 1–10, 2019.
- [29] I. M. Low, J. Somers, H. S. Kho, I. J. Davies, and B. A. Latella, “Fabrication and properties of recycled cellulose fibre-reinforced epoxy composites,” *Compos. Interfaces*, vol. 16, no. 7–9, pp. 659–669, 2009.
- [30] T. C. Fong, N. Saba, C. K. Liew, R. De Silva, M. E. Hoque, and K. L. Goh, “Yarn Flax Fibres for Polymer-Coated Sutures and Hand Layup Polymer Composite Laminates,” in *Manufacturing of natural fibre reinforced polymer composites*, M. S. Salit, M. Jawaid, N. Bin Yusoff, and M. E. Hoque, Eds. Cham: Springer International Publishing, 2015, pp. 155–175.
- [31] E. Rojo, M. Oliet, M. V. Alonso, B. Saz-Orozco, and F. Rodriguez, “Mechanical and Interfacial Properties of Phenolic Composites Reinforced With Treated Cellulose Fibers,” *Polym. Eng. Sci.*, pp. 2228–2238, 2014.
- [32] Y. Zhou, M. Fan, and L. Chen, “Interface and bonding mechanisms of plant fibre composites: An overview,” *Compos. Part B Eng.*, vol. 101, pp. 31–45, 2016.
- [33] M. A. Sawpan, K. L. Pickering, and A. Fernyhough, “Flexural properties of hemp fibre reinforced polylactide and unsaturated polyester composites,” *Compos. Part A Appl. Sci. Manuf.*, vol. 43, no. 3, pp. 519–526, 2012.
- [34] M. J. Carling, “Fracture Mechanics of Short Fibre Composites,” Imperial College of Science and Technology, 1988.
- [35] M. M. Morshed, M. M. Alam, and S. M. Daniels, “Plasma treatment of natural jute fibre by RIE 80 plus plasma tool,” *Plasma Sci. Technol.*, vol. 12, no. 3, pp. 325–329, 2010.
- [36] E. Sinha, “Effect of cold plasma treatment on macromolecular structure, thermal and mechanical behavior of jute fiber,” *J. Ind. Text.*, vol. 38, no. 4, pp. 317–339, 2009.
- [37] R. M. Sullivan, E. Stokes, and E. H. Baker, “Effect of Water on the Thermo-Mechanical Behavior of Carbon Cloth Phenolic,” *NASA/TM*, pp. 1–13, 2011.
- [38] R. Roy, B. K. Sarkar, and N. R. Bose, “Effects of moisture on the mechanical properties of glass fibre reinforced vinylester resin composites,” *Bull. Mater. Sci.*, vol. 24, no. 1, pp. 87–94, 2001.
- [39] A. Khadimallah, M. W. Bird, and K. W. White, “Prediction of tensile power law creep constants from compression and bend data for ZrB₂–20 vol% SiC composites at 1800 °C,” *J. Adv. Ceram.*, vol. 6, no. 4, pp. 304–311, 2017.

- [40] H. Y. Choi and J. S. Lee, "Effects of surface treatment of ramie fibers in a ramie/poly(lactic acid) composite," *Fibers Polym.*, vol. 13, no. 2, pp. 217–223, 2012.