

Soft Matter

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: C. A. Parton-Barr, H. F. Gleeson and R. J. Mandle, *Soft Matter*, 2024, DOI: 10.1039/D3SM01282D.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

Room-temperature ferroelectric nematic liquid crystal showing a large and diverging density

View Article Online
DOI: 10.1039/C3SM01282D

Charles Parton-Barr¹, Helen F. Gleeson¹, Richard J. Mandle^{1,2,*}

¹ School of Physics and Astronomy, University of Leeds, Leeds, LS2 9JT, UK

² School of Chemistry, University of Leeds, Leeds, LS2 9JT, UK

*corresponding author email: r.mandle@leeds.ac.uk

Abstract

The ferroelectric nematic phase (N_F) is a recently discovered phase of matter in which the orientational order of the conventional nematic liquid crystal state is augmented with polar order. Atomistic simulations suggest that the polar N_F phase would be denser than conventional nematics owing to contributions from polar order. Using an oscillating U-tube densitometer, we obtain detailed temperature-dependent density values for a selection of conventional liquid crystals with excellent agreement with earlier reports. Having demonstrated the validity of our method, we then record density as a function of temperature for M5, a novel room-temperature ferroelectric nematic material. We present the first experimental density data for a N_F material as well as density data for a nematic that has not previously been reported. We find that the room-temperature N_F material shows a large ($>1.3 \text{ g/cm}^3$) density at all temperatures studied, notably including phases without polar order. An increase in density at phase transitions is observed. The magnitude of the increase for the intermediate-to-ferroelectric nematic (N_X - N_F) transition is an order of magnitude smaller than the isotropic-nematic (I-N) transition. We then probe potential consequences that may result from an elevated density through measurement of the refractive indices (n_o and n_e). The n_{avg} of M5 is compared with 5CB and polar smectic liquid crystals. We observe how the highly polar nature of the system counteracts the effects of an increase in density. With knowledge of experimental density, we are able to derive an approximation that yields the polar order parameter, $\langle P1 \rangle$, from polarisation measurements. Present results may be typical of ferroelectric nematic materials, potentially guiding material development, and is especially relevant for informing ongoing studies into this emerging class of materials.

Introduction

The nematic (N) phase is the simplest liquid crystalline state, consisting of molecules or particles that have long-range orientational order but lack translational order. Despite this orientational order, the bulk nematic phase is apolar as there are an equal number of molecules oriented parallel and antiparallel.

In the recently discovered ferroelectric nematic (N_F) phase [1-6], the orientational order of the conventional nematic state is augmented by so-called polar order which arises due to parallel alignment of molecular electric dipole moments. This parallel alignment distinguishes it from the nematic phase, and virtually all other fluid states of matter. Depictions of nematic and polar nematic phases are given in Fig. 1.



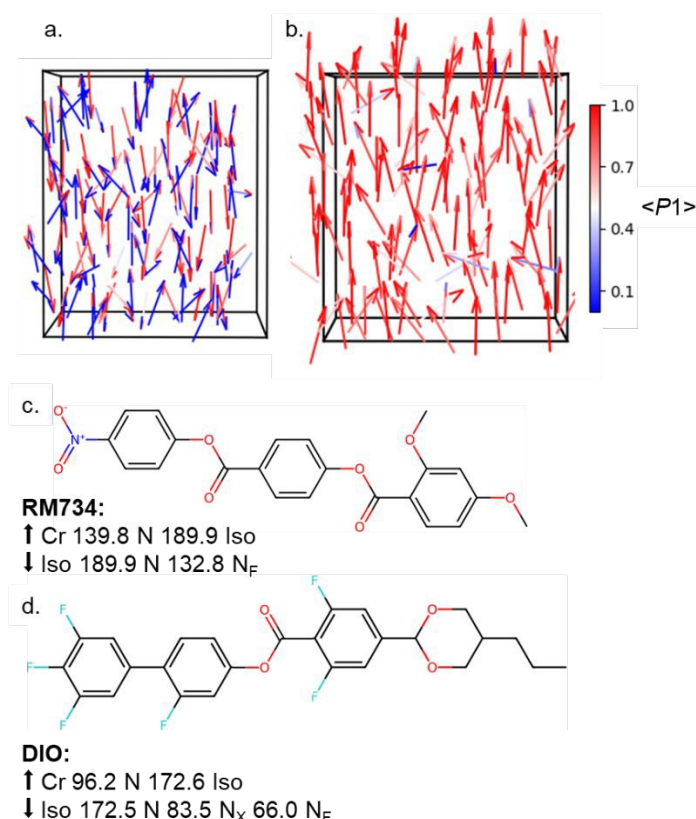


Figure 1: Depictions of the orientations of the molecular electric dipole moments in the (a) nematic and (b) ferroelectric nematic phases; the arrows are color-coded to represent the contribution to the bulk value of the polar order parameter, $\langle P1 \rangle$ which is 0.08 for (a) and 0.86 for (b), respectively, while $\langle P2 \rangle$ is 0.66 and 0.66 for (a) and (b), respectively. In both cases the director is oriented perfectly with the box height (z-axis). The molecular structures of the first reported N_F materials; (c) RM734 [1, 2], and (d) DIO [3] along with their transition temperatures (T, °C) on heating (\uparrow) and cooling (\downarrow)

Having been the subject of some speculation [7-9], the N_F phase has been now experimentally realised in several classes of materials, having originally been observed in RM734 and DIO, (Fig. 1 (c, d)), both reported in 2017. In recent years the number of N_F materials has been increased significantly as derivatives of RM734 and DIO [10-14] have been developed, including those exhibiting a direct I-N_F transition [15].

In RM734 [1, 2] the N-N_F transition is accompanied by a softening of the K₁ splay constant, and a growth of ferroelectric ordering [4, 6]. DIO [3] behaves slightly differently, with an intermediate phase between the N and N_F; crucially however, DIO was also shown to possess these same characteristic macroscopic domains of ferroelectric ordering in the low temperature nematic phase [5]. When studied by DSC, there is a small enthalpy associated with the transition from nematic to polar nematic phase(s). Dielectric measurements have reported large dielectric permittivity values on the order of 10⁴ for RM734[16] and for DIO [3, 17], although the validity of these has been questioned [18, 19]. Polarisation investigations have found values of



spontaneous polarisation for RM734 ($6\mu\text{C}/\text{cm}^2$) [5, 20] and DIO ($2.5\text{--}6\mu\text{C}/\text{cm}^2$) [3, 17] which are comparable with polar columnar ($5.8\mu\text{C}/\text{cm}^2$) [21] and bent core liquid crystals (LCs) ($0.5\text{--}0.8\mu\text{C}/\text{cm}^2$) [22]. The measured N_F spontaneous polarisation values is far larger than typical chiral smectic C materials (e.g. DOBAMBAC, $42.0\text{ nC}/\text{cm}^2$) [23] and somewhat smaller than that achieved by inorganic materials – e.g. the inorganic material $\text{PbSc}_{0.5}\text{Ta}_{0.5}\text{O}_3$ ($30.0\mu\text{C}/\text{cm}^2$) [24].

Our investigations were driven by the predictions of atomistic molecular dynamics (MD) simulations. MD simulations can reproduce the polar nematic ordering and calculate mean densities from atomic scale interactions [25]. Simulations predicted a high mass density, ρ of $1.3\text{ g}/\text{cm}^3$ [25] in RM734. Considering the oft-used assumption that ρ in liquid crystals $\approx 1/\text{cm}^3$, known to be an approximation for some LCs and is unjustified for many others, this raises a potential defining property of N_F materials.

As LCs undergo a first-order phase transition, they exhibit a density change that can be discontinuous [26]. The temperature dependence of density, $\rho(T)$ in a discrete liquid crystal phase can be described by a linear thermal expansion of its specific volume, v_{sp} as described in equation (1) and (2)

$$v_{sp}(T) = 1/\rho(T) \quad (1)$$

$$v_{sp}(T) = v_{sp}^* + \alpha T \quad (2)$$

where v_{sp}^* is the specific volume at 0°C , α is an empirical expansion coefficient describing how the material behaves with temperature changes, and T is the temperature.

The density of LCs has previously been measured by several methods including the capillary tube technique [25], the weight change of a submerged glass cylinder [27] and a dilatometer measuring the height of a mercury interface [28]. These methods all suffer from a difficulty in obtaining the precise temperature control that detailed study over phase transitions demands. Moreover, the lack of experimental density data for all but a handful of common LCs has led to the incorrect (*vide infra*) assumption about ρ being propagated.

Density data were available for 5CB [29–33], 8CB [34–36], and (NCS)PCH6 [37]. A comprehensive list of the data and their properties are given in section 4 of the supplementary information. The 5CB dataset [30] was chosen for comparison with high resolution data (between 5°C and 0.2°C) over a large temperature range. The available data for 8CB consisted of either sparse measurements [35] or data taken over a temperature range near a single transition [34]. The (NCS)PCH6 literature data [37] were used out of necessity as no other data were available. We analyse the agreement of the experimental and literature data through Bland-Altman [38] type plots (SI section S4). We find limits of agreement, l through equation (3) where \bar{d} is the mean difference between our experimental data and its corresponding literature data. σ_d is the standard deviation \bar{d} . Its agreement can then be judged through the data's vicinity to \bar{d} .



$$l = \bar{d} \pm 1.96\sigma_d \quad (3)$$

View Article Online
DOI: 10.1039/D3SM01282D

The largest difference between the agreement comes from a systematic differences between the methods in the capillary tube investigation of 5CB [32] and 8CB [36] where a dilatometer is used. These methods have a systematic difference of approximately 1% and 3% respectively compared to 0.02% [30] and 0.04% [35] of the density meters. This is calculated from the average of the differences used in the Bland-Altman plots (Fig. S9-S17 in SI).

In this article we report an unusually large density ($>1.3\text{gcm}^3$) for a ferroelectric nematic liquid crystal, M5 (Merck Electronics KGaA). A density increase resulting from polar ordering on transition to an N_F state is also shown. We benchmark our results against a set of standard liquid crystals, which we find to be in excellent agreement with the available literature data. Finally, we evaluate potential implications of a large density for liquid crystals by comparing its average refractive index with polar smectic liquid crystals and 5CB. Spontaneous polarisation measurements and an approximation of the polar order of DIO are examined with consideration of the experimentally confirmed N_F density.

Methods and Experimental

Density measurements were performed using an Anton-Paar DMA 4100M densitometer which operates on the oscillating U-tube principle (Fig. 2). A U-shaped borosilicate glass tube is filled with $\approx 1\text{ml}$ material. Samples were loaded using a SGE precision syringe. A syringe heater was used for samples with above-ambient melting points; the syringe outlet was interfaced with the DMA 4100M inlet port using a short section of PTFE tubing with appropriate PEEK/ETFE microfluidic connectors (purchased from Darwin Microfluidics). The presence of bubbles within the tube was assessed through visual inspection. This experimental method requires a large amount of material; however, it can be largely recovered on the completion of the measurements. Recovered material was subjected to purification with a Teledyne Combiflash NextGen 300+ Flash chromatography system and filtration over a 0.2 micron PTFE filter.

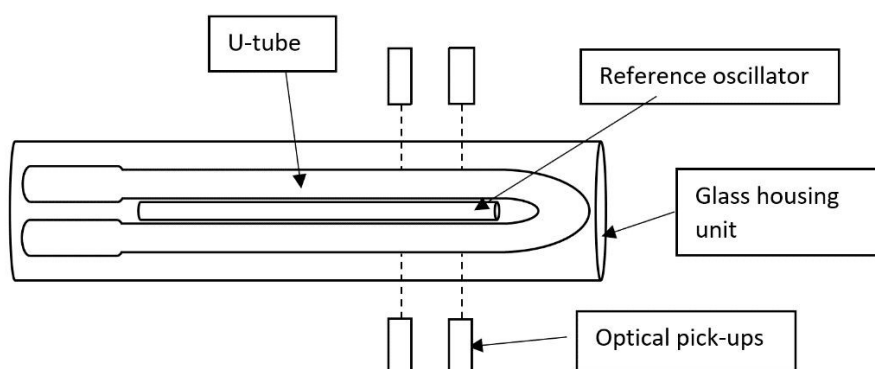


Figure 2. Schematic diagram of the oscillating u-tube setup used to measure density. The optical pickups determine the LC sample's characteristic frequency which corresponds to a density value.



Once filled, the tube is excited to oscillate at its characteristic frequency in the direction of the normal to the tube. The density is calculated from equation (4) View Article Online
DOI: 10.1039/D3SM01282D

$$\rho = A \cdot Q^2 \cdot f_1 - B \cdot f_2 \quad (4)$$

with Q being the quotient of the characteristic frequencies of the measuring tube and a reference tube. A and B are constants specific to the instrument and are calculated by calibrating against substances with a precisely known value for density. f_1 and f_2 are correction factors. The f_1 and f_2 correction factors possess contributions from the viscosity of the sample in the form of damping. An increase in viscosity has an increased damping effect on the characteristic frequency of the oscillating tube, resulting in a greater magnitude of corrections needed. A valid measurement for this machine is three successive measurements that do not deviate beyond 0.0001 g/cm^3 . The repeatability of the temperature during measurement is 0.02°C .

Refractive indices measurements were performed on a Bellingham + Stanley Abbe 60/DR refractometer. The refractometer finds the critical angle of total reflection of an LC sample at a wavelength of 589nm. A polariser is used to differentiate between the ordinary and extraordinary refractive indices. Temperature control is achieved by circulating water with a temperature range from room temperature to $\sim 70^\circ\text{C}$ and an accuracy of $\sim 0.2^\circ\text{C}$.

The temperature dependence of polarisation is measured through its switching current response [39]. A triangular wave voltage with $V_{RMS} = 5\text{V}$ and frequency = 63Hz was produced by an Agilent 33220A waveform generator and applied to DIO in a $4\mu\text{m}$ INSTEC cell with no alignment layer. Temperature control was achieved with a LINKAM THM600 hot stage. The output signal was recorded on RIGOL DHO 4204 oscilloscope. Integration of the current response peaks calculates the P_s through equation 5

$$P_s = \int \frac{I_p}{2AG} dt \quad (5)$$

where I_p is the current due to polarisation reversal, A is the area of the cell and G is the gain of the current-to-voltage amplifier used in the experimental method.

Materials

The materials selected were M5 (Merck Electronics KGaA), 4-cyano-4-pentylbiphenyl (5CB, Fluorochem), 4-cyano-4-octylbiphenyl (8CB, Fluorochem), 1-(trans-4-hexylcyclohexyl)-4-isothiocyanatobenzene ((NCS)PCH6), Sigma-Aldrich and trans-4-(trans-4'-n-propylcyclohexyl)-cyclohexyl-3,4,5-trifluorobenzene (CCU-3-F, prepared according to ref [40]). Both M5 and commercial materials were used as received. Figure 3 presents the transition temperatures for the materials investigated in this work, and chemical structures in the case of single-component materials (Fig. 3a-d). The limits of the density meter's operating temperature range did not allow for measurements of RM734 and DIO.



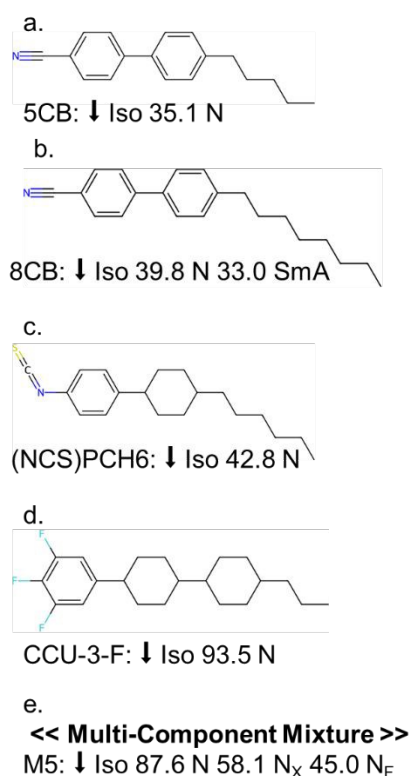


Figure 3. Chemical structures of the materials for which density measurements were undertaken. Transition temperatures (T , °C) on cooling (↓) were determined from density measurements and are in good agreement with DSC data (SI section S1). For single component materials (a-d) molecular structures are given.

Results

Apolar Liquid Crystals

Our initial investigations focused on a set of relatively well-known materials, for some of which density data was available. We selected 5CB as it is an ambient temperature nematic; 8CB as it exhibits a transition between two LC phases (smectic A (SmA), a layered structure and N) and has a high viscosity at ambient temperature; (NCS)PCH6 as a non-nitrile room-temperature nematic LC; CCU-3-F as a fluorinated LC with an above-ambient melting point which enabled us to refine our technique for handling materials with elevated melting points. The temperature-dependent densities for the selected materials are given in Fig. 4.



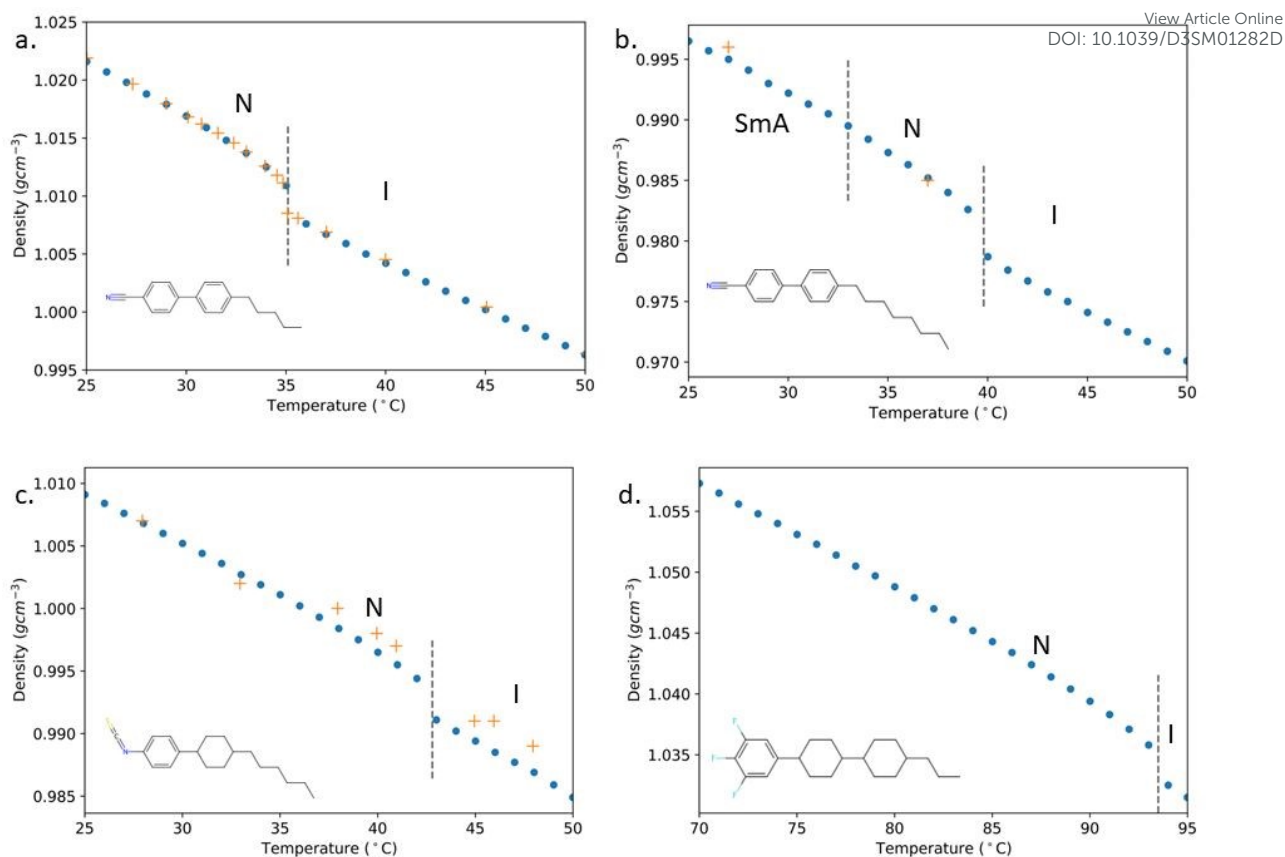


Figure 4. Densities of the liquid crystal materials at 1°C intervals. Dashed lines denote transition temperatures as defined by the temperature of the largest density gradient. The density increases at the phase transition are readily observable for the I-N transitions, but more subtle for the N-SmA transition. Comparison is made with literature data where possible (orange plus points) for (a) 5CB [30], (b) 8CB [35] and (c) (NCS)PCH6 [37]. (d) The CCU-3-F figure is representative of the scarcity of LC density data.

The measurement runs for all materials began in the isotropic phase and were cooled through the phase range into their lowest temperature phase above crystallisation. The present results compare very favourably with available literature data for 5CB, 8CB and (NCS)PCH6. In all cases, the density of the LC materials is around 1 g/cm^3 . The I-N transitions for each material can be clearly observed as discontinuous increase in ρ . At the N-SmA transition (Fig.4 (b)) we do not find a discernible increase in density.

Ferroelectric Nematic Liquid Crystal M5

Having shown our ability to reproduce and expand upon literature densities of common liquid crystals, we next performed density measurements on the room-temperature N_F material M5, a multi-component mixture produced by Merck Electronics KGaA. A cursory inspection of the data in Fig. 5 reveals that, even in the



isotropic liquid, the density of M5 is remarkably high, being $\sim 30\%$ larger than 5CB and of the same magnitude as dichloromethane (1.33 g cm^3 at 25°C). New Article Online
DOI: 10.1039/D3SM01282D

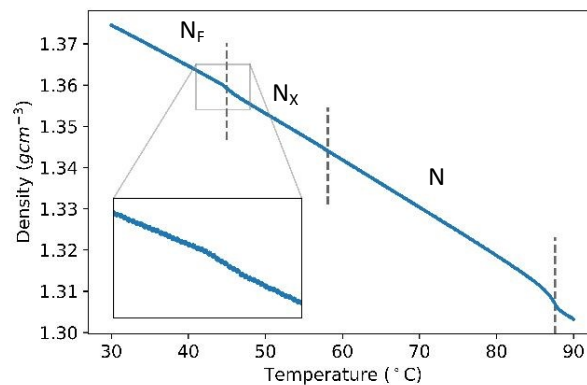


Figure 5. Temperature-dependent density behaviour for the N_F material M5 across its phase range. The initial increase with first nematic ordering is on cooling from the isotropic phase at 87.6°C similar to the other selected materials. There is no discernible change in density at the $N-N_X$ phase transition. There is a small increase at 45°C that can be attributed to the effects of polar ordering. The high average density of M5 should also be noted. Inset: N_X-N_F transition

In M5 there is a constant decrease in the expansion coefficients as it is cooled through its phase range (Table 1). This can also be observed in the rate of density change within the linear regimes of Fig. 5. As with the other materials investigated, an increase in the density can be seen at T_{IN} and this feature is also clear at $T_{N_X N_F}$ though the $T_{N N_X}$ density change appears to be continuous. Fig. 5 presents data obtained at an increased temperature resolution (0.15°C compared to the 1°C given in Fig. 4). The inset facilitates a more detailed look at the behaviour over the N_X-N_F transition where the density increase can be seen.

Material	$\alpha 10^4 \text{ (cm}^3 \text{g}^{-1} \text{K}^{-1}\text{)}$				
	N_F	N_X	SmA	N	I
M5	5.30	6.08	-	6.57	7.09
5CB	-	-	-	9.18	7.96
8CB	-	-	8.16	11.5	8.76
CCU-3-F	-	-	-	7.81	9.00
(NCS)PCH6	-	-	-	8.08	8.80

Table 1. Expansion coefficients, α , of v_{sp} calculated for each material in each phase. These parameters are analogous to the thermal expansion coefficient describing how a material's volume changes with temperature. The parameters are obtained through linear fits to $v_{sp}(T)$ within each specific LC phase.



The linear relationship between density and temperature in a discrete phase can be explored through equation (2). From this, $v_{sp}(T)$ is separated into discrete phases using the transition temperatures in Fig. 4 as their temperature ranges. The gradient of a linear fit of $v_{sp}(T)$ for each phase (see also Fig. S18 in SI) is taken to be the expansion coefficient. Expansion coefficients for the selected materials can be found in table 1. The expansion coefficients are similar, although we do not find an explicit relationship between coefficient and LC phase type as the coefficient can be seen to either increase (5CB, 8CB) or decrease (CCU-3-F, (NCS)PCH6) through the I-N transition.

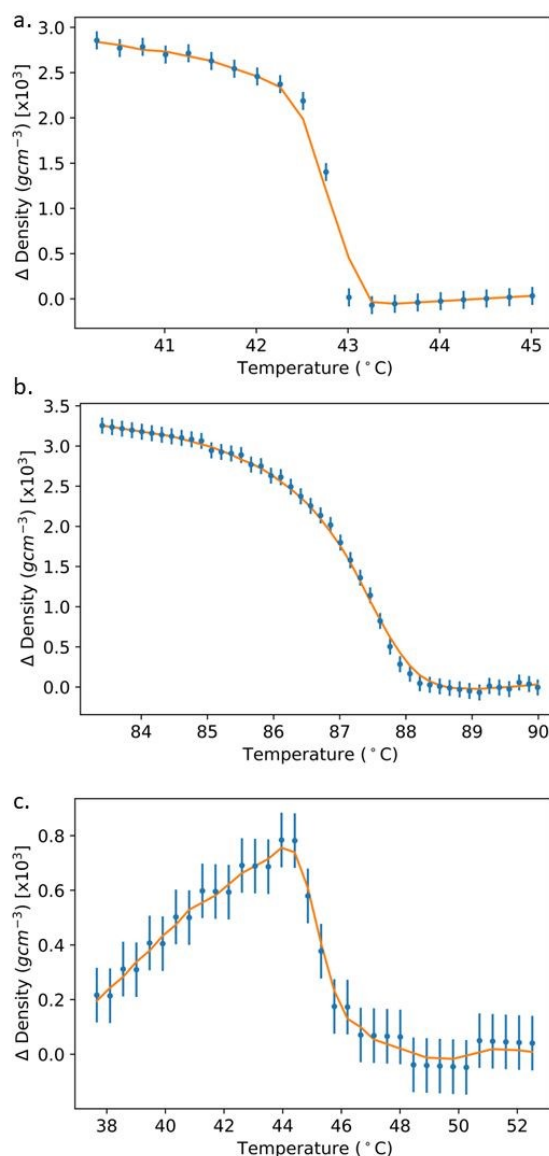


Figure 6. The density deviation ($\Delta\rho = \rho(T) - \rho^{highT}(T)$) through the I-N transition (a, b) of (NCS)PCH6 and M5 respectively. The behaviour in (a, b) is the result of a conventional nematic ordering taking place. C) Shows how the density changes in M5 as a result of polar ordering. Data are presented as scatter points whereas the solid line is a Savitzky-Golay filter [41] smoothing intended to show the trend of $\Delta\rho$.



Material	$\Delta\rho 10^3 (g/cm^3)$			
	I-N	N-N _X	N _X -N _F	N-SmA
M5	3.1	0.05	0.75	-
5CB	2.2	-	-	-
8CB	2.5	-	-	0.20
CCU-3-F	2.0	-	-	-
(NCS)PCH6	2.8	-	-	-

View Article Online
DOI: 10.1039/D3SM01282D

Table 2. The magnitude of the density increases of each transition through the non-linear $\rho(T)$ region. The I-N transitions for all materials are of a similar magnitude as the same sort of ordering takes place. The density change corresponding to M5's N_X-N_F transition is an order of magnitude larger than its N-N_X transition and three times the size of the N-SmA transition of 8CB.

Table 2 gives the density increases for the selected materials. A linear fit of the higher temperature phase ρ^{highT} was extrapolated into the lower temperature phase and used to calculate the density deviation of the lower temperature phase as it cools. The magnitude of change in density that occurs in the non-linear period between two linear regimes is then taken to be the density deviation of that transition. A representative example of this process is given in Fig. S6. The density deviation at (NCS)PCH6's I-N transition can be seen in Fig. 6a. We find $\Delta\rho$ of the I-N transitions for all materials studied to be of the same order of magnitude, presumably a consequence the fact the same type of molecular reorganisation takes place for each material at T_{IN} . For 8CB we find the N-SmA transition is ten times smaller than its I-N transition indicating that the change in molecular packing at the smectic transition is not as a drastic as a nematic one.

M5's increase in density from its I-N and N_X-N_F phase transitions can be seen in Fig. 6 (b, c). The N_X-N_F transition is accompanied by a much smaller density change than that associated with the I-N transition, approximately $0.00075g/cm^3$ vs $0.0031 g/cm^3$ (table 2). The size of this I-N density change is the largest of the investigated materials. The density deviation of the N_X-N_F transition has been calculated at more than three times larger than that of the N-SmA transition. This suggests a significant structural reorganisation taking place through polar ordering when compared to that of the positional ordering of the N-SmA transition. It is interesting to note that M5 does not follow the loose positive correlation between density increase and transitional enthalpy (supplementary table 2), perhaps due to its composition as a mixture.

Implications of a Large Liquid Crystal Density



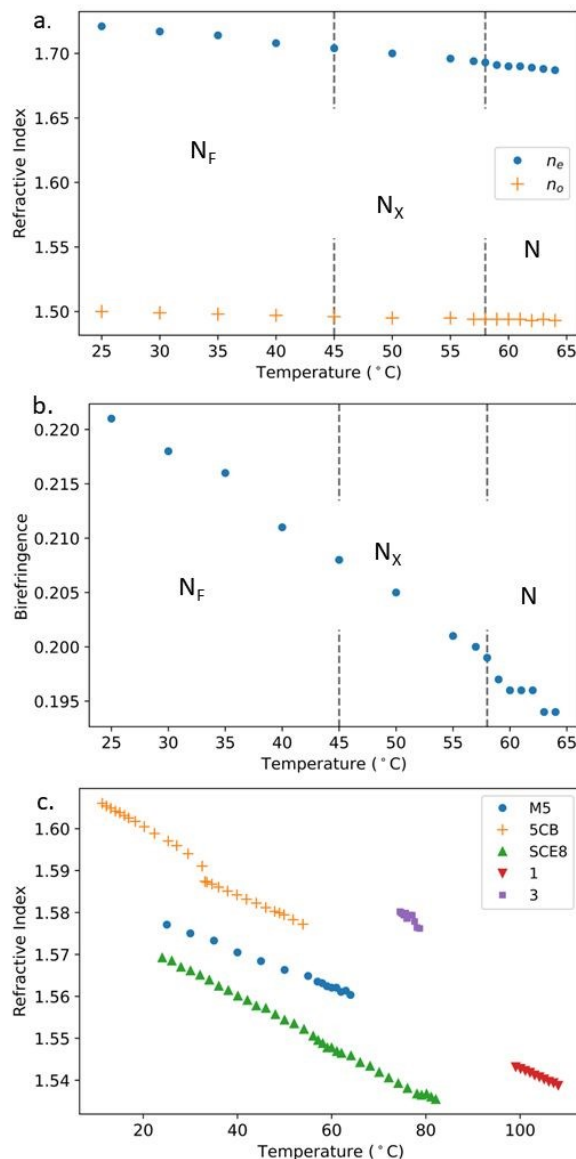


Figure 7. a) The n_o and n_e measurements of M5 at 589nm as the sample is cooled through its N-N_X-N_F phase sequence. b) The resulting birefringence ($\Delta n = n_e - n_o$) values of M5. c) A comparison is made of n_{avg} for M5 and 5CB [42] as well as the polar smectics, SCE8 [43] and compounds **1** and **3** from [44, 45].

As the refractive index (or indices) of a material with induced dipoles depends significantly upon the density according to the Lorentz-Lorenz equation [46], it is interesting to explore whether the anomalously high density and the highly polar nature of M5 (and potentially other N_F materials) impacts their optical properties. We measured the refractive indices and birefringence of M5, finding the latter to be comparable to DIO [47] (but smaller than RM734 [5, 25]); see Figure 7. Due to the temperature limits of the experimental method employed in this work, measurements were performed a significant distance from the I-N transition. Therefore, a pre-transitional monotonic reduction is not observed in the extraordinary, n_e , and ordinary, n_o , refractive indices as the system is heated towards the isotropic phase.



Here, we focus on n_{avg} as n_o , n_e and Δn are more strongly linked to the order parameter. Fig. 7 (c) shows the n_{avg} as calculated by equation (6) for M5.

View Article Online
DOI: 10.1039/D3SM01282D

$$n_{avg} = \sqrt{\frac{2n_o^2 + n_e^2}{3}} \quad (6)$$

We find that n_{avg} is smaller than the equivalent values for the standard nematogen 5CB, a material $\approx 30\%$ less dense than M5 [42]. Here we see direct evidence of contributions from the permanent dipole moments of a highly polar system influencing the refractive indices of a material. The observations of M5 and 5CB where an increased density does not result in a larger n_{avg} confirms that Lorentz-Lorenz equation does not adequately explain/ should not be used in the explaining the behaviour of polar liquid crystal materials. To identify any relationship between n_{avg} and spontaneous polarisation M5 is compared with literature n_{avg} data for the polar smectics SCE8 ($P_s \approx 50 \text{ nCcm}^{-2}$) [43] and compounds **1** and **3** ($P_s \approx 150 \text{ nCcm}^{-2}$) from [44, 45] (structures and phase sequences are given in SI section 6). There is a scattering of values with M5 and its polarisation magnitude of $\approx 5.5 \mu\text{Ccm}^{-2}$ [48] resulting in a lower n_{avg} than the less polar compound **3** indicating there is no such relationship.

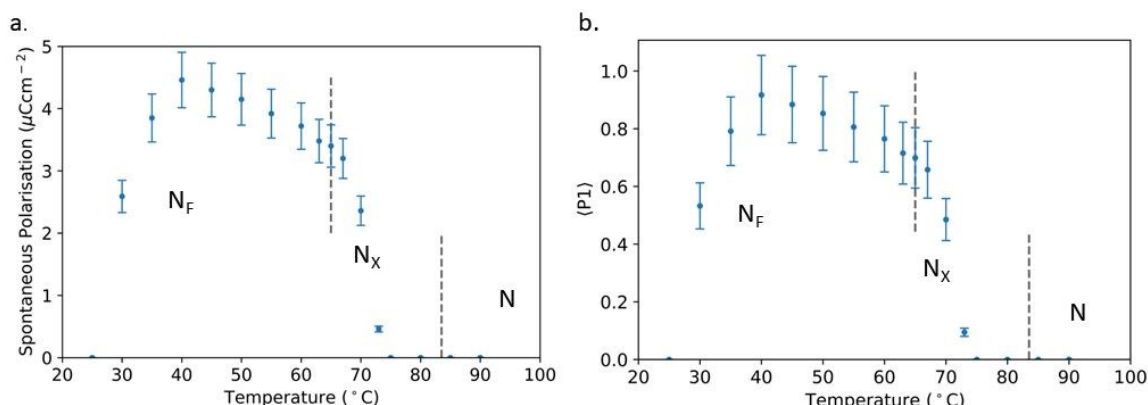


Figure 8. a) Spontaneous polarisation measurements of DIO (see Fig. 1 for DIO's structure and phase sequence) on cooling through its N_F - N_X - N phase sequence until crystallisation. Switching current response peaks are integrated to give the magnitude of polarisation. b) An approximation of $\langle P1 \rangle$ for DIO from the contribution of average molecular dipole alignment to the polarisation.

It is possible to use measurements of the density and spontaneous polarisation in a ferroelectric material, together with knowledge of the molecular dipole moment to deduce a value for the polar order parameter $\langle P1 \rangle$. In this case, as M5 is a multicomponent material of unknown composition it was impossible to measure the polar order. However, as there is a clear indication from simulations that DIO also has a density of 1.3 g/cm^3 , and our measurements of M5, show that such a high value is indeed realistic, the approach was used for that pure material in approximating the polar order parameter. If we consider polarisation as the number density of electric dipoles per unit volume, then we can infer that a larger density will increase the measured polarisation. Following this, we have approximated the polar



order parameter of DIO, $\langle P1 \rangle$ through temperature-dependent spontaneous polarisation measurements (Fig. 8). We define $\langle P1 \rangle$ in equation (7). View Article Online
DOI: 10.1039/D3SM01282D

$$\langle P1 \rangle = \frac{P_s}{P_{max}} \quad (7)$$

where P_s is the spontaneous polarisation. P_{max} is given in equation (8)

$$P_{max} = \frac{\mu_{calc} \rho N_A}{M} \quad (8)$$

where μ_{calc} is the dipole moment calculated at the B3LYP/6-31G(d, p) level of DFT [49, 50], M is the molecular mass, ρ is the density (1.3 g/cm^3) and N_A is Avogadro's number. Calculating $\langle P1 \rangle$ from a P_s measurement approximates the average contribution of the molecular dipole alignment to the P_s where a bulk material with perfect polar order ($\langle P1 \rangle = 1$) gives P_{max} .

As can be seen in Fig. 8, DIO's N phase produces zero measured polarisation values and thus possesses no polar order. On cooling through the N_x phase, some average polar order begins to grow at and below 73°C , resulting in net polarisation. Within the N_F phase the polarisation can be seen to increase until it saturates at a $4.5 \mu\text{Ccm}^{-2} \pm 10\%$. This produces a $\langle P1 \rangle$ of $0.91 \pm 15\%$ with the increased error accounting for any density changes due to a temperature change. As this material is being supercooled, the polarisation decreases past the saturation point until crystallisation and it no longer provides any measured response.

Recalculating with a conventional density assumption of 1 g/cm^3 results in an unphysical $\langle P1 \rangle$ of 1.19. It may be of note that reliable density and polarisation measurements as well a realistic assumption for a maximum P1 order parameter would provide a method for the experimental approximation of dipole moments. From a material design perspective, equation (8) provides a means to estimate P_s directly from electronic structure calculations, although this does not mean that a given material will generate and sustain polar ordering. Additionally, knowledge of the density of a typical N_F material enables the use of equation (8) to check the physical validity of measured P_s values which, for a given material, are limited by the dipole moment and density.

Conclusions

We have shown that the density of the N_F material M5 is significantly larger than conventional liquid crystals, a finding that is in keeping with that determined in the atomistic MD simulations [25]. Here, we find that the N_F material M5 possesses a much higher density ($\sim 1.3 \text{ g/cm}^3$) than that of conventional nematic systems where the density is assumed (and found) to be $\sim 1 \text{ g/cm}^3$. We also observe experimentally an increase in density on entering the N_F phase which is comparable to that seen in silico [25].

Refractive indices measurements of M5 were used to examine the relationship between density, polarisation magnitude and n_{avg} . M5, while being $\approx 30\%$ denser



than 5CB, possesses a lower n_{avg} . We believe this to be a result of M5's highly polar nature. M5 was compared to polar smectic liquid crystals with the polarisation magnitude possessing no direction correlation with n_{avg} . The $\langle P1 \rangle$ of D10 is approximated from temperature-dependent spontaneous polarisation measurements. The calculation of $\langle P1 \rangle$ includes the simulation supported and now experimentally verified density value for an N_F material.

For classical apolar liquid crystals it is customary to assume a density of 1 g/cm^3 if required for measurement or analysis. In the case of N_F materials, we suggest that, in the absence of data for a specific material, a value of 1.3 g/cm^3 be used.

Acknowledgements

The authors thank Merck Electronics KGaA for gifting the sample of M5 used in this work, and for their continued partnership and support. HFG thanks EPSRC for funding via grant number EP/V054724/1. RJM thanks UKRI for funding via a Future Leaders Fellowship, grant number MR/W006391/1, and UoL for funding a PhD studentship for CPB. The authors all thank Diana Nikolova of the University of Leeds for providing DSC data for M5.

References

- [1] R. J. Mandle, S. J. Cowling, and J. W. Goodby, "Rational Design of Rod-Like Liquid Crystals Exhibiting Two Nematic Phases," *Chemistry – A European Journal*, vol. 23, no. 58, pp. 14554-14562, 2017, doi: <https://doi.org/10.1002/chem.201702742>.
- [2] R. J. Mandle, S. J. Cowling, and J. W. Goodby, "A nematic to nematic transformation exhibited by a rod-like liquid crystal," *Physical Chemistry Chemical Physics*, 10.1039/C7CP00456G vol. 19, no. 18, pp. 11429-11435, 2017, doi: 10.1039/C7CP00456G.
- [3] H. Nishikawa *et al.*, "A Fluid Liquid-Crystal Material with Highly Polar Order," *Advanced Materials*, vol. 29, no. 43, Nov 2017, Art no. 1702354, doi: 10.1002/adma.201702354.
- [4] A. Mertelj *et al.*, "Splay Nematic Phase," *Physical Review X*, vol. 8, no. 4, p. 041025, 11/12/ 2018, doi: 10.1103/PhysRevX.8.041025.
- [5] X. Chen *et al.*, "First-principles experimental demonstration of ferroelectricity in a thermotropic nematic liquid crystal: Polar domains and striking electro-optics," *Proceedings of the National Academy of Sciences of the United States of America*, vol. 117, no. 25, pp. 14021-14031, Jun 2020, doi: 10.1073/pnas.2002290117.
- [6] N. Sebastián *et al.*, "Ferroelectric-Ferroelastic Phase Transition in a Nematic Liquid Crystal," *Physical Review Letters*, vol. 124, no. 3, p. 037801, 01/21/ 2020, doi: 10.1103/PhysRevLett.124.037801.
- [7] F. C. Frank, "I. Liquid crystals. On the theory of liquid crystals," *Discussions of the Faraday Society*, vol. 25, pp. 19-28, 1958.
- [8] H. Pleiner and H. Brand, "Spontaneous splay phases in polar nematic liquid crystals," *Europhysics Letters*, vol. 9, no. 3, p. 243, 1989.
- [9] M. Born, "Sitzungsber. Preuss. Akad Wiss," 1916.
- [10] J. Li *et al.*, "General phase-structure relationship in polar rod-shaped liquid crystals: Importance of shape anisotropy and dipolar strength," *Giant*, vol. 11, p. 100109, 2022/08/01/ 2022, doi: <https://doi.org/10.1016/j.giant.2022.100109>.
- [11] E. Cruickshank, R. Walker, J. M. D. Storey, and C. T. Imrie, "The effect of a lateral alkyloxy chain on the ferroelectric nematic phase," *RSC Advances*, 10.1039/D2RA05628C vol. 12, no. 45, pp. 29482-29490, 2022, doi: 10.1039/D2RA05628C.
- [12] Y. Song *et al.*, "Development of emergent ferroelectric nematic liquid crystals with highly fluorinated and rigid mesogens," *Physical Chemistry Chemical Physics*, 10.1039/D2CP01110G vol. 24, no. 19, pp. 11536-11543, 2022, doi: 10.1039/D2CP01110G.
- [13] R. Saha *et al.*, "Multiple ferroelectric nematic phases of a highly polar liquid crystal compound," *Liquid Crystals*, pp. 1-13, 2022, doi: 10.1080/02678292.2022.2069297.
- [14] S. Dai, J. Li, J. Kougo, H. Lei, S. Aya, and M. Huang, "Polar Liquid Crystalline Polymers Bearing Mesogenic Side Chains with Large Dipole Moment," *Macromolecules*, vol. 54, no. 13, pp. 6045-6051, 2021/07/13 2021, doi: 10.1021/acs.macromol.1c00864.
- [15] A. Manabe, M. Bremer, and M. Kraska, "Ferroelectric nematic phase at and below room temperature," *Liquid Crystals*, vol. 48, no. 8, pp. 1079-1086, 2021/06/21 2021, doi: 10.1080/02678292.2021.1921867.
- [16] J. Li *et al.*, "Development of ferroelectric nematic fluids with giant- ϵ ; dielectricity and nonlinear optical properties," *Science Advances*, vol. 7, no. 17, p. eabf5047, 2021, doi: doi:10.1126/sciadv.abf5047.
- [17] S. Brown *et al.*, "Multiple Polar and Non-polar Nematic Phases," *ChemPhysChem*, vol. 22, no. 24, pp. 2506-2510, 2021, doi: <https://doi.org/10.1002/cphc.202100644>.
- [18] N. A. Clark, X. Chen, J. E. MacLennan, and M. A. Glaser, "Dielectric spectroscopy of ferroelectric nematic liquid crystals: Measuring the capacitance of insulating interfacial layers," *arXiv preprint arXiv:2208.09784*, 2022.
- [19] A. Erkořeka, J. Martínez-Perdiguero, R. J. Mandle, A. Mertelj, and N. Sebastián, "Dielectric spectroscopy of a ferroelectric nematic liquid crystal and the effect of the sample thickness," *Journal of Molecular Liquids*, vol. 387, p. 122566, 2023/10/01/ 2023, doi: <https://doi.org/10.1016/j.molliq.2023.122566>.



- [20] X. Chen *et al.*, "Ideal mixing of paraelectric and ferroelectric nematic phases in liquid crystals of distinct molecular species," *Liquid Crystals*, vol. 49, no. 11, pp. 1531-1544, 2022/09/02 2022, doi: 10.1080/02678292.2022.2058101. DOI: 10.1039/D3SM01282D
- [21] H. Takezoe and F. Araoka, "Polar columnar liquid crystals," *Liquid Crystals*, vol. 41, no. 3, pp. 393-401, 2014/03/04 2014, doi: 10.1080/02678292.2013.834079.
- [22] R. A. Reddy and C. Tschierske, "Bent-core liquid crystals: polar order, superstructural chirality and spontaneous desymmetrisation in soft matter systems," *Journal of Materials Chemistry*, 10.1039/B504400F vol. 16, no. 10, pp. 907-961, 2006, doi: 10.1039/B504400F.
- [23] K. Yoshino, M. Ozaki, T. Sakurai, K. Sakamoto, and M. Honma, "Ferroelectric Liquid Crystal with Extremely Large Spontaneous Polarization," *Japanese Journal of Applied Physics*, vol. 23, no. 3A, p. L175, 1984/03/01 1984, doi: 10.1143/JJAP.23.L175.
- [24] B. Nair *et al.*, "Large electrocaloric effects in oxide multilayer capacitors over a wide temperature range," *Nature*, vol. 575, no. 7783, pp. 468-472, 2019/11/01 2019, doi: 10.1038/s41586-019-1634-0.
- [25] R. J. Mandle, N. Sebastián, J. Martínez-Perdiguero, and A. Mertelj, "On the molecular origins of the ferroelectric splay nematic phase," *Nature Communications*, vol. 12, no. 1, p. 4962, 2021/08/16 2021, doi: 10.1038/s41467-021-25231-0.
- [26] P.-G. d. Gennes, *The physics of liquid crystals* (The international series of monographs on physics). Oxford: Clarendon Press, 1974.
- [27] M. J. Press and A. S. Arrott, "Expansion Coefficient of Methoxybenzylidene Butylaniline through the Liquid-Crystal Phase Transition," *Physical Review A*, vol. 8, no. 3, pp. 1459-1465, 09/01/ 1973, doi: 10.1103/PhysRevA.8.1459.
- [28] S. Torza and P. E. Cladis, "Volumetric Study of the Nematic-Smectic-A-Transition of N--Cyanobenzylidene-p-Octyloxylaniline," *Physical Review Letters*, vol. 32, no. 25, pp. 1406-1409, 06/24/ 1974, doi: 10.1103/PhysRevLett.32.1406.
- [29] G. A. Oweimreen, A. K. Shihab, K. Halhouli, and S. F. Sikander, "Density Measurements in the Nematic and Isotropic Phases of 5CB and Dilute Solutions of Tetraethylmethane in 5CB," *Molecular Crystals and Liquid Crystals*, vol. 138, no. 1, pp. 327-338, 1986/08/01 1986, doi: 10.1080/00268948608071767.
- [30] R. Shimada and H. Watanabe, "Thermodynamic Effect on Viscosity and Density of a Mixture of 4-Cyano-4'-pentylbiphenyl (5CB) with Dilute Dimethyl Phthalate (DMP)," *Nihon Reorogi Gakkaishi*, vol. 48, no. 4, pp. 199-206, 2020, doi: 10.1678/rheology.48.199.
- [31] H. R. Zeller, "Dielectric relaxation in nematics and Doolittle's law," *Physical Review A*, vol. 26, no. 3, pp. 1785-1787, 09/01/ 1982, doi: 10.1103/PhysRevA.26.1785.
- [32] M. Tintaru, R. Moldovan, T. Beica, and S. Frunza, "Surface tension of some liquid crystals in the cyanobiphenyl series," *Liquid Crystals*, vol. 28, no. 5, pp. 793-797, 2001/05/01 2001, doi: 10.1080/02678290010025459.
- [33] J. Deschamps, J. P. M. Trusler, and G. Jackson, "Vapor Pressure and Density of Thermotropic Liquid Crystals: MBBA, 5CB, and Novel Fluorinated Mesogens," *The Journal of Physical Chemistry B*, vol. 112, no. 13, pp. 3918-3926, 2008/04/01 2008, doi: 10.1021/jp711211w.
- [34] G. A. Oweimreen, "On the Nature of the Smectic A-to-Nematic Phase Transition of 8CB," *The Journal of Physical Chemistry B*, vol. 105, no. 35, pp. 8417-8419, 2001/09/01 2001, doi: 10.1021/jp011749e.
- [35] D. A. Dunmur, M. R. Manterfield, W. H. Miller, and J. K. Dunleavy, "The Dielectric and Optical Properties of the Homologous Series of Cyano-Alkyl-Biphenyl Liquid Crystals," *Molecular Crystals and Liquid Crystals*, vol. 45, no. 1-2, pp. 127-144, 1978/01/01 1978, doi: 10.1080/00268947808084998.
- [36] A. J. Leadbetter, J. L. A. Durrant, and M. Rugman, "The Density Of 4 n-Octyl-4-Cyano-Biphenyl (8CB)," *Molecular Crystals and Liquid Crystals*, vol. 34, no. 10, pp. 231-235, 1976/10/01 1976, doi: 10.1080/15421407708083712.
- [37] W. Baran, Z. Raszewski, R. Dabrowski, J. Kedzierski, and J. Rutkowska, "Some Physical Properties of Mesogenic 4-(trans-4'-n-Alkylcyclohexyl) Isothiocyanatobenzenes," *Molecular Crystals and Liquid Crystals*, vol. 123, no. 1, pp. 237-245, 1985/02/01 1985, doi: 10.1080/00268948508074781.
- [38] D. G. Altman and J. M. Bland, "Measurement in Medicine: The Analysis of Method Comparison Studies," *Journal of the Royal Statistical Society. Series D (The Statistician)*, vol. 32, no. 3, pp. 307-317, 1983, doi: 10.2307/2987937.
- [39] P. Martinot-Lagarde, "Direct electrical measurement of the permanent polarization of a ferroelectric chiral smectic C liquid crystal," (in English), *Journal de Physique Lettres*, vol. 38, no. 1, pp. 17-19, 1977 1977, doi: 10.1051/jphyslet:0197700380101700.
- [40] D. Demus, Y. Goto, S. Sawada, E. Nakagawa, H. Saito, and R. Tarao, "Trifluorinated Liquid Crystals for TFT Displays," *Molecular Crystals and Liquid Crystals Science and Technology. Section A. Molecular Crystals and Liquid Crystals*, vol. 260, no. 1, pp. 1-21, 1995/02/01 1995, doi: 10.1080/10587259508038680.
- [41] A. Savitzky and M. J. E. Golay, "Smoothing and Differentiation of Data by Simplified Least Squares Procedures," *Analytical Chemistry*, vol. 36, no. 8, pp. 1627-1639, 1964/07/01 1964, doi: 10.1021/ac60214a047.
- [42] J. Li, S. Gauza, and S.-T. Wu, "Temperature effect on liquid crystal refractive indices," *Journal of Applied Physics*, vol. 96, no. 1, pp. 19-24, 2004, doi: 10.1063/1.1757034.
- [43] J. C. Jones, "On the biaxiality of smectic C and ferroelectric liquid crystals," *Liquid Crystals*, vol. 42, no. 5-6, pp. 732-759, 2015/06/03 2015, doi: 10.1080/02678292.2015.1028492.
- [44] N. W. Roberts *et al.*, "An experimental and theoretical investigation into the reflection spectra of SmC* and SmC A* phases," *Journal of Materials Chemistry*, vol. 13, no. 2, pp. 353-359, 2003.
- [45] J. Mills, R. Miller, H. Gleeson, A. Seed, M. Hird, and P. Styring, "The physical properties of a series of antiferroelectric heterocyclic esters," *Molecular Crystals and Liquid Crystals Science and Technology. Section A. Molecular Crystals and Liquid Crystals*, vol. 303, no. 1, pp. 145-152, 1997.
- [46] E. Talebian and M. Talebian, "A general review on the derivation of Clausius-Mossotti relation," *Optik*, vol. 124, no. 16, pp. 2324-2326, 2013, doi: 10.1016/j.ijleo.2012.06.090.
- [47] N. Yadav, Y. P. Panarin, W. H. Jiang, G. H. Mehl, and J. K. Vij, "Spontaneous mirror symmetry breaking and chiral segregation in the achiral ferronematic compound DIO," *Physical Chemistry Chemical Physics*, vol. 25, no. 13, pp. 9083-9091, Mar 2023, doi: 10.1039/d3cp00357d.
- [48] P. J. Tippling, "Liquid Crystals for Energy Applications," 2022.
- [49] A. D. Becke, "Density-functional thermochemistry. III. The role of exact exchange," *The Journal of Chemical Physics*, vol. 98, no. 7, pp. 5648-5652, 1993, doi: 10.1063/1.464913.
- [50] V. A. Rassolov, M. A. Ratner, J. A. Pople, P. C. Redfern, and L. A. Curtiss, "6-31G* basis set for third-row atoms," *Journal of Computational Chemistry*, vol. 22, no. 9, pp. 976-984, 2001, doi: <https://doi.org/10.1002/jcc.1058>.



View Article Online
DOI: 10.1039/D3SM01282D

Open Access Article. Published on 19 December 2023. Downloaded on 12/20/2023 11:57:26 AM.
This article is licensed under a Creative Commons Attribution 3.0 Unported Licence.



Soft Matter Accepted Manuscript