



Performance of cementitious systems containing calcined clay in a chloride-rich environment: a review by TC-282 CCL

Yuvaraj Dhandapani · Alisa Machner · William Wilson · Wolfgang Kunther · Sumaiya Afroz · Taehwan Kim · Franco Zunino · Shiju Joseph · Fragkoulis Kanavaris · Arnaud Castel · Karl-Christian Thienel · Edgardo F. Irassar · Shashank Bishnoi · Fernando Martirena · Manu Santhanam

Received: 24 April 2024 / Accepted: 2 July 2024 / Published online: 23 July 2024
© Crown 2024

Abstract In this review by TC- 282 CCL, a comprehensive examination of various facets of chloride ingress in calcined clay-based concrete in aggressive chloride-rich environments is presented due to its

This article was prepared within the framework of RILEM TC 282-CCL. The article has been reviewed and approved by all members of the TC.

TC Membership: Chair: Fernando Martirena-Hernandez, Cuba; Deputy Chair: Manu Santhanam, India
Members: Eduardo Irassar, Argentina; Arnaud Castel, David Law, Taehwan Kim, Vinh Dao, Australia; Sumaiya Afroz, Bangladesh; Jan Elsen, Ruben Snellings, Belgium; Silvia Viera, Brazil; Arezki Tagnit-Hamou, William Wilson, Abdelmoujib Bahhou, Canada; Zengfeng Zhao, China; Adrian Alujas, Roger Samuel Almenares Reyes Cuba; Andrés Camilo Camilo Diaz Garcia, Oscar Oswaldo VÁSQUEZ, Colombia; Joergen Skibsted; Wolfgang Kunther, Mariana Canut, Denmark; Fabrizio Moro, Francois Avet, Gabriel Pham, Gilles Escadeillas, Pascal Dion, Pascal Boustingorry, Victor Poussardin, France; Alisa Machner, Frank Dehn, Karl-Christian Thienel, Matthias Maier, Mohsen Ben Haha, Germany; Luis Velasquez, Guatemala; Ravindra Gettu, Shashank Bishnoi, Talakokula Visalakshi, Tushar Bansal, India; Luca Valentia, Italy; Joseph Marangu, Kenya; J Ivan Escalante-García, Mexico; Mohamed Boufous, Morocco, Roman Jaskulski, Poland; Angela Nunes, Manuel Vieira, Karyne Santos, Portugal; Guoqing Geng, Singapore; Adrian Alujas-Diaz, Spain; John Provis, Franco Zunino, Karen Scrivener, Switzerland; Daniel Geddes, Wenzhong Zhu, Fragkoulis Kanavaris, Susan Bernal Lopez, Shiju Joseph, Theodore Hanein, Wenzhong Zhu, Yuvaraj Dhandapani, UK; Anuj Parashar, Claire White, Elsa Qoku, Maria C.G. Juenger,

significance in making reinforced concrete structures susceptible to chloride-induced corrosion damages. The review presents a summary of available literature focusing on materials characteristics influencing the chloride resistance of calcined clay-based concrete, such as different clay purity, kaolinite content and other clay minerals, underscoring the significance of pore refinement, pore solution composition, and chloride binding mechanisms. Further, the studies dealing with the performance at the concrete scale, with a particular emphasis on transport properties, curing methods, and mix design, are highlighted. Benchmarking calcined clay mixes with fly ash or slag-based concrete mixes that are widely used in aggressive chloride conditions instead of OPC is recommended. Such comparison could extend the usage of calcined clay as a performance-enhancing mineral admixture in the form of calcined clay or LC2 (limestone-calcined clay). The chloride diffusion coefficient in calcined clay concrete is reported to be significantly lower (about 5–10 times in most literature available

Kyle Riding, USA.

Y. Dhandapani (✉)
School of Civil Engineering, University of Leeds, Leeds, UK
e-mail: Y.dhandapani@leeds.ac.uk



so far) compared to OPC, and even lower compared to fly ash and slag-based concrete at early curing ages reported across recent literature made with different types of cements and concrete mixes. Limited studies dealing with reinforcement corrosion point out that calcined clay delays corrosion initiation and reduces corrosion rates despite the reduction in critical chloride threshold. Most of these results on corrosion performance are mainly from laboratory studies and warrant field evaluation in future. Finally, two case studies demonstrating the application of calcined clay-based concrete in real-world marine exposure conditions are discussed to showcase the promising potential of employing low-purity calcined clay-based concrete for reducing carbon footprint and improving durability performance in chloride exposure.

Keywords Calcined clay · Chloride exposure · Diffusion · Migration · Field exposure

1 Introduction

Chloride-induced corrosion is one of the major durability concerns for reinforced concrete structures [1, 2], specifically for large concrete infrastructure [3, 4]. It leads to significant maintenance

and repair costs and also increases the demand for cement-based materials for the repair and replacement of concrete to maintain the intended service life [5, 6]. It is well understood that cementitious systems with reactive supplementary cementitious materials (SCMs), including fly ashes, slags, silica fume and calcined clays, could have very good resistances against chloride ingress and chloride-induced corrosion based on a large volume of literature on traditional SCMs in the past decades [7–11]. However, calcined clay encompasses a large family of materials with different properties, including purity, mineralogy and reactivity, and is often used in composite multi-component cementitious systems (i.e., in binary forms or in combination with other resources), which could affect physical, chemical and mineralogical characteristics of hydrated cementitious matrix that control the performance [12–21]. Although there is documented evidence of calcined clays being studied and utilised as cement substitutes since the 1950s, large volumes of fly ash availability from thermal power plants led to the wide adoption of fly ash based blended cements in the past few decades [22–29]. Clays belong to the group of phyllo-silicates, which consist of alternating layers of octahedrally coordinated aluminium and tetrahedrally coordinated silicon.

A. Machner
Technical University of Munich, TUM School
of Engineering and Design, Department of Materials
Engineering, Professorship for Mineral Construction
Materials, Munich, Germany

W. Wilson
Université de Sherbrooke, Sherbrooke, QC, Canada

W. Kunther
Technical University of Denmark, Kongens Lyngby,
Denmark

S. Afroz
Bangladesh University of Engineering and Technology,
Dhaka, Bangladesh

T. Kim
University of New South Wales, Sydney, Australia

F. Zunino
ETH Zurich, Zurich, Switzerland

S. Joseph
University of Cambridge, Cambridge, UK

F. Kanavaris
Technical Specialist Services, Materials, Arup, London,
UK

A. Castel
University of Technology Sydney, Sydney, Australia

K.-C. Thienel
Universität Der Bundeswehr Munich, Neubiberg, Germany

E. F. Irassar
Universidad Nacional del Centro de La Provincia de
Buenos Aires, Tandil, Argentina

S. Bishnoi
Department of Civil Engineering, IIT Delhi, New Delhi,
Delhi, India

F. Martirena
UCLV Cuba, Santa Clara, Cuba

M. Santhanam (✉)
Department of Civil Engineering, IIT Madras, Chennai,
India
e-mail: manusanthanam@gmail.com



Clays are complex with various levels of purities, clay mineralogy, and differences in associated minerals, and a detailed summary of the composition and reactivity of clays are discussed in [30–32]. In the context of this paper, low-purity clays are classified as clays that are not commercial metakaolin, henceforth will include clays with lower kaolinite content in them and/or with other impurities or associated minerals and/or mixed clays with more than one dominant clay mineral. Kaolinitic clays, known as 1:1 clays based on Si:Al ratio, is known to be more reactive in comparison to 2:1 clays, such as illite, smectite, etc. [16, 18]. Previous reviews from RILEM TC 282-CCL summarised a range of information related to calcined clay and calcined clay-based cement/concrete, including the mineralogy and availability of clays [30, 31], activation treatment for clays [33], hydration and blend design [34], and fresh and hardened concrete properties [35–37]. The use of calcined clay is acknowledged as natural calcined pozzolana in many existing standards worldwide [38–42] and a more detailed review on the standardisation of calcined clay was carried out by this TC, highlighting potential routes for adopting calcined clay for low clinker cement and calcined clay as manufactured pozzolana [43].

The mineralogy of the calcined clays used as SCMs has several effects on the hydrated phase assemblage and microstructure of hydrated cementitious systems in addition to their workability and strength development [16, 32, 34, 35, 37, 44]. Clay sources including alternative clay types [25, 45–52] and mixed clays containing kaolinite with other clay minerals from sources such as mine tailing, excavation soil, etc. [53–58] and marine clays from excavation and dredging [59, 60] are also increasingly explored due to their wide availability. The chemical and mineralogical composition of the clays used as raw materials influences the phase assemblage formed by the reaction of the calcined clays in the blended Portland cementitious system [12, 16, 61, 62]. Generally, 1:1 clays are known to be more reactive than 2:1 clays [16, 32, 52]. Kaolinite clays are often reported to be more reactive than other clay types, and the higher reactivity, degrees of reaction lead to a denser microstructure [49, 63] and the formation of increased quantities of calcium aluminoferrite hydrate phases (e.g. AFm phases or AFt phases) [20, 64–66] and an increase in the aluminium incorporation into the

C–S–H phase [67, 68]. The type of calcium aluminoferrite hydrates formed depends largely on the availability of sulfates, carbonates or chloride ions in the pore solution [20, 64, 69–72]. The majority of reports on calcined clays have focused on kaolinitic 1:1 clays and their combination with limestone as SCMs [49, 52, 63, 73, 74]. Although an increased replacement of limestone in these binders will lead to differences in phase assemblages and significant variations in strength and permeability depending on the calcined clay-to-limestone ratio [74–76], higher limestone content may lead to a dilution in the reaction products and may result in reduced performance in some instances [74, 77–81]. Besides calcined clay usage to produce limestone calcined clay cement (LC3), there is also increasing interest in using calcined clay as manufactured pozzolan in the form of LC2 (i.e., limestone calcined clay mixture) directly in concrete production as performance enhancers or mineral admixture to produce concrete with improved resistance to chloride and lower CO₂ footprint of the concrete [43, 82, 83].

In this review by RILEM TC 282-CCL, the suitability of calcined clay-based concrete for aggressive conditions dominated by chloride ion exposure, like marine environments, de-icing salts and chloride-contaminated groundwater, is highlighted to increase the uptake of calcined clay adoption for concrete used in such aggressive environments. The performance of calcined clay-based concrete for marine and chloride-rich exposure conditions is summarised with respect to two major aspects: (1) understanding the fundamental chemical interaction of chloride with the microstructure (ingress and binding) of calcined clay systems and (2) comparison of the performance of calcined-clay concrete with other blended cement systems. The paper also addresses some of the challenges in assessing chloride resistance and service-life estimation for calcined clay-based concrete. Hence, this comprehensive review would provide scientific background on how the effects of the chemical and mineralogical composition of calcined clays influence both the permeability and the chloride binding to highlight the improved chloride performance of concrete containing calcined clays. Further challenges associated with improving fundamental knowledge on interaction of chloride with the new composite cement based on calcined clays, and the use of existing testing methodologies and guidelines

for assessing the suitability and performance of calcined clay concrete for marine exposure based on recent literature and case studies are presented in this review to further the adoption of calcined clay in concrete construction.

2 Effect of material characteristics and microstructure on chloride binding and ingress

2.1 Chemical interaction of chlorides

2.1.1 Effect of binder composition on chemical and physical chloride binding

Kaolinite content of clay is known to influence the amount of alumina rich AFm ($\text{Al}_2\text{O}_3\text{-Fe}_2\text{O}_3\text{-mono-phases}$) phases formed and the amount of alumina incorporated in the C–A–S–H phase [20, 84]. Similarly, alumina content and reactivity of clay type, i.e., 1:1 or 2:1, is also known to influence alumina rich hydrated phases that could influence the chemical interaction of chloride with the microstructure [16, 18]. While alumina rich SCMs are generally perceived to improve chloride resistance, the extent of calcined clay additions on increasing the chloride binding capacity of hydrated cementitious materials (compared to the reference Portland cement) is still a major discussion in the literature. Chloride binding can manifest in forms of chemical binding that involves transformation of phases in hydrated cement matrix to chloride bound phases and physical binding, in terms of surface adsorption of chloride ions on hydrated phases [85–87]. Chemical binding of chlorides from the exposure solution by cement hydrates involves AFm phases. AFm phases denote a group of layered structure aluminate hydrates with the general formula $\text{C}_4(\text{A},\text{F})\text{X}_2 \cdot y\text{H}$, where X represents one mole of a monovalent (OH^- , Cl^-) or half a mole of a divalent (SO_4^{2-} , CO_3^{2-}) anion [88–94]. Thus, when exposed to chlorides, AFm phases can incorporate chloride ions in the interlayer and transform into phases such as Friedel's salt, Kuzel's salt or solid solutions [88, 89, 93, 94]. This binding is influenced by numerous factors, including the amount of AFm phases, Al content, calcium hydroxide content, pH of hydrated cement's pore solution and pH of the exposure solution [95]. The formation of Cl-containing

AFm phases, like Friedel's salt, depends on the binder composition and on the chloride exposure solution (concentration and volume). These chloride-containing AFm phases are thermodynamically stable, and consequently their binding in the reaction products can be sustained over time [96–98]. In hydrated cementitious systems containing calcined clays, the amount of AFm phases can be significantly higher compared to plain OPC systems due to the additional Al available to the system from the reaction of calcined clays. This has been shown by means of thermodynamic modelling by Shi et al. [99]. For example, Fig. 1 shows the comparison of phase alterations with increasing chloride ion concentration on the x-axis for OPC, calcined clay paste and calcined clay-limestone paste. As shown in Fig. 1, the AFm and the chloride binding phases in a binary system (Fig. 1B) and a ternary system (Fig. 1C) are much more prevalent than those observed in the plain OPC system. Thus, the maximal chemical binding capacity of these pastes is also expected to be higher compared to plain OPC systems, as reported in several publications [99–101]. However, the AFm phases in real cement pastes can differ from thermodynamic predictions (even after prolonged hydration), because hemihydrate can be stabilized by sulfates and/or chloride, forming solid solutions [69, 102]. Thus, although the total content of AFm can be higher with calcined clays, the actual chemical binding will depend on the chloride content of the AFm solid solutions [103]. For example, studies found that the amount of Friedel's salt formed increased from 10 to 25% as the kaolinite content increased from 20 to 50% and reduce thereafter with increasing kaolinite content in the clays [104].

Chloride binding is experimentally measured and presented in the form of chloride binding isotherms made of a plot of bound chlorides (y-axis) at different concentrations of chloride solution (x-axis). This is studied by exposing a few grams of powder hydrated cement to various concentrations of chloride solution till equilibrium is attained. Finally, the concentration of chloride bound in the cement can be measured directly on cement paste or on exposure solution (i.e., reduction in the concentration of exposure solution). Figure 2 present chloride isotherms from [100, 104] for various composite cement pastes containing fly ashes, slag and calcined clay with/without limestone. Figure 2A showcases how the kaolinite content of the calcined clay modifies the total



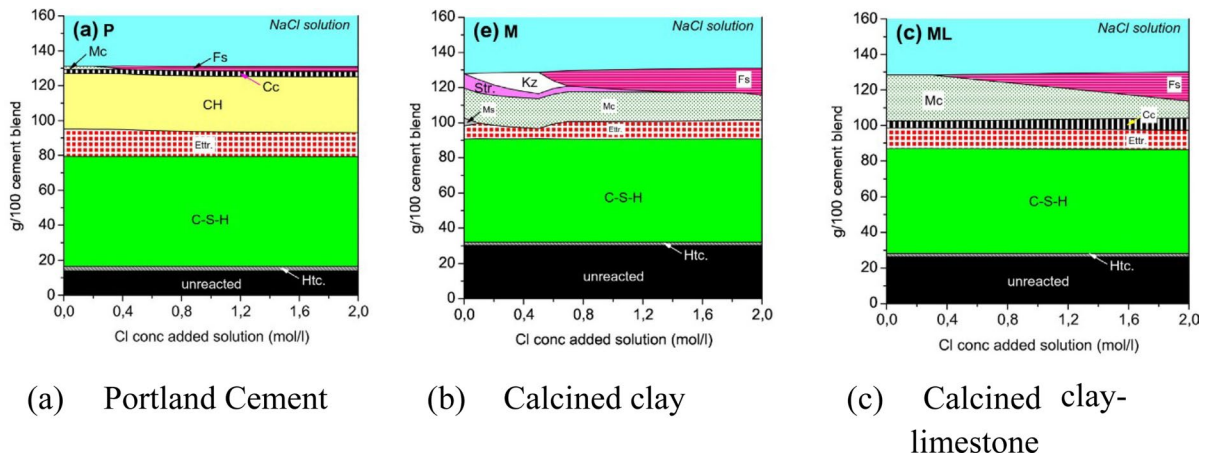


Fig. 1 Thermodynamic prediction of the phase assemblage in hydrated OPC (a), binary blend of cement with calcined clay (b) and a ternary blend of cement, calcined clay and limestone


when in contact with chloride solution of increasing concentration [99]. Reprinted from [99] with copyright permission from Elsevier

binding and shows that maximum binding occurs for calcined clay with kaolinite content between 40 and 80% [104]. Figure 2B demonstrates the variation in binding for composite cements containing calcined clay-limestone, slag-limestone and fly ash-limestone. While the binary calcined clay blend yields improved binding, calcined clay-limestone combination results in similar total chloride binding compared to OPC [100]. Similarly, other studies have shown that the total bound chloride content was not considerably different with the addition of calcined clay or metakaolin [99, 101, 104, 105]. On the other hand, studies on chloride binding with lower addition of metakaolin in the range of 8–30% have shown significant increase in the chloride binding capacity [99, 106]. A more detailed study on clays with different kaolinite content also reported no significant effect of different kaolinite content on chloride binding which could directly explain the performance [104, 105]. Hence, chloride binding cannot be the sole reason for improved chloride resistance with calcined clay-based concretes. Additionally, chloride binding experiments are not standardized and there are no agreed forms of testing, duration, or expression of data which makes it difficult to come up with conclusive arguments on the performance.


Similar to AFm phases, other hydration products, such as hydrotalcite, which belong to the group of layered double hydroxides (LDHs), are able to chemically bind chlorides. Hydrotalcite (e.g.

$\text{Mg}_6\text{Al}_2(\text{OH})_{18}\text{H}_2\text{O}$) is a magnesium and aluminium containing hydration phase with a somewhat variable composition, which is commonly observed to form upon hydration of cement pastes containing ground granulated blast furnace slag [107, 108]. The formation of hydrotalcite has been reported in cement pastes that contain dolomite [$\text{CaMg}(\text{CO}_3)_2$] and small amounts of metakaolin [109] and in MgO-calcined clay combinations [110]. The chloride binding capacity of hydrotalcite depends on its Mg/Al ratio [109] besides other ions in the solution [109], and binding in the hydrotalcite phase could vary from very low amounts [103] of chloride binding to quantities similar to per mol of Friedel's salt [109, 111]. Beside binding of chlorides by AFm or other LDH (Layered Double Hydroxide) phases, chlorides can also be physically bound by C-S-H. This physical binding can be explained by the electric double layer (EDL) theory [112, 113]. When divalent cations, such as Ca^{2+} accumulate in the Stern layer, the originally negative surface charge of C-S-H can be overcompensated [113]. The positively rendered Stern layer leads to the formation of a diffuse layer, in which negatively charged ions, such as chloride (Cl^-) or hydroxyl (OH^-), may accumulate [112, 113]. This accumulation of chloride ions in the diffuse layer of the C-S-H is commonly referred to as physical binding of chlorides by C-S-H. The accumulation of anions, i.e., chlorides, in the diffuse layer depends

Fig. 2 Chloride binding in Calcined clay systems: **A** influence of kaolinite content on chloride binding in PC (plain OPC mixture), LC3 systems using different clays (LC3-50 mixtures with 0% kaolinite content (quartz) to 95 wt% kaolinite content), and two PCC systems (70% OPC and 30% calcined clay mixtures (41.5% and 95.0% kaolinite contents of clays) from [104] and **B** Comparison of binding isotherms in calcined clay and calcined clay-limestone blends compared with OPC, fly ash and slag blends from [100]. Reprinted from [104] with copyright permission from Elsevier

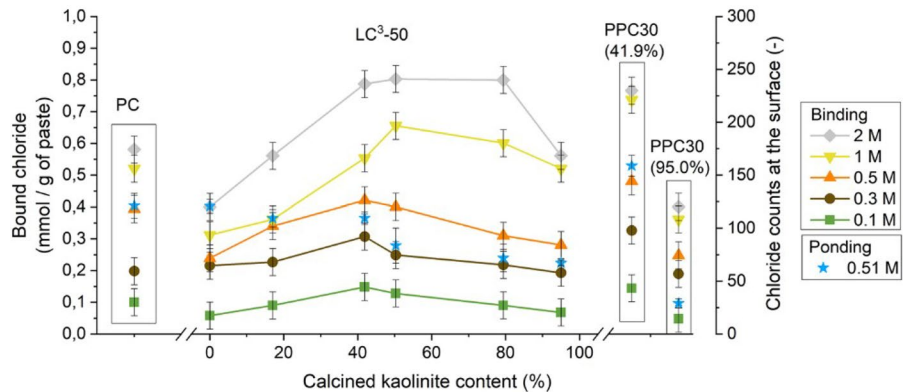

(A)

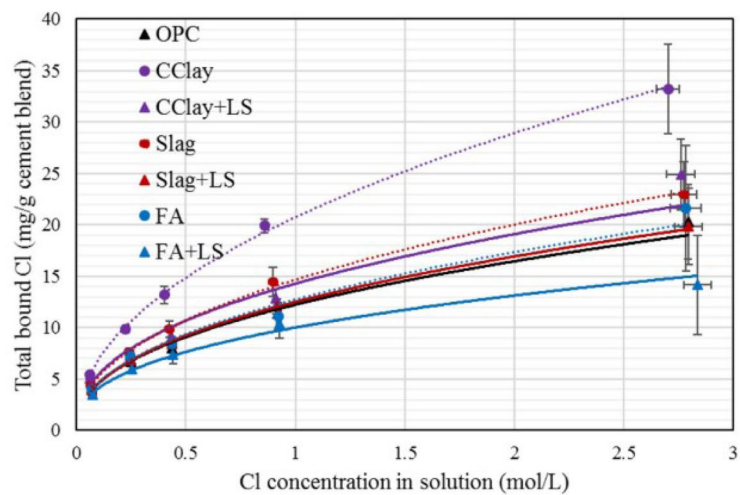

(B)

on the original surface charge of the C–S–H, which depends, amongst others, on its Ca/Si and Al/Si ratio [114–119]. The C–A–S–H formed during the pozzolanic reaction of calcined clays is commonly characterized by a lower Ca/Si and higher Al/Si ratio compared to C–S–H formed during clinker hydration [67, 120]. With decreasing Ca/Si or Ca/(Si + Al) ratios, a decrease in the physical binding of chlorides by C–(A)–S–H has been reported [103, 119, 121]. The effect of Al/Si ratio on the chloride binding capacity of C–A–S–H is less clear. While Yoshida et al. [114] showed that the chloride binding of C–A–S–H decreases with increasing Al/Si ratio, Jin et al. [115] showed that C–A–S–H phases overall show higher Cl-adsorption compared to

C–S–H when comparing the same Ca/(Si + Al) ratio.

The absolute composition of the C–S–H phase depends on the degree of reaction of the cement and the calcined clay and therefore on their mineralogical composition; the calcination temperature of the clay that influences reactivity also plays a role [49, 52, 63, 122, 123]. It should be noted that due to the pozzolanic reaction of calcined clays, more additional C–S–H is formed, which might disguise the variations in total chloride content bound per mol of C–S–H [99, 119, 124]. Therefore, calcined clays with varying reactivities are reported to result in different quantities of anions physically bound by the C–S–H phase [99, 119, 124]. The role of the EDL (physically




bound chlorides) on chloride diffusion is still not well understood nor quantified. This could be a key mechanism to explain the increased chloride resistance of new higher performance binders, like the LC3 as attempted in [125–128].

2.1.2 Effect of pore solution composition


The ionic composition of pore solution and its conductivity influence the chloride ingress in cementitious systems by modifying the ionic diffusion in the microstructure of the hydrated cement paste and impacts the binding capacity. The use of most SCMs causes a slight reduction in the pH of the pore solution of composite cements compared to plain Portland cement due to reduction in clinker content; except for SCMs inherently loaded with alkalis in them. Calcined clay with over 40% kaolinite is often known to consume portlandite completely by 28 days and reduce the pH [20]. Additionally, the use of calcined clay in combination with carbonate source to attain high-volume replacement can also lower the pH further due to reduced clinker content. Chloride binding in cement hydrates increases with this pH reduction [129–131], and this was found to be true in calcined clays binders as well [103]. However, the increased chloride binding upon slight reduction in the pH was explained by combinations of factors such as increased binding by AFm and difference in amount and composition of C–A–S–H phases [105,

129, 132, 133]. Other studies have reported that this effect of pH on the chloride binding by C–(A)–S–H is more prominent in pH of range of 10–12 and often requires sufficient Ca^{2+} ions to be available in the pore solution for their adsorption on the negatively charged C–(A)–S–H surface and the formation of a Stern layer [118, 129]. Increasing the Ca^{2+} concentration in the pore solution (e.g., due to exposure to CaCl_2) has been shown to increase the chloride binding capacity of a system significantly [99, 134]. Next to the effect on the physical chloride binding, the Ca^{2+} concentration in the pore solution also affects the chemical chloride binding by AFm phases especially in Al-rich systems, such as composite cements containing calcined clays [99]. If sufficient amounts of Ca^{2+} ions are available in the pore solution, they can react with alumina delivered from the calcined clay to form additional AFm phases, which can bind chlorides [95, 99, 134–136].

The changes in the pore solution composition also influence the conductivity of pore solution, which governs the diffusion of ions in the microstructure of cementitious systems that contains interlinked capillary porosity that are saturated with pore solution [137–140]. Diffusivity of ions in the solute of a permeable medium has often been linked to conductivity of the solute using the Nernst-Einstein relationship [140]. Figure 3A presents the reduction of total alkali content in the pore solution with increased replacement level of calcined clay and limestone

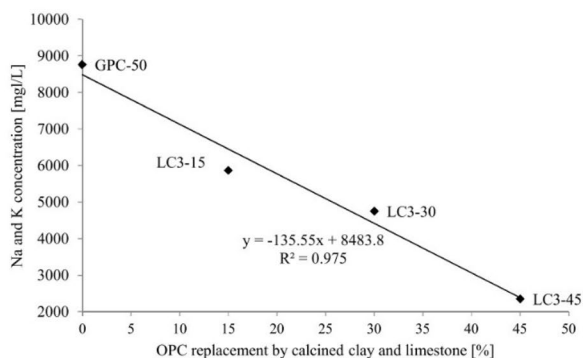

(A)

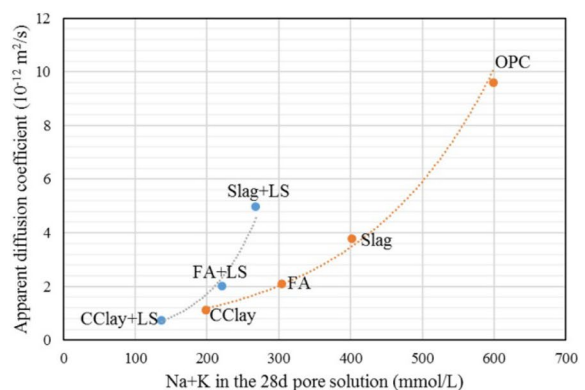

(B)

Fig. 3 **A** Reduction in total alkalis content in the pore solution with increasing replacement of calcined clay-limestone from [141] and **B** Relationship between total alkalis content vs.

apparent diffusion coefficient from [100]. Reprinted from [100] with copyright permission from Elsevier

combinations. The Na+K content decreased by nearly 70% for 50% replacement of the clinker content [141]. In [100], The variation of alkali contents in the pore solution was correlated with the variation of chloride diffusion coefficients in fly ash, slag and calcined clay blended cement systems and the results are reproduced in Fig. 3B from [100]. This shows that lower diffusion coefficient can be obtained for cementitious systems with lower pore solution conductivity such as LC3 systems, despite an equivalent porous network compared to other blended cement pastes [100].

2.2 Physical aspects determining chloride ingress

Deleterious substances, such as chloride ions, are transported into cementitious materials via a combination of different physio-chemical processes, such as diffusion, absorption or convection [142, 143]. Ionic transport in well-cured composite cements is generally slower/reduced compared to plain Portland cement [99, 101, 104, 144–146]. A systematic assessment of factors affecting the chloride diffusivity has shown that the reduction in chloride diffusivity observed in systems containing calcined clay is due to a combination of various factors [147]. The overall transport property of water, gas and ions was often described to be significantly dependent on the total porosity and pore structure of cement matrix [8, 148–150]. Calcined clays additions do not necessarily decrease the total porosity of the cement paste matrix [20, 44], rather resulting in significant refinement of pore size and connectivity [20, 144, 151]. Generally, binders containing calcined clays or a combination of calcined clays and limestone as SCMs are shown to exhibit an excellent resistance against chloride transport [99, 101, 104, 144–146]. Hardened cementitious materials comprise pores of different sizes, which are connected randomly, creating complex paths including impermeable pores and tortuosity for ion diffusion. Apart from the total porosity, the critical pore diameter obtained by MIP, as an indicator for the pore size distribution, exhibited linear correlations with chloride ion diffusion coefficients as reported by several studies [149, 152]. The amount and the connectivity of capillary pores are considered the most important physical parameters controlling the diffusivity of chloride ions because a large part of water and ionic transport occurs through the larger pores

(capillary pores) of the microstructure [10, 149]. The (pozzolanic) reaction of SCMs leads to a refinement of the porosity and an increase in gel pores, which reduces the connectivity of the porosity. This is beneficial in reducing water and ionic transport in concrete, resulting in the good performance of binders containing SCMs such as calcined clays [10, 44, 144, 149, 152]. Calcined clay, in particular, is known to cause significant refinement of pore sizes at early curing ages [20, 44]. However, this effect does vary with the kaolinite content of the clays. Increasing kaolinite from 20 to 50% was found to cause significant pore refinement by 7 days and any increase in kaolinite content had negligible impact on the critical pore entry diameter [20]. In line with the trends of pore refinement with kaolinite content, the diffusion coefficient was found to reduce with increase in kaolinite content from 20 to 50% and remained nearly similar with further increase in kaolinite content [104]. Binary and ternary binders containing limestone were studied for chloride ingress using diffusion experiments using 4 clays with varying kaolinite content from 20 to 65% in [153] and the chloride penetration depth reduced with increasing kaolinite content, confirming the positive influence of kaolinite content and corresponding pore refinement. In order to compare the evolution of pore structure with other SCMs, calcined clay cements were monitored using conductivity measurement on cement paste for early pore refinement [44, 144] and the results are presented in Fig. 4A. Calcined clay was found to cause a significant drop in conductivity by 3 days, correlating well with pore refinement observed using MIP in [20, 44]. Since conductivities are often linked to chloride diffusivities, such relationships were found to be valid for calcined clay concrete as well, which is in line with other SCMs. Figure 4B shows the relationship between bulk conductivity and effective diffusion coefficient showcasing that bulk conductivity could be used to explain chloride ingress in most SCM blended cementitious systems, including calcined clays.

Though the features of capillary pores control the ionic diffusion including chloride, the complex physio-chemical phenomena induced by surface charges in smaller pores i.e. gel pores [116, 117, 126, 154–159] cannot be overlooked when describing the transport of chloride ions in concrete. Also,



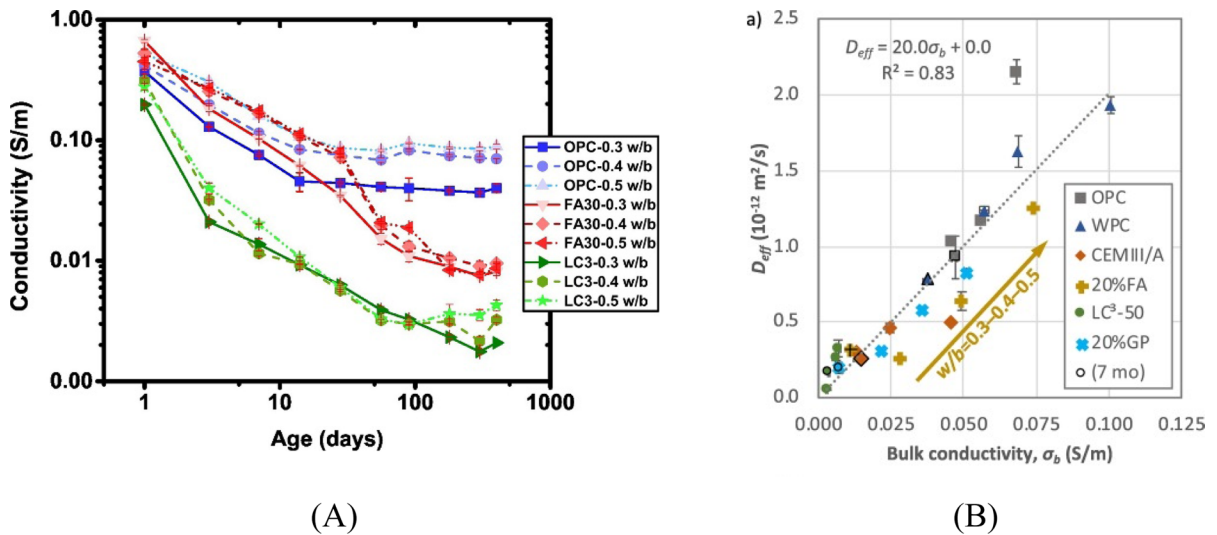


Fig. 4 **A** Comparative drop in conductivities for fly ash and calcined clays with varying water-binder ratios from [144] and **B** correlation between bulk conductivity and effective chloride

diffusion coefficient [147]. Reprinted from [144, 147] with copyright permission from Elsevier


since the physical properties govern the ionic transport in hydrated cementitious materials, it is important to mention that the pore structure of cement paste is different from mortar and further extending to concrete due to the presence of interfacial transition zone (ITZ) formed with the presence of aggregates [129, 160, 161]. The pore structure in the vicinity of ITZ can also influence the transport properties [162–167]. This highlights the importance of sampling for the establishment of any correlation between pore size distribution results and concrete performance. In addition to increased porosity in ITZ, aggregates can introduce variation to the total porous medium i.e., hydrated cementitious matrix in the system. Some studies have attempted to capture in the change in physical structure in concrete using tortuosity factors. Tortuosity is a measure of the distorted path in the pore network [168]. Increased tortuosity was reported to decrease the chloride diffusion coefficient as well as oxygen diffusion [144, 147, 169]. Increased tortuosity factors were used to explain the significantly improved chloride resistance of calcined clay concrete compared with other SCM types [151, 170]. However, these concepts have not been fully explored to allow a quantitative understanding of these effects on ionic transport in microstructures.

3 Chloride ingress in concretes containing calcined clay

3.1 Applicability of existing testing methodologies for chloride ingress to concrete containing calcined clays

Several direct and indicative test methods are used to evaluate the chloride resistance of concrete mixes with the aim of assessing the performance of new SCMs or combinations of SCMs and for specifying performance criteria for concrete to be used in such aggressive environments [143, 149, 171–180]. Often some of the testing methods, specifically accelerated testing methods, capture only a certain portion of contribution that are linked to performance in chloride exposure. For example, the factor governing the non-steady state diffusion/migration coefficient schematically was classified in [147] and the schematic is reproduced in Fig. 5 to highlight various parameters influencing the chloride transport parameter. While factors related to scales of paste, such as binding, pore structure, and pore solution are captured in studies done on paste/mortar in literature, as discussed in Sect. 2, the concrete scale effects, such as, aggregate size and volume, interfacial transition zone (ITZ), distribution of voids (like air entrainment) are often neglected in studies carried out in paste/mortar [152,

Fig. 5 Parameters included in different types of experimental tests, as reported in [147]. Reprinted from [147] with copyright permission from Elsevier

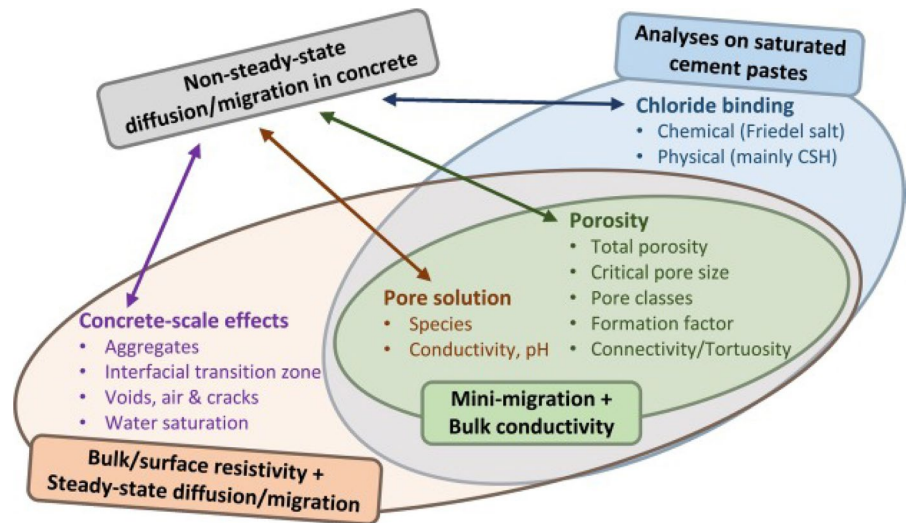

164, 181, 182]. As the construction industry is keen to transition towards performance-based specifications, it is important to ascertain the ‘true performance’ in the scale of concrete and develop limiting values for specifications that are scientifically sound to ensure desired performance. Various standardised testing methods available to determine the performance at the scale of concrete are summarised in Table 1, from [183]. These testing methods are widely used in performance specifications to evaluate the quality of concrete including calcined clay-based concrete. Remarks on the use of these testing methods for calcined clay concrete based on published data are also provided in Table 1. Some of these factors are discussed in the following sections in more detail.

The bulk diffusion test (ASTM C1556, EN 12390-11 or NordTest NT BUILD 443-chloride diffusion test) remains the closest to natural chloride exposure involving direct immersion in chloride-rich solution, followed by profiling the total chloride content in the sample as function of the depth from the exposed surface. The test can be laborious and time-consuming due to rigorous sample collection and testing on chloride content in multiple batches of concrete powder samples. In the ASTM and NordTest methods, the concentration used in laboratory diffusion experiments is about 2.8 M (i.e., 165 g/l) instead of 30 g/l NaCl concentration that is typical of seawater (and which is used in EN 12390-11) to ensure accelerated conditions and also assessment related to de-icing salts conditions.

Other forms of rapid testing methods are typically based on driving the chloride into concrete using an externally applied electrical potential, similar to the works of Tang and Nilsson from 1990s [171]. Such accelerated test methods include ASTM C1202 [175], NT BUILD 492 [174], and other variants of migration test [147, 171, 184]) are often preferred. Although these test methods provide a rapid and acceptable levels of performance assessment, these methods are highly criticised for applicability to different blended Portland cements and alternative cement types. Accelerated chloride migration test is referred in the Model Code for service life design (FIB 34) [185]. However, other rapid test methods like ASTM C1202, ASTM C1876, AASHTO T 358 etc. are constantly studied for extending their validity for new SCMs or combination of SCMs like calcined clay, calcined clay-limestone combinations [149]. These studies are crucial to ensure the uptake of newer breeds of SCM types. Several recent studies have attempted to establish such relationships between accelerated chloride resistance test and diffusion coefficient for calcined clay and calcined clay-limestone systems [82, 83, 128, 144, 147, 183, 186–194]. A recent paper investigated the suitability of these methods to test LC3 concrete [183, 195, 196] by assessing the performance of each accelerated testing method and comparing the results using ASTM C1556 bulk chloride diffusion test as reference. Results obtained using ASTM C1556 bulk diffusion test showed that, the resistance of LC3 concrete against chloride diffusion was greatly improved

Table 1 Testing methodologies for chloride ingress and its usefulness for calcined clay concretes based on [183] with remarks on suitability for calcined clay based concrete

Name of test method	Standards	Parameter obtained	Remarks	Remarks on calcined clay systems	References
Chloride diffusion test	ASTM C1556 [172, 173]	Diffusion coefficient	More realistic but challenging to perform in terms of handling samples and chloride content measurement across different depths. A minimum of 35 days of exposure and more time required for high-performance concrete	Longer exposure time maybe required for calcined clay to obtain sufficient depth of chloride ingress due highly refined pore structure. Typically, ingress depths of 5 mm are observed. However, the surface effect may also influence in the initial depth. Extended exposure beyond 35 days is recommended for calcined clay concrete	[100, 104, 146, 153, 170, 195, 196]
Rapid Chloride migration test	NT Buld 492 [174]	Non-steady state migration coefficient	Relatively quick to perform with testing duration is 2–4 days. It is estimated based on the depth of penetration of chloride, which is more appropriate than current-based measurement—no heating of specimen due to reduced voltage for lower quality concrete	Migration coefficient have been related to the diffusion coefficient for calcined clay concrete. Due to very high initial resistivity, the required Voltage is about 60 V for calcined clay concretes and duration of 96 h is required for calcined clay concrete Lack of relationship with long-term diffusion data for calcined clay concrete may be limiting the usage and conversion factors for migration to diffusion needs to be developed for calcined clay concrete for use in service life design	[128, 144, 145, 147, 183, 189, 197]

Table 1 (continued)

Name of test method	Standards	Parameter obtained	Remarks	Remarks on calcined clay systems	References
Rapid chloride permeability test	ASTM C 1202 [175]	Total Charge passed	Easy to perform. Popular in the construction industry. Testing duration: 6 h + 1 day of specimen conditioning. Sensitive to specimens heating which could affect the measurement in the case of poorer concretes	Charge passed values for calcined clay concrete are found to be significantly low, often below 200 Coulombs for calcined clay concrete. Higher resistivity of concrete could favour the ASTM concrete quality guidelines towards calcined clay concrete. Care should be taken while making meaningful comparison of the data obtained	[44, 145, 187]
Bulk resistivity/conductivity/surface resistivity chloride conductivity	ASTM C1876 [176–178]	Resistivity, Conductivity	Time required < 5 min without sample conditioning. Two standards are available in ASTM for measurement based on AC or DC measurement input. Sensitive to the saturation level of concrete and conditioning. Consistent results can be obtained with proper saturation	Significantly higher resistivity value noted for calcined clay concrete. Different forms of resistivity measurement like bulk and surface are available which provide different values. Interference from pore solution and saturation level can affect the data. Testing protocol should be clearly stated in instance of using this measurement	[44, 82, 83, 100, 144, 145, 151, 183, 187, 198–202]
	AAASHTO T 358 [179]	Surface resistivity	time required < 5 min without sample conditioning. Essential to maintain specimens properly saturated. Measurement can be quite easily adapted for onsite measurement for assessing the quality of cover concrete		

Table 1 (continued)

Name of test method	Standards	Parameter obtained	Remarks	Remarks on calcined clay systems	References
Formation factor	ASTM C1876 [176, 180]	Formation factor	The conductivity of the pore solution is required. Pore solution conductivity can be tedious to obtain	Useful to avoid interference from lower pore solution alkalinity of calcined clay concrete. Although pore solution is integral part of explaining chloride ingress, deviation from in pore solution between cement types, concrete ingredients and pore solution composition in actual field condition can interfere with the conductivity measurement which can be avoided using this approach	[144, 147, 187, 199]

compared to that of reference OPC (referred to as GP, general purpose cement in Australia context) cement-based concrete. The apparent chloride diffusion coefficients of LC3 concrete was 4–5 times lower than that of reference Portland cement-based concrete [99, 104, 144, 147, 192]. However, there is still limited published long-term data on realistic exposure conditions, specifically with low purity clay which is gaining attention in the recent years.

3.2 Transport properties and chloride resistance of concretes containing calcined clays

3.2.1 Impact of kaolinite content, curing duration and time-dependency on performance

SCMs are widely recognised to positively influence the pore structure over time [44, 203–207] and hence, improving transport properties and resistance to chloride ion penetration over time [208–212]. Some of the factors involved in the time dependent changes are curing duration, reactivity of the SCM, water-binder ratio, replacement level etc. [213, 214]. For calcined clay concrete, kaolinite content is found to significantly influence the chloride ingress and chloride diffusion coefficient [104, 153]. Results on binary (labelled CC) and ternary LC3 cement mortars prepared with four different kaolinite contents are presented in Fig. 6, it is seen from the data that chloride ingress is limited with an increase in kaolinite content from 20 to 65% [153]. Similar reduction in diffusion coefficient with kaolinite content up to 50% was reported in [104]. Thereafter the diffusion coefficient remained similar with no further reduction, highlighting that further increase in purity doesn't necessarily improve performance and that low to moderate purity of about 50% is sufficient to produce an improved performance against chlorides.

In case of low reactivity SCMs like fly ashes, the reactions may continue for a longer period of time, thereby resulting in a significant improvement at later ages and make it crucial to incorporate the curing duration and/or time dependency in estimating the long term performance [204, 206, 207]. While calcined clays made of kaolinitic clays are known to rapidly develop refined pore structure, low purity with lower level of kaolinite content or less reactive alternative clay minerals might require extended curing to positively influence the performance. Since chloride

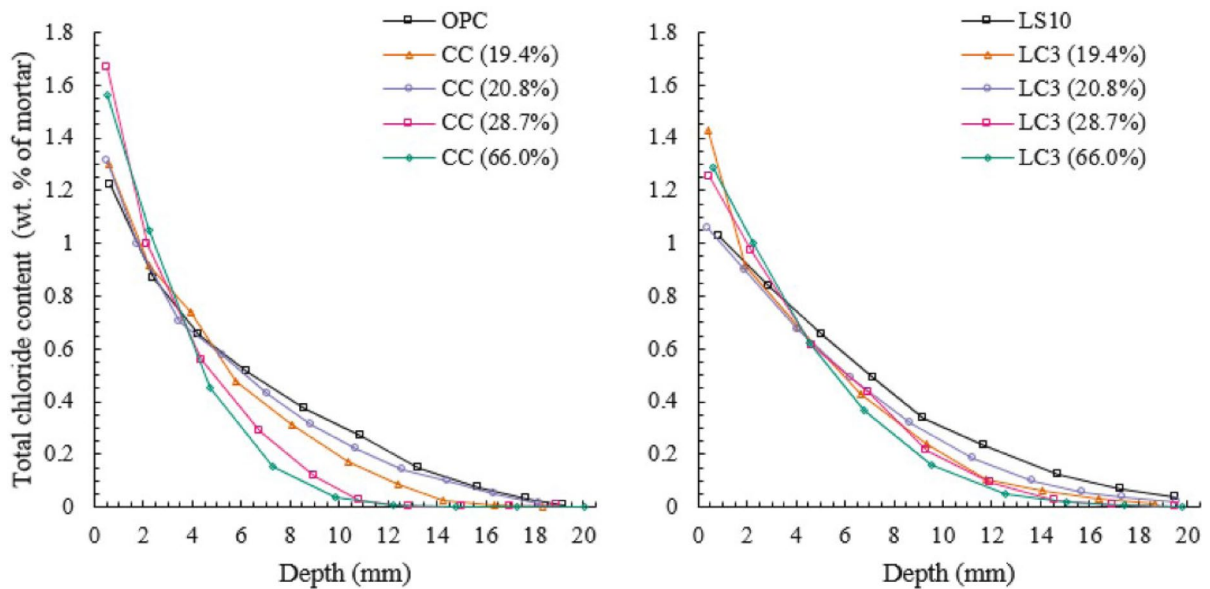


Fig. 6 Influence of kaolinite content on chloride ingress in calcined clay (CC) and calcined clay-limestone (LC3) mortars, from [153]. Reprinted from [153] with copyright permission from Elsevier

exposure predominantly occurs in saturated or high humidity conditions, concrete microstructure can continue to evolve in such conditions. Also chloride ions typically do not manifest in terms of physical damage, at least for sodium chloride, allowing continuous densification of pore structure; thereby reducing the ingress rate over time [215, 216]. Resistivity of concrete is a simple measurement to monitor the time-dependency of transport properties in concrete and it is found to correlate well with other transport properties [44, 138, 217–222] and chloride diffusion, as highlighted in Sect. 2.2. Resistivity development in calcined clay-based concrete mixes can be influenced by the composition, blend design and calcined clay-limestone ratio. For example, results from [199] about additions of gypsum for sulphate balance in calcined clay, as presented in Fig. 7A. The results indicate that gypsum addition can modify the resistivity development with mixes containing 5% gypsum showing higher resistivity throughout the curing duration. Dhandapani and Santhanam [202] studied various calcined clay-limestone ratios for 50% kaolinite content clays and found that calcined clay-limestone combination containing 10–15% limestone showed synergistic resistivity development compared to binary calcined clay (both at 30 and 45% replacement), as shown in Fig. 7B. Another

common observation is that resistivity development in concrete is significantly higher for calcined clay at early age, irrespective of mix design and water-binder ratio compared to other common SCMs, such as fly ash, slag etc. This was confirmed from resistivity monitoring on calcined clay and fly ash concrete on three set of concrete mix designs as shown in Fig. 7C, reproduced from [144]. This has been linked to early refinement of pore structure as discussed in Sect. 2.2. Higher resistivity at early ages implies that transport properties are considerably reduced at early ages and significantly lower chloride diffusion coefficient can be attained with calcined clay containing as low as 30–50% kaolinite content even with shorter curing duration [187].

Time-dependent change in the chloride transport parameter is caused by progressive refinement of the pore structure and the reduced flux of free chloride for further diffusion due to chemical binding. These factors affect the diffusion coefficient obtained from the chloride profile over extended exposure time. Studies have attempted to mathematically denote the time dependency using Eq. 1. Time dependency of chloride transport parameters significantly influences the long-term chloride penetration estimation [223–226]. The simplest form of the long-term chloride prediction is based on Crank's error function solution [227]



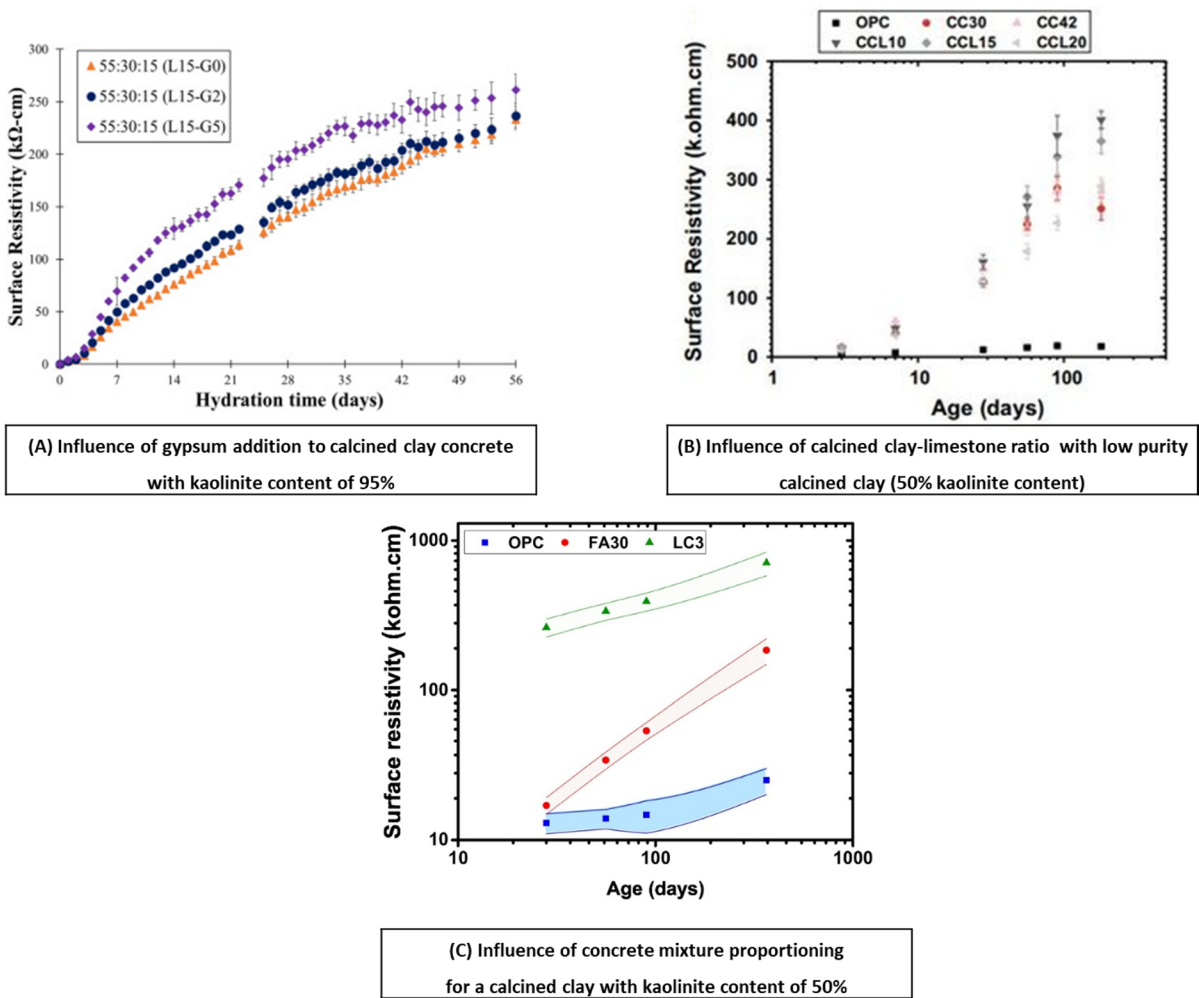


Fig. 7 Surface resistivity development in calcined clay binder. **A** Influence of gypsum addition from [199], **B** influence of calcined clay-limestone ratio from [202], and **C** influence of

concrete mixture proportioning from [144]. Reprinted from [144, 199, 202], with copyright permission from Elsevier and Springer

for Fick’s second law, assuming a constant value for chloride diffusion coefficient and surface chloride concentration [185, 224, 225]. This involves the use of a time dependency function to account for the reduction of chloride diffusion with time using the fitting constant known as the decay coefficient or ageing factor [225]. The ageing factor can be obtained using the negative slope of diffusion coefficient with time plotted on a log–log scale [226, 228–230].

$$D_{cl,t} = D_{cl,ref} \left(\frac{t_{ref}}{t} \right)^m \tag{1}$$

where

$D_{cl,t}$ = Diffusion coefficient at exposure time t ,
 $D_{cl,ref}$ = Diffusion coefficient at a reference time t_{ref} ,
 m = Ageing or decay factor.

A higher value of the ageing coefficient indicates the continuous reduction in diffusion coefficient due to pore refinement or reduced flux from chloride binding. Both these factors can lead to a higher decrease in the diffusion coefficient over time. The ageing factor for OPC concrete and the common SCMs based concrete, like slag (i.e., ground granulated blast furnace slag, GGBS) and fly ashes, are specified in FIB model code (as shown in Table 2) [185], while recommendations are not available for calcined clay concrete.

Table 2 Comparison of ageing factors from FIB and literature

Ageing factor from FIB34		Ageing factor from literature		References
Binder type	m	Binder type	m	
OPC	0.30	OPC	<0.40	[224, 226, 228, 232]
Fly ash	0.60	fly ash	0.40–0.80	
Slag	0.45	slag	0.40–0.60	
Metakaolin (<20% replacement)/cal-cined clay (<40% replacement)	NA	Metakaolin (<20% replacement)/cal-cined clay (<40% replacement)	0.3–0.6	[144, 228, 233]

The available data from the literature is summarised in Table 2. A concrete made with Ordinary Portland Cement (or CEM I) usually exhibits a lower level of decay with the ageing factor varying from 0.2 to 0.3 whereas concrete with blended cement can have a higher decay ranging from 0.5 to 0.7 [223]. Although the FIB model code specifies certain decay value for a particular mineral admixture, other factors, such as reactivity, replacement levels, water-binder ratio may influence the value. No systematic studies on time dependency with kaolinite content or other low purity clays are available in literature, warranting more studies on this aspect in future. As more and more multi-component composite cement types are being standardised, robust methods or recommended values with suitable safety factor to obtain such input parameter to model long-term performance needs to be developed as combinations of two or more SCM can again lead to variability in ageing coefficient. For example, no distinction is made for the composite cement based combination of SCM or with/without limestone for recommendation made in FIB model code. On a parallel development, more sophisticated modelling methods based on fundamental principles on diffusion laws accounting for materials reactivities are being developed [231] which could enable to model and predict performance of composite multi-component cement. However, this modelling is yet to be deployed widely in engineering communities for concrete construction.

3.2.2 Impact of concrete mixture proportioning


Modifying the concrete mixture proportioning, in terms of binder content and water-binder ratio, is widely practiced to control strength requirement and chloride resistance of concrete mixes with available source of SCMs. For example, in the United

Kingdom, BS 8500 [234] recommends varying binder content and water-binder ratio for different cement types for prescriptively specifying concrete in different exposure classes. Modifying the mixture proportioning can also be done to attain levels of resistance as prescribed in the concrete performance specification during mix development phase of the construction project. Studies dealing with materials characteristics such as kaolinite content in clay or calcined clay-limestone ratio are often carried out on mortars or paste which is reasonable for scientific evaluation, but, doesn't necessarily provide the limiting values meeting concrete specification based on combined strength and durability criteria. In a study reported in [145], the non-steady state migration coefficient in calcined clay concrete made with three mix designs was monitored for over 4 years (1 year in curing and remaining 3 years natural exposure). Two concrete mixes were tailored to produce M30 and M50 grade concrete (with normal Portland cement, 30% fly ash blend, and LC3) and the third mix was produced with similar mix design (360 kg/m³ binder content and 0.45 w/b). The results are replotted from the original work reported in [145] and presented in Fig. 8. It was found that calcined clay (50% kaolinite content) concrete showed 10 times lower migration coefficient compared to OPC concretes and this difference remained valid in the long term for a period of 1400 days. The study also compared calcined clay-limestone concrete with three fly ash concrete that managed to show improved performance over time from 90 to 1400 days. Similarly, calcined clay with 50% kaolinite content was found produce 5 times lower diffusion coefficient in concretes in the study reported in [195].

For alternative clay types, chloride profiles of kaolinite clay mixes were compared with illitic clays, and the results showed that kaolinite clay marginally



Fig. 8 Chloride resistance of different strength grade of concrete on the long-term chloride resistance of LC3 concretes containing calcined clay with 50% kaolinite content, adapted based on data presented in [144]

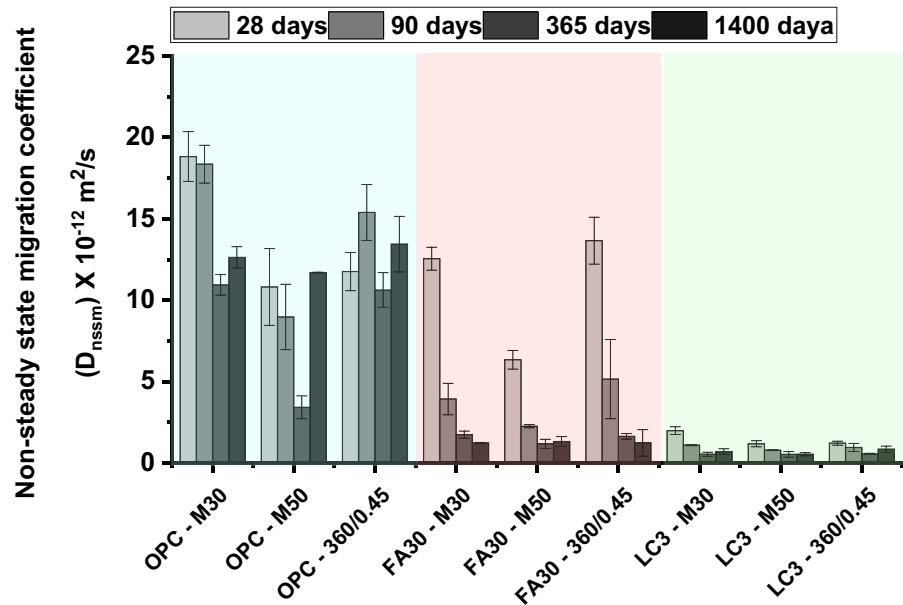

lowered the chloride content across the depth compared to the illitic clays mixes [46]. However, concrete containing other low purity clays and alternative clay types are not well reported for their long-term chloride resistance performance. Based on information available in literature, clays with kaolinite content of about 50% can provide significant improvement in chloride resistance of the order of 5–10 times lower compared to OPC concrete across range of mix designs which shows it is possible to significantly improve the chloride resistance across a wide range of concrete strength without necessarily increasing cement content to improve the durability performance [59, 100, 104, 144–147, 151, 153, 235, 236]. Recent studies on the use of LC2 showed that calcined clay concretes produce similar early improvements in resistivity across several concrete mixes compared to fly ash concrete. Most of the improvements with calcined clays occurred between 3–7 days, as compared to fly ashes that took more than 28 days to show a positive impact, specifically at higher water-binder ratios. Combined use of SCMs with different levels of reactivities for improving concrete performance during concrete mix design stage can be a potential route for uptake of calcined clay along with other SCMs. There is also possibilities of using a combination of clays with varying reactivities or varying calcined clay-limestone ratios to significantly reduce CO₂ footprint of the concrete and ensuring performance

criteria are suitably met based on the demands of the exposure conditions, as shown in literature for LC3 concrete [190, 237] and LC2 additions in concrete [82].

3.2.3 Comparison of calcined clay performance with other SCMs

Blended cement containing slag and fly ashes are already widely used in aggressive marine environments. Hence, it is practically relevant to compare the performance calcined clay with other common SCMs, such as fly ashes and slags, that are widely utilized for concreting in aggressive environments. On comparing metakaolin to slag (GGBS based) concrete with respect to chloride conductivity index, 20% metakaolin was found to show better performance compared to 50% GGCS concrete at all w/b ratios. Similarly, concretes containing low purity calcined clay were found to perform significantly better than fly ash concrete at early ages while fly ashes were found to require extended curing or reduced w/b for improving the performance [145, 187].

The chloride profile of binary and ternary blended systems (with calcined clay) after 1 year exposure of 0.5 M NaCl solution [100] is shown in Fig. 9. OPC exhibits largest chloride penetration depth while calcined clays binary (CClay in Fig. 9) and ternary (CClay + LS in Fig. 9) systems shows better resistance

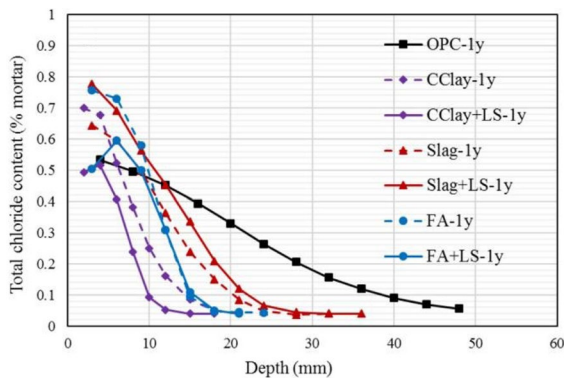


Fig. 9 Chloride profile of calcined clay in comparison with other SCMs determined after 1 year (1y) of exposure [100]. Reprinted from [100] with copyright permission from Elsevier

to chloride penetration in comparison to other SCMs (fly ash and slag with/without limestone). The chloride penetration depth of systems containing calcined clays and limestone is similar or smaller compared to binary systems containing only calcined clays as SCMs [100]. Other studies, also demonstrated superior chloride resistance of calcined clay compared to other SCMs [82, 100, 144, 189, 191, 202, 238].

3.2.4 Chloride ingress in carbonated concrete

One of the key factors to consider for long-term modelling of chloride ingress in low clinker cements is the effect of surface carbonation, which can be a likely scenario in the long term, at least in some instances of air-borne chloride exposure. High volume clinker replacement by calcined clay or using calcined clay-limestone blends leads to reduced carbonation performance and this is summarised in the previous review from the TC in detail [37]. This trend is true for all low clinker concretes. However, the possibility of carbonation in dominant chloride exposure region like tidal or submerged conditions can be significantly lower due to the fact that carbonation tendency reduces at higher humidity conditions. Nevertheless, considering the long-term service life, often > 100 years for some critical infrastructure, the possibility of surface carbonation cannot be neglected, specifically in low clinker cements. Hence, it becomes essential to consider the porosity, transport properties and chloride resistance in carbonated concrete, specifically in low clinker cements, that are

prone to carbonation leading to significant pore structure alterations [239]. In [240], the change in bulk porosity and resistivity was evaluated in concrete specimens subjected to three conditions i.e., curing, oven drying and carbonation exposure. The results shown in Fig. 10 that transport properties and resistivity of calcined clay concrete (H-CC in the plot) worsened upon carbonation compared to OPC concrete (H-PC in the plot) [240].

Besides changes in transport properties, carbonation of concrete cover could also cause redistribution of the chlorides by increasing the concentration of free chlorides [241]. In [242], the corrosion performance of LC3 paste with pre-mixed chloride upon carbonation exposure was investigated. It was found that the steel reinforcement was protected with lower corrosion rates in the chloride contaminated LC3 [242]. However, carbonation of chloride contaminated concrete was found to significantly reduce the corrosion performance based on observations from the accelerated testing conditions in laboratory. Figure 11 presents a schematic representation depicting the scenario of carbonation of chloride exposed concrete and the possibility of corrosion caused by combined effect of chloride ingress, release of free chloride upon carbonation and reduction of pH due to carbonation. Such scenarios may be crucial in concrete elements which may undergo some levels of carbonation and chloride ingress eventually during the service life with carbonation occurring much more slowly compared to chloride ingress leading to increasing free chlorides. Studies dealing with such combined exposure conditions are quite limited in the literature for low clinker cements and calcined clays concrete, and may require more focus in future, to determine performance in realistic conditions that are possible in field exposure.

4 Corrosion resistance and service life prediction of calcined clay concrete

Reinforcement corrosion in cementitious systems is complex with several factors, including environmental factors like exposure conditions, temperature and relative humidity, properties of cover concrete and steel-concrete interface, influencing the performance [243, 244]. Some of the material parameters that could influence corrosion performance include

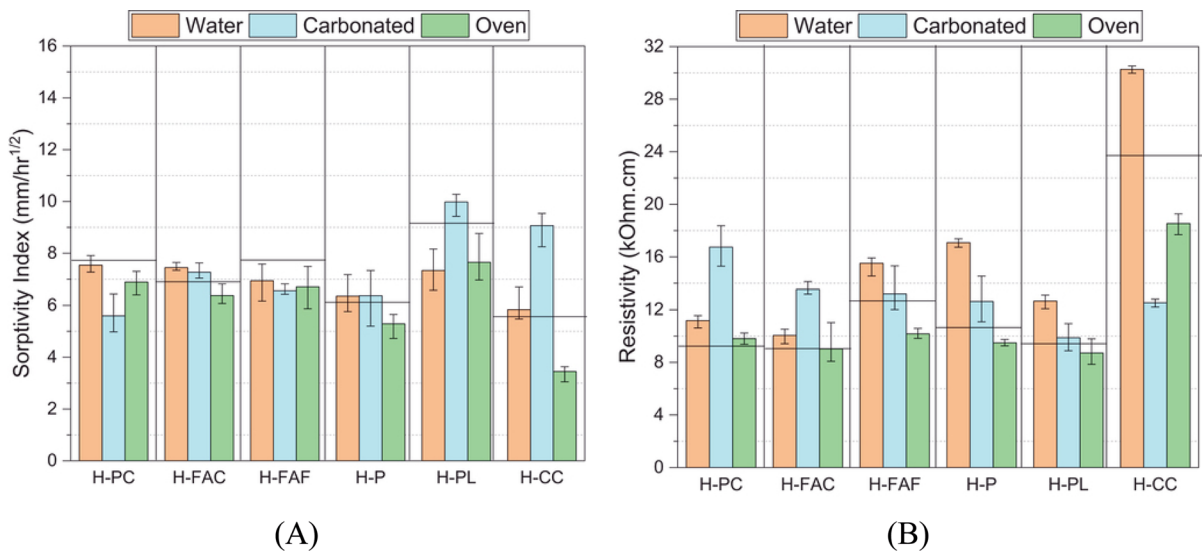


Fig. 10 Transport properties in carbonated concrete [240]. Reprinted from [240] with copyright permission from Taylor & Francis


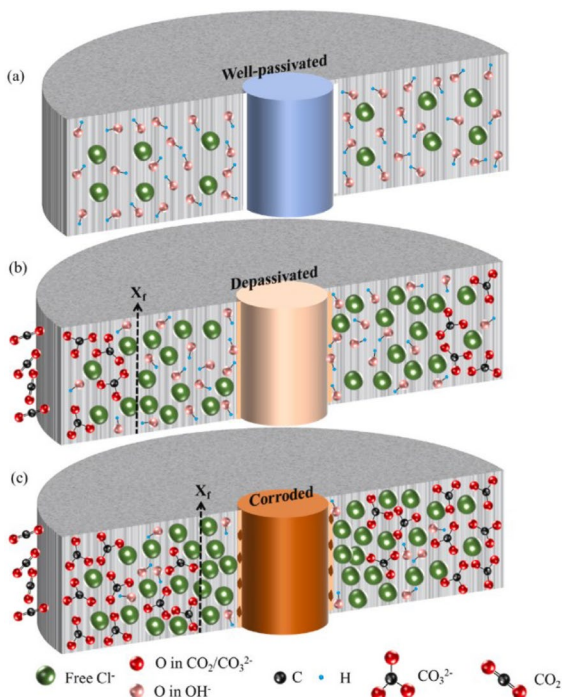


Fig. 11 Schematic representation of corrosion mechanism under coupled carbonation and chloride attack, as presented in [242], depicting the release of chloride as free chloride as carbonation front progress towards the reinforcing steel. Reprinted from [242] with copyright permission from Elsevier

cement composition and physiochemical properties such as chloride/moisture ingress, chloride threshold, and corrosion rate of steel embedded in cementitious systems. Critical chloride threshold is the chloride content at reinforcement level that is sufficient to produce an acceptable level of corrosion by depassivation [245]. There is a wide range of values reported in literature using different testing methodologies for OPC and blended Portland cements [245, 246]. Due to the high resistivity of concrete containing calcined clay, it is challenging to get an accurate estimate of chloride threshold using existing testing methods [201, 247]. In [201], polarization resistance was monitored to identify the onset of corrosion using linear polarization resistance (LPR) and electrochemical impedance spectroscopy (EIS). The results from this study are reproduced in Fig. 12, and indicate that there is lower chloride build-up at the steel surface due to reduced diffusion coefficient (discussed earlier in Sects. 2, 3). The reflection of this benefit is visible in the results from [201] as well with calcined clay mortars taking nearly 10 additional cycles to show visible signs of corrosion. Despite the longer duration, the critical chloride threshold value observed for the onset of corrosion was almost 50% lower in calcined clay systems (0.2% by weight of cement) compared to plain Portland cement (0.4% by weight of cement). Hence, this needs to be accounted properly during the corrosion assessment and service life

Fig. 12 Electrochemical response from EIS and LPR techniques for OPC and LC3 specimens on exposure to chlorides in laboratory conditions [201]. Reprinted from [201] with copyright permission from Elsevier

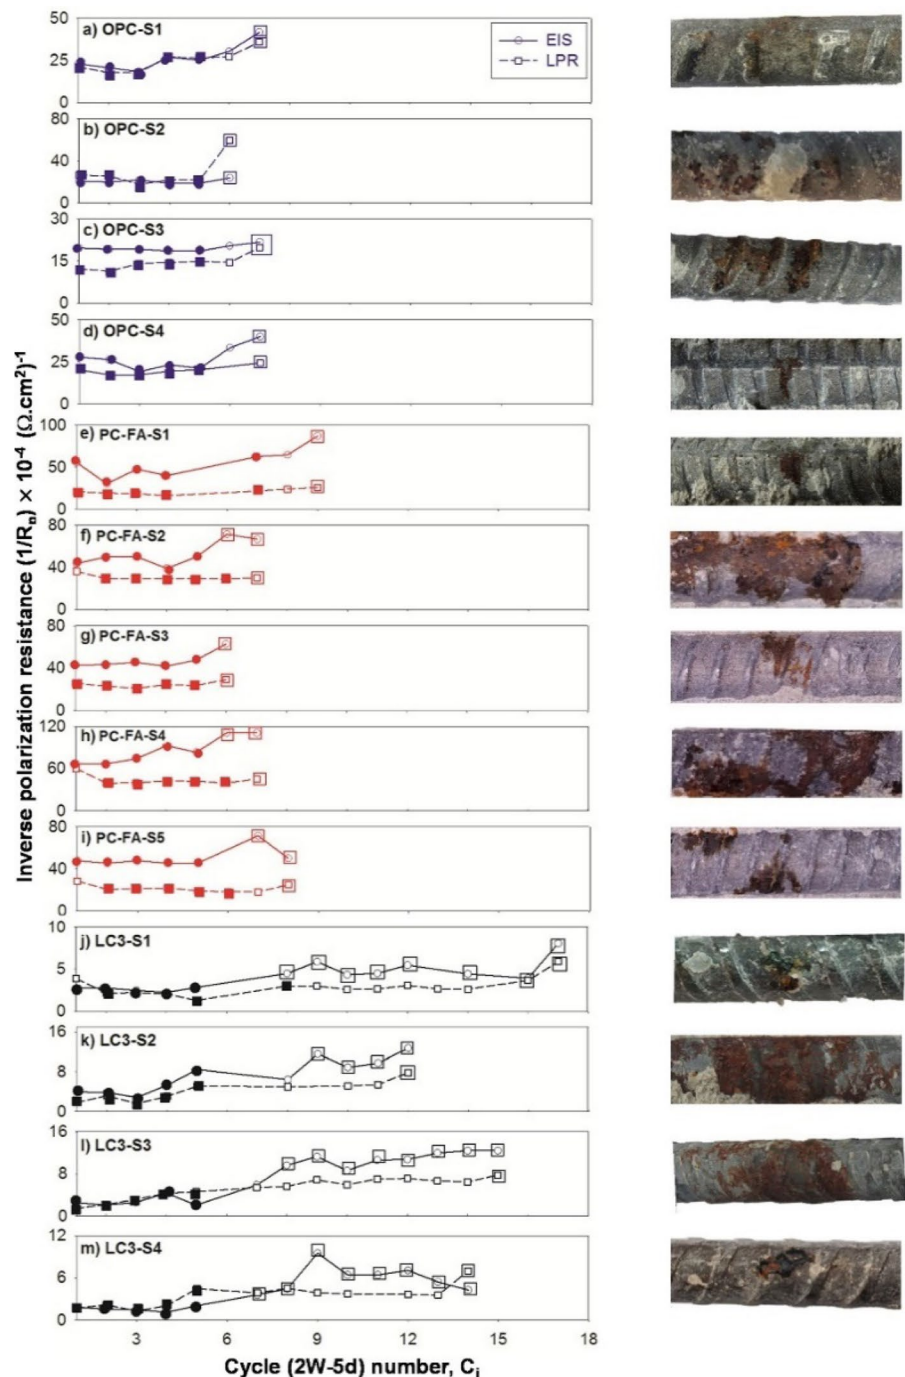

design of concrete containing calcined clays. Similar observations on delayed onset of corrosion initiation were reported for metakaolin addition in the range of 10–20% in [248].

Another parameter governing the extent of damage due to corrosion is corrosion rate, indicating the rate

at which reinforcing steel corrodes. In recent studies, chloride-induced reinforcement corrosion in concrete containing metakaolin (at low replacement <15%), calcined clay and calcined clay-limestone have been investigated for corrosion rate in chloride exposure [192, 248, 249]. Metakaolin addition at lower

replacement levels of 6–20% was found to lower corrosion potential and corrosion current density in addition to delaying in the onset of corrosion initiation [248]. Similarly, corrosion rate was found to decline by nearly 50% with metakaolin addition from 0.006 mm/year to 0.004 and 0.003 mm/year with 5 and 15% metakaolin addition respectively [250]. In [192], corrosion rate of calcined clay-limestone was compared with OPC and fly ash-limestone composite blends under combined chloride-sulfate exposure conditions. The corrosion rate monitored using EIS after drying-wetting cycles by saturation at ambient temperature (25 °C) for 2 days (wetting cycles), followed by drying in a laboratory oven at 60 °C for 5 days—total cycle duration of 7 days. The results showed that calcined clay-limestone blends had lower corrosion rate initially due to higher resistivity of the cementitious matrix and the corrosion rate continued to remain lower throughout testing, as shown in Fig. 13. During the same period of testing (i.e., 16 cycles), OPC showed marked increase in corrosion rate and fly ash-limestone blends showed corrosion rate transitioning from moderate to high corrosion rate values.

For service life estimation using widespread engineering modelling tools, the significantly lower chloride transport parameter was found to ensure that concrete containing calcined clay (with >40% kaolinite content) produced enhanced service life compared to OPC concrete [146]. Predicted service life of calcined

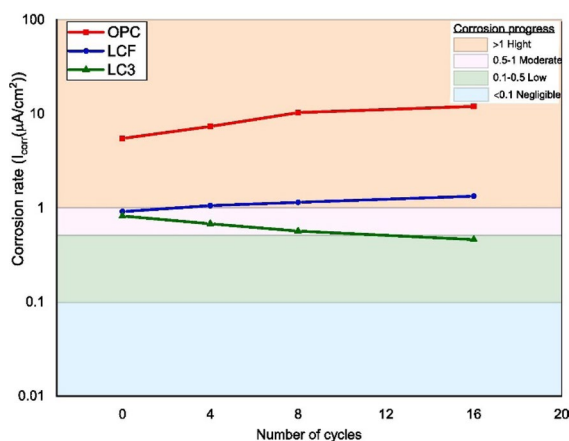


Fig. 13 Comparison of corrosion rate in concretes containing between plain Portland cement and calcined clay binders [192]. Reprinted from [192] with copyright permission from Elsevier

clay-based concrete was found to be considerably longer than OPC concrete and sustainability benefit from the extended durability was evaluated using CO₂ footprint per m³ normalised to the estimated service life [146]. However, when similar approach was adopted in [190] for calcined clay containing 15–20% kaolinite content the results showed only a modest reduction in the chloride transport coefficient with no significant enhancement in service life with respect to OPC with such low purity clays. This highlights that calcined clay usage in the forms of LC2 or LC3 could show variability in performance based on the kaolinite content of the clays and/or calcined clay to limestone ratio even among the clays passing reactivity threshold criteria prescribed for screening clays using rapid screening test methods [251]. Assessing suitability of SCM simply based on reactivity may not reflect the durability performance potential completely in concrete scale. The adoption of performance-based design approaches for concrete design is the best ways to enable the use of a wide range of low carbon cement formulations from the perspective of optimal utilization of all available resources.

5 Case studies from field exposure studies in marine environments

Chloride ingress assessment is typically carried out in accelerated laboratory conditions as the process takes a long time in field conditions. Thus, realistic studies are quite scarce for new SCM types that are currently under development due to limited field applications. This section presents the overview of practical case studies from two marine exposure sites in Cuba [186] and India [252]. The exposure sites and the materials used based on [186, 252] are described and a practical applications of calcined clay-limestone (LC2) as mineral admixture for structures in marine exposure is highlighted from [252].

5.1 Marine exposure sites in Cuba

To simulate the real conditions in which concrete is produced in Cuba, concrete specimens were manufactured in the premixing plant of the Empresa Constructora de Obras del Turismo, ECOT, in Cayo Santa María (CSM) (see Fig. 14). Concrete specimens were cast with a ternary blend containing 50% clinker,



Fig. 14 Concrete blocks produced at ECOT

30% calcined clay (original kaolinite content 48.9%), 15% limestone and 5% gypsum. A reference concrete was cast using a Type I Portland Cement, with 90% clinker, 5% limestone and 5% gypsum. Concrete blocks measuring 60×30×30 cm were prepared, which were cured in the plant for up to 28 days, and subsequently exposed at the Punta Matamoros exhibition site in July 2015. The specimens were placed and continuously monitored in natural conditions since 2015 in at least three exposure classes according to Cuban standards. Three series were cast with cement content and water-to-cement ratio following the prescriptive specifications of the Cuban standard NC 120:2014: (1) H1, less than 500 m from the seashore (high relative humidity and high chloride concentration), (2) H2, between 500 and 1500 m from the seashore (high relative humidity and mid chloride concentration), and (3) H4, more than 20 km from the seashore (mid relative humidity and low chloride concentration). The water-binder ratios of the three concretes, i.e., H1, H2 and H4 were 0.40, 0.45 and 0.55, respectively, and the detailed mix design is present in [37, 186]. Both OPC and LC3 concrete used in H1 conditions had 28 days compressive strength > 30 MPa.

In addition to concrete, mortars were cast with the same cement as used for concrete. The aim of the mortar study was to assess the behaviour of mortars in pure diffusion in lab conditions. The samples were immersed in a pool with a saline solution, with exposure times of 6, 12 and 23 months. The apparent diffusion coefficients were estimated, assuming that Fick's law of diffusion as per ASTM C1556 [173]. Chloride concentrations for mortars immersed in 3% NaCl solution in laboratory conditions 6, 18 and 24 months for are presented in Fig. 15A. The results

are, expressed as a percentage of the total mortar weight.

Figure 15B presents the chloride profiles measured in the studied specimens. It is verified that there is a significant reduction of the total content of chlorides and the depth of penetration in the series of mortars produced with LC3-50 cement. For the same depth (for example 20 mm) the concentration of chlorides in the series produced with OPC is 7 times higher than that produced with LC3-50. This trend coincides with what is referred to in other studies carried out in which this behaviour is justified by the dense and poorly connected network of pores and increased chloride binding in the cementitious matrix of LC3-50 [104, 145], as also discussed in Sect. 2. The values of the apparent diffusion coefficients and ratio of diffusion coefficient of OPC with respect to LC3 across exposure time is shown in Table 3. At all ages, the apparent diffusion coefficient of the series produced with OPC is an order of magnitude higher than that of the series produced with LC3-50, which confirms the high capacity of the LC3 systems to inhibit the entry and migration of chlorides and other ionic species in the cementitious matrix; consistent with several laboratory observation discussion previously in Sect. 3.

Similarly, the total chloride profiles determined on the concretes exposed to field conditions (CSM series) are presented in Fig. 15B. The results show similar trend to laboratory concretes with LC3 concrete showing lower chloride content across the diffusion depth. The difference between chloride concentrations at the same depth of 20 mm is about 2.7 times compared to OPC concrete. These results confirm the beneficial use of calcined clay concrete in high chloride concentration environments.

5.2 Marine exposure sites in India

Several demonstration structures were built with LC3 and/or calcined clay-limestone (LC2) admixture in India during the last decade [187, 252–255]. In this section, two case studies of calcined clay concrete used in marine exposure are highlighted—(1) a single storey demonstration structure built 400 m from the shore using LC2 (Calcined clay: limestone of 2:1) was used at a replacement level of 45% of the OPC and (2) Large Tetrapod concrete elements made using 30% LC2.

Fig. 15 **A** Total chloride profile of mortars produced with the LC3-50 and OPC after 6, 18 and 24 months (m) of immersion in a solution with 3% NaCl. **B** Total chloride profiles of the concretes produced with LC3-50 and OPC in the ECOT CSM, after 18 months of exposure in H1 i.e., 500 m from the seashore with high relative humidity and high chloride concentration



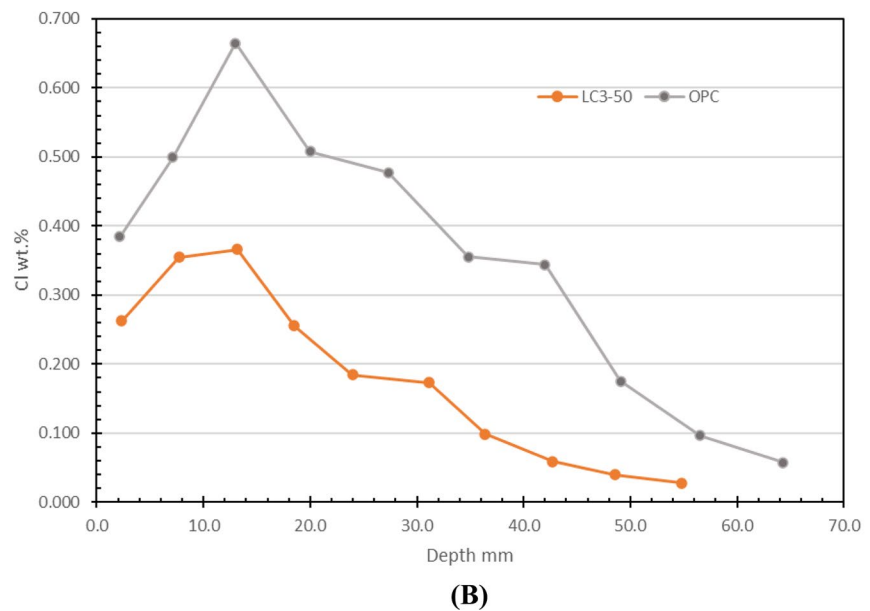


Table 3 Values of apparent diffusivity in mortars produced with OPC and LC3-50, measured at 6, 18 and 24 months of immersion in a 3% NaCl solution

	Apparent diffusion coefficient (m ² /s)		
	6 m	18 m	24 m
LC3-50	2.46×10^{-12}	1.39×10^{-12}	1.19×10^{-12}
OPC	2.62×10^{-11}	1.25×10^{-11}	1.34×10^{-11}
OPC/LC3-50	10.65	8.99	11.26

Figure 16A shows the locations and image of demonstration structure constructed for long-term monitoring of performance in field exposure condition. Mix design of the concrete and properties, including mechanical and durability properties, are summarised in detail [252]. Notably, the chloride resistance of the concrete used to construct the structure was characterised using non-steady state chloride migration test on concrete specimens cured in laboratory conditions and field-like conditions by placing them near the

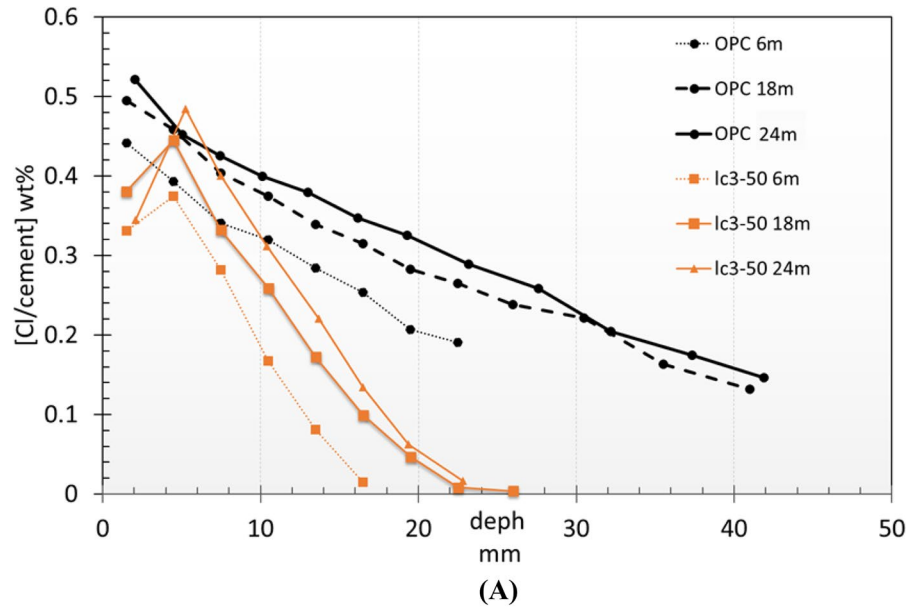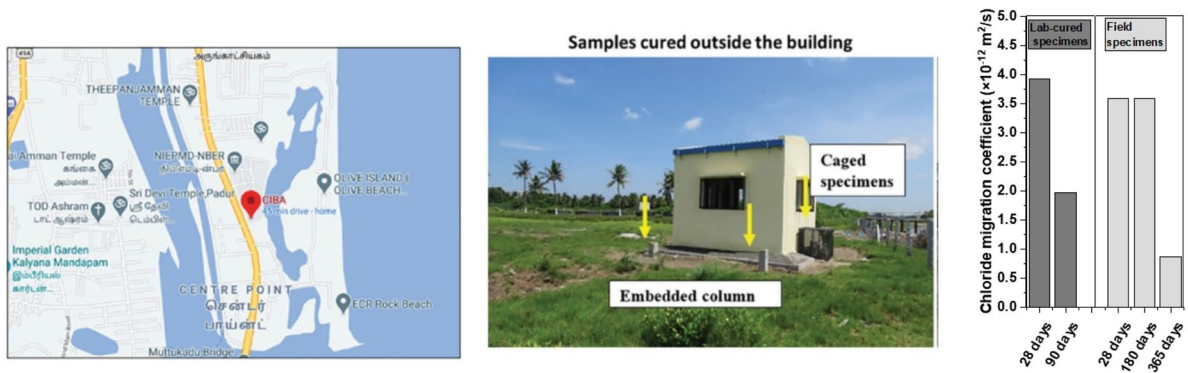

(A) Demonstration concrete structure placed in chloride exposure for long-term monitoring [252]



(B) Tetrapod produced LC2 admixture replacing 30 % of PPC cement [252]

Fig. 16 Practical use of Calcined clay-limestone (LC2) in single storey structure (A) and tetrapods structures (B) in aggressive marine environment

structure. The results presented in [252] are replotted and presented in Fig. 16A. Concrete had a compressive strength of 35 MPa at 28 days and the chloride migration coefficient less than $4 \times 10^{-12} \text{ m}^2/\text{s}$ at 28 days for lab-cured concrete. The specimens placed outside in field exposure conditions showed chloride migration coefficient below $1 \times 10^{-12} \text{ m}^2/\text{s}$ by 1 year of field exposure.

Figure 16B shows the locations and photographs of the tetrapod made with 30% LC2 admixed to PPC (Portland Pozzolana Cement, containing up to 30% fly ash). Total binder content in the concrete mixes used was 350 kg/m^3 and water-binder ratio of 0.4 was used. The details of materials and mix design can be found in [252]. Although the LC2 was used to replace PPC which already had low clinker content (i.e., 70%), the concrete was found to attain 15 MPa after 1 day which was sufficient

for the handling and shifting of the tetrapods. The concrete element placed in his natural aggressive environment will be monitored periodically for long-term performance. LC2 admixed concrete used in the structure was tested for hardened properties related to mechanical and durability performance. The charge passed in the RCPT coulombs was less than 500 and the chloride migration coefficient was about $2 \times 10^{-12} \text{ m}^2/\text{s}$ which again confirmed the good resistance to chloride ingress in the concrete used; these values would suit most performance specifications for marine exposure concretes. Such field implementation of calcined clay showcases the promising potential in various forms i.e., LC3, LC2 or simply as calcined clay, for achieving sustainability through durability enhancement in concrete used in chloride-rich aggressive environments as shown in [146, 237, 256].

6 Summary and conclusions

As calcined clay usage gains more acceptance in construction industry, the performance of calcined clay-based concrete in aggressive environments would drive the use of the materials in reinforced concrete structures that are prone to chloride-induced corrosion. Based on the detailed review of available literature dealing with chloride ingress and chemical interaction with chlorides for calcined clay based cementitious materials, the following conclusion can be drawn:

- Calcined clays can be an ideal SCM for use in chloride environments with excellent chloride resistance. This is due to a combination of factors including pore refinement, lower pore solution conductivity and changes in chloride binding characteristics. Each of these factors changes with materials characteristics such as kaolinite content of clay used, calcined clay-limestone ratio and clay type. In general, the performance of calcined kaolinite clay with about 40–50% kaolinite content is certainly improved compared to OPC, for calcined clay made with kaolinitic clay 50–70% kaolinite content, the performance is significantly improved and at lower kaolinite content below 30% availability of literature is limited to make conclusive recommendations.
- Studies on cement paste, mortar or concrete all converge to show nearly an order of magnitude lower chloride diffusion coefficient for calcined clay system, highlighting the dominant role of pore refinement in the binding matrix. Concrete containing calcined clay (with 50–70% kaolinite content in clays) is typically found to be less dependent on curing than other blended cement concrete containing fly ashes or slags. This is observed in multiple studies indicating early rise in resistivity and lower diffusion/migration coefficient at early curing age, as low as 7 days.
- Transport properties are significantly reduced compared to OPC with addition of calcined kaolinitic clays due to pore refinement while relatively fewer studies have compared lower purity kaolinite clay and other clay types. Future studies can focus on the use of lower kaolinitic content clay (<30% kaolinite content) and alternative clay minerals to assess the potential performance obtained in comparison to calcined clays with over 40% kaolinite content. This would ensure all possible sources of clays could be utilised suitably based on their availability and for optimal utilisation of resources based on the performance requirements required in different exposure conditions.
- While some studies show synergistic development in resistivity and a marginally variation in diffusion coefficient with calcined clay-limestone ratio, there is only a modest difference in binding compared with difference in binding caused due to kaolinite content of the clay. No significant difference in performance were reported for calcined clay systems for limestone additions of 10–20%. Higher dosage may be evaluated in future to increase limestone content that could lower carbon footprint of the concrete.
- Chloride resistance in calcined clay systems is found to be similar or marginally better compared to other conventional SCMs such as fly ash and slags-based concrete. Most importantly, the performance enhancement with calcined clays occurs at early curing duration without requiring extended curing making calcined clay concretes suitable for marine concrete structures. Conventional testing methods available in concrete standards are suitable for calcined clay-based concrete.
- Calcined clay-based concretes with binary or ternary blended cementitious systems (i.e., with and without limestone) show promising results with significantly delay in the onset of corrosion, i.e., longer corrosion initiation despite reduced chloride threshold, and also lower corrosion rate which highlight the benefits of using calcined clay concrete in marine exposure conditions using existing service estimate tools utilized in concrete industry. Studies focused on chloride ingress in carbonated concrete are limited and early results show that free chlorides generated upon carbonation may influence the performance in the long term which warrants more focus in future research.
- Addition of LC2 as a performance enhancing mineral admixture with other forms of blended cements containing fly ashes/slags is also seen potential areas of accelerating uptake of calcined clay for sustainability benefits—reducing CO₂ footprint and enhancing durability of concrete structures against chloride induced corrosion.

Acknowledgements Participation of Y. Dhandapani was sponsored by the National Science Foundation (NSF) through award 1903457 and the UK Engineering and Physical Sciences Research Council (EPSRC) through Grant EP/T008407/1 and EP/W021811/1. Dr. Zunino is supported by the Swiss National Science Foundation (SNSF) through an Ambizione fellowship (Grant 208719). Members of TC-CCL are acknowledged for some of their suggestions and feedbacks on the final version of the article.

Author contributions Section 1: YD, AM, WW, WK, FZ, SJ, FK, MS. Section 2.1: AM, WW, WK, FZ, SJ. Section 2.2: YD, AM, WW, WK, SA, TK. Section 3.1: YD, AC, EI, MS. Section 3.2: YD, WW, FK, KCT, EI, SB. Section 4: YD, AC. Section 5.1: YD, KCT, FM. Section 5.2: YD, MS. Review: YD, AM, WW, SJ, FK, KCT, FM, MS.

Open Access This article is licensed under a Creative Commons Attribution 4.0 International License, which permits use, sharing, adaptation, distribution and reproduction in any medium or format, as long as you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons licence, and indicate if changes were made. The images or other third party material in this article are included in the article's Creative Commons licence, unless indicated otherwise in a credit line to the material. If material is not included in the article's Creative Commons licence and your intended use is not permitted by statutory regulation or exceeds the permitted use, you will need to obtain permission directly from the copyright holder. To view a copy of this licence, visit <http://creativecommons.org/licenses/by/4.0/>.

References

1. François R, Laurens S, Deb F (2018) Corrosion and its consequences for reinforced concrete structures. Elsevier, Amsterdam
2. Stewart MG, Rosowsky DV (1998) Structural safety and serviceability of concrete bridges subject to corrosion. *J Infrastruct Syst* 4:146–155. [https://doi.org/10.1061/\(ASCE\)1076-0342\(1998\)4:4\(146\)](https://doi.org/10.1061/(ASCE)1076-0342(1998)4:4(146))
3. Vassie P (1984) Reinforcement corrosion and the durability of concrete bridges. *Proc Inst Civ Eng* 76:713–723. <https://doi.org/10.1680/iicep.1984.1207>
4. Cavalier P, Vassie P (1981) Investigation and repair of reinforcement corrosion in a bridge deck. *Proc Inst Civ Eng* 70:461–480. <https://doi.org/10.1680/iicep.1981.1784>
5. Koch GH, Brongers MPH, Thompson NG, et al (2002) Corrosion costs and preventive strategies in the United states. *NACE Int* 10
6. Koch G, Varney J, Thompson N, et al (2016) International measures of prevention, application, and economics of corrosion technologies study. *NACE Int* 1–3
7. Neville A (1995) Chloride attack of reinforced concrete: an overview. *Mater Struct* 28:63–70. <https://doi.org/10.1007/BF02473172>
8. Costa A, Appleton A (1999) Chloride penetration into concrete in marine environment—part I: main parameters affecting chloride penetration. *Mater Struct Constr* 32:252–259. <https://doi.org/10.1007/BF02479627>
9. Tang L (1999) Concentration dependence of diffusion and migration of chloride ions Part 1. Theoretical considerations. *Cem Concr Res* 29:1469–1474. [https://doi.org/10.1016/S0008-8846\(99\)00120-9](https://doi.org/10.1016/S0008-8846(99)00120-9)
10. Papadakis VG (2000) Effect of supplementary cementing materials on concrete resistance against carbonation and chloride ingress. *Cem Concr Res* 30:291–299. [https://doi.org/10.1016/S0008-8846\(99\)00249-5](https://doi.org/10.1016/S0008-8846(99)00249-5)
11. Alexander M, Ballim Y, Santhanam M (2005) Performance specifications for concrete using the durability index approach. *Indian Concr J* 79:41–46
12. Poon CS, Lam L, Kou SC et al (2001) Rate of pozzolanic reaction of metakaolin in high-performance cement pastes. *Cem Concr Res* 31:1301–1306. [https://doi.org/10.1016/S0008-8846\(01\)00581-6](https://doi.org/10.1016/S0008-8846(01)00581-6)
13. Sabir B, Wild S, Bai J (2001) Metakaolin and calcined clays as pozzolans for concrete: a review. *Cem Concr Compos* 23:441–454
14. Kaminskas R, Kubiliute R, Prialgauskaitė B (2020) Smectite clay waste as an additive for Portland cement. *Cem Concr Compos* 113:103710. <https://doi.org/10.1016/j.cemconcomp.2020.103710>
15. Snellings R, Cizer Ö, Horckmans L et al (2016) Properties and pozzolanic reactivity of flash calcined dredging sediments. *Appl Clay Sci* 129:35–39. <https://doi.org/10.1016/j.clay.2016.04.019>
16. Fernandez R, Martirena F, Scrivener KL (2011) The origin of the pozzolanic activity of calcined clay minerals: a comparison between kaolinite, illite and montmorillonite. *Cem Concr Res* 41:113–122. <https://doi.org/10.1016/j.cemconres.2010.09.013>
17. Krishnan S, Gopala Rao D, Bishnoi S (2020) Why Low-grade calcined clays are the ideal for the production of limestone calcined clay cement (LC3). In: Bishnoi S (ed) *Calcined clays for sustainable concrete*. Springer, Singapore, pp 125–130
18. Msinjili NS, Gluth GJG, Sturm P et al (2019) Comparison of calcined illitic clays (brick clays) and low-grade kaolinitic clays as supplementary cementitious materials. *Mater Struct Constr*. <https://doi.org/10.1617/s11527-019-1393-2>
19. Avet F, Snellings R, Alujas A et al (2016) Development of a new rapid, relevant and reliable (R3) testing method to evaluate the pozzolanic activity of calcined clays. *Cem Concr Res* 85:1–11. <https://doi.org/10.1016/j.cemconres.2016.02.015>
20. Avet F, Scrivener K (2018) Investigation of the calcined kaolinite content on the hydration of limestone calcined clay cement (LC3). *Cem Concr Res* 107:124–135. <https://doi.org/10.1016/j.cemconres.2018.02.016>
21. Alujas A, Fernández R, Quintana R et al (2015) Pozzolanic reactivity of low grade kaolinitic clays: influence of calcination temperature and impact of calcination products on OPC hydration. *Appl Clay Sci* 108:94–101. <https://doi.org/10.1016/j.clay.2015.01.028>



22. Day RL (1990) Pozzolans for use in low-cost housing. A state of the art report for International Development Research Centre Ottawa, CANADA
23. Chatterjee MK, Lahiri D (1967) Pozzolanic activity in relation to specific surface of some artificial pozzolanas—part I: measurement of surface area from water adsorption isotherms. *Trans Indian Ceram Soc* 26:65–70. <https://doi.org/10.1080/0371750X.1967.10855587>
24. Samanta C, Chatterjee MK (1981) Pozzolana and pozzolanic cements—a review part I: Pozzolana. *Trans Indian Ceram Soc* 40:37–43. <https://doi.org/10.1080/0371750X.1981.10822517>
25. He C, Osbaeck B, Makovicky E (1995) Pozzolanic reactions of six principal clay minerals: activation, reactivity assessments and technological effects. *Cem Concr Res* 25:1691–1702. [https://doi.org/10.1016/0008-8846\(95\)00165-4](https://doi.org/10.1016/0008-8846(95)00165-4)
26. Pera J (2001) Metakaolin and calcined clays. *Cem Concr Compos* 23:69621. [https://doi.org/10.1016/S0958-9465\(00\)00098-6](https://doi.org/10.1016/S0958-9465(00)00098-6)
27. Singh M, Garg M (2006) Reactive pozzolana from Indian clays—their use in cement mortars. *Cem Concr Res* 36:1903–1907. <https://doi.org/10.1016/j.cemconres.2004.12.002>
28. Frías M, Rodríguez O, Vegas I, Vigil R (2008) Properties of calcined clay waste and its influence on blended cement behavior. *J Am Ceram Soc* 91:1226–1230. <https://doi.org/10.1111/j.1551-2916.2008.02289.x>
29. Riding KA, Zayed A (2020) What's old is new again: a vision and path forward for calcined clay use in the USA. In: Bishnoi S (ed) *Calcined clays for sustainable concrete*. RILEM book series, vol 25. Springer, Springer, pp 785–792
30. Snellings R, Reyes RA, Hanein T et al (2022) Paper of RILEM TC 282-CCL: mineralogical characterization methods for clay resources intended for use as supplementary cementitious material. *Mater Struct*. <https://doi.org/10.1617/s11527-022-01973-1>
31. Alujas Diaz A, Almenares Reyes RS, Hanein T et al (2022) Properties and occurrence of clay resources for use as supplementary cementitious materials. *Mater Struct* 55:139. <https://doi.org/10.1617/s11527-022-01972-2>
32. Tironi A, Trezza MA, Scian AN, Irassar EF (2012) Kaolinitic calcined clays: factors affecting its performance as pozzolans. *Constr Build Mater* 28:276–281. <https://doi.org/10.1016/j.conbuildmat.2011.08.064>
33. Hanein T, Thienel K-CC, Zunino F et al (2021) Clay calcination technology: state-of-the-art review by the RILEM TC 282-CCL. *Mater Struct* 55:3. <https://doi.org/10.1617/s11527-021-01807-6>
34. Zunino F, Dhandapani Y, Ben M et al (2022) Hydration and mixture design of calcined clay blended cements: review by the RILEM TC 282-CCL. *Mater Struct Constr*. <https://doi.org/10.1617/s11527-022-02060-1>
35. Dhandapani Y, Joseph S, Geddes DA et al (2022) Fresh properties of concrete containing calcined clays: a review by RILEM TC-282 CCL. *Mater Struct Constr* 55:151. <https://doi.org/10.1617/s11527-022-01971-3>
36. Joseph S, Dhandapani Y, Geddes DA et al (2023) Mechanical properties of concrete made with calcined clay: a review by RILEM TC-282 CCL. *Mater Struct Constr* 56:1–20. <https://doi.org/10.1617/s11527-023-02118-8>
37. Dhandapani Y, Joseph S, Bishnoi S et al (2022) Durability performance of binary and ternary blended cementitious systems with calcined clay: a RILEM TC 282 CCL review. *Mater Struct Constr*. <https://doi.org/10.1617/s11527-022-01974-0>
38. IS-18189:2023 (2023) Portland calcined clay limestone cement—specification. *Bur Indian Stand*
39. BS-8615-2 (2019) Specification for pozzolanic materials for use with Portland cement Part 2: high reactivity natural calcined pozzolana. *BSI Stand Publ* 1–20
40. BS-8615-1 (2019) Specification for pozzolanic materials for use with portland cement Part-1 Natural pozzolana and natural calcined pozzolana. *BSI Stand Publ* 1–16
41. IS-1489 (part-2) (1991) IS 1489 Part-2—Portland pozzolana cement-specification part 2 Calcined Clay based. *Bur Indian Stand*
42. ASTM-C618 (2019) Standard Specification for Coal Fly Ash and Raw or Calcined Natural Pozzolan for Use. *ASTM Stand* 1–5. <https://doi.org/10.1520/C0618>
43. Kanavaris F, Vieira M, Bishnoi S et al (2023) Standardisation of low clinker cements containing calcined clay and limestone: a review by RILEM TC-282 CCL. *Mater Struct Constr*. <https://doi.org/10.1617/s11527-023-02257-y>
44. Dhandapani Y, Santhanam M (2017) Assessment of pore structure evolution in the limestone calcined clay cementitious system and its implications for performance. *Cem Concr Compos* 84:36–47. <https://doi.org/10.1016/j.cemconcomp.2017.08.012>
45. Tironi A, Scian AN, Irassar EF, Eng C (2017) Blended cements with limestone filler and kaolinitic calcined clay: filler and pozzolanic effects. *J Mater Civ Eng* 29:1–8. [https://doi.org/10.1061/\(ASCE\)MT.1943-5533.0001965](https://doi.org/10.1061/(ASCE)MT.1943-5533.0001965)
46. Cordoba GP, Zito SV, Sposito R et al (2020) Concretes with calcined clay and calcined shale: workability, mechanical, and transport properties. *J Mater Civ Eng* 32:1–11. [https://doi.org/10.1061/\(ASCE\)MT.1943-5533.0003296](https://doi.org/10.1061/(ASCE)MT.1943-5533.0003296)
47. Taylor-Lange SC, Lamou EL, Riding KA, Juenger MCG (2015) Calcined kaolinite-bentonite clay blends as supplementary cementitious materials. *Appl Clay Sci* 108:84–93. <https://doi.org/10.1016/j.clay.2015.01.025>
48. Tironi A, Cravero F, Scian AN, Irassar EF (2017) Pozzolanic activity of calcined halloysite-rich kaolinitic clays. *Appl Clay Sci* 147:11–18. <https://doi.org/10.1016/j.clay.2017.07.018>
49. Tironi A, Trezza MA, Scian AN, Irassar EF (2013) Assessment of pozzolanic activity of different calcined clays. *Cem Concr Compos* 37:319–327. <https://doi.org/10.1016/j.cemconcomp.2013.01.002>
50. He C, Makovicky E, Osbaeck B (1996) Thermal treatment and pozzolanic activity of Na- and Ca-montmorillonite. *Appl Clay Sci* 10:351–368. [https://doi.org/10.1016/0169-1317\(95\)00037-2](https://doi.org/10.1016/0169-1317(95)00037-2)
51. Werling N, Kaltenbach J, Weidler PG et al (2022) Solubility of calcined kaolinite, montmorillonite, and illite in high molar NaOH and suitability as precursors for



- geopolymers. *Clays Clay Miner* 70:270–289. <https://doi.org/10.1007/s42860-022-00185-6>
52. Maier M, Beuntner N, Thienel K-CC (2021) Mineralogical characterization and reactivity test of common clays suitable as supplementary cementitious material. *Appl Clay Sci* 202:105990. <https://doi.org/10.1016/j.clay.2021.105990>
 53. Dhandapani Y, Marsh ATM, Rahmon S et al (2023) Suitability of excavated London clay as a supplementary cementitious material: mineralogy and reactivity. *Mater Struct* 56:174. <https://doi.org/10.1617/s11527-023-02260-3>
 54. Salvador S, Pons O (2000) A semi-mobile flash dryer/calculiner unit to manufacture pozzolana from raw clay soils—application to soil stabilisation. *Constr Build Mater* 14:109–117. [https://doi.org/10.1016/S0950-0618\(00\)00005-2](https://doi.org/10.1016/S0950-0618(00)00005-2)
 55. Magnusson S, Lundberg K, Svedberg B, Knutsson S (2015) Sustainable management of excavated soil and rock in urban areas—a literature review. *J Clean Prod* 93:18–25. <https://doi.org/10.1016/j.jclepro.2015.01.010>
 56. Nouairi J, Hajjaji W, Costa CS et al (2018) Study of Zn-Pb ore tailings and their potential in cement technology. *J Afr Earth Sci* 139:165–172. <https://doi.org/10.1016/j.jafrearsci.2017.11.004>
 57. Haas M, Mongeard L, Ulrici L et al (2021) Applicability of excavated rock material: a European technical review implying opportunities for future tunnelling projects. *J Clean Prod* 315:128049. <https://doi.org/10.1016/j.jclepro.2021.128049>
 58. Scialpi G, Perrotti D (2022) The use of urban biowaste and excavated soil in the construction sector: a literature review. *Waste Manag Res* 40:262–273. <https://doi.org/10.1177/07342422X211000430>
 59. Dixit A, Du H, Pang SD (2021) Performance of mortar incorporating calcined marine clays with varying kaolin content. *J Clean Prod* 282:124513. <https://doi.org/10.1016/j.jclepro.2020.124513>
 60. Wang Q, Yan Y, Zhang Z et al (2024) An LC3-type binder produced with marine clay and municipal waste incineration fly ash. *Constr Build Mater* 411:134182. <https://doi.org/10.1016/j.conbuildmat.2023.134182>
 61. Siddique R, Klaus J (2009) Influence of metakaolin on the properties of mortar and concrete: a review. *Appl Clay Sci* 43:392–400. <https://doi.org/10.1016/j.clay.2008.11.007>
 62. Frías M, Cabrera J (2000) Pore size distribution and degree of hydration of metakaolin–cement pastes. *Cem Concr Res* 30:561–569. [https://doi.org/10.1016/S0008-8846\(00\)00203-9](https://doi.org/10.1016/S0008-8846(00)00203-9)
 63. Hollanders S, Adriaens R, Skibsted JJ et al (2016) Pozzolanic reactivity of pure calcined clays. *Appl Clay Sci* 132–133:552–560. <https://doi.org/10.1016/j.clay.2016.08.003>
 64. Kunther W, Dai Z, Skibsted J (2016) Thermodynamic modeling of hydrated white Portland cement–metakaolin–limestone blends utilizing hydration kinetics from ²⁹Si MAS NMR spectroscopy. *Cem Concr Res* 86:29–41. <https://doi.org/10.1016/j.cemconres.2016.04.012>
 65. Avet F, Boehm-Courjault E, Scrivener K (2019) Investigation of C–A–S–H composition, morphology and density in limestone calcined clay cement (LC3). *Cem Concr Res* 115:70–79. <https://doi.org/10.1016/j.cemconres.2018.10.011>
 66. Krishnan S, Emmanuel AC, Bishnoi S (2019) Hydration and phase assemblage of ternary cements with calcined clay and limestone. *Constr Build Mater* 222:64–72. <https://doi.org/10.1016/j.conbuildmat.2019.06.123>
 67. Dai Z, Tran TT, Skibsted J (2014) Aluminum incorporation in the C–S–H phase of white portland cement–metakaolin blends studied by ²⁷Al and ²⁹Si MAS NMR spectroscopy. *J Am Ceram Soc* 97:2662–2671. <https://doi.org/10.1111/jace.13006>
 68. Pegado L, Labbez C, Churakov SV (2014) Mechanism of aluminium incorporation into C–S–H from ab initio calculations. *J Mater Chem A* 2:3477–3483. <https://doi.org/10.1039/c3ta14597b>
 69. Georget F, Lothenbach B, Wilson W et al (2022) Stability of hemicarbonate under cement paste-like conditions. *Cem Concr Res* 153:106692. <https://doi.org/10.1016/j.cemconres.2021.106692>
 70. Matschei T, Lothenbach B, Glasser FP (2007) The AFm phase in Portland cement. *Cem Concr Res* 37:551–558. <https://doi.org/10.1016/j.cemconres.2006.10.013>
 71. Matschei T, Lothenbach B, Glasser FP (2007) Thermodynamic properties of Portland cement hydrates in the system CaO–Al₂O₃–SiO₂–CaSO₄–CaCO₃–H₂O. *Cem Concr Res* 37:1379–1410. <https://doi.org/10.1016/j.cemconres.2007.06.002>
 72. Zajac M, Skocek J, Lothenbach B, Ben M (2020) Late hydration kinetics: indications from thermodynamic analysis of pore solution data. *Cem Concr Res* 129:1–12. <https://doi.org/10.1016/j.cemconres.2020.105975>
 73. Zuena M, Tomasin P, Alberghina MF et al (2019) Comparison between mercury intrusion porosimetry and nuclear magnetic resonance relaxometry to study the pore size distribution of limestones treated with a new consolidation product. *Meas J Int Meas Confed* 143:234–245. <https://doi.org/10.1016/j.measurement.2019.05.021>
 74. Dhandapani Y, Santhanam M, Kaladharan G, Ramathan S (2021) Towards ternary binders involving limestone additions—a review. *Cem Concr Res* 143:106396. <https://doi.org/10.1016/j.cemconres.2021.106396>
 75. Ferreiro S, Herfort D, Damtoft JSS (2017) Effect of raw clay type, fineness, water-to-cement ratio and fly ash addition on workability and strength performance of calcined clay–limestone Portland cements. *Cem Concr Res* 101:1–12. <https://doi.org/10.1016/j.cemconres.2017.08.003>
 76. Zunino F, Scrivener K (2021) The reaction between metakaolin and limestone and its effect in porosity refinement and mechanical properties. *Cem Concr Res* 140:106307. <https://doi.org/10.1016/j.cemconres.2020.106307>
 77. Di Salvo BA, Trezza MA, Irassar EF (2020) Comparison of dolostone and limestone as filler in blended cements. *Bull Eng Geol Environ* 79:243–253. <https://doi.org/10.1007/s10064-019-01549-4>
 78. Di A, Barsi S, Marchetti G et al (2020) Carbonate rocks as fillers in blended cements: physical and mechanical



- properties. *Constr Build Mater* 248:118697. <https://doi.org/10.1016/j.conbuildmat.2020.118697>
79. Tsivilis S, Tsantilas J, Kakali G et al (2003) The permeability of Portland limestone cement concrete. *Cem Concr Res* 33:1465–1471. [https://doi.org/10.1016/S0008-8846\(03\)00092-9](https://doi.org/10.1016/S0008-8846(03)00092-9)
 80. Bentz DP, Irassar EF, Bucher BE, Weiss WJ (2009) Limestone fillers conserve cement part 2: durability issues and the effects of limestone fineness on mixtures. *Concr Int* 31:35–39
 81. Scrivener K, Martirena F, Bishnoi S, Maity S (2018) Calcined clay limestone cements (LC3). *Cem Concr Res* 114:49–56. <https://doi.org/10.1016/j.cemconres.2017.08.017>
 82. Basavaraj AS, Muni H, Dhandapani Y et al (2023) Limestone-calcined clay (LC2) as a supplementary cementitious material for concrete. *RILEM Tech Lett* 8:12–22. <https://doi.org/10.21809/rilemtechlett.2023.172>
 83. Vaasudeva BV, Dhandapani Y, Santhanam M (2021) Performance evaluation of limestone-calcined clay (LC2) combination as a cement substitute in concrete systems subjected to short-term heat curing. *Constr Build Mater* 302:124121. <https://doi.org/10.1016/j.conbuildmat.2021.124121>
 84. Avet F, Li X, Scrivener K (2018) Determination of the amount of reacted metakaolin in calcined clay blends. *Cem Concr Res* 106:40–48. <https://doi.org/10.1016/j.cemconres.2018.01.009>
 85. Justnes H (1998) A review of chloride binding in cementitious systems. *Nord Concr Res ...* 1–16
 86. Suryavanshi AK, Scantlebury JD, Lyon SB (1996) Mechanism of Friedel's salt formation in cements rich in tri-calcium aluminate. *Cem Concr Res* 26:717–727. [https://doi.org/10.1016/S0008-8846\(96\)85009-5](https://doi.org/10.1016/S0008-8846(96)85009-5)
 87. Delagrave A, Marchand J, Ollivier JP et al (1997) Chloride binding capacity of various hydrated cement paste systems. *Adv Cem Based Mater* 6:28–35. [https://doi.org/10.1016/S1065-7355\(97\)00007-2](https://doi.org/10.1016/S1065-7355(97)00007-2)
 88. Kuzel H-JJ, Pöllmann H (1991) Hydration of C3A in the presence of Ca(OH)₂, CaSO₄·2H₂O and CaCO₃. *Cem Concr Res* 21:885–895. [https://doi.org/10.1016/0008-8846\(91\)90183-I](https://doi.org/10.1016/0008-8846(91)90183-I)
 89. Balonis M, Lothenbach B, Le Saout G, Glasser FP (2010) Impact of chloride on the mineralogy of hydrated Portland cement systems. *Cem Concr Res* 40:1009–1022. <https://doi.org/10.1016/j.cemconres.2010.03.002>
 90. Heller L, Ben-Yair M (1961) Formation of calcium chloraluminat by interaction of Portland cement with seawater and chloride solutions. *Nature* 191:474–476
 91. Tritthart J (1989) Chloride binding in cement I. Investigations to determine the composition of porewater in hardened cement. *Cem Concr Res* 19:586–594. [https://doi.org/10.1016/0008-8846\(89\)90010-0](https://doi.org/10.1016/0008-8846(89)90010-0)
 92. Tritthart J (1989) Chloride binding in cement II. The influence of the hydroxide concentration in the pore solution of hardened cement paste on chloride binding. *Cem Concr Res* 19:683–691
 93. Birnin-Yauri UA, Glasser FP (1998) Friedel's salt, Ca₂Al(OH)₆(Cl, OH)·2H₂O: its solid solutions and their role in chloride binding. *Cem Concr Res* 28:1713–1723. [https://doi.org/10.1016/S0008-8846\(98\)00162-8](https://doi.org/10.1016/S0008-8846(98)00162-8)
 94. Renaudin G, Kubel F, Rivera JP, Francois M (1999) Structural phase transition and high temperature phase structure of Friedel's salt, 3CaO · Al₂O₃ · CaCl₂ · 10H₂O. *Cem Concr Res* 29:1937–1942. [https://doi.org/10.1016/S0008-8846\(99\)00199-4](https://doi.org/10.1016/S0008-8846(99)00199-4)
 95. Arya C, Buenfeld NRR, Newman JBB (1990) Factors influencing chloride-binding in concrete. *Cem Concr Res* 20:291–300. [https://doi.org/10.1016/0008-8846\(90\)90083-A](https://doi.org/10.1016/0008-8846(90)90083-A)
 96. De Weerd K, Lothenbach B, Geiker MR (2019) Comparing chloride ingress from seawater and NaCl solution in Portland cement mortar. *Cem Concr Res* 115:80–89. <https://doi.org/10.1016/j.cemconres.2018.09.014>
 97. De Weerd K (2021) Chloride binding in concrete: recent investigations and recognised knowledge gaps: RILEM Robert L'Hermite Medal Paper 2021. *Mater Struct Constr* 54:1–16. <https://doi.org/10.1617/s11527-021-01793-9>
 98. De Weerd K, Orsáková D, Müller ACA et al (2016) Towards the understanding of chloride profiles in marine exposed concrete, impact of leaching and moisture content. *Constr Build Mater* 120:418–431. <https://doi.org/10.1016/j.conbuildmat.2016.05.069>
 99. Shi Z, Geiker MR, De Weerd K et al (2017) Role of calcium on chloride binding in hydrated Portland cement–metakaolin–limestone blends. *Cem Concr Res* 95:205–216. <https://doi.org/10.1016/j.cemconres.2017.02.003>
 100. Sui S, Georget F, Maraghechi H et al (2019) Towards a generic approach to durability: factors affecting chloride transport in binary and ternary cementitious materials. *Cem Concr Res* 124:105783. <https://doi.org/10.1016/j.cemconres.2019.105783>
 101. Shi Z, Geiker MR, Lothenbach B et al (2017) Friedel's salt profiles from thermogravimetric analysis and thermodynamic modelling of Portland cement-based mortars exposed to sodium chloride solution. *Cem Concr Compos* 78:73–83. <https://doi.org/10.1016/j.cemconcomp.2017.01.002>
 102. Sui S, Wilson W, Georget F et al (2019) Quantification methods for chloride binding in Portland cement and limestone systems. *Cem Concr Res* 125:105864. <https://doi.org/10.1016/j.cemconres.2019.105864>
 103. Wilson W, Gonthier JN, Georget F et al (2022) Insights on chemical and physical chloride binding in blended cement pastes. *Cem Concr Res* 156:106747. <https://doi.org/10.1016/j.cemconres.2022.106747>
 104. Maraghechi H, Avet F, Wong H et al (2018) Performance of limestone calcined clay cement (LC3) with various kaolinite contents with respect to chloride transport. *Mater Struct* 51:125. <https://doi.org/10.1617/s11527-018-1255-3>
 105. Avet F, Scrivener K (2020) Influence of pH on the chloride binding capacity of Limestone Calcined Clay Cements (LC3). *Cem Concr Res* 131:106031. <https://doi.org/10.1016/j.cemconres.2020.106031>
 106. Thomas MDA, Hooton RD, Scott A, Zibara H (2012) The effect of supplementary cementitious materials on chloride binding in hardened cement paste. *Cem Concr Res* 42:1–7. <https://doi.org/10.1016/j.cemconres.2011.01.001>
 107. Ben HM, Lothenbach B, Le Saout G, Winnefeld F (2012) Influence of slag chemistry on the hydration



- of alkali-activated blast-furnace slag—part I: effect of MgO. *Cem Concr Res* 41:955–963. <https://doi.org/10.1016/j.cemconres.2011.05.002>
108. Kocaba V (2009) Development and evaluation of methods to follow microstructural development of cementitious systems including slags. 4523
 109. Machner A, Zajac M, Ben Haha M et al (2018) Chloride-binding capacity of hydrotalcite in cement pastes containing dolomite and metakaolin. *Cem Concr Res* 107:163–181. <https://doi.org/10.1016/j.cemconres.2018.02.002>
 110. Shah V, Dhandapani Y, Scott A (2021) Pore structure characteristics of MgO-SiO₂ binder. *J Am Ceram Soc.* <https://doi.org/10.1111/jace.17971>
 111. Ke X, Bernal SA, Provis JL (2017) Uptake of chloride and carbonate by Mg-Al and Ca-Al layered double hydroxides in simulated pore solutions of alkali-activated slag cement. *Cem Concr Res* 100:1–13. <https://doi.org/10.1016/j.cemconres.2017.05.015>
 112. Plusquellec G, Nonat A (2016) Interactions between calcium silicate hydrate (C-S-H) and calcium chloride, bromide and nitrate. *Cem Concr Res* 90:89–96. <https://doi.org/10.1016/j.cemconres.2016.08.002>
 113. Labbez C, Pochard I, Jönsson B, Nonat A (2011) C-S-H/solution interface: experimental and Monte Carlo studies. *Cem Concr Res* 41:161–168. <https://doi.org/10.1016/j.cemconres.2010.10.002>
 114. Yoshida S, Elakneswaran Y, Nawa T (2021) Electrostatic properties of C-S-H and C-A-S-H for predicting calcium and chloride adsorption. *Cem Concr Compos* 121:104109. <https://doi.org/10.1016/j.cemconcomp.2021.104109>
 115. Jin S, Liu K, Zhang G et al (2020) Effect of corrosive ions (Cl⁻, SO₄²⁻, and Mg²⁺) on the nanostructure and chloride binding property of C-A-S-H Gel. *J Wuhan Univ Technol Sci Ed* 35:1061–1072. <https://doi.org/10.1007/s11595-020-2356-8>
 116. Kalinichev AG, Kirkpatrick RJ (2002) Molecular dynamics modeling of chloride binding to the surfaces of calcium hydroxide, hydrated calcium aluminate, and calcium silicate phases. *Chem Mater* 14:3539–3549. <https://doi.org/10.1021/cm0107070>
 117. Kalinichev AG, Wang J, Kirkpatrick RJ (2007) Molecular dynamics modeling of the structure, dynamics and energetics of mineral-water interfaces: application to cement materials. *Cem Concr Res* 37:337–347. <https://doi.org/10.1016/j.cemconres.2006.07.004>
 118. Bernard E, Yan Y, Lothenbach B (2021) Effective cation exchange capacity of calcium silicate hydrates (C-S-H). *Cem Concr Res* 143:106393. <https://doi.org/10.1016/j.cemconres.2021.106393>
 119. Zibara H, Hooton RD, Thomas MD, Stanish K (2008) Influence of the C/S and C/A ratios of hydration products on the chloride ion binding capacity of lime-SF and lime-MK mixtures. *Cem Concr Res* 38:422–442. <https://doi.org/10.1016/j.cemconres.2007.08.024>
 120. Kunther W, Ferreiro S, Skibsted J (2017) Influence of the Ca/Si ratio on the compressive strength of cementitious calcium-silicate-hydrate binders. *J Mater Chem A* 5:17401–17412. <https://doi.org/10.1039/C7TA06104H>
 121. Zhou Y, Hou D, Jiang J et al (2018) Experimental and molecular dynamics studies on the transport and adsorption of chloride ions in the nano-pores of calcium silicate phase: the influence of calcium to silicate ratios. *Microporous Mesoporous Mater* 255:23–35. <https://doi.org/10.1016/j.micromeso.2017.07.024>
 122. Danner T, Geiker MR (2018) Long-term influence of concrete surface and crack orientation on self-healing and ingress in cracks—field observations. *Nord Concr Res* 58:1–16. <https://doi.org/10.2478/ncr-2018-0001>
 123. Danner T, Norden G, Justnes H (2018) Characterisation of calcined raw clays suitable as supplementary cementitious materials. *Appl Clay Sci* 162:391–402. <https://doi.org/10.1016/j.clay.2018.06.030>
 124. Babaahmadi A, Machner A, Kunther W et al (2022) Chloride binding in Portland composite cements containing metakaolin and silica fume. *Cem Concr Res* 161:106924. <https://doi.org/10.1016/j.cemconres.2022.106924>
 125. Friedmann H, Amiri O, Ait-Mokhtar A (2008) Physical modeling of the electrical double layer effects on multi-species ions transport in cement-based materials. *Cem Concr Res* 38:1394–1400. <https://doi.org/10.1016/j.cemconres.2008.06.003>
 126. Chatterji S, Kawamura M (1992) Electrical double layer, ion transport and reactions in hardened cement paste. *Cem Concr Res* 22:774–782. [https://doi.org/10.1016/0008-8846\(92\)90101-Z](https://doi.org/10.1016/0008-8846(92)90101-Z)
 127. Appelo CAJ (2017) Solute transport solved with the Nernst-Planck equation for concrete pores with ‘free’ water and a double layer Cement and Concrete Research Solute transport solved with the Nernst-Planck equation for concrete pores with ‘free’ water and a double layer. <https://doi.org/10.1016/j.cemconres.2017.08.030>
 128. Dhandapani Y (2020) Composite cements with limestone additions: microstructure and transport properties (Ph.D. Thesis, IIT Madras)
 129. Hemstad P, Machner A, De Weerd K (2020) The effect of artificial leaching with HCl on chloride binding in ordinary Portland cement paste. *Cem Concr Res* 130:105976. <https://doi.org/10.1016/j.cemconres.2020.105976>
 130. Ipavec A, Vuk T, Gabrovšek R, Kaučič V (2013) Chloride binding into hydrated blended cements: the influence of limestone and alkalinity. *Cem Concr Res* 48:74–85. <https://doi.org/10.1016/j.cemconres.2013.02.010>
 131. Sergi G, Yu SW, Page CL (1992) Diffusion of chloride and hydroxyl ions in cementitious materials exposed to a saline environment. *Mag Concr Res* 44:63–69. <https://doi.org/10.1680/mac.1992.44.158.63>
 132. Jain A, Gencturk B, Pirbazari M et al (2021) Influence of pH on chloride binding isotherms for cement paste and its components. *Cem Concr Res* 143:106378. <https://doi.org/10.1016/j.cemconres.2021.106378>
 133. Glasser FP, Kindness A, Stronach SA (1999) Stability and solubility relationships in AFm phases. Part I. Chloride, sulfate and hydroxide. *Cem Concr Res* 29:861–866. [https://doi.org/10.1016/S0008-8846\(99\)00055-1](https://doi.org/10.1016/S0008-8846(99)00055-1)
 134. Tritthart J (1989) Chloride binding in cement II. The influence of the hydroxide concentration in the pore solution of hardened cement paste on chloride binding. *Cem*



- Concr Res 19:683–691. [https://doi.org/10.1016/0008-8846\(89\)90039-2](https://doi.org/10.1016/0008-8846(89)90039-2)
135. Zhu Q, Jiang L, Chen Y et al (2012) Effect of chloride salt type on chloride binding behavior of concrete. *Constr Build Mater* 37:512–517. <https://doi.org/10.1016/j.conbuildmat.2012.07.079>
136. De Weerd K, Colombo A, Coppola L et al (2015) Impact of the associated cation on chloride binding of Portland cement paste. *Cem Concr Res* 68:196–202. <https://doi.org/10.1016/j.cemconres.2014.01.027>
137. Garboczi EJ (1990) Permeability, diffusivity, and microstructural parameters: a critical review. *Cem Concr Res* 20:591–601
138. McCarter WJ, Starrs G, Chrisp TM (2000) Electrical conductivity, diffusion, and permeability of Portland cement-based mortars. *Cem Concr Res* 30:1395–1400. [https://doi.org/10.1016/S0008-8846\(00\)00281-7](https://doi.org/10.1016/S0008-8846(00)00281-7)
139. Snyder KA (2001) The relationship between the formation factor and the diffusion coefficient of porous materials saturated with concentrated electrolytes: theoretical and experimental considerations. *Concr Sci Eng*. <https://doi.org/10.1017/CBO9781107415324.004>
140. Page CL, Short NR, Tarras El et al (1981) Diffusion of chloride ions in hardened cement pastes. *Cem Concr Res* 11:395–406. [https://doi.org/10.1016/0008-8846\(81\)90111-3](https://doi.org/10.1016/0008-8846(81)90111-3)
141. Nguyen QD, Khan MSH, Castel A (2018) Engineering properties of limestone calcined clay concrete. *J Adv Concr Technol* 16:343–357. <https://doi.org/10.3151/jact.16.343>
142. Li K, Zhao F, Zhang Y (2019) Influence of carbonation on the chloride ingress into concrete: theoretical analysis and application to durability design. *Cem Concr Res* 123:105788. <https://doi.org/10.1016/j.cemconres.2019.105788>
143. Basheer L, Kropp J, Cleland DJ (2001) Assessment of the durability of concrete from its permeation properties: a review. *Constr Build Mater* 15:93–103. [https://doi.org/10.1016/S0950-0618\(00\)00058-1](https://doi.org/10.1016/S0950-0618(00)00058-1)
144. Dhandapani Y, Santhanam M (2020) Investigation on the microstructure-related characteristics to elucidate performance of composite cement with limestone-calcined clay combination. *Cem Concr Res* 129:105959. <https://doi.org/10.1016/j.cemconres.2019.105959>
145. Dhandapani Y, Sakthivel T, Santhanam M et al (2018) Mechanical properties and durability performance of concretes with limestone calcined clay cement (LC3). *Cem Concr Res* 107:136–151. <https://doi.org/10.1016/j.cemconres.2018.02.005>
146. Pillai RG, Gettu R, Santhanam M et al (2019) Service life and life cycle assessment of reinforced concrete systems with limestone calcined clay cement (LC3). *Cem Concr Res* 118:111–119. <https://doi.org/10.1016/j.cemconres.2018.11.019>
147. Wilson W, Georget F, Scrivener K (2021) Unraveling chloride transport/microstructure relationships for blended-cement pastes with the mini-migration method. *Cem Concr Res* 140:106264. <https://doi.org/10.1016/j.cemconres.2020.106264>
148. Chen JJ, Kwan AKH, Jiang Y (2014) Adding limestone fines as cement paste replacement to reduce water permeability and sorptivity of concrete. *Constr Build Mater* 56:87–93. <https://doi.org/10.1016/j.conbuildmat.2014.01.066>
149. Yang CC (2006) On the relationship between pore structure and chloride diffusivity from accelerated chloride migration test in cement-based materials. *Cem Concr Res* 36:1304–1311. <https://doi.org/10.1016/j.cemconres.2006.03.007>
150. Loser R, Lothenbach B, Leemann A, Tuchschnid M (2010) Chloride resistance of concrete and its binding capacity—comparison between experimental results and thermodynamic modeling. *Cem Concr Compos* 32:34–42. <https://doi.org/10.1016/j.cemconcomp.2009.08.001>
151. Wilson W, Gonthier JN, Georget F, Scrivener K (2020) Tortuosity as a key parameter of chloride diffusion in LC3 systems. In: Bishnoi S (ed) *Calcined clays for sustainable concrete*, pp 593–600
152. Halamickova P, Detwiler RJ, Bentz DP, Garboczi EJ (1995) Water permeability and chloride ion diffusion in portland cement mortars: relationship to sand content and critical pore diameter. *Cem Concr Res* 25:790–802. [https://doi.org/10.1016/0008-8846\(95\)00069-0](https://doi.org/10.1016/0008-8846(95)00069-0)
153. Zolfagharnasab A, Ramezaniapour AA, Bahman-Zadeh F (2021) Investigating the potential of low-grade calcined clays to produce durable LC3 binders against chloride ions attack. *Constr Build Mater* 303:124541. <https://doi.org/10.1016/j.conbuildmat.2021.124541>
154. Elakneswaran Y, Nawa T, Kurumisawa K (2009) Electrokinetic potential of hydrated cement in relation to adsorption of chlorides. *Cem Concr Res* 39:340–344. <https://doi.org/10.1016/j.cemconres.2009.01.006>
155. Phung QT, Maes N, Jacobs E et al (2019) Insights and issues on the correlation between diffusion and microstructure of saturated cement pastes. *Cem Concr Compos* 96:106–117. <https://doi.org/10.1016/j.cemconcomp.2018.11.018>
156. Elakneswaran Y, Iwasa A, Nawa T et al (2010) Ion-cement hydrate interactions govern multi-ionic transport model for cementitious materials. *Cem Concr Res* 40:1756–1765. <https://doi.org/10.1016/j.cemconres.2010.08.019>
157. Korb J-P, McDonald PJ, Monteilhet L et al (2007) Comparison of proton field-cycling relaxometry and molecular dynamics simulations for proton–water surface dynamics in cement-based materials. *Cem Concr Res* 37:348–350. <https://doi.org/10.1016/j.cemconres.2006.02.009>
158. Sparreboom W, van den Berg A, Eijkel JCTT (2009) Principles and applications of nanofluidic transport. *Nat Nanotechnol* 4:713–720. <https://doi.org/10.1038/nnano.2009.332>
159. Chatterji S (1994) Transportation of ions through cement based materials. Part 3 experimental evidence for the basic equations and some important deductions. *Cem Concr Res* 24:1229–1236. [https://doi.org/10.1016/0008-8846\(94\)90107-4](https://doi.org/10.1016/0008-8846(94)90107-4)
160. Zhang Z, Scherer GW (2021) Physical and chemical effects of isopropanol exchange in cement-based materials. *Cem Concr Res* 145:106461. <https://doi.org/10.1016/j.cemconres.2021.106461>



161. Monteiro PJM, Maso JC, Ollivier JP (1985) The aggregate-mortar interface. *Cem Concr Res* 15:953–958. [https://doi.org/10.1016/0008-8846\(85\)90084-5](https://doi.org/10.1016/0008-8846(85)90084-5)
162. Du H, Gao HJ, Pang SD (2016) Improvement in concrete resistance against water and chloride ingress by adding graphene nanoplatelet. *Cem Concr Res* 83:114–123. <https://doi.org/10.1016/j.cemconres.2016.02.005>
163. Delagrave A, Bigas JPP, Ollivier JPP et al (1997) Influence of the interfacial zone on the chloride diffusivity of mortars. *Adv Cem Based Mater* 5:86–92. [https://doi.org/10.1016/S1065-7355\(96\)00008-9](https://doi.org/10.1016/S1065-7355(96)00008-9)
164. Wu K, Xu L, De SG et al (2015) Influence of the interfacial transition zone and interconnection on chloride migration of Portland Cement Mortar. *J Adv Concr Technol* 13:169–177. <https://doi.org/10.3151/jact.13.169>
165. Wang J, Kalinichev AG, Amonette JE, Kirkpatrick RJ (2003) Interlayer structure and dynamics of Cl-bearing hydroxalite: far infrared spectroscopy and molecular dynamics modeling. *Am Miner* 88:398–409. <https://doi.org/10.2138/am-2003-2-316>
166. Shane JD, Mason TO, Jennings HM et al (2000) Effect of the interfacial transition zone on the conductivity of Portland Cement Mortars. *J Am Ceram Soc* 83:1137–1144. <https://doi.org/10.1111/j.1151-2916.2000.tb01344.x>
167. Wong HSS, Zobel M, Buenfeld NRR, Zimmerman RWW (2009) Influence of the interfacial transition zone and microcracking on the diffusivity, permeability and sorptivity of cement-based materials after drying. *Mag Concr Res* 61:571–589. <https://doi.org/10.1680/macr.2008.61.8.571>
168. Pan Z, Fang X, Chen A (2022) Effect of aggregate morphology on physical tortuosity of chloride diffusive path at meso-scale of concrete. *Constr Build Mater* 323:126215. <https://doi.org/10.1016/j.conbuildmat.2021.126215>
169. Ngala VT, Page CL, Ngala VT et al (1997) Effects of carbonation on pore structure and diffusional properties of hydrated cement pastes. *Cem Concr Res* 27:995–1007. [https://doi.org/10.1016/S0008-8846\(97\)00102-6](https://doi.org/10.1016/S0008-8846(97)00102-6)
170. Yang P, Dhandapani Y, Santhanam M, Neithalath N (2020) Simulation of chloride diffusion in fly ash and limestone-calcined clay cement (LC3) concretes and the influence of damage on service-life. *Cem Concr Res* 130:106010. <https://doi.org/10.1016/j.cemconres.2020.106010>
171. Tang L, Lars-Olof N, Luping T et al (1992) Rapid Determination of the chloride diffusivity in concrete by applying an electrical field. *ACI Mater J* 89:40–53. <https://doi.org/10.1364/OPEX.12.001497>
172. Nord Build 443 (1995) NT Build 443 Concrete. Hardened: Accelerated Chloride Penetration. NordTest 1–5
173. ASTM C1556-11a (2011) Standard test method for determining the apparent chloride diffusion coefficient of cementitious mixtures by bulk diffusion. *ASTM Int* 1–7
174. NT Build 492 (1999) Concrete, mortar and cement-based repair materials: Chloride migration coefficient from non-steady-state migration experiments. NordTest 1–8
175. ASTM C1202 (2012) Standard test method for electrical indication of concrete's ability to resist chloride ion penetration. *Am Soc Test Mater*. <https://doi.org/10.1520/C1202-12.2>
176. ASTM C1876 (2019) ASTM standard C1876—standard test method for bulk electrical resistivity or bulk conductivity of hardened concrete. *ASTM Int*. <https://doi.org/10.1520/C1760-12.2>
177. ASTM-C1760 (2012) ASTM standard C1760—standard test method for bulk electrical conductivity of hardened concrete
178. SANS-3001-CO3-3 (2015) SANS 3001-CO3-3 Civil engineering test methods. Part CO3-3: concrete durability index testing—chloride conductivity test
179. AASHTO-T358 (2015) Standard method of test for surface resistivity indication of concrete's ability to resist chloride ion penetration. *Am Assoc State Highw Transp Off*. <https://doi.org/10.1520/C1202-12.2>
180. AASHTO-PP84 (2017) Standard practice for developing performance engineered concrete pavement mixtures. *Am Assoc State Highw Transp Off* 1:1–36
181. Diamond S, Huang J (2001) The ITZ in concrete -a different view based on image analysis and SEM observations. *Cem Concr Compos* 23:179–188. [https://doi.org/10.1016/S0958-9465\(00\)00065-2](https://doi.org/10.1016/S0958-9465(00)00065-2)
182. Elfmarkova V, Spiesz P, Brouwers HJHJH (2015) Determination of the chloride diffusion coefficient in blended cement mortars. *Cem Concr Res* 78:190–199. <https://doi.org/10.1016/j.cemconres.2015.06.014>
183. Dhandapani Y, Santhanam M (2022) On the correlations between different chloride transport parameters and their role in service life estimation. *Sustain Resilient Infrastruct* 00:1–16. <https://doi.org/10.1080/23789689.2022.2097771>
184. Fjendbo S, Sørensen HE, De Weerd K, Geiker MR (2021) The square root method for chloride ingress prediction—applicability and limitations. *Mater Struct Constr* 54:1–19. <https://doi.org/10.1617/s11527-021-01643-8>
185. CEB-FIB bulletin No. 34 (2006) MC-SLD:2006. Model Code for Service Life Design (CEB-FIB bulletin No. 34)
186. Díaz E, Martirena F, Alujas A, Torrent R (2015) Low carbon cement: durability performance assessment with laboratory and site tests. In: Scrivener K, Favier A (eds) *Calcined clays for sustainable concrete*, pp 277–282
187. Dhandapani Y, Santhanam M, Gettu R, Pillai RG (2020) Perspectives on blended cementitious systems with calcined clay–limestone combination for sustainable low carbon cement transition. *Indian Concr J* 94:25–38
188. Nguyen QD, Afroz S, Castel A (2020) Influence of clay calcination method on the mechanical properties and chloride diffusion resistance of limestone calcined clay cement (LC3) concrete, 1–14
189. Ram K, Flegar M, Serdar M, Scrivener KL (2023) Influence of low- to medium-kaolinite clay on the durability of limestone calcined clay cement. *Materials (Basel)* 16:374
190. Ram K, Serdar M, Londono-Zuluaga D, Scrivener K (2023) Does carbon footprint reduction impair mechanical properties and service life of concrete? *Mater Struct Constr*. <https://doi.org/10.1617/s11527-022-02090-9>
191. Liu JC, Hossain MU, Xuan D et al (2023) Mechanical and durability performance of sustainable concretes containing conventional and emerging supplementary



- cementitious materials. *Dev Built Environ* 15:100197. <https://doi.org/10.1016/j.dibe.2023.100197>
192. Ejbouh A, Ech-chebab A, Hassi S et al (2023) Durability assessment of LC3-based reinforced concrete under combined chloride-sulfate environment via the EIS technique. *Constr Build Mater* 366:130194. <https://doi.org/10.1016/j.conbuildmat.2022.130194>
193. Bhavani S, Prasad MLV (2023) Strength and durability properties of SCC developed using limestone calcined clay cement (LC3). *Mater Today Proc.* <https://doi.org/10.1016/j.matpr.2023.04.497>
194. Yadak Yaraghi AH, Ramezani-pour AM, Ramezani-pour AA et al (2022) Evaluation of test procedures for durability and permeability assessment of concretes containing calcined clay. *J Build Eng* 58:105016. <https://doi.org/10.1016/j.jobe.2022.105016>
195. Nguyen QD, Afroz S, Castel A (2020) Influence of calcined clay reactivity on the mechanical properties and chloride diffusion resistance of limestone calcined clay cement (LC3) concrete. *J Mar Sci Eng* 8:1–14
196. Dieu Nguyen Q, Khan MSH, Castel A (2020) Chloride diffusion in limestone flash calcined clay cement concrete. *ACI Mater J* 117:165–175. <https://doi.org/10.14359/51725986>
197. Cordoba G, Sposito R, Köberl M et al (2022) Chloride migration and long-term natural carbonation on concretes with calcined clays: a study of calcined clays in Argentina. *Case Stud Constr Mater.* <https://doi.org/10.1016/j.cscm.2022.e01190>
198. Bakera AT, Alexander MG (2019) Use of metakaolin as a supplementary cementitious material in concrete, with a focus on durability properties. *RILEM Tech Lett* 4:89–102
199. Canbek O, Washburn NR, Kurtis KE (2022) Relating LC3 microstructure, surface resistivity and compressive strength development. *Cem Concr Res* 160:106920. <https://doi.org/10.1016/j.cemconres.2022.106920>
200. Redondo-Soto C, Morales-Cantero A, Cuesta A et al (2023) Limestone calcined clay binders based on a Belite-rich cement. *Cem Concr Res* 163:107018. <https://doi.org/10.1016/j.cemconres.2022.107018>
201. Rengaraju S, Pillai RG (2021) An accelerated chloride threshold test for uncoated steel in highly resistive cementitious systems (hr-ACT test). *Constr Build Mater* 305:124797. <https://doi.org/10.1016/j.conbuildmat.2021.124797>
202. Dhandapani Y, Santhanam M (2020) Influence of calcined clay-limestone ratio on properties of concrete with limestone calcined clay cement (LC3). In: Bishnoi S (ed) *Calcined clays for sustainable concrete: proceedings of 3rd international conference on calcined clays for sustainable concrete*. Springer, Singapore, pp 731–738
203. Beaudoin JJ (1979) Porosity measurement of some hydrated cementitious systems by high pressure mercury intrusion-microstructural limitations. *Cem Concr Res* 9:771–781. [https://doi.org/10.1016/0008-8846\(79\)90073-5](https://doi.org/10.1016/0008-8846(79)90073-5)
204. Khatib JM, Wild S (1996) Pore size distribution of metakaolin paste. *Cem Concr Res* 26:1545–1553. [https://doi.org/10.1016/0008-8846\(96\)00147-0](https://doi.org/10.1016/0008-8846(96)00147-0)
205. Yu Z, Ye G (2013) The pore structure of cement paste blended with fly ash. *Constr Build Mater* 45:30–35
206. Berodier E, Scrivener K (2015) Evolution of pore structure in blended systems. *Cem Concr Res* 73:25–35. <https://doi.org/10.1016/j.cemconres.2015.02.025>
207. Yu Z, Ma J, Ye G et al (2017) Effect of fly ash on the pore structure of cement paste under a curing period of 3years. *Constr Build Mater* 144:493–501. <https://doi.org/10.1016/j.conbuildmat.2017.03.182>
208. Nguyen QH, Lorente S, Duhard-Barone A (2017) Effect of the pore size of cement based materials on ionic transport. *Constr Build Mater* 147:160–167. <https://doi.org/10.1016/j.conbuildmat.2017.04.157>
209. Gluth GJG, Hillemeier B (2012) Pore structure and permeability of hardened calcium aluminate cement pastes of low w/c ratio. *Mater Struct* 46:1497–1506. <https://doi.org/10.1617/s11527-012-9991-2>
210. Neithalath N, Sumanasooriya MS, Deo O (2010) Characterizing pore volume, sizes, and connectivity in pervious concretes for permeability prediction. *Mater Charact* 61:802–813. <https://doi.org/10.1016/j.matchar.2010.05.004>
211. Nokken MR, Hooton RD (2007) Using pore parameters to estimate permeability or conductivity of concrete. *Mater Struct* 41:1–16
212. Cui L, Cahyadi JH (2001) Permeability and pore structure of OPC paste. *Cem Concr Res* 31:277–282. [https://doi.org/10.1016/S0008-8846\(00\)00474-9](https://doi.org/10.1016/S0008-8846(00)00474-9)
213. Wang Y, Shui Z, Gao X et al (2019) Understanding the chloride binding and diffusion behaviors of marine concrete based on Portland limestone cement-alumina enriched pozzolans. *Constr Build Mater* 198:207–217. <https://doi.org/10.1016/j.conbuildmat.2018.11.270>
214. Petcherdchoo A (2013) Time dependent models of apparent diffusion coefficient and surface chloride for chloride transport in fly ash concrete. *Constr Build Mater* 38:497–507. <https://doi.org/10.1016/j.conbuildmat.2012.08.041>
215. Qiao C, Suraneni P, Weiss J (2018) Damage in cement pastes exposed to NaCl solutions. *Constr Build Mater* 171:120–127. <https://doi.org/10.1016/j.conbuildmat.2018.03.123>
216. Qiao C, Suraneni P, Tsui Chang M, Weiss J (2018) Damage in cement pastes exposed to MgCl2 solutions. *Mater Struct Constr* 51:1–15. <https://doi.org/10.1617/s11527-018-1191-2>
217. Cabeza M, Keddam M, Nóvoa XR et al (2006) Impedance spectroscopy to characterize the pore structure during the hardening process of Portland cement paste. *Electrochim Acta* 51:1831–1841. <https://doi.org/10.1016/j.electacta.2005.02.125>
218. Borrachero MV, Monzo J, Amahjour F et al (2001) Enhanced conductivity measurement techniques for evaluation of fly ash pozzolanic activity. *Cem Concr Res* 31:41–49. [https://doi.org/10.1016/S0008-8846\(00\)00434-8](https://doi.org/10.1016/S0008-8846(00)00434-8)
219. Christensen B, Coverdale T, Olson R et al (1994) Impedance spectroscopy of hydrating cement-based materials: measurement, interpretation, and application. *J Ceram Soc* 77:2789–2804



220. Dotelli G, Mari CM (2001) The evolution of cement paste hydration process by impedance spectroscopy. *Mater Sci Eng A* 303:54–59. [https://doi.org/10.1016/S0921-5093\(00\)01886-4](https://doi.org/10.1016/S0921-5093(00)01886-4)
221. Tibbetts CM, Paris JM, Ferraro CC et al (2020) Relating water permeability to electrical resistivity and chloride penetrability of concrete containing different supplementary cementitious materials. *Cem Concr Compos* 107:103491. <https://doi.org/10.1016/j.cemconcomp.2019.103491>
222. Tumidajski PJ, Lin B (1998) On the validity of the Katz–Thompson equation for permeabilities in concrete. *Cem Concr Res* 28:643–647. [https://doi.org/10.1016/S0008-8846\(98\)00032-5](https://doi.org/10.1016/S0008-8846(98)00032-5)
223. Boddy A, Bentz E, Thomas MDA, Hooton RD (1999) Overview and sensitivity study of a multimechanistic chloride transport model. *Cem Concr Res* 29:827–837. [https://doi.org/10.1016/S0008-8846\(99\)00045-9](https://doi.org/10.1016/S0008-8846(99)00045-9)
224. Thomas MDA, Phil B et al (1999) Modelling chloride diffusion in concrete effect of fly ash and slag. *Cem Concr Res* 29:487–495. [https://doi.org/10.1016/S0008-8846\(98\)00192-6](https://doi.org/10.1016/S0008-8846(98)00192-6)
225. Mangat PSS, Molloy BTT (1994) Predicting of long term chloride concentration in concrete. *Mater Struct* 27:338–346. <https://doi.org/10.1007/BF02473426>
226. Andrade C, Castellote M, D'Andrea R (2011) Measurement of ageing effect on chloride diffusion coefficients in cementitious matrices. *J Nucl Mater* 412:209–216. <https://doi.org/10.1016/j.jnucmat.2010.12.236>
227. Crank J (1979) *The mathematics of diffusion*. Oxford University Press, Oxford
228. Nokken M, Boddy A, Hooton RD, Thomas MDA (2006) Time dependent diffusion in concrete—three laboratory studies. *Cem Concr Res* 36:200–207. <https://doi.org/10.1016/j.cemconres.2004.03.030>
229. Rooij D (2002) Time dependency of chloride diffusion. In: *Third RILEM workshop on testing and modelling the chloride ingress into concrete 9–10 September 2002, Madrid, Spain*, pp 421–431
230. Stanish K, Thomas M (2003) The use of bulk diffusion test to establish time dependent concrete chloride diffusion coefficients. *Cem Concr Res* 33:55–62. [https://doi.org/10.1016/S0008-8846\(02\)00925-0](https://doi.org/10.1016/S0008-8846(02)00925-0)
231. Isgor OB, Weiss WJ (2019) A nearly self-sufficient framework for modelling reactive-transport processes in concrete. *Mater Struct* 52:3. <https://doi.org/10.1617/s11527-018-1305-x>
232. Stanish K, Thomas M (2003) The use of bulk diffusion tests to establish time-dependent concrete chloride diffusion coefficients. *Cem Concr Res* 33:55–62. [https://doi.org/10.1016/S0008-8846\(02\)00925-0](https://doi.org/10.1016/S0008-8846(02)00925-0)
233. Boddy A, Hooton RD, Gruber KA (2001) Long-term testing of the chloride-penetration resistance of concrete containing high-reactivity metakaolin. *Cem Concr Res* 31:759–765. [https://doi.org/10.1016/S0008-8846\(01\)00492-6](https://doi.org/10.1016/S0008-8846(01)00492-6)
234. BS-8500:Part-1 (2023) *Concrete—complementary British Standard to BS EN 306*
235. Scrivener K, Avet F, Maraghechi H et al (2018) Impacting factors and properties of limestone calcined clay cements (LC3). *Green Mater* 7:3–14. <https://doi.org/10.1680/jgrma.18.00029>
236. Georget F, Wilson W, Matschei T (2023) Long-term extrapolation of chloride ingress: an illustration of the feasibility and pitfalls of the square root law. *Cem Concr Res* 170:107187. <https://doi.org/10.1016/j.cemconres.2023.107187>
237. Gettu R, Pillai RG, Santhanam M et al (2018) Sustainability-based decision support framework for choosing concrete mixture proportions. *Mater Struct Constr* 51:1–16. <https://doi.org/10.1617/s11527-018-1291-z>
238. Bahman-Zadeh F, Ramezani-pour AA, Zolfagharnasab A (2022) Effect of carbonation on chloride binding capacity of limestone calcined clay cement (LC3) and binary pastes. *J Build Eng* 52:104447. <https://doi.org/10.1016/j.job.2022.104447>
239. von Greve-Dierfeld S, Lothenbach B, Vollpracht A et al (2020) Understanding the carbonation of concrete with supplementary cementitious materials: a critical review by RILEM TC 281-CCC. *Mater Struct Constr*. <https://doi.org/10.1617/s11527-020-01558-w>
240. Shah V, Mackechnie J (2022) Transport characteristics of concrete after carbonation. *Aust J Civ Eng* 00:1–13. <https://doi.org/10.1080/14488353.2022.2089374>
241. Mi T, Li Y, Liu W et al (2023) The effect of carbonation on chloride redistribution and corrosion of steel reinforcement. *Constr Build Mater* 363:129641. <https://doi.org/10.1016/j.conbuildmat.2022.129641>
242. Wang Y, Xu Z, Mi T et al (2023) Corrosion mechanism of reinforcement in LC3 cement pastes under coupled carbonation and chloride attack. *Cem Concr Compos* 140:105080. <https://doi.org/10.1016/j.cemconcomp.2023.105080>
243. Angst UM, Geiker MR, Michel A et al (2017) The steel–concrete interface. *Mater Struct Constr*. <https://doi.org/10.1617/s11527-017-1010-1>
244. Tuutti K, Tutti K (1982) *Corrosion of steel in concrete*. Ph.D Thesis (Lund University)
245. Angst U, Elsener B, Larsen CK, Vennesland Ø (2009) Critical chloride content in reinforced concrete—a review. *Cem Concr Res* 39:1122–1138. <https://doi.org/10.1016/j.cemconres.2009.08.006>
246. Pacheco J, Polder RB (2016) Critical chloride concentrations in reinforced concrete specimens with ordinary Portland and blast furnace slag cement. *Heron* 61:99–120
247. Rengaraju S, Neelakantan L, Pillai RG (2019) Investigation on the polarization resistance of steel embedded in highly resistive cementitious systems—an attempt and challenges. *Electrochim Acta* 308:131–141. <https://doi.org/10.1016/j.electacta.2019.03.200>
248. Li C, Xiao K (2021) Chloride threshold, modelling of corrosion rate and pore structure of concrete with metakaolin addition. *Constr Build Mater* 305:124666. <https://doi.org/10.1016/j.conbuildmat.2021.124666>
249. Nguyen QD, Castel A (2020) Reinforcement corrosion in limestone flash calcined clay cement-based concrete. *Cem Concr Res* 132:106051. <https://doi.org/10.1016/j.cemconres.2020.106051>
250. Güneyisi E, Gesoğlu M, Karaboğa F, Mermerdaş K (2013) Corrosion behavior of reinforcing steel



- embedded in chloride contaminated concretes with and without metakaolin. *Compos Part B Eng* 45:1288–1295. <https://doi.org/10.1016/j.compositesb.2012.09.085>
251. Londono-Zuluaga D, Gholizadeh-Vayghan A, Winnefeld F et al (2022) Report of RILEM TC 267-TRM phase 3: validation of the R3 reactivity test across a wide range of materials. *Mater Struct* 55:142. <https://doi.org/10.1617/s11527-022-01947-3>
252. Santhanam M, Jain S, Bhattacharjee S (2023) Versatile concrete with limestone calcined clay cement. *Indian Concr J* 97:7–17
253. Krishnan S, Emmanuel AC, Shah V et al (2018) Industrial production of limestone calcined clay cement (LC3)—experience and insights. *Green Mater* 7:1–47. <https://doi.org/10.1680/jgrma.18.00003>
254. Bishnoi S, Maity S, Amit M et al (2014) Pilot scale manufacture of limestone calcined clay cement: the Indian experience. *Indian Concr J* 88:22–28
255. Emmanuel AC, Haldar P, Maity S et al (2016) Second pilot production of limestone calcined clay cement (LC3) in India: the experience. *Indian Concr J* 90:57–64
256. Gettu R, Patel A, Rathi V et al (2019) Influence of incorporating supplementary cementitious materials on the sustainability parameters of cements and concrete in the Indian context. *Mater Struct* 52:1–11. <https://doi.org/10.1617/s11527-019-1321-5>

Publisher's Note Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.

