



Deposited via The University of Leeds.

White Rose Research Online URL for this paper:

<https://eprints.whiterose.ac.uk/id/eprint/94849/>

Version: Published Version

Proceedings Paper:

Nampi, PP, Varma, H, Biju, PR et al. (2015) Sodium yttrium fluoride based upconversion nano phosphors for biosensing. In: Journal of Physics, conference series: 6th International Conference on Optical, Optoelectronic and Photonic Materials and Applications (ICOOPMA) 2014. 6th International Conference on Optical, Optoelectronic and Photonic Materials and Applications (ICOOPMA) 2014, 27 Jul - 01 Aug 2014, Leeds, UK. IOP. ISSN: 1742-6588. EISSN: 1742-6596.

<https://doi.org/10.1088/1742-6596/619/1/012043>

Reuse

Items deposited in White Rose Research Online are protected by copyright, with all rights reserved unless indicated otherwise. They may be downloaded and/or printed for private study, or other acts as permitted by national copyright laws. The publisher or other rights holders may allow further reproduction and re-use of the full text version. This is indicated by the licence information on the White Rose Research Online record for the item.

Takedown

If you consider content in White Rose Research Online to be in breach of UK law, please notify us by emailing eprints@whiterose.ac.uk including the URL of the record and the reason for the withdrawal request.

Sodium yttrium fluoride based upconversion nano phosphors for biosensing

This content has been downloaded from IOPscience. Please scroll down to see the full text.

View [the table of contents for this issue](#), or go to the [journal homepage](#) for more

Download details:

IP Address: 129.11.77.203

This content was downloaded on 22/02/2016 at 10:14

Please note that [terms and conditions apply](#).

Sodium yttrium fluoride based upconversion nano phosphors for biosensing

Padmaja Parameswaran Nampi,^{1*} Harikrishna Varma,¹ P R Biju,² Tarun Kakkar,³ Gin Jose,³ Sikha Saha,⁴ Paul Millner⁵

¹Biomedical Technology Wing, Sree Chitra Tirunal Institute for Medical Sciences and Technology, Poojapura, Trivandrum-12, Kerala, INDIA

E-mail: padmavasudev@gmail.com

²School of Pure and Applied Physics, Mahatma Gandhi University, Kottayam, India

³Institute for Materials Research, Houldsworth Building, University of Leeds, Clarendon Road, Leeds LS2 9JT, United Kingdom

⁴Leeds Institute of Genetics, Health and Therapeutics, University of Leeds, Clarendon Road, Leeds LS2 9JT, United Kingdom

⁵School of Biomedical Sciences, University of Leeds, Clarendon Road, Leeds LS2 9JT, United Kingdom

Keywords: Fluorescence, Upconversion, Nanophosphors, Biosensors

Abstract

In the present study, NaYF₄-Yb³⁺/Er³⁺ having the composition NaYF₄-18%Yb³⁺/2%Er³⁺ and NaYF₄-20%Yb³⁺/2%Er³⁺ with and without the addition of PVP (polyvinyl pyrrolidone) have been synthesised by a solution method using NaF, yttrium nitrate, ytterbium nitrate and erbium nitrate as precursors. Upconversion spectra of prepared nanomaterial under 980 nm laser excitation have been studied. The variation in upconversion spectra with new born calf serum and myoglobin has been studied. Myoglobin (Mb) may be helpful when used in conjunction with other cardiac markers for rapid determination of acute myocardial ischemia, especially in patients with a typical chest pain or nonspecific ECG changes. The variation of UC fluorescence with addition of Mb indicates the suitability of using NaYF₄ based UC nanoparticles in cardiac marker detection. The detailed study is currently under progress.

1. Introduction

Rare earth based materials are strongly fluorescent, low in toxicity and readily synthesised in water which greatly facilitates further biofunctionalization. Hence their biological applications have been reported favourably in recent years. The luminescence of lanthanide doped inorganic materials/nanoparticles is characterized by narrow emission band widths determined by the lanthanide ions, which when used in conjunction with different dopant ions and matrices can generate different emission colours. At the same time, lanthanide doped nanoparticles offer substantial advantage over lanthanide chelates such as high photochemical stability and long fluorescent life time up to several milliseconds. Another unique feature of lanthanide doped phosphors is their ability to emit photons in the visible range after being excited with infrared light, in a process known as upconversion. Upconversion fluorescence labels possess several distinct advantages compared to commonly used down-converting phosphors.

- (i) A low optical background is expected due to the absence of autofluorescence of biomolecules upon infrared radiation
- (ii) Due to the large wavelength separation between excitation and emission, the optical train is very simple and so there is no need for time resolved detection and
- (iii) Simultaneous detection of multiple analytes can be realized since different colours of visible light can be obtained from different upconversion phosphors excited by the same IR laser.

The most efficient UC mechanisms are present in solid-state materials doped with rare-earth ions. Lanthanide-doped upconversion materials, which can convert near-infrared lights to visible lights, have attracted growing interest because of their great potentials in biomedical engineering. However, it remains a grand challenge to manoeuvre the intensity ratio between different emission lines and enable tunable upconversion functions. However many previous upconversion phosphors used for biological labelling are somewhat too large in size and thus cannot be used for the sensitive analysis of molecules such as DNA, RNA, or protein biomarkers. Accordingly nano sized upconverting phosphors have received considerable attention. Rare earth fluorides, NaYF₄ in particular are regarded as ideal host materials of low phonon energy and high photochemical stability. And tuneable upconversion emission is feasible with doping of various lanthanide ions. Among various fluoride host low phonon energy NaYF₄ doped either with Yb³⁺:Er³⁺ or Yb³⁺:Tm³⁺ trivalent rare earth ions, is recognized as one of the most efficient host for the infrared-to-visible upconversion processes [1-2]. The IR to visible UC




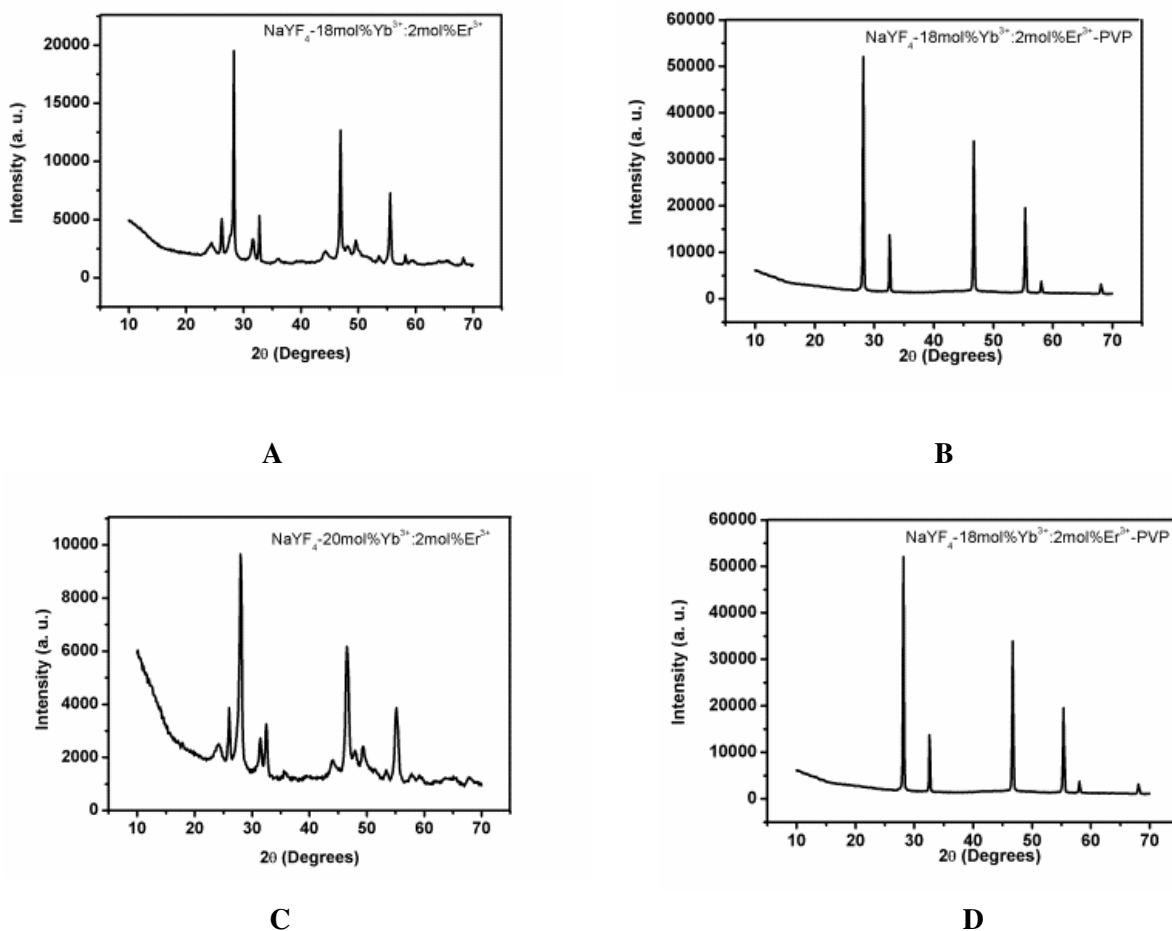


Fig.3 XRD patterns of (A) $\text{NaYF}_4\text{-18mol\%Yb}^{3+}\text{:2mol\%Er}^{3+}$ (B) $\text{NaYF}_4\text{-18mol\%Yb}^{3+}\text{:2mol\%Er}^{3+}$ -PVP (C) $\text{NaYF}_4\text{-20mol\%Yb}^{3+}\text{:2mol\%Er}^{3+}$ (D) $\text{NaYF}_4\text{-20mol\%Yb}^{3+}\text{:2mol\%Er}^{3+}$ -PVP

X-ray diffraction patterns (Fig. 3) show phase pure $\alpha\text{-NaYF}_4/\text{Yb}^{3+}/\text{Er}^{3+}$, for PVP modified samples while mixed phases are observed in the unmodified samples.

Fig. 4 shows the fluorescence upconversion spectra of the selected $\text{NaYF}_4/\text{Yb}^{3+}/\text{Er}^{3+}$ based powder samples. It is observed that sharp peaks having very high intensity has been observed for PVP modified samples especially in the 600-700 nm range (${}^4\text{F}_{9/2} \rightarrow {}^4\text{I}_{15/2}$ transition of the Er^{3+} ions). Significant change is seen in the peak at ~900nm. The peaks at ~800 nm also shows significant increase in PVP modified samples while the intensity is almost zero for unmodified samples. The results show PVP considerably enhances the UC of $\text{NaYF}_4/\text{Yb}^{3+}:\text{Er}^{3+}$ system. But for aqueous

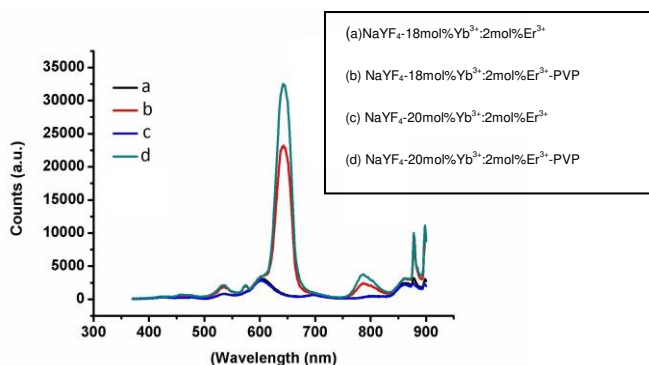

A

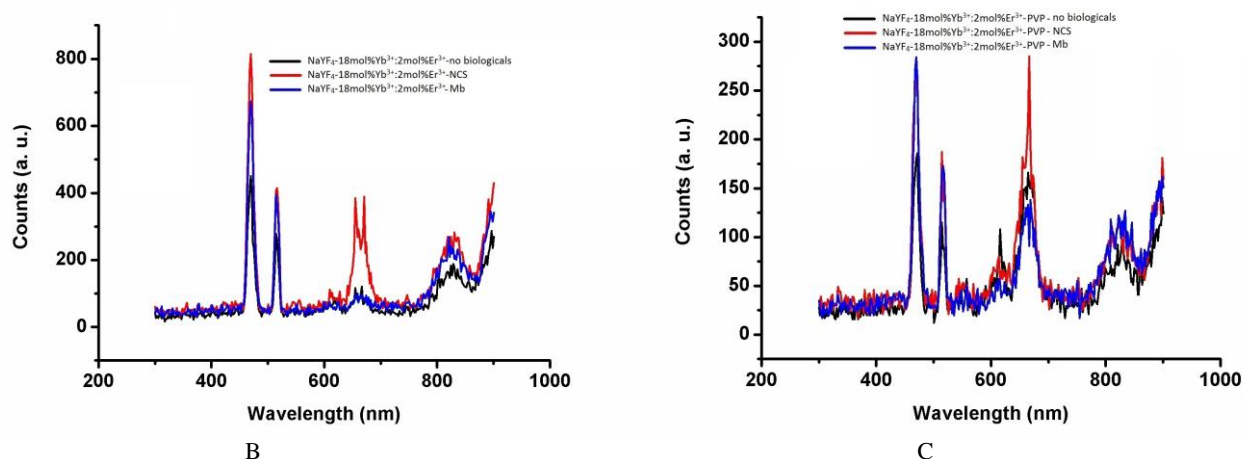


Fig. 4: UC fluorescence spectra of (A) Samples with no biologicals (B) & (C) Sample with NCS and Mb and with out biologicals (aqueous solution)

solutions PVP is not giving much enhancement of fluorescence. But when comparing aqueous solutions with and without biologicals, the peaks observed in the range 400-550 nm ($^2H_{11/2} \rightarrow ^4I_{15/2}$, $^4S_{3/2} \rightarrow ^4I_{15/2}$) is considerably enhanced when NCS and Mb is added to the system, while the peak in the range 600-800 nm shows more sharpness in presence of Mb. While considering the peaks at 800-900 nm, Mb and NCS added samples show a little higher fluorescence. The variation in fluorescence with addition of biomolecules can be a tool for detection. Further optimization is required for elucidating a standardized procedure for detection.

4. Conclusion

Nano - NaYF₄-Yb³⁺:Er³⁺ having various Yb³⁺:Er³⁺ concentration have been synthesised by a wet chemical method. TEM picture shows the nano nature of the samples, with more agglomeration for PVP modified samples. It is observed that PVP modified samples show better UC fluorescence compared to unmodified samples. XRD shows pure cubic phase for PVP modified samples. UC spectra of the synthesised samples and possibilities of using nano - NaYF₄-Yb³⁺:Er³⁺ samples in the field of biosensor have been established using newborn calf serum and calf myoglobin as examples.

5. References

- [1] Tan M C, Al-Baroudi and Riman R E 2011 *ACS Appl. Mater. Inter.* **3** 3910
- [2] Yi G S and Chow G M 2006 *Adv. Funct. Mater.* **16** 2324
- [3] Philips M L F, Hehlen M P, Nguyen K, Sheldon J M and Cockroft N J 2000 *Proc. Electrochem. Soc.* 2000, **99-40** 123
- [4] Scheps R *Prog. 1996 Quantum. Electron.* **20** 271
- [5] Rapaport A, Milliez J, Bass M, Cassanho A and Jenssen H, 2006 *J. Disply Technol.* **2** 68
- [6] Hoeppe H A 2009 *Angew. Chem. Int. Ed.* **48** 3572
- [7] Eliseeva S V and Bunzli J-C G 2010 *Chem. Soc. Rev.* **39** 189
- [8] Naczynski D J, Andelman T, Pal D, Chen S, Riman R E, Roth C M and Moghe P V 2010 *Small*, **106**, 063118/1-063118/12
- [9] Li C and Lin J., 2010 *J. Mater. Chem.* **20** 6831
- [10] Tian G, Gu Z, Zhou L, Yin W, Liu X, Yan L, Jin S, Ren W, Xing G, Li S and Zhao Y 2012 *Adv. Mater.* **24** 1226
- [11] Wang F and Liu X 2009 *Chem. Soc. Rev.* **38** 976
- [12] Nyk M, Kumar R, Ohulchanskyy T Y, Bergey E J and Prasad P N 2008 *Nano Lett.* **8**, 3834

Acknowledgment

One of the authors, PPN acknowledges the Director, Sree Chitra Tirunal Institute for Medical Sciences and Technology for his kind permission to present this work at the ICOOPMA-2014 conference and publish this work in the Journal of Physics: Conference Series (JPCS). PPN also acknowledges the Department of Science and Technology, Government of India for a research fellowship.